



CrossMark
click for updates

Cite this: *RSC Adv.*, 2014, 4, 61652

Received 30th September 2014
Accepted 10th November 2014

DOI: 10.1039/c4ra11558a

www.rsc.org/advances

The selective conversion of β -limonene to p,α -dimethylstyrene†

S. A. Sanchez-Vazquez, T. D. Sheppard, J. R. G. Evans and H. C. Hailes*

Reaction conditions to facilitate the conversion of β -limonene selectively to p,α -dimethylstyrene (DMS) are described, in order to subsequently produce polymeric materials from biomass sourced from food waste. Limonene was dehydrogenated with several palladium catalysts and different solvents and bases, with copper chloride as oxidant at temperatures of 70–120 °C. Reaction conditions were identified using Pd(OAc)₂ for the selective formation of only DMS from limonene in 2–5 hours, enabling the facile separation of DMS from unreacted starting material by vacuum distillation.


Introduction

β -Limonene **1** is the major constituent of citrus peel oil (up to 90% of the monoterpenes present) and a renewable feedstock from citrus peel waste, which has production levels of approximately 12 Tg per annum.¹ Several studies have explored the conversion of limonene into p -cymene **2** and other compounds using for example supported Pd-dehydrogenation catalysts, zeolite supported Pd-catalysts (Ce-promoted), heteropolyacid H₅PMo₁₀V₂O₄₀, silica–alumina supports, and acid activated clays.^{2–8} However, product selectivity can be a problem, for example when using acid-activated bentonite p -cymene was formed in about 15% yield together with polymeric compounds and non-volatile products,⁷ although some reaction conditions do lead to high yields.^{3,4} In other experiments, intermediates and isomers were formed including p -menthene and terpenolene **3**.² Interest in the formation of p -cymene from sustainable feedstocks reflects its importance in many applications including use as a solvent or fragrance ingredient and as an intermediate in fine chemical synthesis.⁹ Further dehydrogenation of p -cymene produces 1-methyl-4-(2-propenyl)benzene, p,α -dimethylstyrene **4** (DMS), which can be polymerized or copolymerized.^{10,11}

The direct conversion of limonene **1** into DMS **4**, is particularly attractive, and a recent report by Jaekel and co-workers has described the use of a catalytic heterogeneous method using palladium(II) trifluoroacetate (Pd(OTFA)₂) and anhydrous copper chloride (CuCl₂) as an oxidant in the presence of 2,6-di-*tert*-butylpyridine (2,6-*t*Bu₂Py) as a sterically hindered base.¹² This built upon previous reports describing the use of palladium(II) in endocyclic alkene dehydrogenations, with either

maleic acid as a hydride acceptor, or dioxygen as an oxidant.^{13,14} Studies established that a heterogeneous catalytic system operated to generate DMS **4** in 65% yield (by GC) with a selectivity in favour of DMS **4** [14.3 : 1 ratio of **4** : (**2** + **3**)] (Scheme 1). The amount of the other products **5** and **6** formed was not indicated (Table 1, entry 1), and it is unclear whether the reported yield refers to DMS alone, or the total amount of DMS and **2** and **3**.¹² Regardless, the formation of DMS alongside these other compounds makes the separation procedure more complex, and the successful purification of DMS was not described.

We are interested in the synthesis of hydrophobic polymers from food wastes, in particular the use of limonene to generate DMS **4**, a strategy intended to reduce raw materials costs as the mineral oil price increases, while removing the conflict over land-use between biomass and food production. One problem to overcome however is that the conversion to DMS needs to be highly selective to achieve a facile separation from any remaining limonene: *i.e.* the formation of side-products with similar physical properties (b.p. at 760 mm Hg: **2** 176–178 °C, **3** 183–185 °C, **4** 186–189 °C, **5** 182 °C, **6** 173 °C) must be avoided. Here the successful conversion of limonene selectively into DMS for subsequent polymerization chemistries has been investigated.

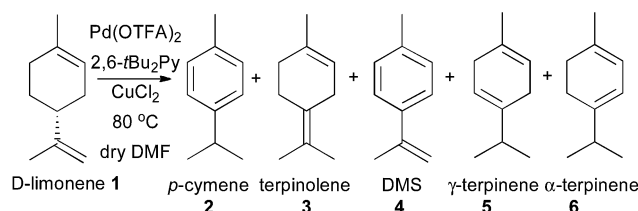

Scheme 1 Conversion of β -limonene to DMS **4** and co-products **2**, **3**, **5** and **6** (Jaekel *et al.*).¹²

Department of Chemistry, University College London, 20 Gordon Street, London WC1H 0AJ, UK. E-mail: h.c.hailes@ucl.ac.uk; Fax: +44 (0)20 7679 7463

† Electronic supplementary information (ESI) available: GC calibration data and example GC analysis traces. See DOI: 10.1039/c4ra11558a



Table 1 Initial limonene conversions into DMS^a

| Entry | Base ^b | Total conversion (%) | DMS 4 (%) | <i>p</i> -Cymene 2 (%) | Terpinolene 3 (%) | γ -Terpinene 5 (%) | α -Terpinene 6 (%) |
|--------------------|---|----------------------|-----------|------------------------|---------------------|---------------------------|---------------------------|
| 1 ^{c,d} | 2,6- <i>t</i> Bu ₂ Py | 74.8 | 65.4 | 14.3 : 1, 4 : 2 + 3 | 14.3 : 1, 4 : 2 + 3 | not given | not given |
| 2 ^{d,e,f} | 2,6- <i>t</i> Bu ₂ Py | 55 | 20 | 0 | 0 | 17 | 18 |
| 3 ^e | 2,6- <i>t</i> Bu ₂ Py anhyd. | 70 | 10 | 17 | 8 | 14 | 21 |
| 4 ^{e,f} | 2,6- <i>t</i> Bu ₂ Py anhyd. | 72 | 57 | 1 | 8 | 1 | 5 |
| 5 ^{e,f} | — | 39 | 11 | 0 | 26 | 0 | 2 |
| 6 ^{e,f} | 2,6-Lutidine anhyd. | 1.4 | 1.4 | 0 | 0 | 0 | 0 |
| 7 ^{e,f,g} | 2,6- <i>t</i> Bu ₂ Py anhyd. | 98 | 1 | 36 | 34 | 2 | 25 |
| 8 ^{e,f,g} | 2,6-Lutidine anhyd. | 18 | 18 | 0 | 0 | 0 | 0 |
| 9 ^{e,g} | 2,6-Lutidine anhyd. | 22 | 22 | 0 | 0 | 0 | 0 |

^a Reactions were carried out in anhydrous DMF at 80 °C (unless indicated) for 40 h using Pd(OTFA)₂ (5 mol%), CuCl₂ (2 equiv.), 2,6-*t*Bu₂Py unless indicated otherwise (3 equiv.). Product ratios determined by GC analysis. ^b Referred to in (ref. 12) as 'additive'. ^c Results from ref. 12. ^d Non-anhydrous DMF used. ^e Reaction performed under Ar. ^f Activated molecular sieves 4 Å added. ^g Reaction carried out at 120 °C.

Results and discussion

Initial reaction conditions and use of alternative bases

In the previous report on the conversion of **1** to **4** and other compounds, the purity of the *D*-limonene used was not stipulated.¹² Nevertheless, in our applications limonene of 97% purity was used (impurities include myrcene, α -pinene), which was felt to be representative of the quality considered for use on a larger scale for DMS production for polymer synthesis. In addition, this was not dried and further purified before use as previously indicated.¹² Using the reported conditions (Scheme 1: 2 equiv. CuCl₂; 3 equiv. 2,6-*t*Bu₂Py) but on a larger scale (6-fold), under an argon atmosphere in DMF (not anhydrous but with the addition of activated 4 Å molecular sieves), although a conversion yield of 55% was noted the selectivity was poor, 4 : 7 for **4** : (**5** + **6**) (Table 1, entry 2). The reaction was repeated using anhydrous DMF and base, but no molecular sieves (Table 1, entry 3), however **6** became the major product with poor selectivity towards DMS. Using activated molecular sieves, and anhydrous solvent and base, the product distribution and yield were closer to that previously reported, with DMS as the major product with a selectivity of 4 : 1 DMS **4** : (**2** + **3** + **5** + **6**), and **6** : 1 **4** : (**2** + **3**) (Table 1, entry 4).¹² This highlighted the sensitivity of the reaction conditions to the presence of water, indeed when adding water instead of base, the dehydrogenation of limonene was completely inhibited. When base was excluded from the reaction the major product was terpinolene **3** (Table 1, entry 5), which is consistent with the proposed mechanism by Jaekel and co-workers.¹² A screen of several non-coordinating hindered bases (*N,N*-diisopropylethylamine, 2,2,6,6-tetramethylpiperidine, 2,4,6-trimethylpyridine and 2,6-lutidine) highlighted that only the pyridines generated DMS as a single dehydrogenation product (1% yield; Table 1, entry 6 for lutidine result) and due to its lower cost 2,6-lutidine was selected for further experiments.

With a view to increasing the amount of DMS produced using 2,6-*t*Bu₂Py the reaction temperature was increased to 120 °C, which gave improved conversion yields (98%) but very little DMS was formed and the major product was *p*-cymene **2** (Table 1, entry 7). When using 2,6-lutidine however at 120 °C, either in the presence or absence of molecular sieves, DMS **4** was formed as the only product in approximately 20% yield (Table 1, entries 8

and 9), and so these conditions were used in subsequent reactions. Although this yield was not high the reaction selectivity was excellent and will have a major impact on the ease of product purification. These results are also interesting because in previous work using Pd(OTFA)₂ in dehydrogenation reactions of cyclohexenes, attempts to neutralise the acid formed using 2,6-lutidine led to a total inhibition of the reaction.¹³

The use of different solvents and catalysts

The use of alternative solvents were then investigated.¹⁵ In cyclopentyl methyl ether (CPME) only *p*-cymene **2** was formed as a single product in 30% yield (Table 2, entry 1).

Another solvent with sound green credentials is 2-methyl THF (2-MeTHF).¹⁵ When used in the presence of molecular sieves only small amounts of **3** and **6** were formed, however, in the absence of molecular sieves **2** and **6** were formed in a much higher combined yield of 55% (Table 2, entries 2 and 3), reflecting problems with the second proposed dehydrogenation step under these conditions.¹² The use of heptane resulted in no conversion, presumably due to the poor stability of charged intermediates in this apolar solvent. Alternative lower cost catalysts were then investigated. Palladium chloride (PdCl₂) when used with 2,6-lutidine in DMF at 80 °C gave no dehydrogenation products, although in acetonitrile gave 7% of DMS after 4 h with no increase in yield after 12 h (Table 2, entry 4). Palladium acetate (Pd(OAc)₂) in DMF gave DMS only in very low yields at 80 °C, but when the reaction temperature was increased to 120 °C DMS **4** only was formed in approximately 20% yield (Table 2, entries 5 and 6; Scheme 2). With unreacted limonene remaining, this gave a yield of >90% (based on remaining unreacted starting material).


When the same conditions as for entry 6 (base and temperature) had been used with Pd(OTFA)₂ (Table 1, entry 9) an almost identical result was observed. Further experiments using Pd(OAc)₂ at 2 mol% and 10 mol% (Table 2, entries 7 and 8) gave less DMS or no products. The reaction was also performed under an oxygen atmosphere without CuCl₂ (Table 2, entry 9): 11% of DMS was produced after 9 h, with no further increase in yield after 12 h. The same level of conversion to **4** was reported previously when using 0.5 equiv. CuCl₂ under 0.25 MPa of oxygen.¹²



Table 2 Effect of solvent and catalyst for limonene conversions into DMS^a

| Entry | Temp. (°C) | Solvent | Catalyst | Total conversion (%) | DMS 4 (%) | Other products |
|------------------|------------|---------------------------|------------------------------|----------------------|-----------|----------------|
| 1 ^b | 90 | CPME | Pd(OTFA) ₂ 5 mol% | 30 | 0 | 30% 2 |
| 2 ^b | 70 | 2-MeTHF anhyd. | Pd(OTFA) ₂ 5 mol% | 3 | 0 | 1% 3, 2% 6 |
| 3 | 70 | 2-MeTHF anhyd. | Pd(OTFA) ₂ 5 mol% | 55 | 0 | 25% 2, 30% 6 |
| 4 ^c | 80 | CH ₃ CN anhyd. | PdCl ₂ 5 mol% | 7 | 7 | 0 |
| 5 ^b | 80 | DMF anhyd. | Pd(OAc) ₂ 5 mol% | 2 | 2 | 0 |
| 6 | 120 | DMF anhyd. | Pd(OAc) ₂ 5 mol% | 19 | 19 | 0 |
| 7 | 120 | DMF anhyd. | Pd(OAc) ₂ 2 mol% | 6 | 5 | 1% 5 |
| 8 | 120 | DMF anhyd. | Pd(OAc) ₂ 10 mol% | 0 | 0 | 0 |
| 9 ^{c,d} | 120 | DMF anhyd. | Pd(OAc) ₂ 5 mol% | 11 | 11 | 0 |
| 10 ^e | 120 | DMF anhyd. | Pd(OAc) ₂ 10 mol% | 39 | 39 | 0 |

^a Reactions were carried out using the catalyst, solvent and temperature indicated for 40 h with CuCl₂ (2 equiv.), 2,6-lutidine (3 equiv.) under argon, unless otherwise indicated. Product ratios determined by GC analysis. ^b Molecular sieves 4 Å added. ^c 12 h reaction. ^d Reaction performed under an oxygen atmosphere without CuCl₂. ^e 3 h with CuCl₂ (4 equiv.), 2,6-lutidine (9 equiv.) under argon. CPME: cyclopentyl methyl ether.

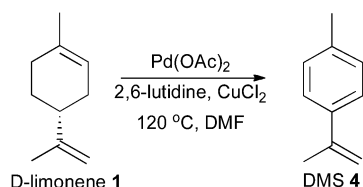

Scheme 2 Reaction conditions for the conversion of limonene 1 to DMS 4 used in further optimisations (Fig. 1).

Reaction monitoring and further optimisations

Using Pd(OAc)₂ (5 mol%), CuCl₂ (2 equiv.), 2,6-lutidine (3 equiv.) and a reaction temperature of 120 °C the progression of the reaction (Scheme 2) was monitored over 40 h, which indicated that after 4 h the conversion was complete (approx. 20% of DMS only). In addition there was no apparent extended induction period as previously reported at 80 °C, perhaps reflecting the use of higher reaction temperatures.¹² The addition of more of the key reagents was investigated (Fig. 1A).

Further addition of oxidant CuCl₂ (2 equiv.) after 4 h had no effect, but the addition of 2,6-lutidine base (3 equiv.) led to the production of more DMS, increasing the overall yield to 28%. The role of the non-coordinating base such as 2,6-*t*Bu₂py and 2,6-lutidine is to remove up to 4 equivalents of HCl generated during the reaction, and was reported previously to enhance the selectivity in the dehydrogenation reaction towards DMS 4. Here it appeared that the removal of remaining HCl, by the addition of >3 equivalents of 2,6-lutidine, could account for the improved conversion to DMS. Therefore, the reaction progression was then followed using initially 2,6-lutidine (9 equiv.) and after 4 h a further 5 mol% of Pd(OAc)₂ catalyst was added (no effect was observed), and then after a further 2 h more CuCl₂ oxidant (2 equiv.) was added, giving DMS 4 in 38% yield (Fig. 1B). Finally, three further experiments were performed using: 2,6-lutidine (9 equiv.) catalyst Pd(OAc)₂ (5 mol% as previously) and oxidant CuCl₂ (4 equiv.), and with increased catalyst Pd(OAc)₂ (10 mol%) (Table 2, entry 10) and oxidant CuCl₂ (6 equiv.). All reactions lead to the formation of DMS in approximately 40% yield, but with less catalyst and oxidant it

took 5 h, compared to 2–3 h. The increased amount of 2,6-lutidine in the reaction as well as having a role in the neutralisation of HCl formed, may also help to stabilise the active

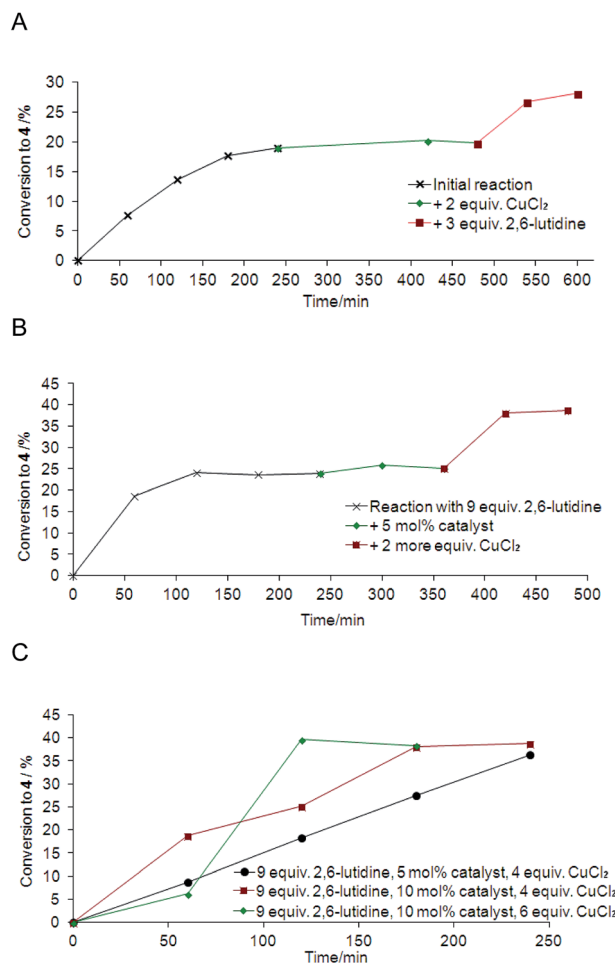


Fig. 1 Reaction monitoring. (A) After 4 h the addition of CuCl₂ (2 equiv.), and after a further 2 h the addition of 2,6-lutidine (3 equiv.); (B) reaction with 9 equiv. 2,6-lutidine; after 4 h the addition of another 5 mol% Pd(OAc)₂, and after a further 2 h the addition of more CuCl₂ (2 equiv.); (C) reaction profile using 9 equiv. 2,6-lutidine with different amounts of catalyst (5–10 mol%) and oxidant CuCl₂ (4–6 equiv.).



catalytic species and prolong its lifetime. In all cases the selectivity of the reaction was exceptional, leading only to the formation of DMS **4** (with limonene starting material remaining).

Comparing the reaction profile data (Fig. 1) to that in Table 2, where an increase in palladium catalyst Pd(OAc)₂ inhibited the reaction (entry 10), an increase in the amount of catalyst combined with more oxidant CuCl₂ to oxidise the catalyst, clearly had a beneficial effect. This highlights that the complexity of the reaction, which involves up to 12 steps, makes the outcome of changing one reagent very difficult to predict. Nevertheless, reaction conditions have been identified to give a method for the conversion of limonene selectively to DMS **4** in 40% yield. The generation of a single dehydrogenated product simplifies significantly the purification of the reaction. Indeed, since **3** and **5** have boiling points within 1–4 °C of DMS **4**, the production of a single dehydrogenation product is particularly valuable. The dehydrogenation reaction was scaled-up (to 3 ml *D*-limonene) using the reaction conditions in Table 2, entry 10, (Scheme 2, Fig. 1C) and the product DMS **4** readily separated by vacuum distillation in 37% isolated yield and >99% purity (no impurities detected). This method of generating DMS could be used in a recirculatory flow reactor, which would recycle the unconverted limonene.

Conclusions

In summary, improved conditions have been developed for the selective dehydrogenation of limonene to the monomer DMS **4** in a highly selective procedure. By performing the reaction at 120 °C with Pd(OAc)₂ catalyst, 2,6-lutidine as a non-coordinating base, and CuCl₂ as an oxidant approx. 40% of DMS was formed. Notably, no products resulting from the isomerization of the exocyclic double bond were observed under these conditions.

Experimental

General experimental details

Reagents were used as supplied: *D*-limonene (Aldrich, 97%); palladium(II) trifluoroacetate; palladium(II) acetate (Aldrich, 98%); palladium(II) chloride (Alfa Aesar, 47% of Pd); anhydrous copper(II) chloride (Alfa Aesar, 98%); 2,6-di-*tert*-butylpyridine (Aldrich, >97%); *N,N*-diisopropylethylamine (Aldrich, >99%); 2,2,6,6-tetramethylpiperidine (Aldrich, >99%); 2,4,6-collidine (Aldrich, 99%), except 2,6-lutidine (Aldrich, >99%) which was dried with 4 Å molecular sieves for 18 h prior to use. Solvents were used as supplied: DMF (Acros, 99.8%); DMSO (Aldrich, 99.6%), and all other solvents (Aldrich, 99.9%).

Dehydrogenation of *D*-limonene **1** to DMS **4**

The following method was used, with the modifications outlined above. *D*-limonene (1 equiv.) was added to a stirred solution of PdX₂ (catalyst, 5 mol%), CuCl₂ (2 equiv.) and base (3 equiv.), unless indicated otherwise, in anhydrous solvent. The reaction was heated for the time and at the temperature

indicated. The reaction was followed by GC analysis (as previously described¹²) using a Hewlett Packard HP4890-A GC with a high performance capillary column HP-5 (crosslinked 5% PH ME siloxane) (30 m × 0.32 mm × 0.25 μm), with He carrier gas and a flow rate of 2 ml min⁻¹. The injector was operated at 250 °C in split mode (ratio 1 : 20). The oven was heated to 50 °C and then increased at 1 °C min⁻¹ to 80 °C. Calibrations were performed for **1–6**, with retention times of approximately **1** 16.9 min, **2** 14.8 min, **3** 22.7 min, **4** 24.0 min, **5** 20.3 min and **6** 14.2 min.

Scaled up reaction

D-limonene (3.00 ml, 18.5 mmol) was added to a mixture of PdOAc₂ (10 mol%), CuCl₂ (4 equiv.), 2,6-lutidine (9 equiv.) and anhydrous DMF (45 ml). The reaction mixture was heated at 120 °C for 3 h, and DMS **4** isolated by vacuum distillation (30 mmHg, 80 °C) in >99% purity (0.904 g, 37%).

Acknowledgements

The authors are grateful to the National Council of Science and Technology of Mexico (CONACYT) for providing a stipend for S. A. S.-V.

Notes and references

- 1 S. A. Sanchez-Vazquez, H. C. Hailes and J. R. G. Evans, *Polym. Rev.*, 2013, **53**, 627.
- 2 R. J. Grau, P. D. Zgolicz, C. Gutierrez and H. A. Taher, *J. Mol. Catal. A: Chem.*, 1999, **148**, 203.
- 3 C. Zhao, W. Gan, X. Fan, Z. Cai, P. J. Dyson and Y. Kou, *J. Catal.*, 2008, **254**, 244.
- 4 P. A. Weyrich and W. F. Holderich, *Appl. Catal., A*, 1997, **158**, 145.
- 5 R. Neumann and M. Lissel, *J. Org. Chem.*, 1989, **54**, 4607.
- 6 M. A. Martín-Luengo, M. Yates, M. J. Martínez Domingo, B. Casal, M. Iglesias, M. Esteban and E. Ruiz-Hitzky, *Appl. Catal., B*, 2008, **81**, 218.
- 7 C. Fernandes, C. Catrinescu, P. Castilho, P. A. Russo, M. R. Carrott and C. Breen, *Appl. Catal., A*, 2007, **318**, 108.
- 8 C. Breen and A. J. Moronta, *Clay Miner.*, 2001, **36**, 467.
- 9 A. K. Mukhopadhyay, *Industrial Chemical Cresols and Downstream Derivatives*, Marcel Dekker, New York, 2005.
- 10 R. B. Seymour, F. F. Harris and I. Branum, *Ind. Eng. Chem.*, 1949, **41**, 1509.
- 11 R. W. Lenz, J. E. Sutherland and L. C. Westfelt, *Makromol. Chem.*, 1976, **177**, 653.
- 12 P. Horrillo-Martínez, M. A. Virolleaud and C. Jaekel, *ChemCatChem*, 2010, **2**, 175.
- 13 B. M. Trost and P. J. Metzner, *J. Am. Chem. Soc.*, 1980, **102**, 3572.
- 14 J. E. Bercaw, N. Hazari and J. A. Labinger, *J. Org. Chem.*, 2008, **73**, 8654.
- 15 R. K. Henderson, C. Jimenez-Gonzalez, D. J. C. Constable, S. R. Alston, G. G. A. Inglis, G. Fisher, J. Sherwood, S. P. Binks and A. D. Curzons, *Green Chem.*, 2011, **13**, 854.

