

Preparation and Properties of π -Conjugated Poly(1,10-phenanthroline-3,8-diyl)


Yutaka Saitoh and Takakazu Yamamoto*

Research Laboratory of Resources Utilization, Tokyo Institute of Technology, 4259, Nagatsuta, Midori-ku, Yokohama 226

(Received June 5, 1995)


Poly(1,10-phenanthroline-3,8-diyl) has been synthesized by dehalogenation polycondensation of 3,8-dibromo-1,10-phenanthroline with a zerovalent nickel complex. The polymer has molecular weight of 6800 and is electrochemically reduced at $E_{pa} = 2.24$ V vs Ag/Ag^+ .

π -Conjugated poly(arylene)s have been the subject of recent many papers.¹ On the other hand, chemistry of π -conjugated chelating ligands (e.g., 2,2'-bipyridine and 1,10-phenanthroline) and their metal complexes has been extensively explored. However, examples of π -conjugated chelating polymer ligands (e.g., poly(2,2'-bipyridine-5,5'-diyl) PBpy²) have been limited. We here report preparation and properties of new π -conjugated poly(arylene), poly(1,10-phenanthroline-3,8-diyl) PPhen, constituted of recurring 1,10-phenanthroline units.



PBpy is considered to take an *s-trans* structure and rotation of the C-C bond is necessitated for the metal complex formation. In the case of PPhen, it has a more rigid chelating structure and recently interesting electrical and optical properties of metal complexes of 1,10-phenanthroline derivatives have been reported.³

PPhen has been prepared by Ni-promoted dehalogenation polycondensation² of 3,8-dibromo-1,10-phenanthroline, which is prepared by bromination of 1,10-phenanthroline.⁴

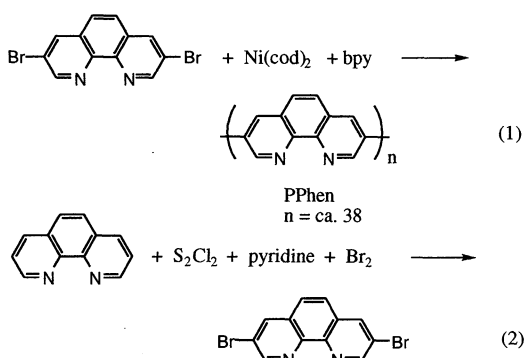

The dehalogenation polycondensation of the monomer (650 mg, 1.9 mmol) with a Ni(0) complex (a mixture of bis(1,5-cyclooctadiene)nickel(0) $Ni(cod)_2$ (650 mg, 2.4 mmol), 2,2'-bipyridine (310 mg, 2.0 mmol), and 1,5-cyclooctadiene (1.2 cm³)) gave reddish brown PPhen, which was isolated in a manner similar to that applied to the isolation of PBpy: yield =

80.7%.⁵ PPhen is soluble in formic acid and partially soluble in sulfuric acid, however, it is not soluble in common organic solvents. PPhen has molecular weight of 6.8×10^3 , which corresponds to the degree of polymerization of 38, as determined by a light-scattering method. The polymer shows intrinsic viscosity of 0.40 dl g⁻¹ (dl = 100 cm³) as measured in formic acid. Casting from a formic acid solution of PPhen gives a film free from formic acid and with good optical and mechanical quality.

The $\pi - \pi^*$ absorption band of PPhen appears at a considerably longer wavelength ($\lambda_{max} = 382$ nm) in formic acid (Figure 1a) than that ($\lambda_{max} = 277$ nm) of 1,10-phenanthroline

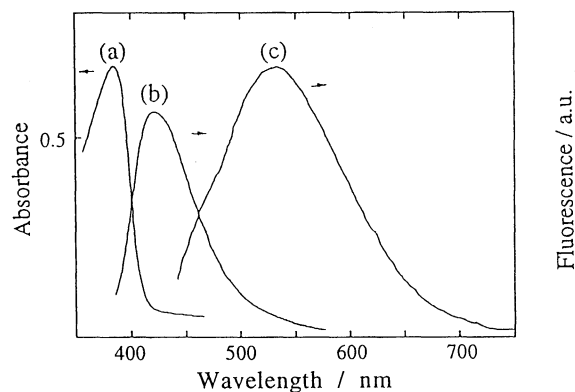


Figure 1. UV-visible spectrum of PPhen in formic acid (a), fluorescence spectrum of PPhen in formic acid (b), and fluorescence spectrum of PPhen film on a quartz glass plate (c); a.u. = arbitrary unit.

revealing the expansion of the π -conjugation system along the polymer chain. The casting film of PPhen exhibits the $\pi - \pi^*$ absorption band at the same position. The formic acid solution of PPhen shows a strong fluorescence with a peak at 413 nm when excited by 384 nm light (Figure 1b). The fluorescence peak position agree with the onset position of the $\pi - \pi^*$ absorption as usually observed with fluorescent π -conjugated compounds. On the other hand, a PPhen film prepared by casting from the formic acid solution gives a shifted fluorescence band with λ_{max} of 535 nm (Figure 1c), which lies apart from the onset position of the $\pi - \pi^*$ absorption. A similar shift of fluorescence peak in film has also been observed with PBpy and the shift has been ascribed to formation of an excimer-like adduct between the rigidly linear PBpy molecules aligned in the film.²

Cyclic voltammogram (Figure 2) of the polymer film in a dry acetonitrile solution containing tetrabutylammonium tetrafluoroborate shows a redox cycle with cathodic and anodic peaks at -2.24 V, -1.98 V vs Ag/Ag^+ , respectively, and the peaks are assigned to n-doping and n-undoping of PPhen.

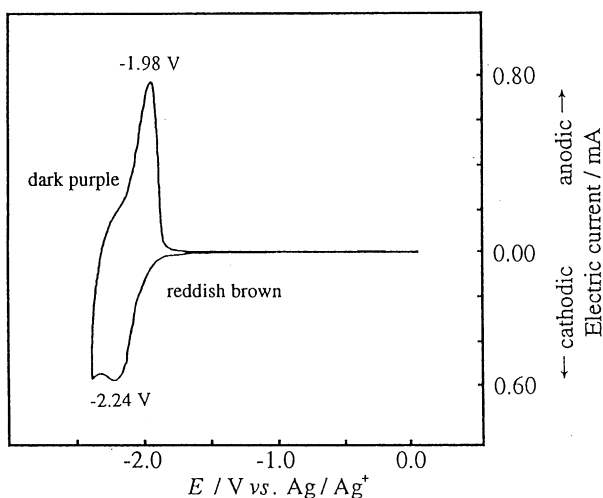
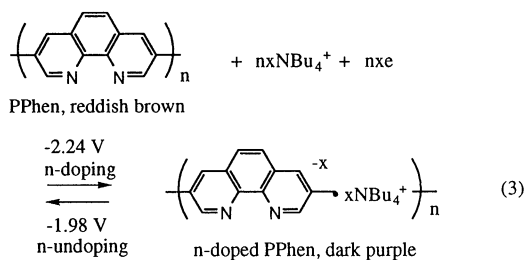


Figure 2. Cyclic voltammogram of a film of PPhen on a platinum plate in a CH_3CN solution of 0.1 M $[\text{N}(\text{n-C}_4\text{H}_9)_4][\text{BF}_4]$. Sweep rate = 5 mVs^{-1} .

The n-doping and n-undoping are accompanied by color change shown in Eq. 3 and repeated without change of the cyclic voltammogram. The doping level (x in Eq. 3) is about 0.5 as estimated from the n-doping current. In contrast to the facile n-doping, PPhen is inert against p-type doping (oxidation) up to

1.0 V vs Ag/Ag^+ . These electrochemical properties agree with previously observed results that poly(arylene)s containing electron-withdrawing imine nitrogen(s) are active for the n-doping but inactive for p-doping. Treatment of PPhen with a THF solution of sodium naphthalide at room temperature gives dark purple product, which has electrical conductivity of about $10^{-5} \text{ S cm}^{-1}$ as measured with compressed powder.

References and Notes

- 1 T. A. Skotheim, Ed. *Handbook of Conducting Polymers*, Vols. I and II, Marcel Dekker, New York (1986).
- 2 T. Yamamoto, T. Maruyama, Z. -H. Zhou, T. Ito, T. Fukuda, Y. Yoneda, F. Begum, T. Ikeda, S. Sasaki, H. Takezoe, A. Fukuda, and K. Kubota, *J. Am. Chem. Soc.*, **116**, 4832 (1994).
- 3 T. Tsutsui, N. Takada, and S. Saito, and E. Ogino, *Appl. Phys. Lett.*, **65**, 1868 (1994).
- 4 Preparation of 3,8-Dibromo-1,10-phenanthroline : To 1,10-phenanthroline monohydrate (5.0 g, 28 mmol) dissolved in 200 cm^3 of 1-chlorobutane were added S_2Cl_2 (11.3 g, 83 mmol), pyridine (6.9 g, 87 mmol) and Br_2 (10 g, 63 mmol), and the reaction mixture was refluxed for 12 h. The precipitate formed was separated by decantation and dissolved in chloroform. After treatment with a SiO_2 short column, the CHCl_3 solution was condensed to about 60 cm^3 , and Br_2 (3.0 g, 19 mmol) was added to the condensed solution to obtain an orange solid of a Phen- Br_2 complex. After 30 min, the solid was collected by filtration and purified by SiO_2 column chromatography and recrystallization from benzene to yield white needles of Phen Br_2 (26% yield). Anal. Found : C, 42.7; H, 1.8; N, 8.4; Br, 47.0%. Calcd for $\text{C}_{12}\text{H}_6\text{N}_2\text{Br}_2$: C, 42.6; H, 1.8; N, 8.3; Br, 47.3%. IR (KBr, cm^{-1}) : 3024, 1583, 1475, 1411, 1204, 1101, 906, 892, 776, 720; $^1\text{H NMR}(\text{CDCl}_3)$ δ : 7.73 (s, 2H), 8.39 (d, J = 2.2 Hz, 2H), 9.17 (d, J = 2.2 Hz, 2H).
- 5 Anal. Found : C, 74.9; H, 3.6; N, 14.4; Br, 0%. Calcd for $(\text{C}_{12}\text{H}_6\text{N}_2 \cdot 0.8\text{H}_2\text{O})_n$: C, 74.8; H, 4.0; N, 14.5%. IR (KBr, cm^{-1}) : 1419, 901, 730.