

Catalyst activity or stability: the dilemma in  
Pd-catalyzed polyketone synthesis†Cite this: *Dalton Trans.*, 2013, **42**, 14583Francesco Amoroso,<sup>a,b</sup> Ennio Zangrando,<sup>a</sup> Carla Carfagna,<sup>c</sup> Christian Müller,<sup>d</sup> Dieter Vogt,<sup>e</sup> Mohamed Hagar,<sup>f</sup> Fabio Ragaini\*<sup>g</sup> and Barbara Milani\*<sup>a</sup>

A series of Pd-complexes containing nonsymmetrical bis(aryl-imino)acenaphthene (Ar-BIAN) ligands, characterized by substituents on the *meta* positions of the aryl rings, have been synthesized, characterized and applied in CO/vinyl arene copolymerization reactions. Crystal structures of two neutral Pd-complexes have been solved allowing comparison of the bonding properties of the ligand. Kinetic and mechanistic investigations on these complexes have been performed. The kinetic investigations indicate that in general ligands with electron-withdrawing substituents give more active, but less stable, catalytic systems, although steric effects also play a role. The good performance observed with nonsymmetrical ligands is at least in part due to a compromise between catalyst activity and lifetime, leading to a higher overall productivity with respect to catalysts based on their symmetrical counterparts. Additionally, careful analysis of the reaction profiles provided information on the catalyst deactivation pathway. The latter begins with the reduction of a Pd(II) Ar-BIAN complex to the corresponding Pd(0) species, a reaction that can be reverted by the action of benzoquinone. Then the ligand is lost, a process that appears to be facilitated by the contemporary coordination of an olefin or a CO molecule. The so formed Pd(0) complex immediately reacts with another molecule of the initial Pd(II) complex to give a Pd(I) dimeric species that irreversibly evolves to metallic palladium. Mechanistic investigations performed on the complex with a nonsymmetrical Ar-BIAN probe evidence that the detected intermediates are characterized by the Pd–C bond *trans* to the Pd–N bond of the aryl ring bearing electron-withdrawing substituents. In addition, the intermediate resulting from the insertion of 4-methylstyrene into the Pd–acyl bond is a five-member palladacycle and not the open-chain  $\eta^3$ -allylic species observed for complexes with Ar-BIANs substituted in *ortho* position.

Received 31st May 2013,  
Accepted 19th July 2013

DOI: 10.1039/c3dt51425k

www.rsc.org/dalton

## Introduction

$\alpha$ -Diimine ligands, having a 1,4-diaza-1,3-butadiene or an acenaphthene skeleton (Ar-BIAN) and aryl rings on the imine

nitrogen atoms, have been known since 1969.<sup>1</sup> However, only in 1992 the first straightforward synthetic procedure was reported by Elsevier.<sup>2</sup> Afterwards, the main application of these molecules as ancillary ligands in homogeneous catalysis was brought to the attention of a wider scientific community by Brookhart's discovery that the relevant nickel and palladium complexes generate extremely efficient catalysts for polyethylene synthesis.<sup>3</sup> This finding had an impressive impact, in the field of catalysis for polymerization, resulting in a huge development of ligands of this family.<sup>4</sup> The same palladium complexes were also revealed to be able to catalyze the copolymerization of ethylene with polar vinyl monomers, a highly challenging reaction.<sup>5–7</sup>

Ar-BIANs applied as ancillary ligands in catalysts for polymerization reactions share some common features: (i) the two nitrogen atoms bear identical aryl rings; (ii) these aryl rings are almost invariably substituted in the *ortho* and/or *para* positions; (iii) the nature and the number of substituents affect the yield, the selectivity,<sup>4,8</sup> and the microstructure of the polymer<sup>8</sup> and the relative amount of comonomers inserted into the polymer chain in both  $\alpha$ -olefins<sup>9</sup> and in ethylene/polar vinyl monomer copolymerization.<sup>6,10,11</sup>

<sup>a</sup>Dipartimento di Scienze Chimiche e Farmaceutiche, Università di Trieste, Via Licio Giorgieri 1, 34127 Trieste, Italy. E-mail: milaniba@units.it; Fax: +39 040 5583903; Tel: +39 040 5583956

<sup>b</sup>Dipartimento di Chimica, Fisica e Ambiente, Università di Udine, Via del Cotonificio 108, 33100 Udine, Italy. E-mail: francesco.amoroso@uniud.it; Fax: +39 0432 558803; Tel: +39 0432 558755

<sup>c</sup>Dipartimento di Scienze Biomolecolari, Università di Urbino, Piazza Rinascimento 6, 61029 Urbino, Italy. E-mail: carla.carfagna@uniurb.it; Fax: +39 0722 303311; Tel: +39 0722 303312

<sup>d</sup>Institut für Chemie und Biochemie-Anorganische Chemie, Freie Universität Berlin, 14195 Berlin, Germany. E-mail: c.mueller@fu-berlin.de; Tel: +49 30 838 54004

<sup>e</sup>School of Chemistry, University of Edinburgh, Edinburgh EH9 3JJ, Scotland, UK. E-mail: d.vogt@ed.ac.uk; Tel: +44 (0)131 651 7767

<sup>f</sup>Chemistry Department, Alexandria University, Ibrahimia, Alexandria 21321, Egypt

<sup>g</sup>Dipartimento di Chimica, Università di Milano, Via C. Golgi 19, 20133 Milano, Italy. E-mail: fabio.ragaini@unimi.it; Fax: +39 02 50314405; Tel: +39 02 50314373

†Electronic supplementary information (ESI) available. CCDC 942156 and 942157. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c3dt51425k

Palladium complexes with *ortho* substituted Ar-BIANs (<sup>o</sup>Ar-BIANs) were applied as model compounds to unravel the mechanism of the polymer chain growth during the CO/alkene copolymerization.<sup>12</sup> Some of these complexes were also tested as precatalysts in the CO/4-Me-styrene copolymerization (4-Me-styrene = 4-methylstyrene): low productivity (15 g CP per g Pd; g CP per g Pd = grams of copolymer per gram of palladium) or inactivity was observed depending on the substituents on the *ortho* positions. Nevertheless, polyketones made of isotactic stereoblocks of opposite relative configuration were obtained despite the C<sub>2v</sub> symmetry of the ligands.<sup>13–15</sup>

For the first time we introduced nonsymmetrical Ar,Ar'-BIANs characterized by different aryl rings substituted in *meta* position on the two N-donors.<sup>16</sup> The organometallic palladium complexes, [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(<sup>m</sup>Ar-BIAN)](PF<sub>6</sub>), with symmetrically and nonsymmetrically *meta* substituted Ar-BIANs (<sup>m</sup>Ar-BIANs), were applied as catalysts in CO/vinyl arene copolymerization. We found that moving the substituents on the aryl rings of Ar-BIAN from the *ortho* to the *meta* positions resulted in an enhancement of productivity of more than two orders of magnitude, and a productivity value of 3.70 kg CP per g Pd was reached.<sup>17</sup> Polyketones with an atactic microstructure and an M<sub>w</sub> of 47 000 (M<sub>w</sub>/M<sub>n</sub> = 2.0) were produced. Both productivity and molecular weight were affected by the nature and the number of substituents on the <sup>m</sup>Ar-BIANs. The catalysts with the nonsymmetrical Ar,Ar'-BIAN are more productive than those having the corresponding symmetrical ligands and lead to polyketones of higher molecular weight.

The positive effect of nonsymmetrical Ar,Ar'-BIAN ligands has been very recently demonstrated even in the ethylene/methyl acrylate cooligomerization: the catalyst with the nonsymmetrical ligand showed a higher productivity and a higher content of the inserted polar monomer with respect to those with the related symmetrical ligands.<sup>18</sup>

These catalytic results suggest that the subtle unbalance of the electronic and steric properties of the N-donor atoms of the Ar-BIAN ligands has a positive effect on the catalyst performance and, thanks to the similarity between these two

copolymerization reactions, it might indicate the validity of a more general principle.

With the aim to unravel the nature of the different catalytic behaviors of complexes with symmetrical and nonsymmetrical Ar-BIANs we have chosen the CO/vinyl arene copolymerization as the model reaction, and on palladium complexes with selected ligands (Fig. 1) we have performed: (1) kinetic investigations; (2) the related modelization; (3) *in situ* NMR mechanistic studies on the reactivity of the complexes with the comonomers. In addition, with these purposes the series of nonsymmetrical ligands has been extended to a new component, ligand 3, characterized by one aryl ring substituted in *meta* and *para* positions with methoxy groups and the other aryl ring having fluorine atoms in the *meta* positions.

## Results and discussion

### Synthesis and characterization of the new ligands and the related Pd-complexes

Ligands 3 and 7 are reported here for the first time. The synthetic methodology for ligand 7 is based on the well known condensation reaction of acenaphthenequinone with 3,5-difluoro aniline in the presence of ZnCl<sub>2</sub> as a templating agent.<sup>19,20</sup>

The synthesis of the new nonsymmetrical Ar,Ar'-BIAN 3 was performed by the transimination reaction between the zinc derivative of ligand 7 and 3,4,5-trimethoxy aniline (Scheme 1), similar to what was previously described by some of us for other nonsymmetrical Ar,Ar'-BIAN derivatives.<sup>16</sup> The reaction proceeds quickly and the mixed ligand could be isolated in 52% yield after chromatographic purification. It should be noted that previously mixed ligands had only been obtained by this methodology when the starting compound had two trifluoromethyl groups on each aryl ring, according to the idea



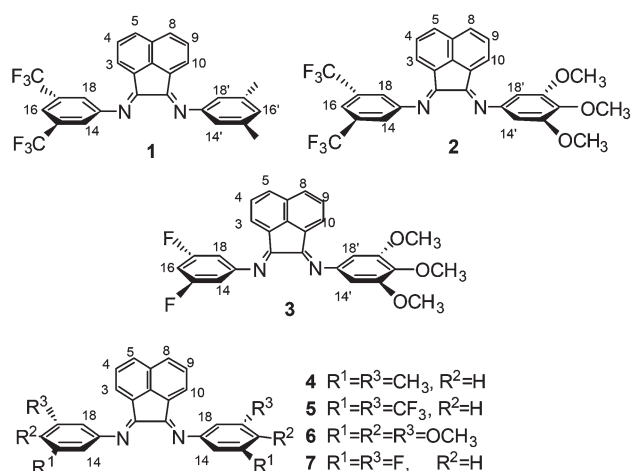


Fig. 1 The studied Ar-BIANs and their numbering scheme.

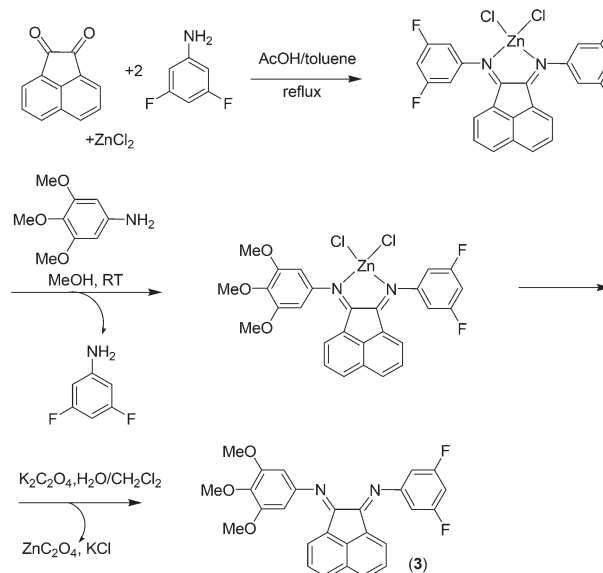

Scheme 1 Synthetic pathway for ligand 3.

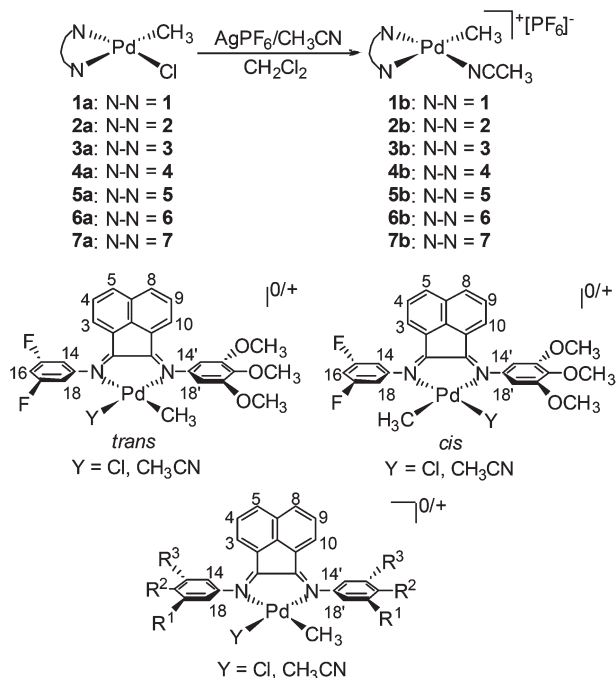

**Scheme 2** Synthetic pathway for the monocationic complexes **1b–7b** and the numbering scheme for both neutral and monocationic derivatives.

that electron-withdrawing substituents on the starting Ar-BIAN should render transimination easier. The present result indicates that even less electron-withdrawing groups can be efficiently used in this protocol.

The monocationic Pd complexes, [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(Ar-BIAN)][PF<sub>6</sub>], **1b–7b**, applied as precatalysts in the model reaction were synthesized by halogen abstraction on the corresponding neutral derivatives, [Pd(CH<sub>3</sub>)Cl(Ar-BIAN)][PF<sub>6</sub>], **1a–7a**, following the literature methodology (Scheme 2).<sup>17,21</sup>

Ligands **3** and **7** and the related palladium complexes were characterized in solution by NMR spectroscopy. For Ar-BIANs, (*E,E*) and (*E,Z*) isomers are possible according to the relative configuration of the aryl rings with respect to the C=N imine bonds. In general, only the *E,E* isomer is observed for symmetrical Ar-BIANs,<sup>19</sup> but a variable amount of the *E,Z* isomer is always found in the case of nonsymmetrical Ar,Ar'-BIAN derivatives<sup>16–18,20</sup> and for alkyl-BIANs.<sup>22,23</sup> For both ligands **3** and **7**, the <sup>1</sup>H NMR spectrum recorded at room temperature in CDCl<sub>3</sub> and CD<sub>2</sub>Cl<sub>2</sub>, respectively, indicated the presence in solution of the *E,E* isomer only. Though this was expected for the latter, it is surprising for the former. The NMR characterization of complexes **7a** and **7b** was in line with data reported in the literature for analogous compounds with symmetrically substituted Ar-BIANs.<sup>12,17,18</sup> In the case of complexes **3a** and **3b**, bearing the nonsymmetrical ligand **3** on palladium, in analogy with what we reported for complexes **1a**, **2a** and **1b**, **2b**,<sup>17</sup> *cis* and *trans* isomers were observed in solution differing in the relative position of the Pd–CH<sub>3</sub> fragment with respect to the two halves of the ligand. We define as *trans* the isomer having the Pd–CH<sub>3</sub> fragment, or more generally the Pd–C bond, *trans* to the Pd–N bond of the aryl ring substituted with

electron-withdrawing groups (Scheme 2). According to the <sup>1</sup>H NMR spectra the *trans* to *cis* ratio was 3 : 1 and 5 : 1 for **3a** and **3b**, respectively.

Single crystals suitable for X-ray analysis were obtained for complexes **1a** and **3a** by slow diffusion of diethyl ether into a CD<sub>2</sub>Cl<sub>2</sub> solution of the complexes kept at 4 °C for one week. The crystal structure of the complex [Pd(CH<sub>3</sub>)Cl(**5**)] with the symmetrically substituted <sup>m</sup>Ar-BIAN with CF<sub>3</sub> groups in *meta* position has already been reported,<sup>24</sup> thus allowing a comparison of its structural features with those of **1a** and **3a**.

In the crystals of complexes with the nonsymmetrical Ar, Ar'-BIANs **1** and **3**, only the *trans* isomer was detected in the unit cell (Fig. 2, Table 1), in agreement with the NMR characterization in solution that showed this species to be the prevailing isomer. This confirms our previous report regarding the complex [Pd(CH<sub>3</sub>)Cl(**8**)], where **8** is the nonsymmetrical Ar, Ar'-BIAN characterized by one aryl ring substituted by CH<sub>3</sub> groups in *ortho* position and the other ring having CF<sub>3</sub> substituents in *meta*.<sup>18</sup>

In the complexes the palladium ion attains the expected square planar coordination geometry. In agreement with the *trans* influence of the Pd–CH<sub>3</sub> fragment, in both complexes the Pd–N1 bond distance *trans* to it is remarkably longer than the other Pd–N bond length. If a comparison of coordination bond distances is limited to complexes **1a**, **3a** and **5a** (all having <sup>m</sup>Ar-BIAN), the Pd–N1 bond length is 2.225(8), 2.205(5) and 2.227(4) Å, respectively. This indicates that ligand **3** appears to be more strongly bonded to palladium, as a result of lower steric hindrance and electron-withdrawing effect of F with respect to CF<sub>3</sub>. This is also supported by the corresponding values measured for the Pd–N2 bond distance, *trans* to chloride, which is the shortest among the three (2.042(5) Å for **3a** vs. 2.063(7) and 2.073(5) Å for **1a** and **5a**, respectively).

Another similarity in the structural features of the studied complexes is concerned with the orientation of the substituted phenyl rings with respect to the BIAN plane. The dihedral angle between the BIAN plane and the aryl ring on the side of the Pd–Cl bond falls in the range 52.5°–64.5°, while that on the side of the Pd–CH<sub>3</sub> bond is 76.4°–80.06° indicating that the aryl ring is almost orthogonally oriented with respect to the BIAN plane. These values indicate a greater conformational freedom on the Pd–Cl side than on the Pd–CH<sub>3</sub> part, reasonably due to the less steric hindrance of chloride with respect to that of the methyl group.

For the complexes with the nonsymmetrical Ar,Ar'-BIANs, the preference, both in solution and in the solid state, towards the *trans* isomer is in agreement with the literature data on palladium complexes with bidentate nitrogen-donor ligands having electronically nonequivalent N atoms<sup>21,25–28</sup> and with the general trend that the weakest ligand (here the nitrogen atom bearing the fluorine substituted aryl ring) is found *trans* to the stronger *trans*-labilizing ligand (here the methyl group). The opposite preference towards the *cis* isomer was observed in the case of high steric hindrance around the palladium centre.<sup>29</sup>

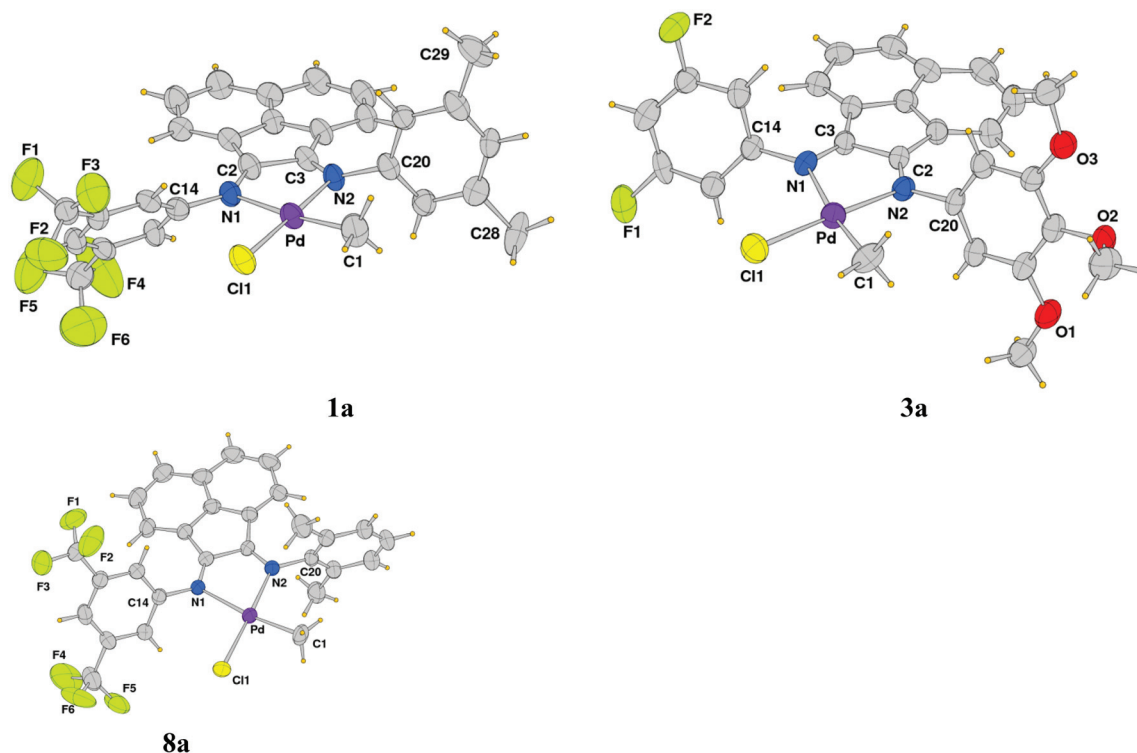


Fig. 2 The ORTEP drawing (thermal ellipsoids at the 35% probability level) of complexes **1a**, **3a** and **8a**.<sup>18</sup>

Table 1 Selected bond lengths and angles for complexes **1a** and **3a**

	<b>1a</b>	<b>3a</b>
<i>Lengths (Å)</i>		
Pd–N(1)	2.225(8)	2.205(5)
Pd–N(2)	2.063(7)	2.042(5)
Pd–C(1)	2.011(10)	2.020(6)
Pd–Cl(1)	2.294(3)	2.279(2)
<i>Angles (°)</i>		
N(1)–Pd–N(2)	78.3(3)	78.7(2)
N(1)–Pd–C(1)	171.6(3)	172.1(3)
N(1)–Pd–Cl(1)	99.2(2)	100.56(15)
N(2)–Pd–C(1)	93.3(4)	93.9(3)
N(2)–Pd–Cl(1)	177.3(2)	177.17(17)
C(1)–Pd–Cl(1)	89.2(3)	87.0(2)

### Kinetic investigations and modeling

**General outcome.** We reported that the monocationic complexes **1b**, **2b**, **4b–6b** generated active catalysts for the CO/styrene and the CO/4-Me-styrene copolymerization yielding the corresponding polyketones with an atactic microstructure.<sup>17</sup> Both the productivity and the molecular weight of the synthesized copolymers were affected by the nature of the substituents. Even though some differences in the order of productivity of the catalysts were observed for the two alkenes and the effect of the ligand nature was more pronounced in the case of styrene than for 4-methylstyrene, for both alkenes the catalysts with the nonsymmetrical Ar,Ar'-BIANs **1** and **2** were found to be the most productive within the series.<sup>17</sup> In particular, with styrene, ligand **2** generated the most

productive catalyst among those tested (3.70 kg CP per g Pd), while in the case of 4-Me-styrene the highest productivity was reached with the catalyst obtained from complex **1b** (2.36 kg CP per g Pd). For both alkenes, the catalyst with ligand **1** showed a productivity remarkably higher than that of the catalysts with the related symmetrically substituted *m*-Ar-BIANs, **4** and **5**. The same trend was observed for the CO/styrene copolymerization catalyzed by **2b** with respect to **5b** and **6b**, while in the CO/4-Me-styrene copolymerization the productivity obtained with **2b** was slightly lower than that obtained with **6b** (1.64 kg CP per g Pd vs. 1.95 kg CP per g Pd).<sup>17</sup> Moreover, in the CO/styrene copolymerization no formation of inactive palladium metal was observed, whereas in the case of CO/4-Me-styrene copolymerization, catalyst decomposition was sometimes observed even in the presence of 1,4-benzoquinone.<sup>17</sup>

To have a better understanding of the catalytic behavior of these complexes some kinetic investigations were performed by taking advantage of an automated parallel reactor (AMTEC SPR16), allowing us to monitor the CO uptake during the copolymerization reactions. All the catalytic tests were carried out in 2,2,2-trifluoroethanol (TFE) in the presence of 1,4-benzoquinone [BQ; [BQ]/[Pd] = 5], at  $T = 30^\circ\text{C}$ , under a preferential CO pressure of 5 bar, and with a ratio [alkene]/[Pd] = 22 000 for the runs involving 4-methylstyrene and 25 000 for those with styrene. The large excess of the vinyl arene used ensures conditions of pseudo-zero order with respect to the alkene even for a longer reaction time.

As a general comment, depending on the nature of the ligand bonded to palladium, within the first 24 hours of

reaction some catalysts show an almost linear dependence of CO uptake with time while others deactivate to a much higher extent. This catalytic behavior is different from that found by us for analogous palladium complexes with ligands belonging to the family of 1,10-phenanthroline<sup>21</sup> that over a range of 90 h showed a linear dependence of CO uptake with time, in agreement with the stronger coordinating capability of phenanthroline ligands with respect to that of Ar-BIANs.<sup>20</sup>


The comparison of the CO uptake curves of precatalyst **1b** with those of complexes **4b** and **5b** having the corresponding symmetrical *m*-Ar-BIANs probes evidences that for both alkenes the catalyst with ligand **5** is deactivated within the first hour of reaction, while for the catalyst with ligand **1** deactivation is limited and the complex with **4** is the only one that does not show any deactivation process for at least 24 hours (Fig. 3). With 4-Me-styrene, the active species containing the nonsymmetrical ligand **1** is remarkably more productive than the catalysts with the two symmetrical counterparts (Fig. 3, left), while for styrene the same trend is observed in the first 14 hours of

reaction. Afterwards the activity of the catalyst with ligand **1** decreases and becomes lower than that of the catalyst with ligand **4** (Fig. 3, right).


When the same comparison is made among the catalysts with the nonsymmetrical ligand **2** and those with the related symmetrical ligands **5** and **6**, the active species containing ligand **6** was found to be much more productive than that having the related nonsymmetrical Ar,Ar'-BIAN **2** in the CO/4-Me-styrene copolymerization (Fig. 4, left).

The lower productivity of **2b** with respect to that of **6b** might be related to the presence of the CF<sub>3</sub> groups on one of the aryl rings of **2** that might have a negative effect for steric reasons. This hypothesis is supported by the investigation of the catalytic behavior of complex **3b**, where the nonsymmetrical Ar,Ar'-BIAN **3** is analogous to **2** but with fluorine substituents in place of CF<sub>3</sub> groups (Fig. 5).

By comparing the CO uptake curves of **3b**, **6b** and **7b** it is evident that, in analogy with the trends involving **5b**, the symmetrical ligand with the electron-withdrawing substituent

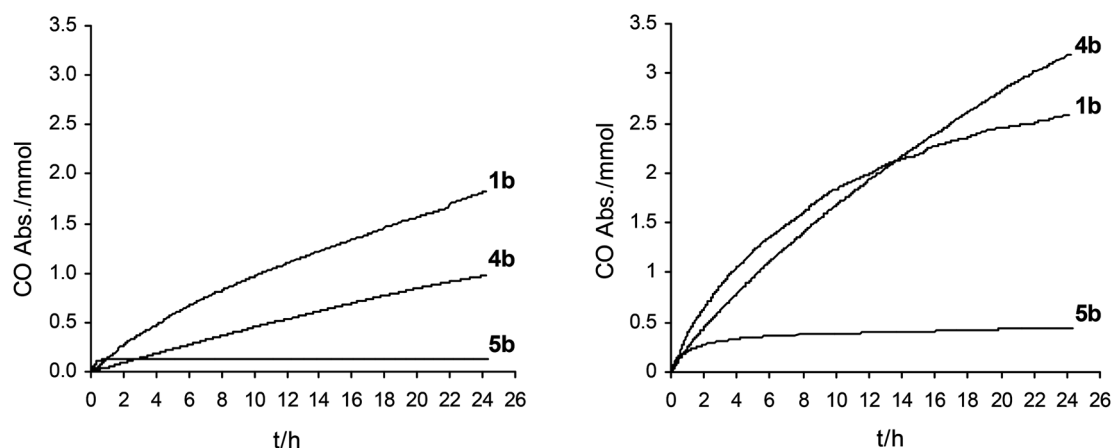


**Fig. 3** CO/vinyl arene copolymerization: effect of Ar-BIAN ligand on CO uptake. Catalyst precursor: [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(Ar-BIAN)][PF<sub>6</sub>] (**1b**, **4b**, **5b**). Reaction conditions:  $n_{\text{Pd}} = 0.106 \times 10^{-5}$  mol,  $T = 30$  °C, TFE  $V = 5$  mL,  $P_{\text{CO}} = 5$  bar,  $t = 24$  h,  $[\text{BQ}]/[\text{Pd}] = 5$ , vinyl arene  $V = 3$  mL,  $[\text{styrene}]/[\text{Pd}] = 25\,000$ ,  $[\text{4-Me-styrene}]/[\text{Pd}] = 22\,000$ . Left: CO/4-Me-styrene; right: CO/styrene copolymerization.

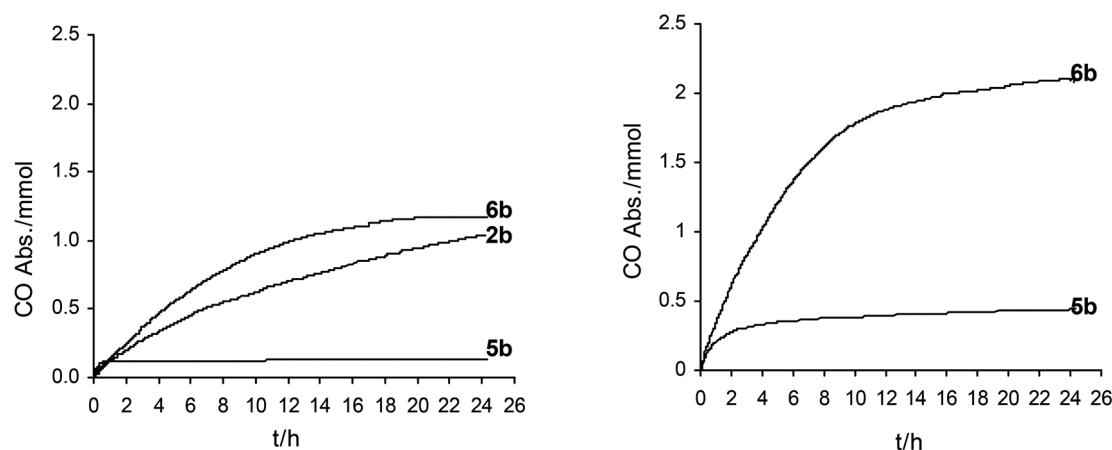

**Fig. 4** CO/vinyl arene copolymerization: effect of Ar-BIAN ligand on CO uptake. Catalyst precursor: [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(Ar-BIAN)][PF<sub>6</sub>] (**2b**, **5b**, **6b**). Reaction conditions: see Fig. 3. Left: CO/4-Me-styrene; right: CO/styrene.



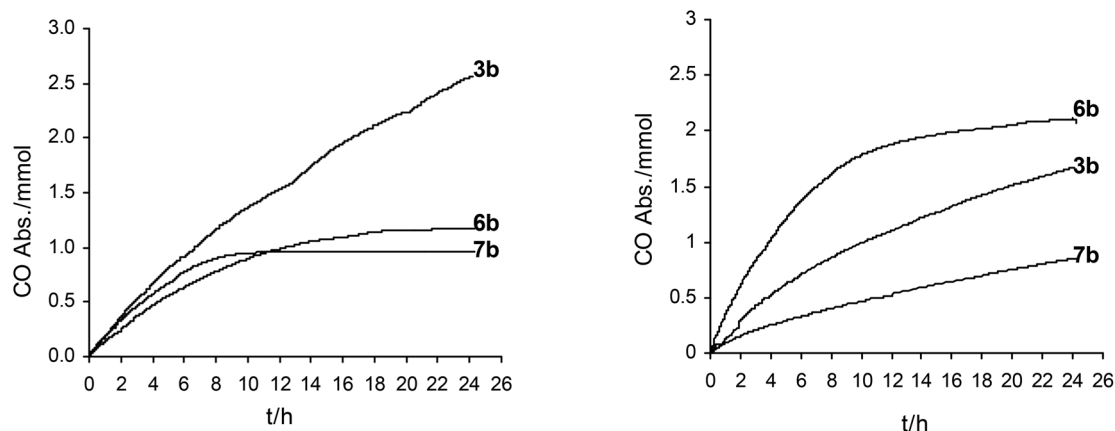


**Fig. 5** CO/vinyl arene copolymerization: effect of Ar-BIAN ligand on CO uptake. Catalyst precursor:  $[\text{Pd}(\text{CH}_3)(\text{CH}_3\text{CN})(\text{Ar-BIAN})][\text{PF}_6]$  (**3b**, **6b**, **7b**). Reaction conditions: see Fig. 3. Left: CO/4-Me-styrene; right: CO/styrene.

fluorine, **7**, generates the least productive species for both alkenes. The catalyst with the nonsymmetrical ligand **3** is found to be less productive than that with the corresponding symmetrical methoxy-substituted Ar-BIAN **6** for the CO/styrene copolymerization (Fig. 5, right), whereas in the CO/4-Me-styrene copolymerization, the catalyst with **3** shows a remarkably higher productivity than the active species with the symmetrically substituted ligand **6** (Fig. 5, left). Thus, at least for the 4-Me-styrene the replacement of the  $\text{CF}_3$  groups with fluorine atoms had a remarkable positive effect, in agreement with the lower value of both the Hammett  $\sigma$  constant (electronic effect) and the Taft parameter (steric effect) of fluorine with respect to  $\text{CF}_3$ .<sup>30</sup>

**Set up of the kinetic modeling.** Although the aforementioned differences in total productivity are well defined, a closer examination of the reaction profiles evidences that the reason for these behaviors is far from clear-cut. In most cases productivity inversions are noted over time with different catalysts and some of those showing the lowest final productivity are indeed the most active in the early stages of the reaction, suggesting that catalyst deactivation plays a relevant role in the final productivity order.

In order to gain a better understanding of the kinetic outcome of the different reactions and of the productivity inversions mentioned above, we engaged in a mathematical modeling of the reaction profiles that could take into account both the chain propagation and the catalyst deactivation. The followed approach is not a standard one and several problems needed to be solved. In order to keep the article text as compact as possible, only a general description of the method employed is reported, whereas more details can be found in the ESI.†

A general reaction pathway evidencing the catalyst decomposition is shown in Scheme 3. A palladium(II) species catalyzes the copolymerization reaction with a kinetic constant  $k_p$  (the kinetic order with respect to the reagents has been left unspecified for the moment). Since the olefin is present in large excess and CO is continuously replenished, the

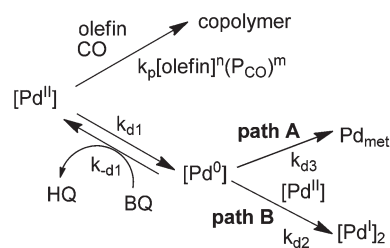

**Scheme 3** Simplified reaction pathways for kinetic modeling.

concentration of both reagents is constant during the reaction and the rate depends only on the active palladium concentration, which decreases with time because of catalyst decomposition:

$$\text{rate} = k_1[\text{Pd}^{\text{II}}] \quad (1)$$

where  $k_1$  is the apparent first order kinetic constant with respect to the active catalyst concentration.

Experimentally, the actual reaction rate is measured by the CO consumption ( $\text{mmol h}^{-1}$ ), but in order to have the kinetic constants expressed in the usual  $(\text{time})^{-1}$  units (for first order kinetics) it is better to divide the CO absorption (in mmol) by the reaction solution volume ( $V = 8 \text{ mL}$  for all reactions). That is:

$$\begin{aligned} \text{rate} &= d[(\text{CO abs./mmol})/(V/\text{mL})]/dt \\ &= k_p[\text{Pd}^{\text{II}}][\text{olefin}]^n(\text{P}_{\text{CO}})^m = k_1[\text{Pd}^{\text{II}}] \end{aligned} \quad (2)$$

where  $[\text{Pd}^{\text{II}}]$  depends on time.

As far as catalyst decomposition is concerned, it is well recognized that in the present catalytic system this is due to palladium(II) reduction, as supported by the fact that benzoquinone retards such deactivation by oxidizing back the palladium(0) complex (processes associated with  $k_{d1}$  and  $k_{-d1}$  in Scheme 3) and that metallic palladium is observed sometimes after complete catalyst deactivation. There is little doubt that the initial step of decomposition is the reduction of a single


palladium(II) complex to palladium(0). Although several possibilities exist for such a process, it is almost surely described by a first order kinetics with respect to palladium(II). What occurs later is less obvious. Several papers have been devoted to the kinetics of metallic nanoparticles formation, but they usually focus on later stages of the reaction.<sup>31,32</sup> As far as the early stages of decomposition are concerned, we can identify two general reaction pathways.

In the first pathway (path A in Scheme 3), the palladium(0) complex decomposes by an irreversible unimolecular pathway, *e.g.* an irreversible loss of the nitrogen ligand, eventually giving metallic palladium. Alternatively, the palladium(0) complex can react with a palladium(II) complex to afford an inactive palladium(I) dimer (path B in Scheme 3). Precedents exist for such a process.<sup>33–35</sup> Very recently some of us identified a series of complexes of general structure  $[\text{Pd}^{\text{I}}\text{L}^2\text{X}(\mu\text{-CO})]_2$  ( $\text{L}^2 = 1,10\text{-phenanthroline}, 2,2'\text{-bipyridine}$  or their substituted analogues,  $\text{X} = \text{halide}, \text{carboxylate}, \text{-C(O)OMe}$ ) as intermediates in the reduction of palladium(II) complexes by CO and water or alcohols under conditions close to those employed in the presently studied system<sup>36</sup> and the formation of the corresponding Ar-BIAN complexes may as well occur easily.<sup>37</sup>

Modeling the complete system without knowing the benzoquinone concentration *vs.* time profile is not possible in general, even if the steady state approximation is applied to the Pd(0) complex. However, in those cases in which deactivation is limited, it can be approximated that benzoquinone concentration is essentially constant during the reaction. Under these conditions paths a and b can be, respectively, approximately described by a first and a second kinetics with respect to palladium(II) concentration (Scheme 4). Note that the exact identity of the inactive species formed during the decomposition is not known and differs between the two pathways. However, this is not relevant at all to the kinetic of the copolymerization reaction as experimentally measured.

The first order decomposition is described by eqn (3) and (4):

$$\frac{d[\text{Pd}^{\text{II}}]}{dt} = -k_2[\text{Pd}^{\text{II}}] \quad (3)$$

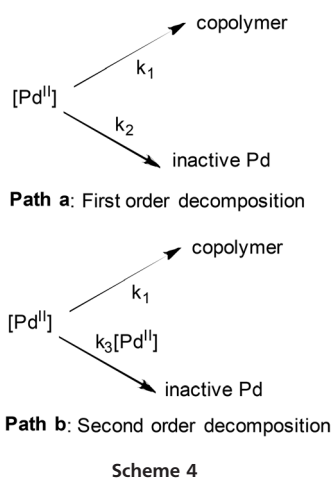

Scheme 4

$$[\text{Pd}^{\text{II}}]_t = [\text{Pd}^{\text{II}}]_0 e^{-k_2 t} \quad (4)$$

where  $[\text{Pd}^{\text{II}}]_0$  and  $[\text{Pd}^{\text{II}}]_t$  are the palladium(II) concentrations at time zero and  $t$  respectively.

From eqn (4) and (2), eqn (5) is derived, which leads to eqn (6) after integration.

$$\text{rate} = d[(\text{CO abs})/V]/dt = k_1[\text{Pd}^{\text{II}}]_0 e^{-k_2 t} \quad (5)$$

$$(\text{CO abs})/V = (k_1/k_2)[\text{Pd}^{\text{II}}]_0(1 - e^{-k_2 t}) \quad (6)$$

where  $[\text{Pd}^{\text{II}}]_0 = 1.32 \times 10^{-4} \text{ M}$ .

Eqn (6) is of the type  $Y = a(1 - e^{-bx})$ , a Stirling type function that can be modeled by a suitably modified fitting function in the program Origin, to give the best  $a$  and  $b$  values, from which  $k_1$  and  $k_2$  are immediately calculated.

For the second order decomposition pathway, an analogous procedure leads to the equations:

$$d[\text{Pd}^{\text{II}}]/dt = -k_3[\text{Pd}^{\text{II}}]^2 \quad (7)$$

$$[\text{Pd}^{\text{II}}]_t = [\text{Pd}^{\text{II}}]_0 / (1 + k_3[\text{Pd}^{\text{II}}]_0 t) \quad (8)$$

$$\text{rate} = d[(\text{CO abs})/V]/dt = k_1[\text{Pd}^{\text{II}}]_0 / (1 + k_3[\text{Pd}^{\text{II}}]_0 t) \quad (9)$$


$$(\text{CO abs})/V = (k_1/k_3) \ln(1 + k_3[\text{Pd}^{\text{II}}]_0 t) \quad (10)$$

Eqn (10) corresponds to a logarithmic function that can again be modeled in Origin.

**Fitting by integration of the 4-Me-styrene experiments run under 5 bar CO.** The most extensive series of experiments both with styrene and 4-methylstyrene were run under 5 bar CO and at  $[\text{BQ}]/[\text{Pd}] = 5$ . Since deactivation was clearly lower with the latter substrate, we will start analyzing the corresponding set of data. The plots of CO absorption *vs.* time for selected reactions are reported in Fig. 3–5, while the corresponding plots for the complete set of experiments presently discussed are reported in the ESI (Fig. S1†).

Even from a quick examination of Fig. 6 it is clear that eqn (10) fits very well the data in the whole time region, whereas eqn (6) tends to underestimate catalyst decomposition (which is proportional to the second derivative of the CO absorption plot; see later) at the beginning of the reaction and to overestimate it later. The initial underestimation is especially significant. In fact, if the assumption that the benzoquinone concentration is approximately constant was wrong, then catalyst decomposition should be slower than that calculated during the first part of the reaction, when benzoquinone is more abundant. This would result in the model giving an even worse fitting of the data and cannot justify the observed discrepancies. Thus it is clear that the process associated with path a must be discarded as a relevant deactivation mode for palladium, whereas the goodness of the fit obtained by modeling path b strongly supports its operation. It is worth noting that such a good fit was obtained with only two floating parameters, which would be unlikely to occur if the physical basis of the model were wrong.

Eqn (10) could be used to fit the data of five of the reaction profiles with an excellent approximation ( $\text{adj. } R^2 > 0.999$ ), but

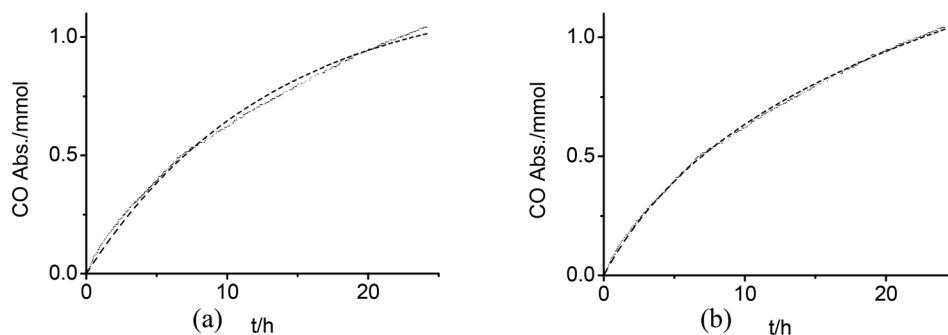

**Fig. 6** Data for the copolymerization of 4-Me-styrene under 5 bar CO ([BQ]/[Pd] = 5) with ligand **2**, 3,5-(CF<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>;3,4,5-(CH<sub>3</sub>O)<sub>3</sub>C<sub>6</sub>H<sub>2</sub>-BIAN. (a) Fitting by eqn (6) (first order decomposition). (b) Fitting by eqn (10) (second order decomposition). Fitting functions are shown as dashed lines (---).

**Table 2**  $k_1$  and  $k_3$  values calculated from eqn (10) and  $k'_1$  and  $k'_3$  values calculated as detailed in the ESI for reactions run with 4-Me-styrene under 5 bar CO ([BQ]/[Pd] = 5)

Ligand	$\Sigma\sigma/2$	$k_1/\text{h}^{-1}$	$k'_1/\text{h}^{-1}$	$k_3/\text{h}^{-1} \text{ M}^{-1}$	$k'_3/\text{h}^{-1} \text{ M}^{-1}$
[3,5-(CH <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ] <sub>2</sub> -BIAN ( <b>4</b> )	-0.14	46	45	$1.27 \times 10^2$	$1.33 \times 10^2$
[3,4,5-(CH <sub>3</sub> O) <sub>3</sub> C <sub>6</sub> H <sub>2</sub> ] <sub>2</sub> -BIAN ( <b>6</b> )	-0.03		182		$7.85 \times 10^2$
Ph <sub>2</sub> -BIAN	0	149	144	$2.79 \times 10^2$	$2.05 \times 10^2$
3,5-F <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,4,5-(CH <sub>3</sub> O) <sub>3</sub> C <sub>6</sub> H <sub>2</sub> -BIAN ( <b>3</b> )	0.325	173	151	$5.48 \times 10^2$	$2.85 \times 10^2$
3,5-(CH <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,5-(CF <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> -BIAN ( <b>1</b> )	0.36	125	123	$6.09 \times 10^2$	$1.40 \times 10^3$
3,5-(CF <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,4,5-(CH <sub>3</sub> O) <sub>3</sub> C <sub>6</sub> H <sub>2</sub> -BIAN ( <b>2</b> )	0.415	105	122	$1.36 \times 10^3$	$1.12 \times 10^3$
[3,5-F <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ] <sub>2</sub> -BIAN ( <b>7</b> )	0.68		188		$2.51 \times 10^3$
[3,5-(CF <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ] <sub>2</sub> -BIAN ( <b>5</b> )	0.86		553		$3.35 \times 10^4$

gave significant deviations in the remaining three cases (ligands [3,5-(CF<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>]<sub>2</sub>-BIAN **5**, [3,4,5-(CH<sub>3</sub>O)<sub>3</sub>-C<sub>6</sub>H<sub>2</sub>]<sub>2</sub>-BIAN **6**, [3,5-F<sub>2</sub>C<sub>6</sub>H<sub>3</sub>]<sub>2</sub>-BIAN **7**), where catalyst decomposition is more evident and the assumption that benzoquinone concentration does not vary is clearly untenable. The values of  $k_1$  and  $k_3$  best fitting the data for these five cases are reported in Table 2.

A discussion of the  $k_1$  and  $k_3$  trends specific for this set of data can be found in the ESI.<sup>†</sup> However, we have developed a mathematical approach to obtain the desired data even for the three reactions that did not give a good fitting with the procedure described above and only the results of the full set of experiments will be described here.

The new approach, described in detail in the ESI,<sup>†</sup> is based on the following considerations:

(1) Since the CO pressure is kept constant and the olefin concentration is high enough that it can be considered constant during the reaction (pseudo zero order kinetics with respect to both CO and olefin), the reaction rate is proportional only to the active palladium concentration. The reaction rate as a function of time can be obtained by differentiating the CO absorption curve.

(2) Given what was said above, the opposite of the derivative of the active catalyst concentration with respect to time, corresponding to the second derivative of the CO absorption plot, is the rate of decomposition of the catalytic system.

Developing these concepts, a series of parallel values for the  $k_1$  and  $k_3$  values could be determined and are also presented in Table 2. We named the values calculated in this way  $k'_1$  and  $k'_3$  to distinguish them from those calculated by the


fitting procedure described in the previous paragraph, although  $k_1$  and  $k'_1$  should ideally be the same. A comparison between the  $k_1$  and  $k'_1$  values in Table 2 for corresponding reactions shows that the agreement is excellent in three out of five cases ([3,5-(CH<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>]<sub>2</sub>-BIAN, **4**:  $k_1 = 46$ ,  $k'_1 = 45$ ; Ph<sub>2</sub>-BIAN:  $k_1 = 149$ ,  $k'_1 = 144$ ; 3,5-(CH<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>;3,5-(CF<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>-BIAN, **1**:  $k_1 = 125$ ,  $k'_1 = 123$ ), but it is acceptable even for the other two, thus validating the mathematical approach employed.

Plots of the first and second derivatives of CO absorption of representative reactions are shown in Fig. 7 and 8. Plots for all the reactions are presented in the ESI (Fig. S6 and S7<sup>†</sup>).


Even a qualitative inspection of derivative plots reveals that the more active systems deactivate more quickly and also confirms that electron-withdrawing substituents give more active systems. The activity and deactivation rates of the catalyst with [3,5-(CF<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>]<sub>2</sub>-BIAN, **5**, as ligand, are striking. Although on a long timescale, **5b** gave worse conversion (see Fig. 3), from Fig. 7 it appears that at short reaction times it affords by far the more active catalytic system, although the corresponding deactivation rate is also extremely high (Fig. 8).

In previous papers some of us have shown that the logarithm of the relative coordinating strength of substituted Ar-BIAN ligands shows a good correlation with the Hammett  $\sigma$  constants.<sup>20,38</sup> When two substituents were present, the correlation was maintained if the sum of the two individual  $\sigma$  was employed, whereas ligands having different substituents on the two aryl rings followed the same trend if the arithmetic average of the Hammett  $\sigma$  constants for the two rings was employed in the correlation.<sup>16</sup> In general, this corresponds to



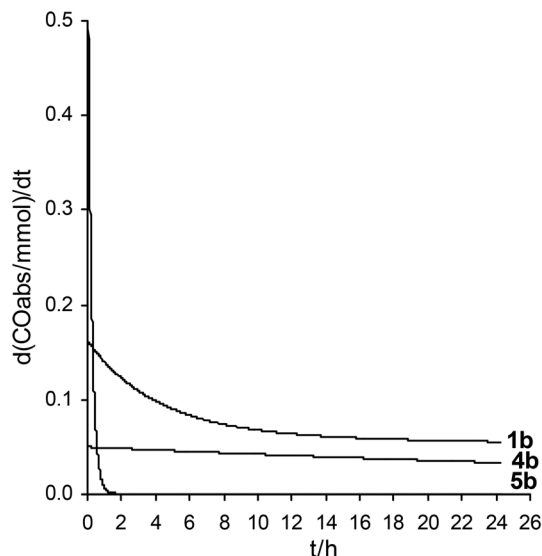

**Fig. 7** 1<sup>st</sup> derivative plot for CO/4-Me-styrene copolymerization. Catalyst precursor: [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(Ar-BIAN)][PF<sub>6</sub>] (**1b**, **4b**, **5b**). Reaction conditions: see Fig. 3.

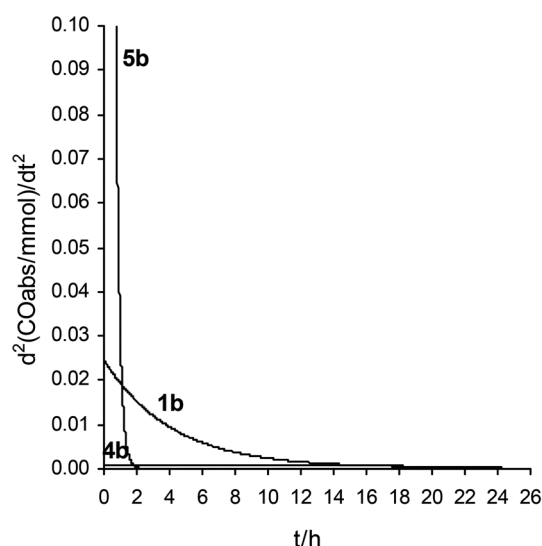


**Fig. 8** 2<sup>nd</sup> derivative plot for CO/4-Me-styrene copolymerization. Catalyst precursor: [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(Ar-BIAN)][PF<sub>6</sub>] (**1b**, **4b**, **5b**). Reaction conditions: see Fig. 3.

employing for both symmetrical and nonsymmetrical ligands the value of  $\Sigma\sigma/2$  (where the sum is extended to all substituents on the two rings), which is also shown in Table 2.

A logarithmic plot of  $k'_1$  with respect to  $\Sigma\sigma/2$  is shown in Fig. 9.

From the plot it appears that as a general rule electron-withdrawing groups lead to more active systems, although a clean linearity of  $\ln k'_1$  vs.  $\Sigma\sigma/2$  is not observed.

Ligand **6** with six methoxy groups is that which deviates more strongly from the value expected based on its  $\Sigma\sigma/2$  and steric hindrance. In general, ligands having an aryl ring with three methoxy groups are those that fit less the correlation

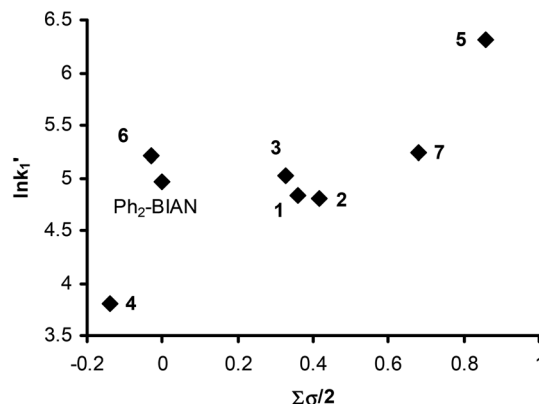

**Fig. 9** Plot of  $\ln k'_1$  vs.  $\Sigma\sigma/2$  for the copolymerization reactions of 4-Me-styrene with CO (5 bar).


even for the reactions of unsubstituted styrene to be discussed in the following and [3,4,5-(CH<sub>3</sub>O)<sub>3</sub>C<sub>6</sub>H<sub>2</sub>]<sub>2</sub>-BIAN is that which deviates more from the correlation even with the latter substrate. It should be considered that the methoxy group has strong and opposing inductive and resonance effects and the  $\Sigma\sigma$  value appears to afford a worse quantification of the electronic effects of the trimethoxyphenyl group than for other substituents. It should also be recalled that the catalytic reactions were run in trifluoroethanol, a solvent that gives strong hydrogen bonds. The methoxy oxygen is a likely donor for such hydrogen bonds and their formation would result in a decrease of the electron-donating properties of the trimethoxyphenyl group. As a matter of fact, the data for trimethoxy-substituted ligands statistically deviate from the general plot in the direction expected for a more electron-poor ligand.

The quantitative agreement between  $k'_3$  and  $k_3$  values is worse than in the case of  $k_1$ , but this was expected because now even the approximations involved in the determination of the second derivative are involved. However, the trend is the same for both series of values and a logarithmic plot of  $k'_3$  vs.  $\Sigma\sigma/2$  is shown in Fig. 10 (the corresponding plot of  $k_3$  vs.  $\Sigma\sigma/2$  is presented in the ESI†).


From the plots (Fig. 10 and S4†) it is evident that the presence of electron-withdrawing substituents leads to catalytic systems that deactivate at a faster rate (higher  $k_3$  and  $k'_3$  values) and an approximately linear correlation with  $\Sigma\sigma/2$  exists. Again the methoxy-substituted ligands are those that statistically deviate more from the correlation.

**Fitting of the data of the styrene experiments run under 5 bar CO.** A series of experiments paralleling those just described, but employing unsubstituted styrene as the substrate was also performed. The plots of some of the reactions were already presented in Fig. 3–5. The plots of all reactions are reported in the ESI (Fig. S10†). The experiment using 3,5-(CF<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>;3,4,5-(CH<sub>3</sub>O)<sub>3</sub>C<sub>6</sub>H<sub>2</sub>-BIAN, **2**, as ligand gave some problems and has been discarded.

The data were subjected to the same mathematical treatment as that described for the 4-Me-styrene reactions. Given the negative results previously obtained with the first order

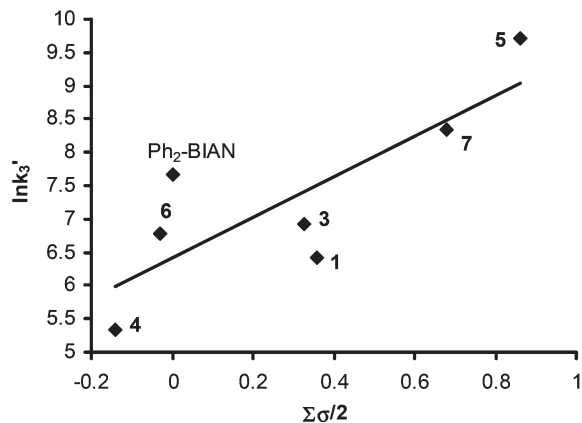

**Fig. 10** Plot of  $\ln k'_3$  vs.  $\Sigma\sigma/2$  for the copolymerization reactions of 4-Me-styrene with CO (5 bar).

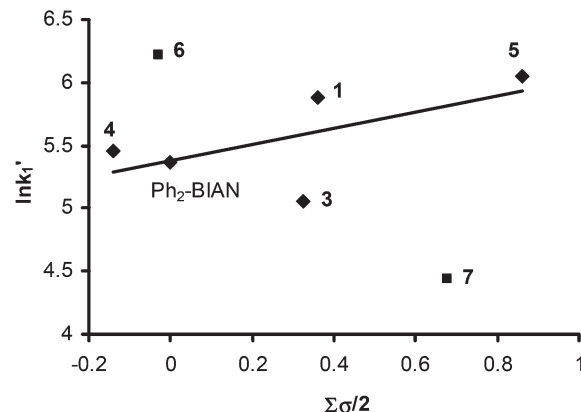


**Fig. 11** Plot of  $\ln k'_1$  vs.  $\Sigma\sigma/2$  for the copolymerization reactions of styrene with CO (5 bar). The straight line corresponds to the best fit to the data points, excluding those for [3,4,5-(CH<sub>3</sub>O)<sub>3</sub>C<sub>6</sub>H<sub>2</sub>]<sub>2</sub>-BIAN, **6**, and [3,5-F<sub>2</sub>C<sub>6</sub>H<sub>3</sub>]<sub>2</sub>-BIAN, **7**.

decomposition model, only the fit to the second order one was performed. The same three ligands that had failed to give data series that could be fitted by eqn (10) in the case of 4-Me-styrene also gave a poor fit in the present case, which leaves only four data points for which very good results were obtained. The calculated values of  $k_1$  and  $k_3$  are reported in Table 3 and are graphically represented in Fig. S11 and S12 (ESI†).

To get information even from the remaining three reactions, the same interpolation/differentiation procedure as that described for 4-Me-styrene was then applied. The corresponding derivative plots are shown in Fig. S13 and S14 (ESI†).

From these plots, the  $k'_1$  and  $k'_3$  values can be calculated as described for the 4-Me-styrene reactions. Results are also presented in Table 3 and logarithmic plots of  $k'_1$  and  $k'_3$  vs.  $\Sigma\sigma/2$  are shown in Fig. 11 and 12, respectively. As for the case of 4-Me-styrene, only the most complete data series is discussed here, but a complete discussion of the results of the two data series can be found in the ESI.†

As in the case of 4-Me-styrene, there is good agreement between corresponding  $k_1$  and  $k'_1$  values and worse agreement between  $k_3$  and  $k'_3$  values, but the general trends are maintained. The  $k'_1$  value for [3,5-F<sub>2</sub>C<sub>6</sub>H<sub>3</sub>]<sub>2</sub>-BIAN, **7**, appears to be abnormally low, which may be due to extensive decomposition before the measurement of the consumed CO was started, as better discussed in the ESI.†

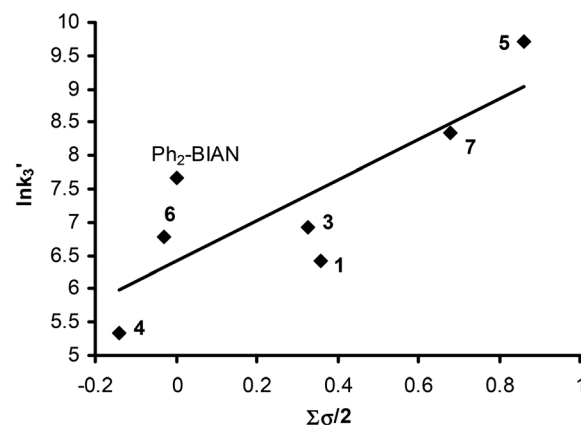

**Fig. 12** Plot of  $\ln k'_3$  vs.  $\Sigma\sigma/2$  for the copolymerization reactions of styrene with CO (5 bar). The straight line corresponds to the best fit to all data points.

In general the data follow the same trend as that evidenced for the 4-Me-styrene experiments, that is, electron-withdrawing substituents lead to more active but less stable, catalytic systems.

A more interesting comparison can be made between the corresponding  $k_1$  (or  $k'_1$ ) and  $k_3$  (or  $k'_3$ ) values for the two substrates. In a previous paper in which some of the same ligands employed here had been tested, it had been noted that a higher productivity was obtained with unsubstituted styrene,<sup>17</sup>

**Table 3**  $k_1$  and  $k_3$  values calculated from eqn (10) and  $k'_1$  and  $k'_3$  values calculated as detailed in the ESI for reactions run with styrene under 5 bar CO ([BQ]/[Pd] = 5)

Ligand	$\Sigma\sigma/2$	$k_1/\text{h}^{-1}$	$k'_1/\text{h}^{-1}$	$k_3/\text{h}^{-1} \text{ M}^{-1}$	$k'_3/\text{h}^{-1} \text{ M}^{-1}$
[3,5-(CH <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ] <sub>2</sub> -BIAN ( <b>4</b> )	-0.14	208	234	$4.94 \times 10^2$	$2.08 \times 10^2$
[3,4,5-(CH <sub>3</sub> O) <sub>3</sub> C <sub>6</sub> H <sub>2</sub> ] <sub>2</sub> -BIAN ( <b>6</b> )	-0.03		503		$8.88 \times 10^2$
Ph <sub>2</sub> -BIAN	0	231	213	$1.13 \times 10^3$	$2.16 \times 10^3$
3,5-F <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,4,5-(CH <sub>3</sub> O) <sub>3</sub> C <sub>6</sub> H <sub>2</sub> -BIAN ( <b>3</b> )	0.325	153	157	$1.11 \times 10^3$	$1.01 \times 10^3$
3,5-(CH <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,5-(CF <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> -BIAN ( <b>1</b> )	0.36	425	358	$3.05 \times 10^3$	$6.09 \times 10^2$
[3,5-F <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ] <sub>2</sub> -BIAN ( <b>7</b> )	0.68		85		$4.17 \times 10^3$
[3,5-(CF <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ] <sub>2</sub> -BIAN ( <b>5</b> )	0.86		422		$1.67 \times 10^4$

**Table 4**  $k_1$ ,  $k'_1$ ,  $k_3$  and  $k'_3$  values for reactions run at different CO pressures with different ligands (styrene as the substrate,  $[BQ]/[Pd] = 5$ )

Ligand		3 bar	5 bar	10 bar
3,5-F <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,4,5-(CH <sub>3</sub> O) <sub>3</sub> C <sub>6</sub> H <sub>2</sub> -BIAN (3)	$k_1$	77	153	
	$k'_1$	73	157	125
	$k_3$	$3.12 \times 10^2$	$1.11 \times 10^3$	
	$k'_3$	$2.16 \times 10^2$	$1.01 \times 10^3$	$1.03 \times 10^3$
3,5-(CH <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,5-(CF <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> -BIAN (1)	$k_1$	124	425	
	$k'_1$	125	358	
	$k_3$	$1.07 \times 10^3$	$3.05 \times 10^3$	
	$k'_3$	$3.66 \times 10^2$	$6.09 \times 10^2$	

contrary to what was generally reported in the literature.<sup>39–43</sup> The new, more extensive, series of data supports this observation, but also shows that the higher activity is also associated with a faster deactivation, since not only  $k_1$ , but also  $k_3$  values are consistently higher in the case of styrene. To the best of our knowledge, an active role of the olefin in the deactivation process has not been proposed before. We will discuss this aspect in more detail later, after having reported the rest of the results.


The faster deactivation is responsible for the less good agreement between  $k_1$  and  $k'_1$  and  $k_3$  and  $k'_3$  values, since all approximations become larger.

**Effects of CO pressure.** To investigate the effect of the carbon monoxide pressure, selected reactions were performed under either 3 or 10 bar CO. The fitted values are presented in Table 4, together with the corresponding  $k'_1$  and  $k'_3$  values, calculated as in the other cases. Note that the values for the reactions at 5 bar, already reported in Table 3, are shown again here for an immediate comparison.

The reactions under 5 bar are faster than those under 3 bar, but a further increase in pressure leads to a decrease in activity.<sup>44</sup> The additional information we get from the numerical simulations is that the decrease in productivity on going to 10 bar is not due to a faster catalyst deactivation in the last case. Indeed even  $k_1$  or  $k'_1$  decreases at 10 bar and moreover the values of  $k_3$  and  $k'_3$  increase on going from 3 to 5 bar, but are of the same order of magnitude for reactions run at 5 or 10 bar. This indicates that the rate of deactivation is higher under 5 rather than 3 bar of CO, but no faster deactivation takes place at higher CO pressures. Thus, the decrease in activity in the latter case is due to the inhibiting role of CO. This is a phenomenon well known for this reaction and the value of CO pressure at which this effect becomes evident depends on the catalyst nature, if dicationic<sup>45</sup> or monocationic<sup>21</sup> precatalysts are applied, and on the nature of the ancillary ligand bonded to palladium.<sup>21,46</sup>

**Effect of a longer reaction time and a larger amount of benzoquinone.** The effect of a longer reaction time was investigated by running selected reactions for 70 h instead of 25 h, under 10 bar CO. Since it was expected that deactivation would occur, a higher benzoquinone amount ( $[BQ]/[Pd] = 40$ ) was also added (Fig. 13).

From Fig. 13 it is evident that the addition of a larger amount of benzoquinone strongly stabilizes the catalytic system. Deactivation is very low during the first 24 hours,

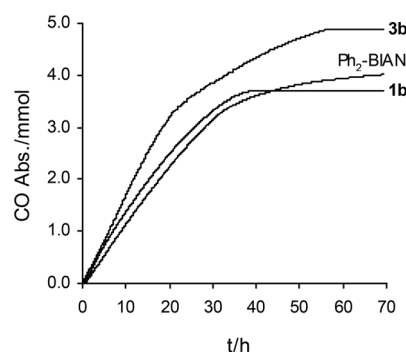

**Fig. 13** CO/styrene copolymerization: effect of reaction time and a higher  $[BQ]/[Pd]$  ratio. Catalyst precursor:  $[Pd(CH_3)(CH_3CN)(Ar-BIAN)][PF_6]$ . Reaction conditions:  $n_{Pd} = 0.106 \times 10^{-5}$  mol,  $T = 30$  °C, TFE  $V = 5$  mL,  $P_{CO} = 10$  bar,  $t = 70$  h,  $[BQ]/[Pd] = 40$ , styrene  $V = 3$  mL,  $[styrene]/[Pd] = 25\ 000$ .

contrary to what was previously observed under the same conditions, but with  $[BQ]/[Pd] = 5$ . The rate decrease that is observed in all cases after about 3.2 mmol CO have been absorbed is due to the polyketone precipitation in the reaction mixture with the switch of the catalytic system from homogeneous to a mixture of homogeneous and heterogeneous species, each of them displaying its own kinetic behavior. This phenomenon was previously pointed out in both the CO/ethylene<sup>47</sup> and CO/vinyl arene copolymerizations.<sup>43</sup> Thus, this decrease cannot be described by our models and we have limited the modeling to the first 24 h of reaction. Due to the increased catalyst stability, good fitting by the second order deactivation mode was obtained in all cases, but in order to have a direct comparison with data with the lower benzoquinone amount,  $k'_1$  and  $k'_3$  values were also calculated. All constant values are presented in Table 5. Good agreement exists between the two calculation approaches, except for the  $k'_3$  value for 3,5-(CH<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>;3,5-(CF<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>-BIAN, which appears to be overestimated.

Only one direct comparison can be made between reaction runs working at  $[BQ]/[Pd]$  ratios of 5 and 40 respectively, but otherwise under exactly the same conditions (styrene, 10 bar CO) as that involving 3,5-F<sub>2</sub>C<sub>6</sub>H<sub>3</sub>;3,4,5-(CH<sub>3</sub>O)<sub>3</sub>C<sub>6</sub>H<sub>2</sub>-BIAN. The  $k'_1$  value marginally increased (from 125 to 188; values in Tables 4 and 5, respectively) upon an increase in the benzoquinone amount, which may be due to the approximations in neglecting the deactivation before the gas consumption starts to be measured. However, it is  $k'_3$  that is most affected,

**Table 5** Values of  $k_1$ ,  $k_3$ ,  $k'_1$  and  $k'_3$  for reactions run with styrene, under 10 bar CO and with [BQ]/[Pd] = 40

Ligand	$\Sigma\sigma/2$	$k_1/\text{h}^{-1}$	$k'_1/\text{h}^{-1}$	$k_3/\text{h}^{-1} \text{ M}^{-1}$	$k'_3/\text{h}^{-1} \text{ M}^{-1}$
Ph <sub>2</sub> -BIAN	0	125	124	107	92
3,5-F <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,4,5-(CH <sub>3</sub> O) <sub>3</sub> C <sub>6</sub> H <sub>2</sub> -BIAN (3)	0.325	177	188	157	170
3,5-(CH <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> ;3,5-(CF <sub>3</sub> ) <sub>2</sub> C <sub>6</sub> H <sub>3</sub> -BIAN (1)	0.36	159	167	265	438

decreasing from  $1.03 \times 10^3$  to 170. This variation is in agreement with the literature about the role of the oxidant that affects catalyst stability but not catalytic rate.<sup>48,49</sup>


**General trends in the activity vs. time plots.** The fitting procedure allows us to estimate the values of the rate constants for both the propagation step of the polymer chain and the decomposition pathway of the catalyst for the two vinyl arenes and to correlate them to the nature of the Ar-BIAN bonded to palladium (Tables 2 and 3). The CO uptake curves with time highlight that all the studied Ar-BIAN catalysts were found to be more active in CO/styrene than in CO/4-Me-styrene copolymerization. This trend is in agreement with the productivity data obtained in the batch copolymerization reactions,<sup>17</sup> but is the opposite of that found in the case of the phenanthroline-containing catalysts.<sup>21,43</sup> The kinetic analysis shows that the higher activity of the present catalysts in the CO/styrene copolymerization is also associated with a faster deactivation, since not only  $k_1$ , but also  $k_3$  values are consistently higher than in the case of 4-Me-styrene (Tables 2 and 3). The values of the kinetic constants highlight that in the series of catalysts with the symmetric Ar-BIANs, those with electron-donating substituents show the lowest propagation and decomposition rate, while the ligands symmetrically substituted with CF<sub>3</sub> or F yield the most active catalysts, but also show the highest deactivation rate, in particular in the CO/4-Me-styrene copolymerization. These trends are in agreement with simple considerations about the coordination chemistry of the two comonomers: electron-donating substituents increase the electron density on palladium, disfavoring the nucleophilic attack of the alkene and increasing the  $\pi$ -back donation to CO, resulting in a stronger bond to the metal center. This in turn enhances its competing role, the combination of these effects being a slow reaction rate. On the other hand ligands with electron-donating substituents are more strongly bonded to palladium and, since the decomposition pathway requires ligand dissociation, the catalysts are more stable. In contrast, electron-withdrawing substituents decrease the electron density on the metal center favoring the attack of the alkene and decreasing the  $\pi$ -back donation to CO. The combination of these effects is a higher reaction rate. On the other hand ligands with electron-withdrawing substituents are more weakly bonded to palladium resulting in less stable catalysts. These considerations are correct from a general point of view; nevertheless, in peculiar cases the explanation is more complex. Indeed, the introduction of CF<sub>3</sub> groups to the ancillary ligands of catalysts for polymerization was reported to

result in either positive or negative effects depending on the position of the group with respect to the metal center. For instance, Ni(II) complexes with symmetrical <sup>o</sup>Ar-BIANs substituted on one *ortho* position only with a CF<sub>3</sub> group catalyzed ethylene polymerization, leading to oligomers instead of polymers for steric reasons, but with higher TOF than the catalyst with the related CH<sub>3</sub> substituted ligand for electronic effects.<sup>50</sup> Instead, when the CF<sub>3</sub> group is in a proper remote position of the ligand, as is the case for nickel-phenoxyiminato catalysts, an enhancement of catalyst activity and thermal stability and of molecular weight of the produced polyethylene was observed. These effects were attributed to C–H...F–C interactions between the hydrogen atom on the  $\beta$ -C atom of the growing polymer chain and the fluorine atom of the ligand, rather than to inductive effects.<sup>51</sup> In the present investigation the introduction of CF<sub>3</sub> groups to *meta* positions of the aryl rings has a detrimental effect on catalyst stability, despite the positive effect on catalyst activity.

This kinetic investigation highlights that among the catalysts with the nonsymmetrical ligands, that with ligand 3 is the most active and the slowest to decompose for CO/4-Me-styrene. The same is valid for CO/styrene but in this case the catalyst with ligand 1 is more active (Tables 2 and 3). By analyzing all the data as a whole, it is clear that the catalyst with ligand 3 represents the best compromise between the activity and rate of deactivation. By supposing that catalyst deactivation proceeds through ligand dissociation, the observed slow deactivation is in agreement with the higher stability of the active species thanks to the shorter Pd–N bond distances observed in the solid state in the neutral palladium derivative.

**Further details of the catalyst decomposition pathway.** The faster catalyst deactivation observed with ligands bearing electron-withdrawing groups may have different origins, including the formation of complexes bearing two Ar-BIAN ligands and the comproportionation reaction of monomeric palladium(II) and palladium(0) complexes also having a bound ligand. However, the fact that all data point to a ligand dissociation step during the early (kinetically relevant) stages indicates that a deactivation process of the kind described should be a minor pathway during catalyst deactivation and the ligand must be lost at some stage, even if it may be regained at a later stage.

In addition, one has to take into account the positive role of benzoquinone in retarding catalyst decomposition. Benzoquinone is known to act as an oxidant towards palladium(0) complexes and the mechanism of its action has been investigated.<sup>52</sup> In addition, complexes of the kind [(N–N)Pd(BQ)] (N–N = 2,2'-bipyridine, Ar-BIAN) are known and can be intermediates in the palladium(0) reoxidation.<sup>53–55</sup> Oxidation even of palladium(I) dimers by benzoquinone has been considered to be a possibility,<sup>56</sup> but, to the best of our knowledge, such a process has never been experimentally observed. The fact that catalyst deactivation follows a second order kinetics with respect to palladium suggests that such a dimer oxidation either does not occur at all or is sensibly slower than the oxidation of palladium(0) and only occurs in a few cases.

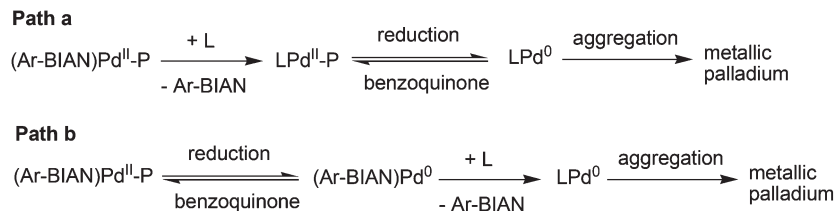

**Scheme 5** Alternative pathways for ligand loss.

Otherwise a higher order in palladium should be observed for the decomposition. Thus we will not consider palladium(i) reoxidation as a possibility in the following.

As far as ligand dissociation is concerned, we have two main alternatives. In the first (path a in Scheme 5), the ligand is lost from a palladium(II) compound, to yield a less stabilized and more easily reducible species. The ligand (L in the Scheme) substituting Ar-BIAN may be a solvent molecule, CO or the olefin. P is the growing polymer chain and may also play the role of a ligand.

Alternatively, reduction can precede ligand substitution, as shown in path b. If this is the case, it may be advanced that ligand loss would generate a palladium(0) species that would aggregate at a rate much faster than that with which it can be reoxidized by benzoquinone. Indeed it should be realized that the Ar-BIAN ligand renders the complex more electron-rich, at the same time occupying two coordination sites. The first feature should favor oxidation, whereas the second should inhibit aggregation with respect to a complex lacking such a ligand.

Such a kind of alternative is present in most, if not all catalytic cycles in which palladium is involved, but we are not aware of any case in which experimental data have been provided that allow discriminating among the two. Both pathways are consistent with the kinetic data of any single reaction and cannot be distinguished looking at them independently.

At this stage we can analyze the trends in  $k_3$  or  $k'_3$  vs. the Hammett  $\sigma$  constant on a more quantitative basis. We have already mentioned that the coordination strength of Ar-BIAN ligands is correlated with the  $\sigma$  value of the substituents.<sup>20</sup> More precisely, a linear correlation is observed between the logarithm of the equilibrium constant for the substitution of  $\text{Ph}_2\text{-BIAN}$  by a generic  $[\text{RC}_6\text{H}_4]_2\text{-BIAN}$  and the  $\sigma$  value of R. When two substituents are present, the correlation is maintained if the two  $\sigma$  values are summed up. Nonsymmetrical Ar, Ar'-BIAN fitted the common plot if the average of the  $\sigma$  values for the two different rings was employed in the correlation.<sup>16</sup> What is most important to the present discussion is that the slope of these linear plots ( $\rho_{\text{BIAN}}$ ) is sensitive to the Lewis acidity of the metal fragment<sup>38</sup> and is generally lower for complexes in which the palladium atom is zerovalent with respect to those in which it has the formal oxidation state two. The lowest sensitivity to electronic effects that could be measured ( $\rho_{\text{BIAN}} = -1.57$ ) corresponds to the series  $[\text{Pd}(\text{Ar-BIAN})(\text{DMFU})]$  (DMFU = dimethyl fumarate). By comparison the series  $[\text{Pd}(\text{Ar-BIAN})(\text{CH}_3)(\text{Cl})]$  has  $\rho_{\text{BIAN}} = -2.71$  and the series  $[\text{Pd}(\text{Ar-BIAN})$

$(\text{COD-OCH}_3)]^+$  (COD-OCH<sub>3</sub> is the ligand resulting from the attack of a methoxide anion onto coordinated 1,5-cyclooctadiene), featuring a cationic palladium(II) complex similar to some complexes that are formed as intermediates in the present catalytic polymerization, has  $\rho_{\text{BIAN}} = -3.47$ . The slope of the  $\log k_3$  or  $k'_3$  vs. Hammett  $\sigma$  constant plots shown in the previous figures (once corrected for the fact that decimal logarithms are used in the calculation of  $\rho_{\text{BIAN}}$  instead of natural ones) shows some scatter (1.50, 1.89, 1.08, 1.31, 0.86, 1.47, respectively, for the plots in Fig. S4, 10 (= S9), S12, 12 (= S16), S21 and S23†), as expected given the small number of data points in some cases, but the average value is 1.35 (1.15 if only the more precise  $k_3$  values are considered). The value is positive, contrary to those previously collected, but it should be remembered that now we are looking at a ligand dissociation process, whereas the previous values referred to a ligand coordination process, so that the sign is reversed. If the absolute values are compared, it clearly emerges that the present process is associated with the ligand loss from very electron-rich complexes. This clearly excludes any palladium(II) complex, especially if positively charged, and indicates that the Ar-BIAN detachment is occurring from a complex being more electron-rich than  $[\text{Pd}(\text{Ar-BIAN})(\text{DMFU})]$ . Given the compounds available in solution, by far the only likely candidates for this type of compound are  $[\text{Pd}(\text{Ar-BIAN})(\text{olefin})]$  (olefin = styrene or 4-methylstyrene) or  $[\text{Pd}(\text{Ar-BIAN})(\text{CO})_n]$  ( $n = 1, 2$ ). Palladium(0) complexes with nitrogen ligands and olefins lacking electron-withdrawing substituents have not been reported in the literature. Although, to the best of our knowledge, ligand substitution by an olefin has never been proposed as a relevant step in palladium catalysts deactivation, limited precedents exist for it. Vrieze and co-workers have reported that substituted diazabutadienes (R-DAB) could be substituted by an olefin in  $[\text{Pd}^0(\text{R-DAB})(\text{olefin})]$  complexes<sup>57</sup> and theoretical calculations by Elsevier and co-workers indicate that  $[\text{Pd}(\text{R-DAB})(\text{ethylene})]$  is thermodynamically unstable with respect to  $[\text{Pd}(\text{ethylene})_3]$  and R-DAB.<sup>58</sup>

It should be noted that a substitution of an Ar-BIAN ligand bound to a palladium(0) complex by an olefin as a key step in catalyst deactivation is also consistent with the observed higher instability of the catalytic system when styrene rather than 4-methylstyrene is employed as the substrate. In fact it has long been known that electron-poor olefins coordinate better to palladium(0) complexes than those lacking this feature and some quantitative data on this trend have been recently gained.<sup>59</sup> Note that exactly the opposite would be expected if



Ar-BIAN loss were occurring from a palladium(II) intermediate, thus further supporting the conclusions reached.

Palladium(0) carbonyl complexes with nitrogen ligands are also unknown and only metallic palladium is invariably obtained when palladium(II) complexes with nitrogen ligands are reduced in the presence of CO. Loss of Ar-BIAN from a  $[\text{Pd}(\text{Ar-BIAN})(\text{CO})_n]$  complex is consistent with the higher  $k_3$  and  $k'_3$  measured at 5 bar CO with respect to those at 3 bar and may also be consistent with the  $\rho_{\text{BIAN}}$  value observed, although a direct comparison with a reference compound is not available. Our data cannot distinguish between loss of the ligand from a palladium-olefin or a palladium-CO complex. The different deactivation rates observed in the case of the reactions run in styrene with respect to those run in 4-methylstyrene suggest that the former kind of complex is at least in part involved, although deactivation originating from the carbonyl complex is likely to also occur as a competitive pathway.


### Reactivity studies

Catalytic and kinetic investigations show that Pd complexes containing nonsymmetrical ligands generate better performing catalysts than those with symmetrical Ar-BIANs. To get some insights into the nature of this phenomenon we investigated by means of NMR spectroscopy the reactivity of complex **1d**, having the nonsymmetrical ligand **1**, with both comonomers, CO and 4-Me-styrene (Scheme 6). The Pd-carbonyl-methyl complex **1d** represents the active species and it was obtained in high yield as a red solid through reaction of the corresponding Pd-acyl-chloride species **1c** with a stoichiometric amount of NaBARf. In complex **1d**, in place of the  $\text{PF}_6^-$  counterion, the less coordinating tetraarylborate is present to favor alkene insertion in the stoichiometric reactions. In turn, **1c** was isolated as a dark green solid by dissolving **1a** in dichloromethane previously saturated with carbon monoxide at  $-20^\circ\text{C}$  (Scheme 6). It is straightforward to note that,

whereas **1a** and **1d** complexes are a mixture of *trans* and *cis* isomers in the ratio 10 : 1 and 3 : 1, respectively, in the NMR spectrum of **1c** only the signals of the isomer characterized by the acetyl group *trans* to the  $\text{CF}_3$ -substituted aryl ring are observed.

Starting from complex **1d** the intermediates resulting from the migratory insertion reactions of the two comonomers were investigated. When **1d** is treated with one equivalent of 4-Me-styrene in  $\text{CH}_2\text{Cl}_2$  at  $-20^\circ\text{C}$  the five-member palladacycle **1e** is obtained as a dark red solid. Analogous palladacycles were formed from the reaction of 4-Me-styrene with palladium complexes having ligands belonging to the family of phenanthrolines,<sup>60</sup> bisoxazolines<sup>42</sup> and diisopropyl diazabutadiene.<sup>61</sup> Instead, in the case of complexes with *o*-Ar-BIANs the reaction with 4-Me-styrene did not lead to the palladacycle, but to an intermediate involving an  $\eta^3$ -allyl bond between Pd and the inserted styrene unit.<sup>62</sup> This result clearly correlates the different catalytic behavior of complexes with *ortho* and *meta*-substituted Ar-BIANs to the nature of the intermediates formed after the vinyl arene migratory insertion: when the migratory insertion leads exclusively to the  $\eta^3$ -allyl intermediate, low or negligible catalytic activity is observed, while when it yields the palladacycle the copolymerization reaction proceeds much faster. Analogous observations were proposed to be at the origin of the inactivity of palladium complexes with diphosphine ligands (P-P) in the CO/vinyl arene copolymerization, in contrast to the activity of the related complexes with the phosphino-phosphite ligand BINAPHOS, leading to the metallacycle intermediate.<sup>63,64</sup> In the latter case it was demonstrated that the CO insertion into the Pd-allyl bond is much less efficient than into the Pd-alkyl bond.<sup>65</sup>

The observation in the NMR-2D-NOESY spectrum of **1e** of a strong cross-peak between  $\text{H}_a$  of the styrene unit and  $\text{H}_{ortho}$  of the  $\text{CH}_3$ -substituted aryl ring, together with the lack of such interactions with the  $\text{H}_{ortho}$  of the  $\text{CF}_3$ -substituted aryl ring, probes evidence that only the isomer characterized by the Pd-C

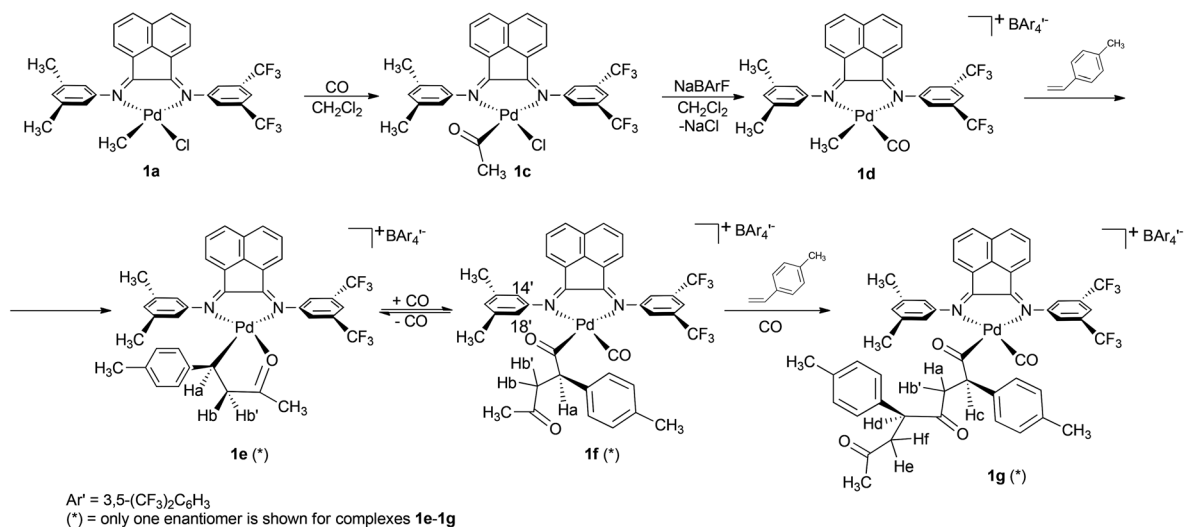

**Scheme 6** Synthesis of the active species **1d** and reaction pathway for the first steps of the copolymerization reaction. While **1f** and **1g** have been detected, the intermediate **1e** has been isolated.

bond *trans* to the Pd–N bond of the CF<sub>3</sub>-substituted aryl ring is formed. This compound is the result of two migratory insertions: the migratory insertion of CO into the Pd–CH<sub>3</sub> bond followed by that of 4-Me-styrene into the Pd–acyl bond which takes place with secondary regiochemistry, exclusively.

In the next step the reactivity of **1e** with CO was studied by bubbling the gaseous reagent into the NMR tube containing a CD<sub>2</sub>Cl<sub>2</sub> solution of **1e** at –30 °C. The complete formation of the Pd–acyl–carbonyl intermediate, **1f**, was observed within 10 min. Some relevant features of the <sup>1</sup>H NMR spectrum of **1f** are: (i) only the signals of one species are detectable; (ii) the signal of H<sub>a</sub> is shifted from 3.51 in **1e** to 4.61 ppm in **1f** due to the deshielding effect of the adjacent CO group; (iii) in the 2D-NOESY spectrum a cross-peak is present between H<sub>a</sub> and H<sup>14,18'</sup>; (iv) the resonances of protons H<sub>b,b'</sub> of the CH–CH<sub>2</sub> fragment do not exhibit a diamagnetic shift of the type that was observed in the case of the complexes with <sup>o</sup>Ar-BIANs, suggesting that the CH<sub>2</sub> group in the present case is not inside the shielding cone of the aromatic ring of the ligand; (v) two signals are observed for the methyl groups of the aryl ring, while in complexes **1a–1e** only one singlet was observed, indicating that in **1f** the rotation of the aryl ring is hindered. This NMR analysis shows that **1f** is the Pd–acyl–carbonyl species with the growing polymer chain oriented towards the CH<sub>3</sub>-substituted aryl ring (Scheme 6).

The solution of **1f** was treated with 1 equivalent of 4-Me-styrene under a CO atmosphere. After 4 days at –18 °C no signals of **1f** and free vinyl arene are present, while signals of the new species **1g** are observed. The complexity of the <sup>1</sup>H NMR spectrum of the double olefin insertion product **1g** suggests the presence of two diastereoisomeric complexes with an *RR* and *RS* (or *SS* and *SR*) configuration of the CH–Ph stereogenic centers, corresponding to *like* and *unlike* dyads in the polymeric chain. This result is in agreement with the atactic stereochemistry of the synthesized polyketones and indicates that no enantioface discrimination takes place since the insertion of the second molecule of vinyl arene. Finally, in the spectrum of **1g** the region of the signals of the aromatic protons is crowded due to the signals of the two inserted 4-methylstyrene molecules; thus the NOE experiments are not clear-cut as it was for **1f** in indicating that the growing polymer chain is *trans* to the CF<sub>3</sub>-substituted aryl ring.

Thanks to this NMR investigation it was possible to detect the intermediates formed at the beginning of the copolymerization reaction and to demonstrate that when the ancillary ligands are nonsymmetrical molecules there is a preferential coordination site for the growing polymer chain, which is *trans* to the N atom with lowest Lewis basicity. Thus, each time this is not the isomer resulting from the migratory insertion, an isomerization process takes place before the next insertion reaction proceeds. For the present complexes there is a *site selective coordination* of the growing polymer chain. This phenomenon is well known as *back-skip* in the catalytic synthesis of isotactic polypropylene.<sup>66</sup> In the case of CO/alkene copolymerization the *site selective coordination* of the alkene

was observed for both palladium complexes with amine–imine ligands,<sup>27</sup> with hybrid P–N ligands<sup>48</sup> and with the phosphino–phosphite (P–PO) molecule BINAPHOS.<sup>67</sup> A mechanistic hypothesis involving *cis/trans* isomerization was invoked.

Very recently, both in the polyethylene synthesis and in the ethylene/methyl acrylate copolymerization catalyzed by Pd-complexes with phosphino–sulfonate (P–O) ligands the *cis/trans* isomerization was indicated as an important step of the catalytic cycle.<sup>68,69</sup> In all the mentioned examples the preferential polymer chain coordination site is determined by an electronic differentiation of the two donor atoms, *i.e.* hard and soft for the P–O and N<sub>sp3</sub>–N<sub>sp2</sub> ligands, or *trans* influence in the hybrid P–N catalysts. For the catalysts with the bis(imine) Ar-BIANs, the topic of the present investigation, the difference in electronic features of the two N-donor atoms should be less pronounced than that in the other two series. Nevertheless, it appears to be sufficient for driving the preferential coordination of the polymer chain.

## Conclusions

Palladium complexes with α-diimine ligands having an acenaphthene skeleton and aryl rings on the imine nitrogen atoms have been widely applied as homogeneous catalysts for (co)polymerization reactions. In the past we demonstrated that the best performing catalysts within this ligand family, both in the CO/vinyl arene and ethylene/methyl acrylate copolymerization, are characterized by nonsymmetrically substituted Ar,Ar'-BIANs. The library of the Ar,Ar'-BIANs has now been extended to a new molecule characterized by a *meta*-F-substituted aryl ring and a *meta,para*-methoxy-substituted ring.

The kinetic study together with its modelization reported in this paper allows us to quantitatively distinguish between catalyst activity and its decomposition rate and to mainly correlate them to the electronic properties of the substituents on the aryl rings. Catalysts having symmetrical Ar-BIANs substituted with electron-donating groups show the lowest propagation and decomposition rate, whereas those having symmetrical Ar-BIANs substituted with electron-withdrawing groups yield the most active catalysts, but with the highest deactivation rate. Thus, the best performing catalysts are those with the nonsymmetrical Ar,Ar'-BIANs and, among them, the active species with the new ligand **3** represents the best compromise between activity and rate of deactivation.

When studying a catalytic system one usually tries to employ experimental conditions that minimize catalyst decomposition and quantitative kinetic studies are usually performed only under conditions in which decomposition is negligible. In this work we have quantitatively investigated the behavior of a series of catalysts that deactivate to a variable and sometime high extent. This allowed us to gain important information on the catalyst deactivation pathways, which are probably much more general. The deactivation was shown to involve the following steps:

(1) Palladium reduction from +2 to zero oxidation state. This step can be reverted easily by reaction with benzoquinone.

(2) Chelating ligand loss, likely due to displacement by the olefin or CO. Reoxidation after ligand dissociation appears not to compete effectively with the next step in the deactivation.

(3) The resulting palladium(0) complex reacts with another palladium(II) unit to generate a palladium(I) dimer that cannot be oxidized back under the reaction conditions and either accumulates or irreversibly evolves towards metallic palladium.

These results suggest two strategies to increase catalyst life. Since ligand loss is an equilibrium reaction, this should be shifted to the reactants side by adding an excess of free nitrogen ligand in solution, resulting in catalyst stabilization. In addition, if ligand loss is favored by simultaneous olefin coordination, decreasing olefin concentration may also result in a more stable catalytic system, although activity may also decrease. These strategies will be investigated in the future and will be the topic of a future study.

## Experimental

### Materials and methods

[Pd(OAc)<sub>2</sub>] was a gift from Engelhard Italia and was used as received. All the solvents were purchased from Sigma-Aldrich and used without further purification for synthetic, spectroscopic and catalytic purposes, with the only exception of the dichloromethane used for the synthesis of complexes, which was purified through distillation over CaH<sub>2</sub> under an argon atmosphere and was used freshly distilled. Carbon monoxide (grade 4.7) was supplied by Linde Gas for kinetic investigations and by Air Liquide (CP grade 99.99%) for mechanistic studies. NMR spectra of ligands and complexes were recorded using a Jeol EX 400 and a Varian 500 spectrometer at 298 K and at 400 and 500 MHz, respectively; NMR studies for mechanistic investigations were performed using a Bruker-AC200 spectrometer. The resonances were referenced to the solvent peak *versus* TMS: CDCl<sub>3</sub> at  $\delta$  7.26 (<sup>1</sup>H) and  $\delta$  77.0 (<sup>13</sup>C), CD<sub>2</sub>Cl<sub>2</sub> at  $\delta$  5.32 (<sup>1</sup>H). <sup>13</sup>C NMR spectra of polyketones were recorded in 1,1,1,3,3,3-hexafluoro-2-propanol (HFIP) with a small amount of CDCl<sub>3</sub> for locking purposes at 125.68 MHz and referenced at  $\delta$  77.0. IR spectra of monocationic complexes were recorded in Nujol using a Perkin Elmer System 2000 FT-IR.

NMR spectra for ligands 3 and 7 were recorded using Bruker Avance 300-DRX or Avance 400-DRX spectrometers. Chemical shifts (ppm) are reported relative to TMS. The <sup>1</sup>H NMR signals of the compounds described in the following have been attributed by COSY and NOESY techniques. Assignment of the resonance in <sup>13</sup>C NMR was made using the APT pulse sequence and HSQC and HMBC techniques. **CAUTION:** when NMR spectra of Ar-BIAN ligands containing electron-withdrawing substituents are recorded in CDCl<sub>3</sub>, it is essential that the solvent is purified by passing it over a short column of basic alumina to eliminate acidic impurities. Otherwise, partial hydrolysis of the ligand is observed.

Ligands 1, 2, and 4–6 and the related palladium complexes were synthesized by following literature procedures.<sup>17,19–21,38</sup>

### Synthesis of ligands 3 and 7

**Ligand 3.** The procedure is adapted from ref. 38. To a Schlenk flask were added ZnCl<sub>2</sub>(3,5-F<sub>2</sub>C<sub>6</sub>H<sub>3</sub>-BIAN), obtained as described below (0.500 g, 0.93 mmol), 3,4,5-trimethoxyaniline (174.0 mg, 0.95 mmol), and dry methanol (60 mL). The suspension was stirred under dinitrogen for 2 hours and, then it was evaporated *in vacuo* and the obtained solid was washed with a hexane–toluene 1:1 mixture (10 mL). The remaining solid was dissolved in dichloromethane (25 mL) in a separating funnel and decomplexed by shaking with a saturated solution of potassium oxalate (10 mL). The organic layer was separated and washed with water (3 × 10 mL). The organic layer was then dried over sodium sulfate, filtered and evaporated *in vacuo*. The product was purified by column chromatography on silica (eluent hexane–triethylamine 9.5:0.5). The nonsymmetrical ligand was eluted first (220 mg, 52% yield), followed by some [3,4,5-(CH<sub>3</sub>O)<sub>3</sub>C<sub>6</sub>H<sub>2</sub>]<sub>2</sub>-BIAN.

Elemental analysis: C, 70.74; H, 4.40; N, 6.11. Found: C, 70.51; H, 4.50; N, 6.09.

$\delta_{\text{H}}$  (400 MHz; CDCl<sub>3</sub>, 298 K), 7.98 (d,  $J$  = 8.2 Hz, 1H, H<sup>5</sup> or H<sup>8</sup>), 7.96 (d,  $J$  = 8.2 Hz, 1H, H<sup>8</sup> or H<sup>5</sup>), 7.47 (pst,  $J$  = 7.8 Hz, 2H, H<sup>4</sup>, H<sup>9</sup>), 7.14 (d,  $J$  = 7.3 Hz, 1H, H<sup>10</sup>), 6.99 (d,  $J$  = 7.2 Hz, 1H, H<sup>3</sup>), 6.72 (pst,  $J$  = 9.0 Hz, 1H, H<sup>16</sup>), 6.66 (d,  $J$  = 8.0 Hz, 2H, H<sup>14</sup>, H<sup>18</sup>), 6.38 (s, 2H, H<sup>14'</sup>, H<sup>18'</sup>), 3.94 (s, 3H, *p*-OCH<sub>3</sub>), 3.83 (s, 6H, *m*-OCH<sub>3</sub>).  $\delta_{\text{C}}$  (75 MHz, CDCl<sub>3</sub>, 298 K) 162.7 (C<sup>1,12</sup>), 154.7 (C<sup>15,17</sup>), 147.7 (C<sup>13</sup> or C<sup>7</sup>), 131.7 (C<sup>6</sup>), 130.2 (C<sup>5</sup> or C<sup>8</sup>), 129.7 (C<sup>5</sup> or C<sup>8</sup>), 128.4 (C<sup>4</sup> or C<sup>9</sup>), 128.2 (C<sup>4</sup> or C<sup>9</sup>), 124.8 (C<sup>10</sup>), 124.5 (C<sup>3</sup>), 102.1 (d,  $J_{\text{C-F}}$  = 27.0 Hz, C<sup>14,18</sup>), 99.9 (C<sup>16</sup>), 95.8 (C<sup>14',18'</sup>), 61.62 (*p*-OCH<sub>3</sub>), 56.6 (*m*-OCH<sub>3</sub>). Eight quaternary carbons were not detected. <sup>19</sup>F{<sup>1</sup>H} NMR (376 MHz, CDCl<sub>3</sub>, 298 K),  $\delta$ , ppm, –108.2 (s, F).

**Ligand 7.** The procedure is adapted from ref. 20. To a Schlenk flask under a dinitrogen atmosphere were added acenaphthenequinone (313.0 mg, 1.72 mmol), dry ZnCl<sub>2</sub> (606.5 mg, 4.45 mmol), and AcOH (4.7 mL). The suspension was heated to about 50–60 °C and 3,5-F<sub>2</sub>C<sub>6</sub>H<sub>3</sub>NH<sub>2</sub> (521.6 mg, 4.04 mmol) was then added. The solution was reflux heated for 45 min and then filtered on a Büchner funnel while hot. The solid was washed on the filter with diethyl ether to help remove the acetic acid and dried *in vacuo* to give ZnCl<sub>2</sub>(7) (733.3 mg, 1.36 mmol, 79.1% yield). Care must be taken to eliminate any residue of the acetic acid employed as the solvent in the synthesis, as this has a strong negative effect on the effectiveness of the separation in the following step. Note also that the addition of toluene to the solution mixture is generally required when anilines bearing trifluoromethyl groups are employed, to make precipitation of the complex easier.<sup>20</sup> However, with difluoroaniline this addition was not necessary.

ZnCl<sub>2</sub>(7) (717.1 mg, 1.33 mmol) was then placed in a flask in the air and suspended in CH<sub>2</sub>Cl<sub>2</sub> (65 mL). A solution of K<sub>2</sub>C<sub>2</sub>O<sub>4</sub> (1.48 g, 8.14 mmol) in water (9 mL) was then added and the biphasic mixture vigorously stirred for 15 min. The phases were separated and the organic layer was washed with

water ( $2 \times 10$  mL), dried with  $\text{Na}_2\text{SO}_4$ , filtered and evaporated to dryness affording the analytically pure **7** (456.7 mg, 1.13 mmol, 85.0% yield).

Elemental analysis: C, 71.30; H, 2.99; N, 6.93. Found: C, 71.12; H, 3.15; N, 6.84.

$\delta_{\text{H}}$  (400 MHz;  $\text{CDCl}_3$ , 298 K) 7.99 (2H, d,  $J_{\text{H-H}} = 8.3$  Hz,  $\text{H}^{5,8}$ ), 7.50 (2H, pt,  $J_{\text{H-H}} = 7.5$  Hz,  $\text{H}^{4,9}$ ), 7.05 (2H, d,  $J_{\text{H-H}} = 7.2$  Hz,  $\text{H}^{3,10}$ ), 6.73 (2H, tt,  $J_{\text{H-F}} = 9.0$  Hz,  $J_{\text{H-H}} = 2.2$  Hz,  $\text{H}^{16}$ ), 6.67 (4H, dd,  $J_{\text{H-F}} = 7.9$  Hz,  $J_{\text{H-H}} = 2.2$  Hz,  $\text{H}^{14,18}$ ) ppm.  $\delta_{\text{C}}$  (100 MHz,  $\text{CDCl}_3$ , 298 K) 169.9 (dd,  $J_{\text{C-F}}^1 = 247.2$ ,  $J_{\text{C-F}}^3 = 1.4$  Hz,  $\text{C}^{15,17}$ ), 161.7 ( $\text{C}^{1,12}$ ), 153.8 (d,  $J_{\text{C-F}}^3 = 1.2$  Hz,  $\text{C}^{13}$ ), 142.1 ( $\text{C}^7$ ), 131.4 ( $\text{C}^6$ ), 129.9 ( $\text{C}^{5,6}$ ), 127.6 ( $\text{C}^{2,11}$ ), 123.9 ( $\text{C}^{3,10}$ ), 101.7 (dd,  $J_{\text{C-F}}^2 = 19.4$ ,  $J_{\text{C-F}}^4 = 7.4$  Hz,  $\text{C}^{14,18}$ ), 99.7 (d,  $J_{\text{C-F}}^2 = 25.4$  Hz,  $\text{C}^{16}$ ).  $\delta_{\text{F}}$  (376 MHz;  $\text{CDCl}_3$ , 298 K)  $-108.4$  (pt,  $J = 8.0$  Hz).

## Synthesis of Pd complexes

All syntheses were performed using standard vacuum-line and Schlenk techniques under an argon atmosphere and at room temperature, according to the published procedures.<sup>19,21</sup>

### [Pd(CH<sub>3</sub>)Cl(Ar-BIAN)] (**3a**, **7a**)

**General synthesis.** [Pd(CH<sub>3</sub>)Cl(cod)] (201.5 mg, 0.76 mmol) was kept in a Schlenk flask and dissolved in  $\text{CH}_2\text{Cl}_2$  (3 mL). A solution of the ligand (0.84 mmol) in  $\text{CH}_2\text{Cl}_2$  (3 mL) was added. The reaction mixture was protected from light, stirred at r.t. for 1 h, and then concentrated at half volume under reduced pressure. Upon the addition of diethyl ether a red solid was obtained.

### [Pd(CH<sub>3</sub>)Cl(**3**)] (**3a**). Yield: 89%. Dark red solid.

Elemental analysis: C, 54.65; H, 3.77; N, 4.55. Found: C, 54.76; H, 3.83; N, 4.75.

$\delta_{\text{H}}$  (400 MHz;  $\text{CD}_2\text{Cl}_2$ ; 298 K; M = major, m = minor) 8.19–8.10 (m,  $\text{H}^{5,8}_{\text{M,m}}$ ), 7.59–7.51 (m,  $\text{H}^{4,9}_{\text{M,m}}$ ), 7.46 (1H, d,  $\text{H}^{10}_{\text{M}}$ ), 7.25 (1H, d,  $\text{H}^3_{\text{M}}$ ), 6.93–6.84 (m,  $\text{H}^{14,16,18}_{\text{M,m}}$  and  $\text{H}^{10}_{\text{M}}$ ), 6.79 (1H, d,  $\text{H}^3_{\text{M}}$ ), 6.66 (2H, s,  $\text{H}^{14',18'}_{\text{M}}$ ), 6.49 (2H, s,  $\text{H}^{14',18'}_{\text{M}}$ ), 3.89 (s,  $^p\text{OCH}_{3,\text{M,m}}$ ), 3.84 (s,  $^m\text{OCH}_{3,\text{M,m}}$ ), 0.91 (3H, s, Pd- $\text{CH}_{3,\text{M}}$ ), 0.80 (3H, s, Pd- $\text{CH}_{3,\text{m}}$ ).

### [Pd(CH<sub>3</sub>)Cl(**7**)] (**7a**). Yield: 87%. Red solid.

Elemental analysis: C, 53.50; H, 2.69; N, 4.99. Found: C, 53.90; H, 2.58; N, 4.98.

$\delta_{\text{H}}$  (500 MHz;  $\text{CD}_2\text{Cl}_2$ ; 298 K) 8.18 (2H, m,  $\text{H}^{5,8}$ ), 7.58 (2H, m,  $\text{H}^{4,9}$ ), 7.28 (1H, d,  $\text{H}^3$ ), 7.01–6.83 (7H, m,  $\text{H}^{14,14',16,16',18,18',10}$ ), 0.85 (3H, s, Pd- $\text{CH}_3$ ).

### [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(Ar-BIAN)][PF<sub>6</sub>] (**3b**, **7b**)

**General synthesis.** A solution of  $\text{AgPF}_6$  (0.401 mmol) in  $\text{CH}_3\text{CN}$  (1 mL) was added to a solution of the neutral complex (0.349 mmol) in  $\text{CH}_2\text{Cl}_2$  (2 mL). The solution was stirred at r.t. for 30 min, and then  $\text{AgCl}$  was filtered over celite; the solution was then concentrated to half volume under vacuum. Upon the addition of diethyl ether the product precipitated as a solid.

### [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(**3**)][PF<sub>6</sub>] (**3b**). Yield: 77%. Orange solid.

$\delta_{\text{H}}$  (400 MHz;  $\text{CD}_2\text{Cl}_2$ ; 298 K; M = major, m = minor) 8.25–8.19 (2H, m,  $\text{H}^{5,8}_{\text{M,m}}$ ), 7.66–7.57 (m,  $\text{H}^{4,9}_{\text{M,m}}$ ), 7.47 (1H, d,  $\text{H}^{10}_{\text{M}}$ ), 7.33 (1H, d,  $\text{H}^3_{\text{M}}$ ), 7.06–6.99 and 6.89 (m,  $\text{H}^{14,16,18}_{\text{M,m}}$ ), 6.84 (1H, d,  $\text{H}^{10}_{\text{M}}$ ), 6.81 (1H, d,  $\text{H}^3_{\text{M}}$ ), 6.63 (2H, s,  $\text{H}^{14',18'}_{\text{M}}$ ), 6.48 (2H, s,  $\text{H}^{14',18'}_{\text{M}}$ ), 3.90, 3.88, 3.85 (s,  $^p\text{OCH}_{3,\text{M,m}}$  and

$^m\text{OCH}_{3,\text{M,m}}$ ), 2.20 (3H, s, Pd- $\text{NCCH}_{3,\text{M}}$ ), 2.17 (3H, s, Pd- $\text{NCCH}_{3,\text{m}}$ ), 1.00 (3H, s, Pd- $\text{CH}_{3,\text{M}}$ ), 0.87 (3H, s, Pd- $\text{CH}_{3,\text{m}}$ ).

Elemental analysis: C, 47.05; H, 3.42; N, 5.49. Found: C, 46.98; H, 3.44; N, 5.35.

### [Pd(CH<sub>3</sub>)(CH<sub>3</sub>CN)(**7**)][PF<sub>6</sub>] (**7b**). Yield: 72%. Yellow solid.

$\delta_{\text{H}}$  (500 MHz;  $\text{CD}_2\text{Cl}_2$ , 298 K) 8.26 (2H, t,  $\text{H}^{5,8}$ ), 7.65 (2H, dt,  $\text{H}^{4,9}$ ), 7.37 (1H, d,  $\text{H}^3$ ), 7.05–6.90 (6H, m,  $\text{H}^{14,14',16,16',18,18'}$ ), 6.83 (1H, d,  $\text{H}^{10}$ ), 2.21 (3H, s, Pd- $\text{NCCH}_3$ ), 0.95 (3H, s, Pd- $\text{CH}_3$ ).

Elemental analysis: C, 45.56; H, 2.55; N, 5.90. Found: C, 45.44; H, 2.45; N, 5.85.

**Reactivity studies.** Isolation of intermediates of the copolymerization reaction.

### [Pd(COCH<sub>3</sub>)(Cl)(**1**)] (**1c**). Yield: 92%. Dark green solid.

Compound **1a** (100 mg, 0.153 mmol) was dissolved at  $-20$  °C under CO atmosphere in 2.5 mL of dichloromethane previously saturated with CO. The solution was slowly warmed to 25 °C, stirred for 1 h, and then filtered through celite to remove traces of metallic Pd. A dark-green solid was obtained after evaporation of the solvent under vacuum which was washed with hexane ( $3 \times 5$  mL) and dried, yielding compound **1c** (96 mg, 0.141 mmol, 92%).

$\delta_{\text{H}}$  (200 MHz,  $\text{CD}_2\text{Cl}_2$ , 298 K) 8.17 (2H, dd,  $\text{H}^{5,8}$ ), 7.98 (1H, s,  $\text{H}^{16}$ ), 7.87 (2H, s,  $\text{H}^{14,18}$ ), 7.55 (2H, dt,  $\text{H}^{4,9}$ ), 7.14 (2H, m,  $\text{H}^{16}$  and  $\text{H}^3$ ), 6.93 (s, 3H,  $\text{H}^{14',18'}$  and  $\text{H}^{10}$ ), 2.43 (6H, s,  $-(\text{CH}_3)_2\text{-Ar}$ ), 2.24 (3H, s,  $\text{CH}_3\text{-CO}$ ).  $\delta_{13\text{C}}$  (50.33 MHz,  $\text{CD}_2\text{Cl}_2$ , 298 K) 220.26 (CO-Pd), 144.61 (s, *ipso*-C-Ph- $\text{CF}_3$ ), 140.00 (s, *ipso*-C-Ph- $\text{CH}_3$ ), 132.17, 131.34 (s,  $\text{CH}^{5,8}$ ), 129.40 (s,  $\text{CH}^{16}$ ), 128.97, 128.45 (s,  $\text{CH}^{4,9}$ ), 126.08 (s,  $\text{CH}^3$ ), 125.21 (s,  $\text{CH}^{10}$ ), 122.33 (s,  $\text{CH}^{14,18}$ ), 120.95 (s,  $\text{CH}^{16'}$ ), 117.98 (s,  $\text{CH}^{14',18'}$ ), 32.65 (s,  $\text{CH}_3\text{CO}$ ), 21.11 (s,  $\text{CH}_3\text{-Ar}$ ).

### [Pd(CH<sub>3</sub>)(CO)(**1**)][BARF] (**1d**). Yield: 91%. Red solid.

Compound **1c** (90 mg, 0.132 mmol) was reacted with Na-[BARF] (117 mg, 0.132 mmol) at  $-40$  °C in 2.5 mL of dichloromethane. The reaction mixture was slowly warmed to 0 °C, and the solution was filtered through celite to remove NaCl. Then solvent was evaporated in vacuum, and the resulting solid was washed with hexane ( $3 \times 5$  mL). A 182.38 mg sample of the red compound **1d** (0.121 mmol, 91%) was collected.

$\delta_{\text{H}}$  (200 MHz,  $\text{CD}_2\text{Cl}_2$ , 298 K) 8.25 (2H, dd,  $\text{H}^{5,8}$ ), 8.01 (1H, s,  $\text{H}^{16}$ ), 7.75 (10H, brs,  $\text{H}^{14,18}$ , Ar'-*Ho*), 7.57 (6H, dt,  $\text{H}^{4,9}$ , Ar'-*Hp*), 7.28 (2H, brs,  $\text{H}^{16'}$  and  $\text{H}^3$ ), 7.08 (2H, brs,  $\text{H}^{14',18'}$ ), 6.64 (1H, s,  $\text{H}^{10}$ ), 2.46 (6H, s,  $-(\text{CH}_3)_2\text{-Ar}$ ), 1.31 (3H, s,  $\text{CH}_3\text{-Pd}$ , major-*trans*), 1.07 (3H, s,  $\text{CH}_3\text{-Pd}$ , minor-*cis*).  $\delta_{13\text{C}}$  (50.33 MHz,  $\text{CD}_2\text{Cl}_2$ , 298 K) 174.38 (s, CO-Pd, *trans*), 172.77 (s, CO-Pd, *cis*), 161.73 (q,  $J_{\text{CB}} = 49.8$  Hz, Ar'-*Cipso*), 147.57, 147.27 (s, C=N), 141.26 (s, *ipso*-C-Ph- $\text{CH}_3$ ), 141.04 (s, *ipso*-C-Ph- $\text{CF}_3$ ), 134.71 (s, Ar'-*Co*), 134.20 (s,  $\text{CH}^{5,8}$ ), 133.71 (s,  $\text{CH}^{16}$ ), 128.70 (q,  $J_{\text{CF}}^2 = 28.33$  Hz, *Cm*-Ar'), 126.35 (s,  $\text{CH}^{4,9}$ ), 124.84 (q,  $J_{\text{CF}}^1 = 272.28$  Hz,  $\text{CF}_3$ ), 124.05, 123.26 (s,  $\text{CH}^{14,18}$ ), 121.78 (s,  $\text{CH}^{10}$ ), 121.43 (s,  $\text{CH}^{16}$ ), 117.95 (s,  $\text{CH}^{14',18'}$ ), 117.50 (s, Ar'-*Cp*), 21.29 (s,  $\text{CH}_3\text{-Ph}$ ), 12.09 (s,  $\text{CH}_3\text{-Pd}$ , *trans*), 9.11 (s,  $\text{CH}_3\text{-Pd}$ , *cis*).

[Pd(CH(*p*- $\text{CH}_3\text{-Ph}$ )) $\text{CH}_2\text{C}(\text{O})\text{CH}_3$ )(**1**)] [BARF] (**1e**). Yield: 83%. Dark red solid.

*p*-Methylstyrene (13.00  $\mu\text{L}$ , 0.1 mmol) was added to a solution of **1d** (150 mg, 0.099 mmol) in 2.5 mL of dichloromethane cooled to  $-20$  °C. After 20 min the solvent was evaporated



under vacuum, and the resulting solid was washed with hexane ( $2 \times 4$  mL). A 132.46 mg sample of the dark-red compound **1e** (0.083 mmol, 83%) was collected. This complex is stable in solution only for a few hours.

$\delta_{\text{H}}$  (200 MHz,  $\text{CD}_2\text{Cl}_2$ , 298 K) 8.13 (2H, dd,  $\text{H}^{5,8}$ ), 8.11 (3H, m,  $\text{H}^{16}$  and  $\text{H}^{14,18}$ ), 7.74 (8H, s,  $\text{Ar}'\text{-Ho}$ ), 7.56 (6H, s,  $\text{H}^{4,9}$  and  $\text{Ar}'\text{-Hp}$ ), 7.24 (2H, m,  $\text{H}^{16'}$  and  $\text{H}^3$ ), 6.97 (2H, s,  $\text{H}^{14',18'}$ ), 6.88 (2H, m,  $\text{CHo-Ph}$ ), 6.59 (1H, s,  $\text{H}^{10}$ ), 6.55 (2H, s,  $\text{CHm-Ph}$ ), 3.51 (1H, dd,  $\text{CHa}$ ), 2.87 (1H, d,  $\text{CHb}$ ), 2.47 (6H, s,  $-(\text{CH}_3)_2\text{-Ar}$ ), 2.10 (3H, s,  $\text{CH}_3(\text{CO})$ ), 1.98 (1H, d,  $\text{CHb}'$ ), 1.89 (3H, s,  $\text{CH}_3\text{-Ph}$ ).

$[\text{Pd}(\text{C}(\text{O})\text{CH}(\text{p-CH}_3\text{-Ph})\text{CH}_2\text{C}(\text{O})\text{CH}_3)(\text{CO})(1)][\text{BAr}'_4](\text{1f})$ . Bubbling CO at  $-30$  °C for 10 min into a  $\text{CD}_2\text{Cl}_2$  solution (0.6 mL) of **1e** (60 mg) resulted in the formation of **1f**. This complex is stable in solution only for a few hours.

$\delta_{\text{H}}$  (200 MHz,  $\text{CD}_2\text{Cl}_2$ , 250.9 K) 8.16 (2H, dd,  $\text{H}^{5,8}$ ), 8.10 (1H, s,  $\text{H}^{16}$ ), 7.87 (2H, s,  $\text{H}^{14,18}$ ), 7.77 (8H, s,  $\text{Ar}'\text{-Ho}$ ), 7.64 (2H, dt,  $\text{H}^{4,9}$ ), 7.56 (s, 4H,  $\text{Ar}'\text{-Hp}$ ), 7.23 (2H, m,  $\text{H}^{16'}$  and  $\text{H}^3$ ), 7.18 (4H, m,  $\text{CH-Ph}$ ), 6.95 (2H, s,  $\text{H}^{14',18'}$ ), 6.86 (1H, s,  $\text{H}^{10}$ ), 4.64 (1H, t,  $\text{CHa}$ ), 2.81 (1H, d,  $\text{CHb}$ ), 2.76 (d, 1H,  $\text{CHb}'$ ), 2.36 (3H, s,  $\text{CH}_3\text{-Ph}$ ), 2.27, 2.13 (6H, s,  $-(\text{CH}_3)_2\text{-Ar}$ ), 1.96 (3H, s,  $\text{CH}_3(\text{CO})$ ).

$[\text{Pd}(\text{C}(\text{O})\text{CH}(\text{p-CH}_3\text{-Ph})\text{CH}_2\text{C}(\text{O})\text{CH}_3)(\text{CO})(1)][\text{BAr}'_4](\text{1g})$ . *p*-Methylstyrene (4.3  $\mu\text{L}$ , 0.1 mmol) was added into a  $\text{CD}_2\text{Cl}_2$  solution (0.6 mL) of **1f** (50 mg, 0.033 mmol) cooled to  $-30$  °C. The solution was left for 16 h at  $-18$  °C to yield compound **1g**. This complex is stable in solution only for a few hours.

$\delta_{\text{H}}$  (200 MHz,  $\text{CD}_2\text{Cl}_2$ , 243 K) 8.13 (2H, dd,  $\text{H}^{5,8}$ ), 7.89 (3H, brs,  $\text{H}^{14,16,18}$ ), 7.78 (10H, brs,  $\text{H}^{4,9}$ ,  $\text{Ar}'\text{-Ho}$ ), 7.49 (4H, s,  $\text{Ar}'\text{-Hp}$ ), 7.49–7.41 (2H, m,  $\text{H}^{16'}$  and  $\text{H}^3$ ), 7.30–6.85 (11H, m,  $\text{CH-Ph}$ ,  $\text{H}^{14',18'}$ ,  $\text{H}^{10}$ ), 4.25–3.75 (2H, m,  $\text{CHc}$  and  $\text{CHd}$ ), 3.50–3.10 (2H, m,  $\text{CHa}$  and  $\text{CHe}$ ), 2.80–2.50 (2H, m,  $\text{CHb}$  and  $\text{CHf}$ ), 2.50–2.00 (9H, m,  $-(\text{CH}_3)_2\text{-Ar}$ ,  $\text{CH}_3\text{-Ph}$ ), 1.84 (3H, s,  $\text{CH}_3(\text{CO})$ ).

### CO/vinyl arenes copolymerization reactions at 3–10 bar

Catalytic experiments were performed simultaneously in the parallel autoclave system AMTEC SPR16, equipped with pressure sensors and a mass-flow controller suitable for monitoring and recording gas uptakes throughout the reactions. Four stainless steel autoclaves (12 mL) of the AMTEC SPR16 were flushed with argon. A solution of the Pd catalyst and 1,4-benzoquinone in trifluoroethanol (20 mL) was prepared and the reactors were charged each with 5 mL of the catalyst solution as well as 3 mL of the alkene comonomer. The atmosphere was exchanged with carbon monoxide (gas exchange cycle 1) and the reactors were pressurized to the desired value. After heating to the desired temperature (30 °C), the final pressures were adjusted and kept constant throughout the experiment. The carbon monoxide uptake was monitored and recorded automatically.

### X-ray crystallography

Collection data of **1a** and **3a** were carried out at room temperature using a Nonius DIP-1030H system equipped with Mo-K $\alpha$  radiation ( $\lambda = 0.71073$  Å). Cell refinement, indexing and scaling of the data sets were carried out using Denzo<sup>70</sup> and Scalepack.<sup>70</sup> The structures were solved by direct methods and subsequent Fourier analyses<sup>71</sup> and refined by the full-matrix

**Table 6** Crystallographic data for compounds **1a** and **3a**

	<b>1a</b>	<b>3a</b>
Empirical formula	$\text{C}_{29}\text{H}_{21}\text{ClF}_6\text{N}_2\text{Pd}$	$\text{C}_{28}\text{H}_{23}\text{ClF}_2\text{N}_2\text{O}_3\text{Pd}$
Fw	653.33	615.33
Crystal system	Monoclinic	Monoclinic
Space group	$P2_1/c$	$P2_1/c$
<i>a</i> (Å)	12.138(4)	14.707(4)
<i>b</i> (Å)	24.329(5)	14.627(3)
<i>c</i> (Å)	8.973(4)	12.192(3)
$\beta$ (°)	94.82(4)	103.82(3)
<i>V</i> (Å <sup>3</sup> )	2640.4(16)	2546.8(11)
<i>Z</i>	4	4
<i>D</i> calcd (g cm <sup>-3</sup> )	1.644	1.605
$\mu$ (Mo-K $\alpha$ ), (mm <sup>-1</sup> )	0.868	0.882
<i>F</i> (000)	1304	1240
$\theta$ range (°)	1.67–27.10	1.43–27.05
No. of reflns collcd	28 892	29 141
No. of indep reflns	5799	5547
<i>R</i> <sub>int</sub>	0.1192	0.0870
No. of reflns ( <i>I</i> > 2 $\sigma$ ( <i>I</i> ))	2762	2614
No. of refined params	353	334
Goodness-of-fit ( <i>F</i> <sup>2</sup> )	0.916	0.901
<i>R</i> <sub>1</sub> , <i>wR</i> <sub>2</sub> ( <i>I</i> > 2 $\sigma$ ( <i>I</i> )) <sup>a</sup>	0.0647, 0.1449	0.0463, 0.0928
Residuals (e Å <sup>-3</sup> )	0.793, −0.665	0.486, −0.463

$$^a R_1 = \sum ||F_o| - |F_c|| / \sum |F_o|, wR_2 = [\sum w(F_o^2 - F_c^2)^2 / \sum w(F_o^2)^2]^{1/2}.$$

least-squares method based on *F*<sup>2</sup> with all observed reflections.<sup>71</sup> All the calculations were performed using the WinGX System, Ver. 1.80.05.<sup>72</sup> Crystal data and details of refinement for **1a** and **3a** are summarized in Table 6.

## Acknowledgements

Collaborative research was carried out by D.V. and B.M. in the framework of the COST D40 project of the EC that is also acknowledged for the financial support of an STSM of F.A. to Eindhoven University of Technology. This work was supported by MIUR (PRIN no. 2007HMTJWP\_002; PRIN no. 2008A7P7YJ\_003). We thank Dr F. Ferretti and A. Caselli for help in the synthesis and characterization of ligands **3** and **7** and Dr P. Natanti for the characterization of complexes **1a–1g**. Engelhard Italia is gratefully acknowledged for a generous gift of  $[\text{Pd}(\text{AcO})_2]$ . Fondazione CRTrieste is also gratefully acknowledged for the generous donation to the Dipartimento di Scienze Chimiche e Farmaceutiche of a Varian 500 NMR spectrometer.

## References

- 1 I. Matei and T. Lixandru, *Chem. Abstr.*, 1969, **70**, 3623.
- 2 R. Van Asselt and C. J. Elsevier, *Organometallics*, 1992, **11**, 1999.
- 3 L. K. Johnson, C. M. Killian and M. Brookhart, *J. Am. Chem. Soc.*, 1995, **117**, 6414.
- 4 S. D. Ittel, L. K. Johnson and M. Brookhart, *Chem. Rev.*, 2000, **100**, 1169.
- 5 L. K. Johnson, S. Mecking and M. Brookhart, *J. Am. Chem. Soc.*, 1996, **118**, 267.



- 6 S. Mecking, L. K. Johnson, L. Wang and M. Brookhart, *J. Am. Chem. Soc.*, 1998, **120**, 888.
- 7 A. Nakamura, S. Ito and K. Nozaki, *Chem. Rev.*, 2009, **109**, 5215.
- 8 D. Pappalardo, M. Mazzeo, S. Antinucci and C. Pellicchia, *Macromolecules*, 2000, **33**, 9483.
- 9 J. Kieseewetter and W. Kaminsky, *Chem.-Eur. J.*, 2003, **9**, 1750.
- 10 C. S. Popeney, D. H. Camacho and Z. Guan, *J. Am. Chem. Soc.*, 2007, **129**, 10062.
- 11 L. Guo, H. Gao, Q. Guan, H. Hu, J. Deng, J. Liu, F. Liu and Q. Wu, *Organometallics*, 2012, **31**, 6054.
- 12 R. van Asselt, E. E. C. G. Gielens, R. E. Rülke and C. J. Elsevier, *J. Chem. Soc., Chem. Commun.*, 1993, 1203.
- 13 G. Bellachioma, B. Binotti, G. Cardaci, C. Carfagna, A. Macchioni, S. Sabatini and C. Zuccaccia, *Inorg. Chim. Acta*, 2002, **330**, 44.
- 14 B. Binotti, C. Carfagna, C. Zuccaccia and A. Macchioni, *Chem. Commun.*, 2005, 92.
- 15 B. Binotti, G. Bellachioma, G. Cardaci, C. Carfagna, C. Zuccaccia and A. Macchioni, *Chem.-Eur. J.*, 2007, **13**, 1570.
- 16 M. Gasperini, F. Ragaini, E. Gazzola, A. Caselli and P. Macchi, *Dalton Trans.*, 2004, 3376.
- 17 A. Scarel, M. R. Axet, F. Amoroso, F. Ragaini, C. J. Elsevier, A. Holuigue, C. Carfagna, L. Mosca and B. Milani, *Organometallics*, 2008, **27**, 1486.
- 18 A. Meduri, T. Montini, F. Ragaini, P. Fornasiero, E. Zangrando and B. Milani, *ChemCatChem*, 2013, **5**, 1170.
- 19 R. Van Asselt, C. J. Elsevier, W. J. J. Smeets, A. L. Spek and R. Benedix, *Recl. Trav. Chim. Pays-Bas*, 1994, **113**, 88.
- 20 M. Gasperini, F. Ragaini and S. Cenini, *Organometallics*, 2002, **21**, 2950.
- 21 J. Durand, E. Zangrando, M. Stener, G. Fronzoni, C. Carfagna, B. Binotti, P. C. J. Kamer, C. Müller, M. Caporali, P. W. N. M. van Leeuwen, D. Vogt and B. Milani, *Chem.-Eur. J.*, 2006, **12**, 7639.
- 22 F. Ragaini, M. Gasperini, P. Parma, E. Gallo, N. Casati and P. Macchi, *New J. Chem.*, 2006, **30**, 1046.
- 23 M. Hagar, F. Ragaini, E. Monticelli, A. Caselli, P. Macchi and N. Casati, *Chem. Commun.*, 2010, **46**, 6153.
- 24 J. Zhou, H. Sun, K. Harms and J. Sundermeyer, *Z. Anorg. Allg. Chem.*, 2008, **634**, 1517.
- 25 A. Bastero, A. Ruiz, C. Claver, B. Milani and E. Zangrando, *Organometallics*, 2002, **21**, 5820.
- 26 A. Scarel, J. Durand, D. Franchi, E. Zangrando, G. Mestroni, B. Milani, S. Gladiali, C. Carfagna, B. Binotti, S. Bronco and T. Gragnoli, *J. Organomet. Chem.*, 2005, **690**, 2106.
- 27 M. R. Axet, F. Amoroso, G. Bottari, A. D'Amora, E. Zangrando, F. Faraone, D. Drommi, M. Saporita, C. Carfagna, P. Natanti, R. Seraglia and B. Milani, *Organometallics*, 2009, **28**, 4464.
- 28 A. Bastero, C. Claver, A. Ruiz, S. Castillon, E. Daura, C. Bo and E. Zangrando, *Chem.-Eur. J.*, 2004, **10**, 3747.
- 29 A. D'Amora, L. Fanfoni, D. Cozzula, N. Guidolin, E. Zangrando, F. Felluga, S. Gladiali, F. Benedetti and B. Milani, *Organometallics*, 2010, **29**, 4472.
- 30 J. March, *Advanced organic chemistry*, John Wiley & Sons, Inc., 1992.
- 31 C. Besson, E. E. Finney and R. G. Finke, *J. Am. Chem. Soc.*, 2005, **127**, 8179.
- 32 M. A. Watzky and R. G. Finke, *J. Am. Chem. Soc.*, 1997, **119**, 10382.
- 33 P. H. M. Budzelaar, P. W. N. M. Van Leeuwen, C. F. Roobeek and A. G. Orpen, *Organometallics*, 1992, **11**, 23.
- 34 M. Tromp, J. R. A. Sietsma, J. A. van Bokhoven, G. P. F. van Strijdonck, R. J. van Haaren, A. M. J. van der Eerden, P. W. N. M. van Leeuwen and D. C. Koningsberger, *Chem. Commun.*, 2003, 128.
- 35 M. Portnoy, F. Frolow and D. Milstein, *Organometallics*, 1991, **10**, 3960.
- 36 F. Ragaini, H. Larici, M. Rimoldi, A. Caselli, F. Ferretti, P. Macchi and N. Casati, *Organometallics*, 2011, **30**, 2385.
- 37 The possibility that the irreversible step of the decomposition is the reaction of two palladium(0) complexes should also be considered. However, palladium(0) complex concentrations should be very low at any moment and this process is quite unlikely to play a relevant role in the present system. From a kinetic point of view, a process of this kind would be distinguishable from that in path B only if the concentration/time profile for benzoquinone were also known, which is not the case, and so we will ignore it in the following.
- 38 M. Gasperini and F. Ragaini, *Organometallics*, 2004, **23**, 995.
- 39 Note that the same "volume" amount of the two olefins was employed. Given the higher  $M_w$  and molar volume of the methyl-substituted substrate, the molar concentration of the latter was actually a little lower than that of styrene during the reactions. However, the reactivity difference is much larger than that attributable to such a small dilution effect and must have a different origin.
- 40 M. Brookhart, M. I. Wagner, G. G. A. Balavoine and H. A. Haddou, *J. Am. Chem. Soc.*, 1994, **116**, 3641.
- 41 S. Bartolini, C. Carfagna and A. Musco, *Macromol. Rapid Commun.*, 1995, **16**, 9.
- 42 C. Carfagna, G. Gatti, D. Martini and C. Pettinari, *Organometallics*, 2001, **20**, 2175.
- 43 A. Scarel, B. Milani, E. Zangrando, M. Stener, S. Furlan, G. Fronzoni, G. Mestroni, S. Gladiali, C. Carfagna and L. Mosca, *Organometallics*, 2004, **23**, 5593.
- 44 The experiment at 10 bar with 3,5-(CH<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>;3,5-(CF<sub>3</sub>)<sub>2</sub>C<sub>6</sub>H<sub>3</sub>-BIAN was also performed. It is not included in the discussion because the data are of poor quality. However, even if quantitative data are inaccurate, the reaction rate was without doubt slower than that of both the reactions run under 3 and 5 bar with the same ligand.
- 45 B. Milani, G. Corso, G. Mestroni, C. Carfagna, M. Formica and R. Seraglia, *Organometallics*, 2000, **19**, 3435.
- 46 M. Sperrle, A. Aeby, G. Consiglio and A. Pfaltz, *Helv. Chim. Acta*, 1996, **79**, 1387.
- 47 W. P. Mul, A. W. van der Made, A. A. Samaardijk and E. Drent, in *Catalytic synthesis of copolymers and terpolymers*, ed. A. Sen, Dordrecht, 2003.

- 48 A. Gsponer, T. M. Schmid and G. Consiglio, *Helv. Chim. Acta*, 2001, **84**, 2986.
- 49 J. Durand, A. Scarel, B. Milani, R. Seraglia, S. Gladiali, C. Carfagna and B. Binotti, *Helv. Chim. Acta*, 2006, **89**, 1752.
- 50 D. P. Gates, S. A. Svejda, E. Onate, C. M. Killian, L. K. Johnson, P. S. White and M. Brookhart, *Macromolecules*, 2000, **33**, 2320.
- 51 M. P. Weberski, C. Chen, M. Delferro, C. Zuccaccia, A. Macchioni and T. J. Marks, *Organometallics*, 2012, **31**, 3773.
- 52 H. Grennberg, A. Gogoll and J. E. Baeckvall, *Organometallics*, 1993, **12**, 1790.
- 53 R. A. Klein, C. J. Elsevier and F. E. Hartl, *Organometallics*, 1997, **16**, 1284.
- 54 R. A. Klein, P. Witte, R. van Belzen, J. Fraanje, K. Goubitz, M. Numan, H. Schenk, J. M. Ernsting and C. J. Elsevier, *Eur. J. Inorg. Chem.*, 1998, 319.
- 55 B. Milani, A. Anzilutti, L. Vicentini, A. Sessanta o Santi, E. Zangrando, S. Geremia and G. Mestroni, *Organometallics*, 1997, **16**, 5064.
- 56 E. Drent and P. H. M. Budzelaar, *Chem. Rev.*, 1996, **96**, 663.
- 57 K. J. Cavell, D. J. Stufkens and K. Vrieze, *Inorg. Chim. Acta*, 1981, **47**, 67.
- 58 A. M. Kluwer, C. J. Elsevier, M. Bühl, M. Lutz and A. L. Spek, *Angew. Chem., Int. Ed.*, 2003, **42**, 3501.
- 59 B. V. Popp, J. L. Thorman, C. M. Morales, C. R. Landis and S. S. Stahl, *J. Am. Chem. Soc.*, 2004, **126**, 14832.
- 60 M. Brookhart, F. C. Rix, J. M. DeSimone and J. C. Barborak, *J. Am. Chem. Soc.*, 1992, **114**, 5894.
- 61 B. Binotti, C. Carfagna, G. Gatti, D. Martini, L. Mosca and C. Pettinari, *Organometallics*, 2003, **22**, 1115.
- 62 C. Carfagna, G. Gatti, L. Mosca, A. Passeri, P. Paoli and A. Guerri, *Chem. Commun.*, 2007, 4540.
- 63 K. Nozaki, H. Komaki, Y. Kawashima, T. Hiyama and T. Matsubara, *J. Am. Chem. Soc.*, 2001, **123**, 534.
- 64 B. Milani, F. Paronetto and E. Zangrando, *J. Chem. Soc., Dalton Trans.*, 2000, 3055.
- 65 J. A. Iggo, Y. Kawashima, J. Liu, T. Hiyama and K. Nozaki, *Organometallics*, 2003, **22**, 5418.
- 66 L. Resconi, L. Cavallo, A. Fait and F. Piemontesi, *Chem. Rev.*, 2000, **100**, 1253.
- 67 K. Nozaki, N. Sato, Y. Tonomura, M. Yasutomi, H. Takaya, T. Hijama, T. Matsubara and N. Koga, *J. Am. Chem. Soc.*, 1997, **119**, 12779.
- 68 D. Guironnet, L. Caporaso, B. Neuwald, I. Gottker-Schnetmann, L. Cavallo and S. Mecking, *J. Am. Chem. Soc.*, 2010, **132**, 4418.
- 69 S. Noda, A. Nakamura, T. Kochi, L. W. Chung, K. Morokuma and K. Nozaki, *J. Am. Chem. Soc.*, 2009, **131**, 14088.
- 70 Z. Otwinowski and W. Minor, in *Macromolecular Crystallography, part A*, ed. C. W. Carter Jr. and R. M. Sweet, New York, 1997, p. 307.
- 71 G. M. Sheldrick, *Acta Crystallogr., Sect. A: Fundam. Crystallogr.*, 2008, **64**, 112.
- 72 L. J. Farrugia, *J. Appl. Crystallogr.*, 1999, **32**, 837.