

Nanomagnetically modified polyphosphoric acid ($\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$): an efficient, fast, and reusable catalyst for the synthesis of 2-thioxoquinazolinones under solvent-free conditions

Hossein Eshghi · Amir Khojastehnezhad ·
Farid Moeinpour · Mehdi Bakavoli ·
Nafiseh Zeinabi · Sadegh Allameh

Received: 8 August 2014 / Accepted: 2 November 2014
© Springer Science+Business Media Dordrecht 2014

Abstract Polyphosphoric acid functionalized silica-coated magnetic nanoparticles with core-shell structure ($\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$) has been used as a magnetically recyclable green catalyst for the one-pot three-component synthesis of 2-thioxoquinazolinones by the reaction of isatoic anhydride, primary amines and thiourea under neat conditions. The catalyst is readily recovered by simple magnetic decantation and can be recycled five times with no significant loss of catalytic activity.

Keywords Polyphosphoric acid · Magnetic nanoparticles · One-pot, three-component · 2-Thioxoquinazolinones · Isatoic anhydride

Introduction

In recent years, much attention has been directed toward the production of magnetic nanoparticles (MNPs) [1–3], because these nanoparticles can be well dispersed in the reaction mixtures without a magnetic field providing large surfaces for ready access of substrate molecules. More importantly, after completing the reactions, the MNP catalysts can be isolated efficiently from the product solution through a simple

H. Eshghi · M. Bakavoli
Department of Chemistry, Faculty of Sciences, Ferdowsi University of Mashhad, Mashhad, Iran

A. Khojastehnezhad · N. Zeinabi · S. Allameh
Department of Chemistry, College of Science, Islamic Azad University, Mashhad Branch, Mashhad, Iran

F. Moeinpour (✉)
Department of Chemistry, College of Science, Islamic Azad University, Bandar Abbas Branch, 7915893144 Bandar Abbas, Iran
e-mail: f.moeinpour@gmail.com; fmoeinpour52@iauba.ac.ir


magnetic separation process. The strategy of magnetic separation, taking advantage of MNPs, is typically more effective than filtration or centrifugation as it prevents loss of the catalyst [4, 5]. Magnetic separation of super MNPs is simple, economical, and promising for industrial applications. From both economic and environmental viewpoints, organic reactions under solvent-free conditions using recoverable catalysts have gained significant attention [5–8]. Rostamnia et al. reported the synthesis of MNPs for immobilizing sulfuric acid as a heterogeneous catalyst, and showed that their synthesized catalyst can act as a magnetic separable catalyst and after completing the reaction can be easily isolated by using an external magnet [9]. In another study, Mamani and et al. reported supporting sulfonic acid on silica-coated MNPs, and obtained good results in the catalytic activity of these catalysts [10]. Polyphosphoric acid (PPA) is an inorganic acid which is used as a catalyst in organic synthesis [11, 12], but because it is homogeneous, its separation is difficult after completing the reaction. Thus, we decided to support this acid on silica-coated MNPs.

Thioxoquinazolinones have been the object of intensive investigation due to their different biological properties such as antimycobacterial [13], antifungal [14], antihypertensive [15], antihistaminic [16], enzyme inhibitor [17], anticancer [18] and antiviral activities [19]. Although various procedures have been reported for the synthesis of thioxoquinazolinone derivatives [20–22], most of the methods have encountered some drawbacks, such as low yields, prolonged reaction time, expensive catalysts and use of toxic organic solvents. Thus, the development of an environmentally benign and high yielding methodology for the synthesis of thioxoquinazolinones is in great demand.

Recently, we developed approaches for the synthesis of biologically interesting products via multicomponent reactions [23–26]. The challenge in this field was developing efficient and rapid green methods. Based on our earlier success in the preparation of magnetic nanoparticles as catalysts [27–30] combined with our achievements in this area, we present here the results of an extended investigation into the activity of the PPA functionalized magnetic nanocatalyst [27] $\text{NiFe}_2\text{O}_4\text{@SiO}_2\text{-PPA}$, as an efficient catalyst for the synthesis of 2-thioxoquinazolinones. Facile separation of the catalyst by using an external magnet and the recyclability of the catalyst (up to five times) are other important benefits of this system. To the best of our knowledge, there are no examples of the use of $\text{NiFe}_2\text{O}_4\text{@SiO}_2\text{-PPA}$ as a catalyst for the synthesis of thioxoquinazolinones from the condensation of isatoic anhydride, primary amines and thiourea under solvent-free conditions. Therefore, we wish to report a simple, rapid and an efficient synthetic method for the synthesis of thioxoquinazolinones using $\text{NiFe}_2\text{O}_4\text{@SiO}_2\text{-PPA}$ as a heterogeneous and reusable catalyst without the requirement for any solvent, salt, or additive (Scheme 1).

Experimental

Melting points were determined on an Electrothermal type 9100 melting point apparatus. IR spectra were recorded using a 4300 Shimadzu spectrophotometer with

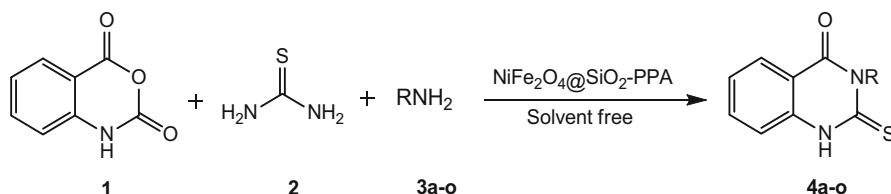

Scheme 1 Synthesis of thioxoquinazolinones catalyzed by NiFe₂O₄@SiO₂-PPA

KBr plates. ¹H NMR spectra were recorded on a Bruker DRX500 spectrometer. The products (**4a–o**) were isolated and characterized by comparison of physical and spectral data with those of known samples.

Preparation of NiFe₂O₄@SiO₂-PPA

The magnetic nanoparticles (NiFe₂O₄; Fig. 1) were synthesized by a chemical co precipitation technique using ferric and nickel ions [31]. Based on our previous report [27], coating a layer of silica on the surface of the NiFe₂O₄ nanoparticles and then functionalization of the iron oxide with polyphosphoric acid were achieved by treatment with tetraethyl orthosilicate (TEOS) followed by polyphosphoric acid. As shown in Fig. 1, the SEM image of NiFe₂O₄ nanoparticles demonstrates that these MNPs are almost spherical and regular in shape. However, aggregation of the nanoparticles was found and this aggregation might occur during the coating and supporting process [27–30].

General procedure for the preparation of 3-(aryl)-2-thioxo-2,3-dihydroquinazolin-4(1H)-ones (**4a–i**)

A mixture of isatoic anhydride (2.0 mmol), primary amines (2.0 mmol) with thiourea (2.0 mmol) under solvent-free condition at 120 °C in the presence of (0.02 g) of NiFe₂O₄@SiO₂-PPA was heated in an oil bath for 18–30 min. Upon completion, cold ethanol was added to the reaction mixture (the product is soluble in ethanol) and the NiFe₂O₄@SiO₂-PPA was placed on the side wall of the reaction vessel with the aid of an external magnet, then the catalyst was washed and dried to be reused in the next run. The solvent was evaporated and the resulting crude product was collected and gives compounds (**4a–o**) in high yields.

The spectral data of some representative 3-(aryl)-2-thioxo-2,3-dihydroquinazolin-4(1H)-ones are the following:

3-phenyl-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (4a): mp 307–309 °C, ¹H NMR (500 MHz, DMSO-*d*₆): δ 7.2–8 (m, 9H, Ar-H), 13 (br, 1H, N-H exchanges with D₂O), IR (KBr disc): 1,662 (C=O), 1,229 (C=S), 3,243 cm⁻¹ (N-H).

3-(4-Methylphenyl)-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (4d): mp 305–307 °C, ¹H NMR (500 MHz, DMSO-*d*₆): δ 2.38 (s, 3H, CH₃), 7.1–8 (m, 8H, Ar-H), 13 (br,

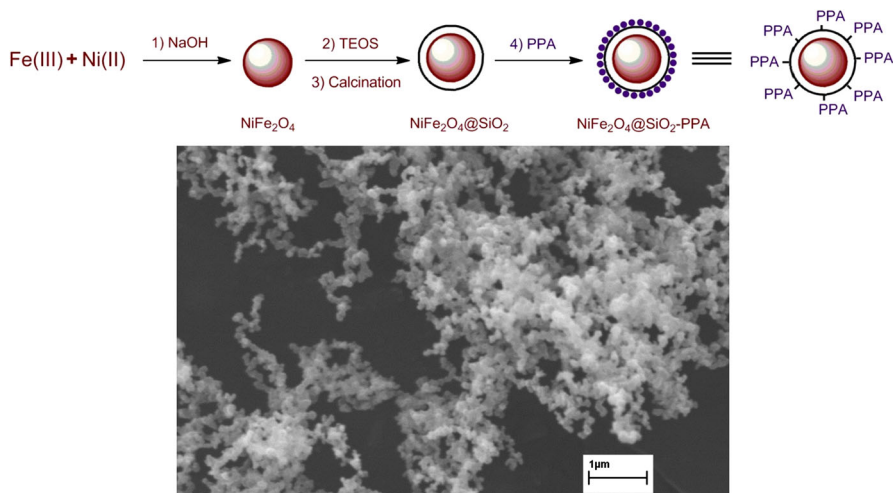


Fig. 1 Preparation of polyphosphoric acid supported on $\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$ and its SEM image

^1H , N–H exchanges with D_2O), IR (KBr disc): 1,662 (C=O), 1,199 (C=S), 3,243 cm^{-1} (N–H).

3-Benzyl-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (4e): mp 254–255 °C, ^1H NMR (500 MHz, $\text{DMSO}-d_6$): δ 5.6 (s, 2H, CH_2), 7.2–8 (m, 9H, Ar–H), 13 (br, 1H, N–H exchanges with D_2O), IR (KBr disc): 1,688 (C=O), 1,179 (C=S), 3,200 cm^{-1} (N–H).

3-(4-Chlorophenyl)-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (4f): mp 318–320 °C, ^1H NMR (500 MHz, $\text{DMSO}-d_6$): δ 7.2–8 (m, 8H, Ar–H), 13 (br, 1H, N–H exchanges with D_2O), IR (KBr disc): 1,661 (C=O), 1,233 (C=S), 3,244 cm^{-1} (N–H).

3-(2-Methylphenyl)-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (4h): mp 265–267 °C, ^1H NMR (500 MHz, $\text{DMSO}-d_6$): δ 2.94 (s, 3H, CH_3), 7.1–8 (m, 8H, Ar–H), 13 (br, 1H, N–H exchanges with D_2O), IR (KBr disc): 1,662 (C=O), 1,199 (C=S), 3,286 cm^{-1} (N–H).

Results and discussion

In order to determine the optimum conditions, the reaction between isatoic anhydride (2.0 mmol), aniline (2.0 mmol) with thiourea (2.0 mmol) at 120 °C were chosen as a model reaction. The best result has been obtained at 0.02 g of catalyst (Table 1) and under solvent-free conditions (Table 2). For comparison, and to show the effect of $\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$ as a solid acid catalyst, synthesis of the model compound **4a**, was also investigated using $\text{SiO}_2\text{-PPA}$, PPA, and SiO_2 under solvent free conditions separately. The results are given in Table 3 and, as shown, $\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$ gave the best result (entry 1). Using $\text{SiO}_2\text{-PPA}$ as the catalyst

Table 1 Comparison of the amount of NiFe₂O₄@SiO₂-PPA and yields for synthesis of 3-phenyl-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (**4a**)

Entry	Catalyst mol% (g)	Time (min)	Yield (%)
1	None	120	None
1	0.4 (0.008)	60	31
1	0.5 (0.010)	30	54
2	1.0 (0.020)	30	67
3	2.0 (0.040)	18	91
4	4.0 (0.080)	18	92
5	5.0 (0.10)	18	91

Table 2 Comparison of different solvents for synthesis of 3-phenyl-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (**4a**) using NiFe₂O₄@SiO₂-PPA

Entry	Solvent	Time (min)	Yield (%)
1	<i>p</i> -xylene	180	79
2	DMF	120	70
3	Toluene	300	57
4	DMAC	120	41
5	EtOH	480	67
6	Solvent-free	18	91

Table 3 Comparison of various conditions for synthesis of 3-phenyl-2-thioxo-2,3-dihydroquinazolin-4(1H)-one (**4a**)

Entry	Catalyst (g)	Time (min)	Yield (%)
1	NiFe ₂ O ₄ @SiO ₂ -PPA (0.04)	18	91
2	SiO ₂ -PPA (0.05)	30	84
3	PPA (0.05)	30	68
4	SiO ₂ (0.10)	60	No reaction















Isatoic anhydride (2.0 mmol), aniline (2.0 mmol) and thiourea (2.0 mmol) at 120 °C under solvent-free conditions

gave the product **4a** in good yield (84 %) (entry 2), but separation and recovery of SiO₂-PPA were not easy, because we needed filtration or centrifugation, which are not eco-friendly processes. Also, we used PPA as a catalyst and the yield of the reaction was relatively good (68 %), but it was not recyclable (entry 3). Therefore, NiFe₂O₄@SiO₂-PPA can act as a solid acid catalyst in the synthesis of 2-thioxoquinazolinones derivatives. The generality of this process was demonstrated by the wide range of substituted primary amines to synthesize the corresponding products in high yields (Table 4). Unlike some previously reported methods, the present method does not require toxic organic solvents to produce the 2-thioxoquinazolinones derivatives (**4a–o**). All the products were characterized by NMR, IR and melting point and also by comparison with the data reported in literature.

Table 4 NiFe₂O₄@SiO₂-PPA-catalyzed one-pot synthesis of 3-(aryl)-2-thioxo-2,3-dihydroquinazolinone-4(1H)-ones (**4a–o**)

Entry	R	Product ^a	Time (min)	Yield (%) ^b	Mp (°C)	Lit. Mp (°C)
1		 4a	18	91	303–304	302 [32]
2		 4b	25	86	318–320	320 [32]
3		 4c	22	88	273–274	274 [32]
4		 4d	19	79	299–300	298 [32]
5		 4e	20	92	254–255	253–254 [33]
6		 4f	18	90	318–320	319–321 [33]
7		 4g	20	89	282–284	282–284 [34]
8		 4h	22	83	260–262	260–262 [34]


Table 4 continued

Entry	R	Product ^a	Time (min)	Yield (%) ^b	Mp (°C)	Lit. Mp (°C)
9		 4i	25	88	260–262	261–263 [35]
10		 4j	25	91	328–329	330–332 [36]
11		 4k	30	88	254–256	254–256 [36]
12		 4l	25	85	268–269	270–271 [37]
13		 4m	25	90	198–199	199–200 [20]
14		 4n	30	87	246–248	246–248 [36]
15		 4o	20	90	170–172	171–172 [37]

Isatoic anhydride (2.0 mmol), aniline (2.0 mmol), thiourea (2.0 mmol) and NiFe₂O₄@SiO₂-PPA (0.02 g) at 120 °C

^a All the products were identified by comparing of their melting points and spectral data (IR and ¹H NMR) with those of authentic samples

^b Isolated yields

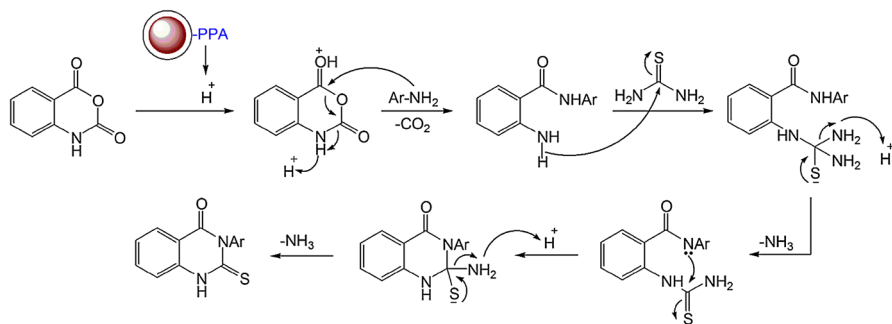

Scheme 2 Plausible reaction mechanism for the synthesis of 2-thioxoquinazolinones in the presence of $\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$ as a catalyst

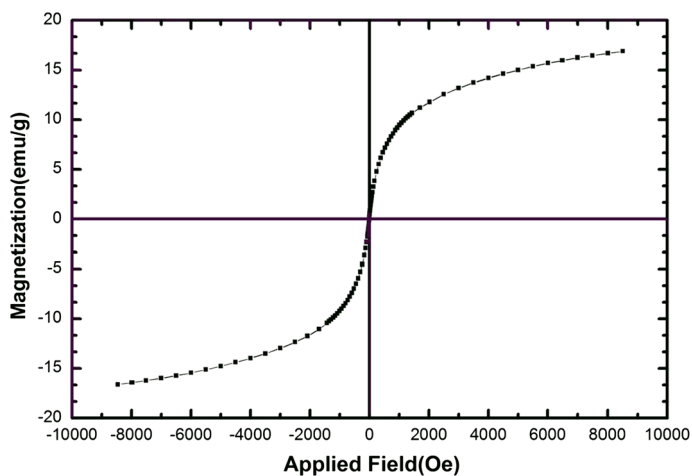


Fig. 2 VSM curve of NiFe_2O_4 at r.t

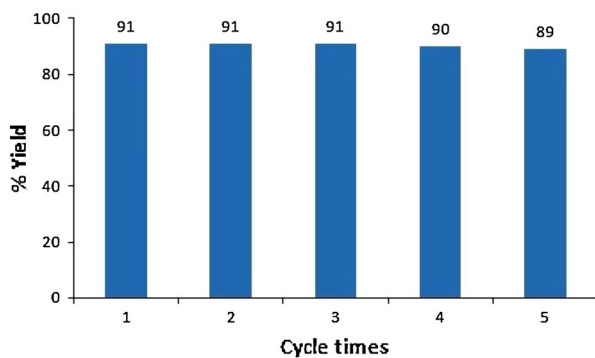


Fig. 3 Reusability of $\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$ for the model reaction

A probable mechanism for condensation of isatoic anhydride, aniline, thiourea and $\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$ (as an acidic catalyst) for the synthesis of 2-thioxoquinazolinones is proposed as shown in Scheme 2.

It is of great importance that the core/shell material should possess sufficient magnetic and superparamagnetic properties for its practical applications. Magnetic hysteresis measurements for the NiFe_2O_4 were done in an applied magnetic field at r.t., with the field sweeping from $-10,000$ to $+10,000$ Oersted. As shown in Fig. 2, the M (H) hysteresis loop for the samples was completely reversible, showing that the nanoparticles exhibit superparamagnetic characteristics. The hysteresis loops of them reached saturation up to the maximum applied magnetic field. The magnetic saturation value of the NiFe_2O_4 is 16.71 emu g^{-1} at r.t. These particles showed high permeability in magnetization, and their magnetization was sufficient for magnetic separation with a conventional magnet (Fig. 2).

At the end of the reaction, to determine the applicability of catalyst recovery, ethanol was added to the reaction mixture to dissolve the product. With the aid of an external magnet, the catalyst was held on the side wall of the reaction vessel, while the solution was decanted. The catalyst was washed with diethyl ether to remove residual product, dried at 100°C under vacuum, and reused in subsequent reactions in excellent yields (91, 91, 91, 90 and 89 %). It showed the same activity as the fresh catalyst without any significant loss of its activity (Fig. 3).

Conclusion

We have reported a simple new catalytic method for the synthesis of 2-thioxoquinazolinones by one-pot three-component condensation reaction of isatoic anhydride, primary amines and thiourea using $\text{NiFe}_2\text{O}_4@\text{SiO}_2\text{-PPA}$ as an efficient, reusable, and green heterogeneous catalyst under solvent-free conditions. Moreover, the catalyst could be readily separated by use of a magnetic force and reused without any significant loss of catalytic activity after five runs.

Acknowledgment The authors are grateful to Islamic Azad University, Bandar Abbas and Mashhad Branches for financial support.

References

1. V. Polshettiwar, R. Luque, A. Fihri, H. Zhu, M. Bouhrara, J.M. Basset, *Chem. Rev.* **111**, 3036 (2011)
2. M.M. Lin, H.H. Kim, H. Kim, M. Muhammed, D.K. Kim, *Nano Rev.* **1**, 4883 (2010)
3. D. Astruc, F. Lu, J.R. Aranzas, *Angew. Chem. Int. Ed.* **44**, 7852 (2005)
4. A. Hu, G.T. Yee, W. Lin, *J. Am. Chem. Soc.* **127**, 12486 (2005)
5. M. Mojtahedi, M.S. Abaee, T. Alishiri, *Tetrahedron Lett.* **50**, 2322 (2009)
6. L. Mamani, A. Heydari, M. Sheykhan, *Appl. Catal. A* **384**, 122 (2010)
7. B. Karimi, E. Farhangi, *Adv. Synth. Catal.* **355**, 508 (2013)
8. F. Shahbazi, K. Amani, *Catal. Commun.* **55**, 57 (2014)
9. S. Rostamnia, K. Lamei, M. Mohammadquli, M. Sheykhan, A. Heydari, *Tetrahedron Lett.* **53**, 5257 (2012)
10. L. Mamani, M. Sheykhan, A. Heydari, M. Faraji, Y. Yamini, *Appl. Catal. A* **377**, 64 (2010)
11. D.W. Hein, R.J. Alheim, J.J. Leavitt, *J. Am. Chem. Soc.* **79**, 427 (1957)

12. E. Alcalde, I. Dinarés, L. Pérez-García, T. Roca, *Synthesis* **1992**, 395 (1992)
13. V. Agarsamy, R. Giridhar, M.R. Yadav, R. Revathi, K. Ruckmani, *Ind. J. Pharm. Sci.* **68**, 532 (2006)
14. A. Rajasekaran, V. Rajamanickam, S. Darlinquine, *Eur. Rev. Med. Pharmacol. Sci.* **17**, 95 (2013)
15. R. Cortez, I.A. Rivero, R. Somanathan, G. Aguirre, F. Ramirez, E. Hong, *Synth. Commun.* **21**, 285 (1991)
16. V. Alagarsamy, R. Giridhar, M.R. Yadav, *J. Pharm. Pharmacol.* **58**, 1249 (2006)
17. M. Redondo, J.G. Zarruk, P. Ceballos, D.I. Perez, C. Perez, A.P. Castillo, M.A. Moro, J. Brea, C. Val, M.I. Cadavid, M.I. Loza, N.E. Campillo, A. Martinez, C. Gil, *Eur. J. Med. Chem.* **47**, 175 (2012)
18. H.M. Jen, H.L. Jiau, K.S. Chu, X.Y. Bastow, B. Kenneth, N.K. Hamel, E. Lee, K. Hsiung, *J. Med. Chem.* **43**, 4479 (2000)
19. S.K. Krishnan, S. Ganguly, R. Veerasamy, B. Jan, *Eur. Rev. Med. Pharmacol. Sci.* **15**, 673 (2011)
20. F. Wanga, P. Zhaoa, C. Xi, *Tetrahedron Lett.* **52**, 231 (2011)
21. S. Allameh, M.M. Heravi, M.M. Hashemi, F.F. Bamoharram, *Chin. Chem. Lett.* **22**, 131 (2011)
22. A. Saeed, U. Shaheena, M. Bolteb, *J. Chin. Chem. Soc.* **57**, 82 (2010)
23. A. Khojastehnezhad, F. Moeinpour, A. Davoodnia, *Chin. Chem. Lett.* **22**, 807 (2011)
24. A. Khojastehnezhad, F. Moeinpour, A.R. Shams, *Synth. React. Inorg. Met. Org. Chem.* **42**, 273 (2012)
25. F. Moeinpour, N. Dorostkar-Ahmadi, A. Sardashti-Birjandi, A. Khojastehnezhad, M. Vafaei, *Res. Chem. Intermed.* **40**, 3145 (2014)
26. F. Moeinpour, N. Dorostkar, M. Vafaei, *Synth. Commun.* **42**, 2367 (2012)
27. A. Khojastehnezhad, M. Rahimizadeh, F. Moeinpour, H. Eshghi, M. Bakavoli, *C. R. Chim.* **17**, 459 (2014)
28. A. Khojastehnezhad, M. Rahimizadeh, H. Eshghi, F. Moeinpour, M. Bakavoli, *Chin. J. Cat.* **35**, 376 (2014)
29. H. Eshghi, A. Khojastehnezhad, S.M. Seyedi, F. Moeinpour, M. Abbasi, M. Bakavoli, *RSC Adv.* **4**, 39782 (2014)
30. M. Rahimizadeh, S.M. Seyedi, M. Abbasi, H. Eshghi, A. Khojastehnezhad, F. Moeinpour, M. Bakavoli, *J. Iranian, Chem. Soc.* (2014). doi:[10.1007/s13738-014-0546-z](https://doi.org/10.1007/s13738-014-0546-z)
31. D. Zins, V. Cabuil, R. Massart, *J. Mol. Liq.* **83**, 217 (1999)
32. R. Lakhan, M. Srivastava, *Proc. Indian. Acad. Sci. Chem. Sci.* **105**, 11 (1993)
33. J. Azizian, A.A. Mohammadi, A.R. Karimi, *Synth. Commun.* **33**, 415 (2003)
34. D. Guo-lan, W. Man-Man, H. Zhi-Bin, S. Da-Qing, J. Het, *Chem.* **46**, 645 (2009)
35. V.K. Tiwari, D.D. Singh, H.A. Hussain, B.B. Mishra, A. Singh, *Monatsh. Chem.* **139**, 43 (2008)
36. I. Yavari, S. Beheshti, *Helv. Chim. Acta* **94**, 1825 (2011)
37. T. Kappe, W. Steiger, E. Ziegler, *Monatsh. Chem.* **98**, 214 (1967)