

# Highly Efficient Quenching of Nanoparticles for the Detection of Electron-Deficient Nitroaromatics

Patrick Marks,<sup>1</sup> Sage Cohen,<sup>2</sup> Mindy Levine<sup>1</sup>

<sup>1</sup>Department of Chemistry, University of Rhode Island, 51 Lower College Road, Kingston, Rhode Island 02881

<sup>2</sup>South Kingstown High School, South Kingstown, Rhode Island

Correspondence to: M. Levine (E-mail: mlevine@chm.uri.edu)

Received 29 April 2013; accepted 9 June 2013; published online 26 June 2013

DOI: 10.1002/pola.26824

**ABSTRACT:** Reported herein is the highly efficient quenching of fluorescent organic nanoparticles by 2,4-dinitrotoluene and 2,4,6-trinitrotoluene. These fluorescent nanoparticles are formed from the hydrophobic collapse of fluorescent polymer chains and display quenching efficiencies that are in line with the highest reported literature values. Moreover, the fluorescent quenching occurs only for the fluorescent nanoparticles, and not for the precursor polymer solutions, which display

marked insensitivity to the presence of nitroaromatics. This aggregation-dependent fluorescent quenching has numerous applications for the detection of small-molecule electron-deficient analytes. © 2013 Wiley Periodicals, Inc. *J. Polym. Sci., Part A: Polym. Chem.* **2013**, *51*, 4150–4155

**KEYWORDS:** conducting polymers; fluorescence; nanoparticles

**INTRODUCTION** Researchers have had remarkable success in developing detection methods for electron-deficient nitroaromatic explosives such as 2,4,6-trinitrotoluene (TNT), and for the nonexplosive but structurally related 2,4-dinitrotoluene (DNT) (Chart 1).<sup>1–3</sup> These detection methods have significant practical applications for national security and have been used in airport screening systems<sup>4</sup> and in the detection of land mines in Iraq and Afghanistan.<sup>5</sup> Such methods include the use of amplified fluorescent quenching of conjugated poly(phenyleneethynylenes)<sup>6,7</sup> and other fluorescent polymers,<sup>8</sup> quenching of fluorescent silica nanoparticles,<sup>9</sup> and quenching of metallic nanoparticles.<sup>10</sup> Using such methodology, detection limits as low as 1 fg (femtogram) have been obtained.<sup>11</sup>

Many of the previously reported detection methods rely on the quenching of fluorescent polymers in the solid state, for example, in spin-cast thin films or in capillary tubes. The fluorescence quenching in such aggregated states is generally higher than quenching observed in solution, due to the ability of the fluorescent polymers to have inter-chain exciton migration in addition to intra-chain migration.<sup>12</sup>

Another way to ensure inter-chain communication between polymer chains is to confine them in noncovalently linked fluorescent nanoparticles, often referred to as “polymer dots.”<sup>13</sup> Such particles can be fabricated in a number of ways, including: (a) the hydrophobic collapse of the polymer chain when introduced into an aqueous solvent, also called

“re-precipitation,”<sup>14,15</sup> and (b) synthesis in mini-emulsions stabilized by surfactants.<sup>16</sup> Despite the ubiquity of such nanoparticles in biological detection schemes,<sup>17</sup> they have been used only rarely for explosive detection. In one example, polythiophene nanoparticles were used for DNT detection, with a reported quenching constant of  $2706\text{ M}^{-1}$ .<sup>18</sup> Oligo(tetraphenyl)silole nanoparticles have also been used, with a quenching constant of up to  $5000\text{ M}^{-1}$  in the presence of DNT.<sup>19</sup> The quenching of other fluorescent nanoparticles by nitroaromatics has not been reported.

Reported herein is the use of fluorescent nanoparticles fabricated by re-precipitation methods from 2,1,3-benzoxadiazole-*alt*-polyfluorene (PFBO, Compound **5**) and 2,1,3-benzothiadiazole-*alt*-polyfluorene (PFBT, Compound **6**) for the detection of DNT and TNT (Chart 2). Quenching constants up to  $6.9 \times 10^3\text{ M}^{-1}$  were observed for PFBO nanoparticles exposed to DNT (0.17 mM DNT), and  $1.2 \times 10^4\text{ M}^{-1}$  for PFBT nanoparticles in the presence of TNT (0.14 mM TNT). These quenching efficiencies clearly establish the general use of fluorescent nanoparticles in nitroaromatic-induced quenching schemes.


## EXPERIMENTAL

### Materials and Methods

All chemicals were purchased from Sigma-Aldrich Chemical Company, with the exception of DNT (purchased from MP Biomedicals, Inc.) and TNT (ampules of 1 mg/mL solution in

Additional Supporting Information may be found in the online version of this article.

© 2013 Wiley Periodicals, Inc.

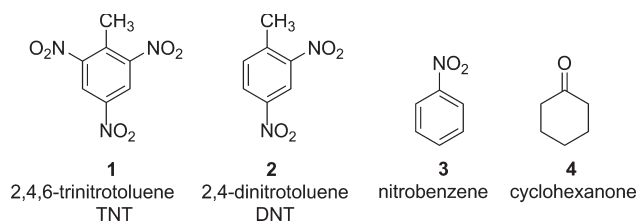

**CHART 1** Electron-deficient analytes under investigation.

acetonitrile were purchased from Ultra Scientific).  $^1\text{H}$  NMR spectra were obtained using a Bruker 300 MHz spectrometer. Ultraviolet-visible (UV-Vis) spectra were obtained using an Agilent 8453 spectrometer equipped with a photodiode array detector. Fluorescence spectra were obtained using a Shimadzu RF-5301PC spectrophotofluorimeter and integrated versus wavenumber. Dynamic light scattering (DLS) data were acquired using a Malvern Zetasizer Instrument. Gel permeation chromatography (GPC) data were acquired using a Waters GPC liquid chromatography system with an internal refractive index detector and two Waters Styragel HR-5E columns. Retention times were calibrated against polystyrene standards (Polymer Laboratories, Amherst, MA) to produce number average molecular weight ( $M_n$ ) and weight average molecular weight ( $M_w$ ) values. Thin films were spun using a Laurell Technologies Spin Processor.

### Polymer Synthesis

The synthesis of polymers PFBO and PFBT followed literature-reported procedures.<sup>20,21</sup> The synthetic schemes for each polymer are shown below (Schemes 1 and 2).

### GPC

The molecular weight and size distribution of the newly synthesized polymers were determined by GPC, and the results are shown below:

#### PFBO 5:


$$\begin{aligned} M_n &= 6.1976 \times 10^3 \text{ g mol}^{-1} \\ M_w &= 8.8652 \times 10^3 \text{ g mol}^{-1} \\ \text{PDI} &= 1.43 \end{aligned}$$

#### PFBT 6:

$$\begin{aligned} M_n &= 6.3503 \times 10^3 \text{ g mol}^{-1} \\ M_w &= 1.7003 \times 10^4 \text{ g mol}^{-1} \\ \text{PDI} &= 2.68 \end{aligned}$$

### Nanoparticle Fabrication

Nanoparticles were formed following literature-reported procedures.<sup>22</sup> Briefly, 2 mL of a polymer solution ( $0.01 \text{ g L}^{-1}$ )

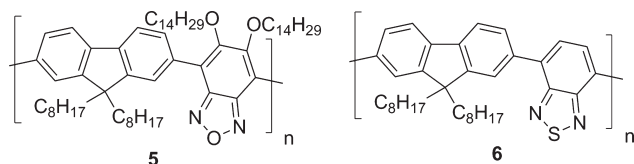

**CHART 2** Structures of the fluorescent organic polymers.

dissolved in THF was quickly added to 8 mL of deionized water, while sonicating the water. After addition of the polymer solution, nitrogen was bubbled through the solution for 1 h to remove the THF.

### Fluorescence Quenching Experiments

In quenching experiments, two solutions were made: one containing dilute particles in water with acetonitrile (Solution A), and one with dilute particles in water and DNT in acetonitrile (Solution B).

The water-acetonitrile solutions were allowed to equilibrate for 1 h before analysis. Absorbance spectra of all particle solutions were recorded, and the absorbance at the excitation wavelength was checked to be below 0.1 absorbance units.

A total of 2.5 mL of the particle solution in water/acetonitrile (Solution A) was added to the cuvette, and the fluorescence was recorded. Three 500  $\mu\text{L}$  aliquots of the DNT/particle solution (Solution B) were added to the cuvette, and the fluorescence was re-recorded after each addition. The cuvette was then filled with 1.25 mL Solution A and 1.25 mL Solution B. Three 500  $\mu\text{L}$  aliquots of B were added, and fluorescence recorded after each addition. Finally, the fluorescence of Solution B by itself was recorded.

All PFBO solutions were excited at 400 nm, and all PFBT solutions were excited at 420 nm.


The fluorescence emission spectra were integrated versus wavenumber on the X-axis. Plotting the concentration of analyte (DNT or TNT) in molarity on the X-axis versus  $I_0/I$  (initial integrated emission in the absence of the analyte divided by the integrated emission in the presence of the analyte) on the Y-axis yielded Stern-Volmer plots. The data were fit to linear relationships to determine the Stern-Volmer quenching constants. The  $R^2$  values for all linear fits were above 0.93.

### Thin Film Quenching


Thin films were spun-cast on a square glass cover slip (dimensions: 1 cm  $\times$  1 cm), by adding 0.2 mL of a 0.1 mg  $\text{mL}^{-1}$  solution of THF to the slip, then spinning it at 1000 rpm for 20 s. Thin film quenching was assessed by adding 10 mg of DNT (Compound 2) to a cuvette, and covering the cuvette for 2 h. After 2 h, the polymer thin film was dropped in, the cuvette was covered, and fluorescence intensity was immediately recorded. The intensity was recorded at a single wavelength in 1 s intervals for 20 min. (Polymer 5: Excitation at 430 nm; emission monitoring at 500 nm; polymer 6: excitation at 450 nm; emission monitoring at 533 nm).

## RESULTS AND DISCUSSION

The newly synthesized polymers were characterized by  $^1\text{H}$  NMR, GPC, UV-Vis absorption spectroscopy, and fluorescence spectroscopy, and the results are summarized in Table 1. The fluorescent nanoparticles were characterized by absorption and fluorescence spectroscopy (Table 2), and the formation of the particles was confirmed by DLS measurements.

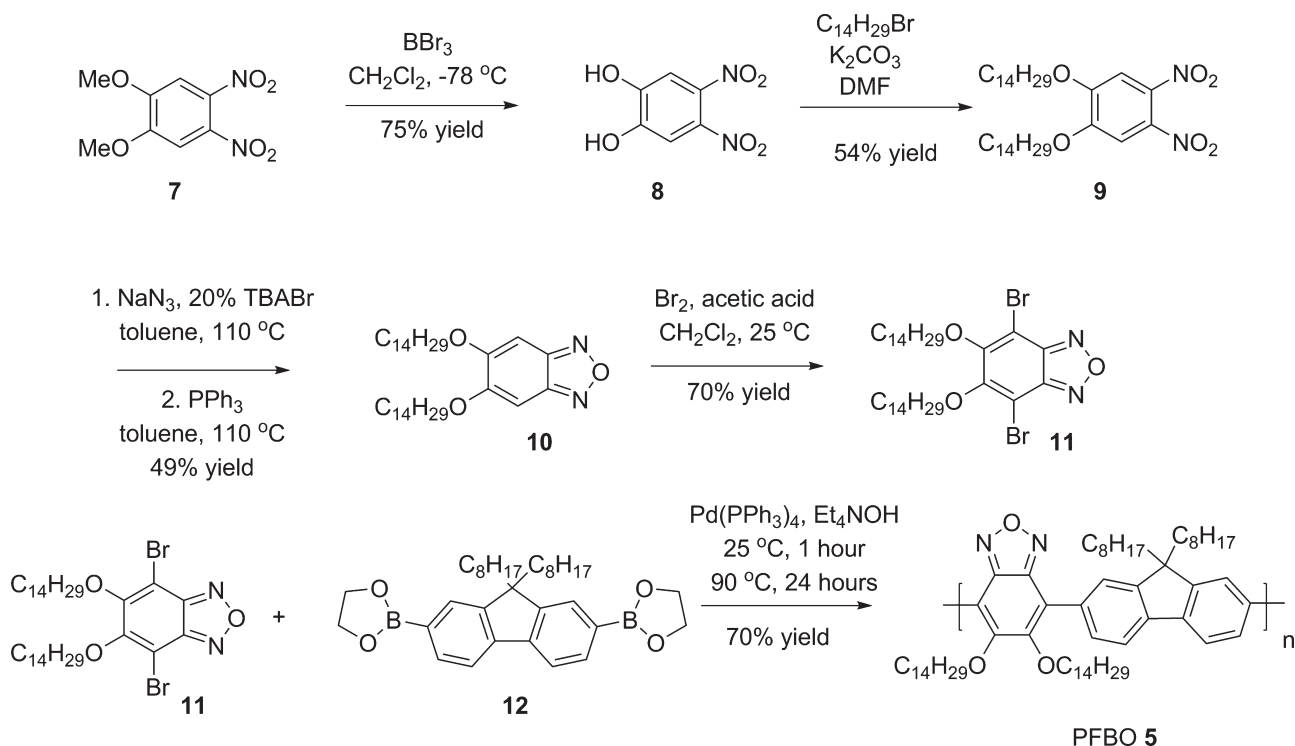

SCHEME 1 Synthesis of PFBO 5.

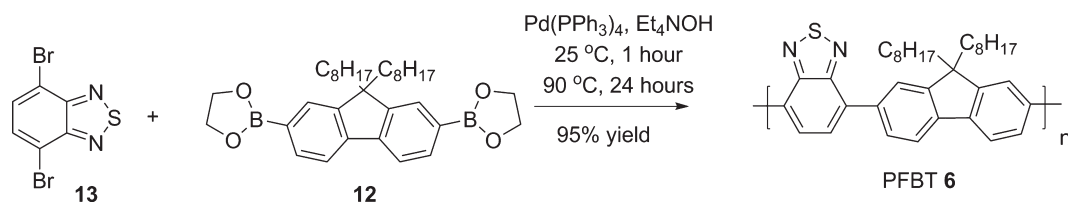

SCHEME 2 Synthesis of PFBT 6.

Remarkably, the fluorescent nanoparticles demonstrated highly efficient quenching in the presence of DNT and TNT, whereas the fluorescent polymers (from which the particles were synthesized) displayed no fluorescence quenching. All the quenching efficiencies were fitted to the Stern-Volmer equation and displayed excellent linear fits. A summary of the Stern-Volmer constants for each particle-analyte combination is shown in Table 3, and examples of the quenching are shown in Figure 1.

This quenching displayed the following key features:

a. *Low limits of detection*: The concentration of analytes required to achieve full quenching are shown in Table 3 (0.17 and 0.14 mM for DNT and TNT, respectively). However, in all cases, noticeable quenching was observed at substantially lower analyte concentrations. The addition of as little as 29  $\mu$ M of TNT to the nanoparticle solutions resulted in quenching, as did the addition of 23  $\mu$ M of DNT. Although these detection limits are substantially greater than those reported by Trogler and coworkers<sup>23</sup> and Rochat and Swager<sup>24</sup> for analogous thin-film systems, the use of nanoparticles to achieve quenching in this case provides operational advantages.

TABLE 1 Properties of the PFBO and PFBT Polymers

	PFBO 5	PFBT 6
$\lambda_{\max}$ abs	413 nm	452 nm
$\lambda_{\max}$ em.	507 nm	532 nm
$M_w$	$8.8652 \times 10^3$ g mol <sup>-1</sup>	$1.7003 \times 10^4$ g mol <sup>-1</sup>
PDI	1.43	2.68

TABLE 2 Properties of the PFBO and PFBT-Derived Nanoparticles


	PFBO particles (5)	PFBT particles (6)
$\lambda_{\max}$ abs	411 nm	458 nm
$\lambda_{\max}$ em.	534 nm	536 nm
Average size (DLS)	24.4 nm	18.2 nm

**TABLE 3** Stern-Volmer Constants Obtained for Each Analyte-Fluorophore Combination (Maximum Analyte Concentrations in Parentheses)

	DNT	TNT
PFBT particles	4169 M <sup>-1</sup> (0.17 mM DNT)	11974 M <sup>-1</sup> (0.14 mM TNT)
PFBO particles	6867 M <sup>-1</sup> (0.17 mM DNT)	6737 M <sup>-1</sup> (0.14 mM TNT)
PFBT polymer	No quench	No quench
PFBO polymer	No quench	No quench


3.13% acetonitrile in water;  $2.5 \times 10^{-4}$  mg mL<sup>-1</sup> nanoparticles; 420 nm excitation wavelength for PFBT and 400 nm excitation wavelength for PFBO.


b. *Requirement of aggregation:* Although polymer-derived nanoparticles demonstrated efficient quenching, the polymers dissolved in tetrahydrofuran solution displayed little to no quenching under otherwise identical conditions. Moreover, polymer-derived thin films, like polymer-derived nanoparticles, were efficiently quenched by DNT, which confirms that noncovalent aggregation of the polymer chains is necessary for efficient energy transfer. These thin films were fabricated from Polymers 5 and 6 (see experimental section and ESI for details), and their fluorescence emission was monitored in the presence of DNT vapor

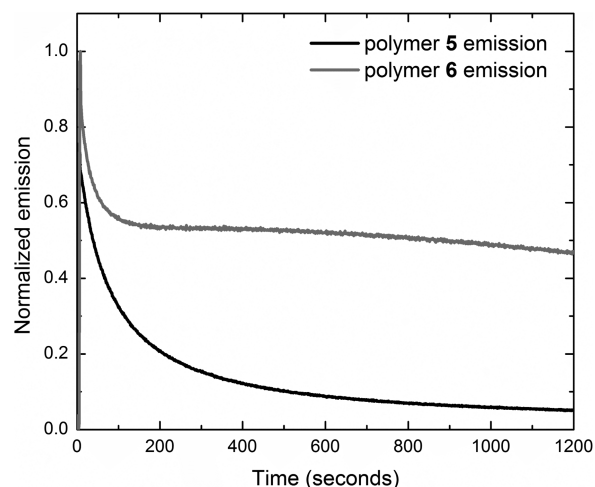**FIGURE 2** Quenching of fluorescent thin films in the presence of DNT vapor. Polymer 5 emission monitored at 500 nm; Polymer 6 emission at 533 nm.

(Fig. 2). After 20 min, the fluorescence emission of Polymer 5 in the film decreased to 10% of its maximum value, and the emission of Polymer 6 decreased to 48% of its initial value.

c. *Significant solvent dependence:* The quenching of Polymer 6-derived nanoparticles also displayed a substantial

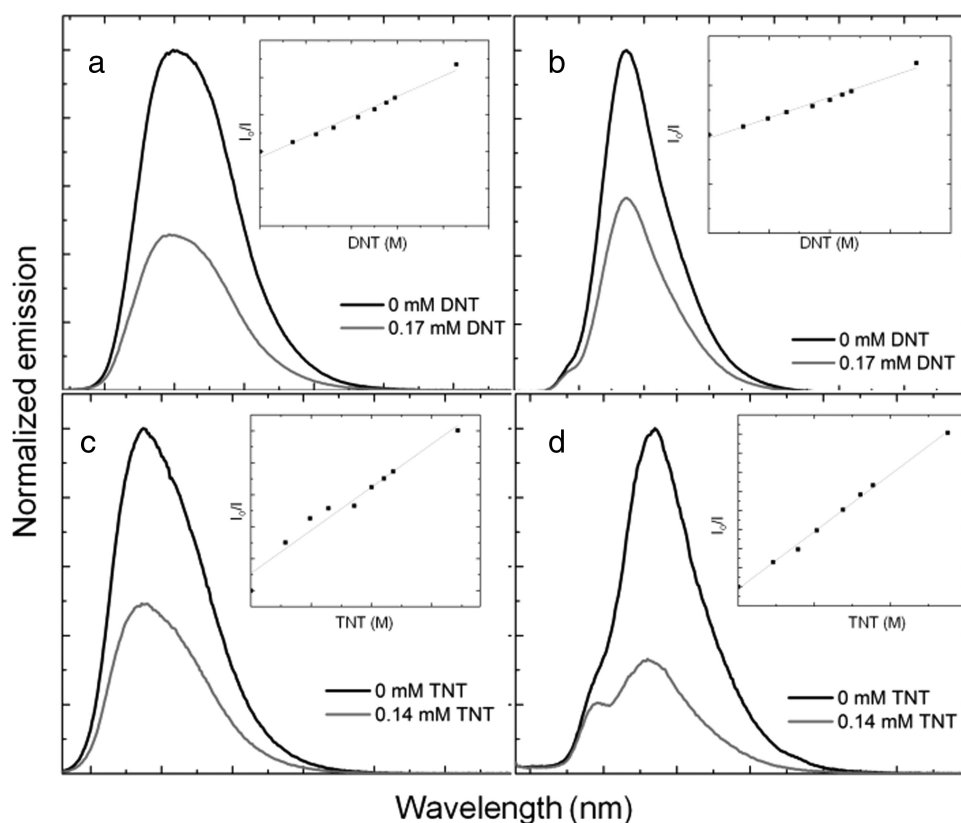**FIGURE 1** Examples of fluorescence quenching of (a) PFBT (6) particles with DNT (b) PFBO (5) particles with DNT (c) PFBT (6) particles with TNT and (d) PFBO (5) particles with TNT. Stern-Volmer plots are included as insets for each example.

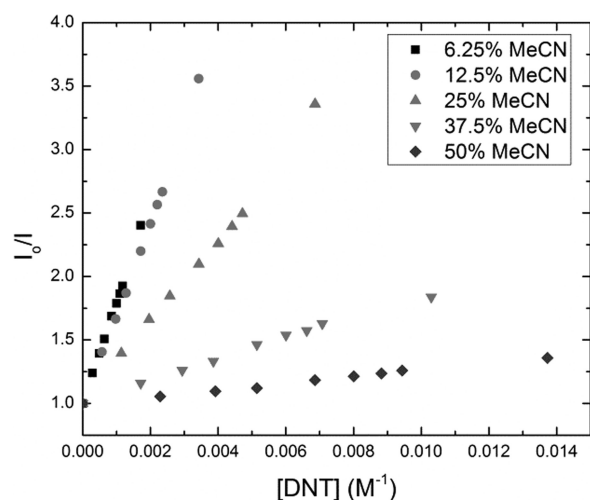

**FIGURE 3** Dependence of  $K_{sv}$  values on the acetonitrile/water ratio. Measurements were obtained for PFBT nanoparticles ( $2.5 \times 10^{-4}$  mg mL $^{-1}$ ) in the presence of DNT.

dependence on the percentage of acetonitrile in the solution, with higher amounts of acetonitrile leading to less efficient fluorescent quenching. An example of such dependence is shown in Figure 3. With 6.25% acetonitrile in water, the quenching proceeded with  $K_{sv} = 804$  M $^{-1}$ , whereas a 50% water-acetonitrile mixture yielded a  $K_{sv}$  of 27 M $^{-1}$ .

To explain this solvent dependence, DLS measurements of the particles in mixed solvents were collected, and the results are shown in Figure 4. For Polymer 5 nanoparticles, the addition of acetonitrile increased in the average particle diameter from 24 to 38 nm, but further addition of acetonitrile led to no noticeable change in the particle size (particles in 3.1% and 50% acetonitrile displayed the same average diameter).

Polymer 6 nanoparticles, by contrast, showed a marked increase in average diameter with increasing amounts of acetonitrile. Switching from 0% to 3.1% to 50% acetonitrile


caused the particle diameter to increase from 18 to 58 to 78 nm. This solvent-induced swelling caused the individual polymer chains in the nanoparticles to separate, which limited inter-chain aggregation and thus the nitroaromatic-induced quenching efficiencies.

The increased susceptibility of Polymer 6 compared with Polymer 5 is likely a result of the long alkyl chains on Polymer 5 protecting the particles from swelling and acetonitrile-induced collapse. The lower density of alkyl chains on Polymer 6 increases the particle susceptibility.

**d. Fluorescence lifetime decrease:** Preliminary lifetime data indicate that the fluorescence lifetime of the nanoparticles is significantly decreased in the presence of nitroaromatic quenchers (lifetime of Polymer 5 nanoparticles decreased from 1.8 to 1.7 ns; Polymer 6 nanoparticles decreased from 0.73 (major species) to 0.47 ns (major species)). These decreases indicate that dynamic quenching is likely occurring in this system.<sup>25</sup>

The generality of this fluorescent quenching was assessed by measuring the response of the nanoparticles to nitrobenzene (Compound 3) and cyclohexanone (Compound 4) (Chart 1). No significant quenching was observed for either nitrobenzene or cyclohexanone, for either nanoparticles or polymers. This selectivity is in line with similar literature reports,<sup>26,27</sup> which indicate improved selectivity for DNT and TNT over nitrobenzene and other small-molecule analytes.

Finally, the complete insensitivity of the polymers to the presence of such nitroaromatics was determined by exposing THF solutions of PFBO and PFBT polymers to DNT concentrations 100 times higher than those used for significant quenching of nanoparticles. Even at such high concentrations, **NO** detectable quenching of the polymer fluorescence was observed (Fig. 5), which again indicates the significant necessity of nanoparticle formation for the detection of electron-deficient analytes.

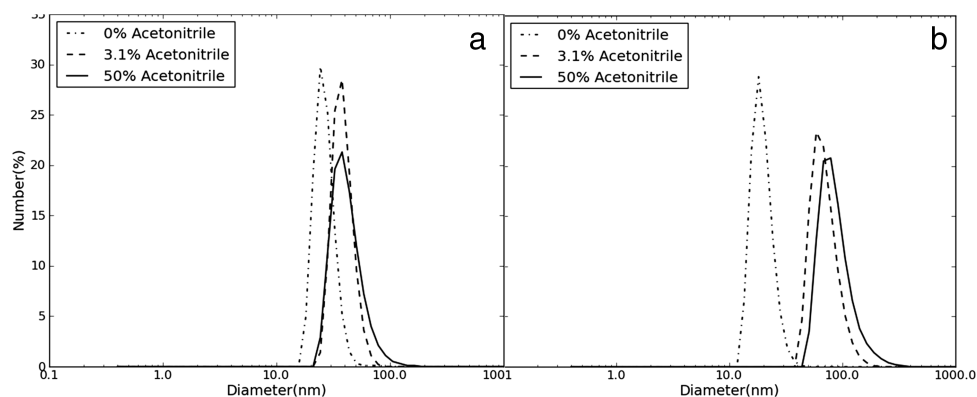

**FIGURE 4** DLS measurements of (a) polymer 5 nanoparticles and (b) polymer 6 nanoparticles in the presence of increasing amounts of acetonitrile.



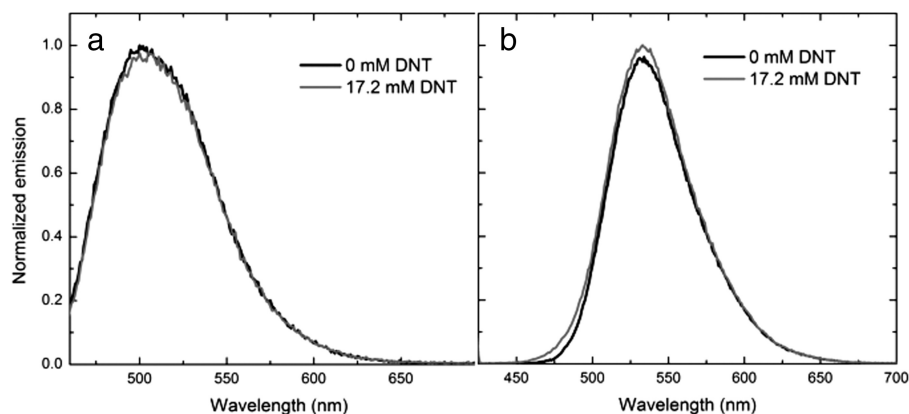


FIGURE 5 Insensitivity of (a) PFBO and (b) PFBT polymers to 17.2 mM concentrations of DNT.

## CONCLUSIONS

In summary, highly efficient quenching of fluorescent nanoparticles has been demonstrated with both TNT and DNT as analytes. The high sensitivity (as determined by  $K_{sv}$  values) and selectivity (no response to cyclohexanone or nitrobenzene), means that such quenching has potentially significant applications in turn-off detection schemes. Efforts toward developing such systems are currently in progress and results will be reported in due course.

## ACKNOWLEDGMENTS

S. Cohen thanks the American Chemical Society Project SEED for support of this work, and P. Marks thanks the University of Rhode Island Foundation for support of this work.

## REFERENCES AND NOTES

- 1 S. J. Toal, W. C. Trogler, *J. Mater. Chem.* **2006**, *16*, 2871–2883.
- 2 A. Rose, Z. Zhu, C. F. Madigan, T. M. Swager, V. Bulovic, *Nature* **2005**, *434*, 876–879.
- 3 D. Li, J. Liu, R. T. K. Kwok, Z. Liang, B. Z. Tang, J. Yu, *Chem. Commun.* **2012**, *48*, 7167–7169.
- 4 R. A. Potyrailo, N. Nagraj, C. Surman, H. Boudries, H. Lai, J. M. Slocik, N. Kelley-Loughnane, R. R. Naik, *Trends Anal. Chem.* **2012**, *40*, 133–145.
- 5 M. E. Fisher, M. la Grone, J. Sikes, *Proc. SPIE Int. Soc. Opt. Eng.* **2003**, *5089*, 991–1000.
- 6 J.-S. Yang, T. M. Swager, *J. Am. Chem. Soc.* **1998**, *120*, 11864–11873.
- 7 J.-S. Yang, T. M. Swager, *J. Am. Chem. Soc.* **1998**, *120*, 5321–5322.
- 8 B. Balan, C. Vijayakumar, M. Tsuji, A. Saeki, S. Seki, *J. Phys. Chem. B* **2012**, *116*, 10371–10378.
- 9 J. Geng, P. Liu, B. Liu, G. Guan, Z. Zhang, M.-Y. Han, *Chem. Eur. J.* **2010**, *16*, 3720–3727.
- 10 R. Tu, B. Liu, Z. Wang, D. Gao, F. Wang, Q. Fang, Z. Zhang, *Anal. Chem.* **2008**, *80*, 3458–3465.
- 11 A. Rose, C. G. Lugmair, Y.-J. Miao, J. Kim, I. A. Levitsky, V. E. Williams, T. M. Swager, *Proc. SPIE Int. Soc. Opt. Eng.* **2000**, *4038*, 512–518.
- 12 T. L. Andrew, T. M. Swager, *J. Polym. Sci., Part B: Polym. Phys.* **2011**, *49*, 476–498.
- 13 D. Tuncel, H. V. Demir, *Nanoscale* **2010**, *2*, 484–494.
- 14 Z. Tian, J. Yu, C. Wu, C. Szymanski, J. McNeill, *Nanoscale* **2010**, *2*, 1999–2011.
- 15 Y. Mai, A. Eisenberg, *Acc. Chem. Res.* **2012**, *45*, 1657–1666.
- 16 N. Joumaa, M. Lansalot, A. Theretz, A. Elaissari, A. Sukhanova, M. Artemyev, I. Nabiev, J. H. M. Cohen, *Langmuir* **2006**, *22*, 1810–1816.
- 17 C. Wu, T. Schneider, M. Zeigler, J. Yu, P. G. Schiro, D. R. Burnham, J. D. McNeill, D. T. Chiu, *J. Am. Chem. Soc.* **2010**, *132*, 15410–15417.
- 18 S. Satapathi, L. Li, R. Anandakathir, L. A. Samuelson, J. Kumar, *J. Macromol. Sci. Part A: Pure Appl. Chem.* **2011**, *48*, 1049–1054.
- 19 S. J. Toal, D. Magde, W. C. Trogler, *Chem. Commun.* **2005**, 5465–5467.
- 20 J. Hu, D. Zhang, S. Jin, S. Z. D. Cheng, F. W. Harris, *Chem. Mater.* **2004**, *16*, 4912–4915.
- 21 J. Bouffard, T. M. Swager, *Macromolecules* **2008**, *41*, 5559–5562.
- 22 C. Szymanski, C. Wu, J. Hooper, M. A. Salazar, A. Perdomo, A. Dukes, J. McNeill, *J. Phys. Chem. B* **2005**, *109*, 8543–8546.
- 23 H. Sohn, R. M. Calhoun, M. J. Sailor, W. C. Trogler, *Angew. Chem. Int. Ed. Engl.* **2001**, *40*, 2104–2105.
- 24 S. Rochat, T. M. Swager, *ACS Appl. Mater. Interfaces* **2013**, *5*, 4488–4502.
- 25 P. Bonancia, I. Vaya, M. J. Climent, T. Gustavsson, D. Markovitsi, M. C. Jimenez, M. A. Miranda, *J. Phys. Chem. A* **2012**, *116*, 8807–8814.
- 26 S. Content, W. C. Trogler, M. J. Sailor, *Chem. Eur. J.* **2000**, *6*, 2205–2213.
- 27 S. S. Nagarkar, B. Joarder, A. K. Chaudhari, S. Mukherjee, S. K. Ghosh, *Angew. Chem. Int. Ed. Engl.* **2013**, *52*, 2881–2885.