

Formation of a Specific Co-ordination Cavity for a Chiral Amino Acid by Template Synthesis of a Polymer Schiff Base Cobalt(III) Complex

Yuki Fujii,* Katsuhiro Matsutani, and Katsuhiro Kikuchi

Department of Chemistry, Ibaraki University, Mito, 310, Japan

A template polymer complex, which incorporates *N*-benzyl-D-valine with almost 100% stereospecificity, was synthesised by copolymerization of $\Delta\text{-}\beta_2\text{-[Co}\{(R,R)\text{-}N,N'\text{-bis[4-(p-vinylbenzyloxy)salicylidene]-1,2-diaminocyclohexane}\}(N\text{-benzyl-D-valine)]}$ (**3**), styrene, and divinylbenzene, followed by dissociation of the co-ordinated amino acid.

Template synthesis of macromolecules is an attractive method for preparing active sites and/or specific cavities in the field of biomimetic and separation chemistry.¹ We have applied the template synthesis method to a Co^{III} -Schiff base complex with *N*-benzyl-D-valine and succeeded in forming a polymer complex which discriminates between the stereoisomers of

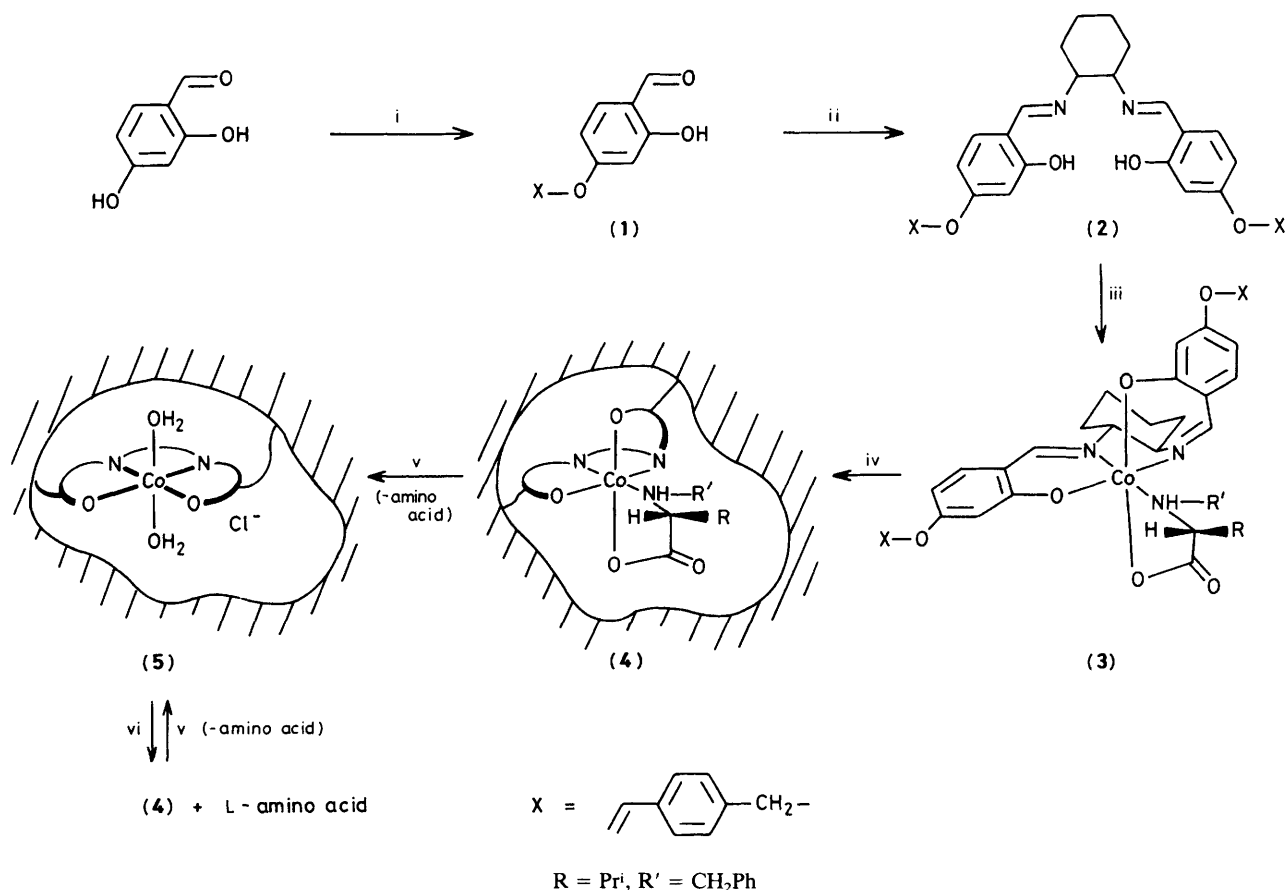
this *N*-benzyl-amino acid with high stereospecificity.

The preparative method is shown in Scheme 1. 4-(*p*-Vinylbenzyloxy)salicylaldehyde (**1**) was prepared from 4-hydroxysalicylaldehyde and *p*-chloromethylstyrene in about 40% yield,² and treatment with (1*R*,2*R*)-1,2-diamino cyclohexane³ gave the Schiff base ligand (**2**) (90%). The mixed

Table 1. Optical yield of the recovered amino acid (a.a.) *N*-benzylvaline.

Complex	Optical purity/%		Mol ratio reacted: unreacted a.a.	K^a	ΔG° kJ mol ⁻¹
	Reacted (D-a.a.)	Unreacted (L-a.a.)			
Template polymer complex (5)	99.5	26.2	3.80	682	16.2
Non-template polymer complex ^b	86.5	14.5	5.97	18.5	7.2
<i>trans</i> -[Co(2)(H ₂ O) ₂]Cl	88.2	21.8	4.05	24.8	8.0

^a $K = \{[\text{Co(D-a.a.)}][\text{L-a.a.H}]\} / \{[\text{Co(L-a.a.)}][\text{D-a.a.H}]\}$. ^b Prepared by copolymerization to Schiff base (2) with styrene and divinylbenzene (mol fraction 1 : 20 : 4) in THF followed by reaction with CoCl₂ under air oxidation conditions.

**Scheme 1.** Reagents: i, *p*-chloromethylstyrene, NaOH; ii, (1*R*,2*R*)-1,2-diaminocyclohexane; iii, Co(OAc)₂, *N*-benzyl-D-valine, O₂; iv, styrene, divinylbenzene; v, 3 M HCl; vi, *N*-benzyl-D,L-valine.

ligand Co^{III} complex (3) was synthesized from Co(OAc)₂, ligand (2), and *N*-benzyl-D-valine under air oxidation conditions^{4,5} (90%). The $\Delta\beta_2$ -structure of the complex was confirmed by its electronic and c.d. spectra.^{5,6} Complex (3) was then copolymerized with styrene and divinylbenzene (mol fraction 1 : 20 : 4) in tetrahydrofuran (THF) at about 60 °C for one day using azoisobutyronitrile as initiator. The green polymer complex (4) thus formed (70% yield) is insoluble in tetrahydrofuran (THF), CHCl₃, MeOH, *etc.*, whereas (3) (green) is soluble in organic solvents. Complex (4) was treated with 3 M HCl in MeOH to produce (5) quantitatively. Complex (5) is brown and insoluble in organic solvents. Its reflectance spectrum (300–1000 nm) closely resembled that of the corresponding *N,N'*-bis(salicylidene)ethylene-diaminediaqua complex.⁷ When (5) (about 200 mesh) was

treated with an excess of racemic *N*-benzylvaline in MeOH–CHCl₃ (1 : 1 v/v), it became green within a few hours affording (4), with incorporation of $\sim 1.2 \times 10^{-4}$ mol of amino acid per g of (5). On treatment with 3 M HCl complex (5) and free *N*-benzylvaline were recovered, with the optical purity given in Table 1.

In order to evaluate the template effect, the chiral recognition of the *trans*-[Co(2)(H₂O)₂]Cl^{5,7} complex itself and also the non-template polymer Schiff base complex, prepared without *N*-benzyl-D-valine co-ordination was tested by the method used for (5), as the Co–(2) complex itself can discriminate between the chirality of amino acids to some extent.^{4,5} The results are given in Table 1. The chiral discrimination of the template polymer complex (5) reaches almost 100% and is higher than that of *trans*-[Co(2)(H₂O)₂]Cl

and the non-template polymer complex by at least 8.0 kJ mol⁻¹ in ΔG° value. These results then, clearly indicate that the template effect operates quite effectively in this system.

This study was supported in part by a Grant-in-Aid for Scientific Research from the Ministry of Education, Science and Culture, Japan.

Received, 10th December 1984; Com. 1735

References

- 1 K. J. Shea, E. A. Thompson, S. D. Pandey, and P. S. Beauchamp, *J. Am. Chem. Soc.*, 1980, **102**, 3149; G. Wulff, A. Sarhan, and K. Zabrochi, *Tetrahedron Lett.*, 1973, **44**, 4329; G. Wulff and W. Verper, *J. Chromatogr.*, 1978, **167**, 171; G. Wulff, R. Kemmerer, J. Vietmeier, and H. G. Poll, *Nouv. J. Chim.*, 1982, **6**, 681; S. N. Gupta and D. C. Neckers, *J. Polym. Sci., Polym. Chem. Ed.*, 1982, **20**, 1609.
- 2 J. Daly, L. Horner, and B. Witkop, *J. Am. Chem. Soc.*, 1961, **83**, 4787.
- 3 R. G. Asperger and C. F. Liu, *Inorg. Chem.*, 1965, **4**, 1492.
- 4 Y. Fujii, M. Sano, and Y. Nakano, *Bull. Chem. Soc. Jpn.*, 1977, **50**, 2609.
- 5 Y. Fujii, M. Matsufuru, A. Saito, and S. Tsuchiya, *Bull. Chem. Soc. Jpn.*, 1981, **54**, 2029.
- 6 Y. Kushi, T. Tada, Y. Fujii, and H. Yoneda, *Bull. Chem. Soc. Jpn.*, 1982, **55**, 1834.
- 7 A. Bigotto, G. Costa, G. Mestroni, G. Pellizer, A. Puxeddu, E. Reisenhofer, L. Stefani, and G. Tauzher, *Inorg. Chim. Acta*, 1970, **4**, 41.