# **RSC Advances**



**PAPER** 

View Article Online
View Journal | View Issue



Cite this: RSC Adv., 2015, 5, 80542

# Perfluorinated gelators for solidifying fluorous solvents: effects of chain length and molecular chirality†

Tomoko Yajima,\*<sup>a</sup> Erika Tabuchi,<sup>a</sup> Emiko Nogami,<sup>a</sup> Akihiko Yamagishi<sup>b</sup> and Hisako Sato\*<sup>c</sup>

Received 30th June 2015 Accepted 16th September 2015

DOI: 10.1039/c5ra12656h

www.rsc.org/advances

With a purpose of solidifying fluorous solvents, a novel series of perfluorinated gelators based on 1,2-diaminocyclohexane (denoted as CFn: n= the number of carbon chain in perfluoroalkanoyl moiety) were developed. The gelation ability for  $C_6F_6$  was investigated. The length of a perfluoroalkyl chain (n=4–9) was found to affect critically the gelation properties such as gel stability, chirality effects and aggregation modes in fibrils.

# Introduction

Gelation of highly fluorinated solvents is a demand of various practical uses such as the delivery systems of oxygen or drugs and the treatment of industrial waste. For these purposes, there have been several attempts using gelators with perfluorinated chains. Gelation is reported to be accelerated by the hydrophobic and lipophobic interactions of the fluorinated groups with solvent molecules. However the reports on the gelation of fluorous solvents are limited. A few compounds that gelate one fluorocarbons are reported. Hut the compounds that can gelate multiple perfluorinated liquids are very few. Accordingly the development of gelators for fluorous solvents is highly anticipated.

We have studied the gelation behavior of a series of perfluorinated compounds. They were synthesized on the basis of chiral diaminocyclohexane moieties. The compounds are denoted as RR-CFn or SS-CFn (n=4–10), indicating the stereochemistry and the number of carbon atoms (n) in a perfluoroalkanoyl chain (Chart 1). The N-alkalnoyl derivatives of diaminocyclohexane (denoted as RR-Cn or SS-Cn) were first reported by Hanabusa  $et\ al.$  as an efficient gelator. The gelation of chiral CF7 and CF8 was studied using CH<sub>3</sub>CN or 2-butanol as a solvent. For both gelators, helical fibrils were observed in gels. The conformation of a gelator molecule

In the present study, the effect of chain length on gelation was investigated using  $C_6F_6$  as a solvent. It was shown that the variation of perfluorinated chains by one  $-CF_2$ – unit resulted in the remarkable change of gelation properties such as the stability of a gel, the effects of molecular chirality and the aggregation modes in fibrils. Single crystal X-ray analyses were performed for racemic and enantiopure **CF4**.

## Results and discussion

#### Measurement of critical gel concentrations

Gelation by enantiopure and racemic  $\mathbf{CF}n$ 's was studied for three fluorinated solvents,  $C_6F_6$  (hexafluorobenzene),  $C_6F_{14}$  (perfluorohexane) and BTF (benzotrifluoride). No gelation of  $C_6F_{14}$  was observed on adding any of  $\mathbf{CF}n$ 's. The critical gel concentration (CGC) of enantiopure and racemic  $\mathbf{CF}n$ 's was

Chart 1 Molecular structures of RR-Cn. SS-Cn. RR-CFn or SS-CFn.

was investigated by means of vibrational circular dichroism spectroscopy (VCD).<sup>20-25</sup> A model for molecular packing in a helical fibril was postulated.<sup>26</sup>

<sup>&</sup>lt;sup>a</sup>Department of Chemistry, Ochanomizu University, 2-1-1 Otsuka, Bunkyo-ku, Tokyo, Japan. E-mail: yajima.tomoko@ocha.ac.jp

<sup>&</sup>lt;sup>b</sup>Department of Chemistry, Toho University, Funabashi, Chiba, Japan

<sup>&#</sup>x27;Graduated School of Science and Engineering, Ehime University, Matsuyama, Ehime, Japan. E-mail: sato.hisako.my@ehime-u.ac.jp

<sup>†</sup> Electronic supplementary information (ESI) available: DSC data, SEM images, crystallographic data, sol-gel transition temperature, photographs of the investion test and HPLC charts. CCDC 1022936 and 1040719. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c5ra12656h

Table 1 The critical gel concentrations of CFn's<sup>a</sup>

Solvent	$C_6F_6$	$\mathrm{C_6F_{14}}$	BTF
Chiral CF4 $(n=3)$	tg (36.0)	р	р
Chiral CF5 $(n=4)$	р	р	p
Chiral <b>CF6</b> $(n=5)$	p	p	p
Chiral CF7 $(n=6)$	cg (20)	р	cg (5.8)
Chiral CF8 $(n=7)$	cg (37.5)	р	cg (17)
Chiral <b>CF9</b> $(n=8)$	cg (7.5)	р	cg (16.4)
Chiral <b>CF10</b> $(n=9)$	tg (24.5)	р	р
Racemic CF4 $(n = 3)$	p	p	p
Racemic CF5 $(n = 4)$	р	р	p
Racemic <b>CF6</b> $(n = 5)$	tvs	_	_
Racemic CF7 $(n = 6)$	cg (13.0)	р	tg (30.0)
Racemic <b>CF8</b> $(n=7)$	cg (6.8)	p	cg (4.1)
Racemic <b>CF9</b> $(n = 8)$	cg (6.9)	p	р
Racemic <b>CF10</b> $(n = 9)$	cg (8.6)	p	p

 $<sup>^{</sup>a}$  cg = clear gel; tg = turbid gel; p = crystal precipitated; tvs = turbid viscous solution. The values in parentheses denote the critical gel concentration at 298 K in terms of g L<sup>-1</sup>. The values in Table 1 were the average obtained for the results for RR- and SS-gelators.

measured for C<sub>6</sub>F<sub>6</sub> and BTF. The results are summarized in Table 1. For both solvents, the gelation ability of a gelator was dependent remarkably on the length of perfluorinated chains. For example, in case of C<sub>6</sub>F<sub>6</sub>, chiral CF4 gave a turbid gel, CF5, CF6 crystal precipitated and CF7-CF10 stable turbid or clear gels. Fig. 1 shows the effects of chain length and molecular chirality in case of CF7-CF10. As for the effect of chirality, the CGC values were smaller for the racemic mixtures than for the enantiomers. The CGC value showed a shallow minimum around CF8 and CF9 for racemic gelators, while the odd-even effect appeared with the minimum value at RR- (or SS)-CF9 for enantiopure gelators.

The fact that the racemic forms of CFn's showed considerable gelation ability was in marked contrast with what was observed for Cn's. In case of the latter compounds with n = 8-12, only the enantiomeric form acted as a gelator. The racemic compounds were precipitated as a crystal. These facts demonstrated the important role of perfluorinated chains in forming fibrils. The formation of gels was confirmed by the inversion tests. The photograph of the example is given in the ESI.†




Fig. 1 The variation of the critical gel concentration of  $C_6F_6$  for racemic or enantiopure CF7-CF10. Open circle; chiral and solid triangle; racemic.

#### SEM observation on the dried samples of gels or viscous solutions

SEM images were obtained for the xerogels or dried samples of viscous solutions containing the enantiopure or racemic gelators. The results for CF8, CF9 and CF10 are shown in Fig. 2(a)-(c), respectively. The results for CF4-CF6 are shown in the ESI.† The SEM results for CF7 were already reported previously. 18

In all samples, the networks of thin string-like fibers of ca. 0.1 nm in diameter were observed. In case of CF4-CF6, the fibers formed a plate-like aggregate with a size of 1-20 µm in width and >0.3 μm in thickness. The aggregates were as long as 100 µm with no winding or curving, indicating that they were rigid. In case of CF7-CF9, the thin string-like fibers aggregated to less extent so that some formed a network as a separate unit. The fibers were curved or entangled, suggesting that they were flexible. In case of CF10, the thin fibers formed a large plate-like aggregate. They were straight with no winding. In all samples, no helical structure was detected and little difference was observed between the enatiopure and racemic samples.

#### Measurement of IR and VCD spectra on enantiopure gels or viscous solvents

Vibrational circular dichroism (VCD) spectra<sup>26–30</sup> were measured on C<sub>6</sub>F<sub>6</sub> gels or viscous solutions or solids containing enantiopure compounds. For obtaining the VCD spectra in case of CF8 and CF9, an isotropic C<sub>6</sub>F<sub>6</sub> solution containing a gelator a little over the critical gel concentration was prepared. It was mounted onto a sandwich-type cell at 70 °C. The spectrum was recorded during 0-15 minutes after the sample was cooled down to room temperature.

Fig. 3(a) and (b) show the results for CF8 and CF9, respectively. The results for CF8 were similar to those of CF7, which were reported previously.18,29 The lower and upper curves in each figure represent IR and VCD spectra, respectively. Both CF7 and CF8 gave stable spectra during the measurements. In contrast, CF9 showed the opposite sign of the peaks assigned to C=O stretching as shown in Fig. 3(b).

All of the measured spectra exhibited a mirror-image relation between the samples containing RR- or SS-enantiomers in the whole wavenumber range. The rotation of a cell around an incident light gave no change in the spectra, confirming the reliability of the measurements. In the VCD spectra, the strong couplet around 1688 cm<sup>-1</sup> was assigned to the stretching vibration of C=O bonds. The multiple peaks in the region of 1238-1170 cm<sup>-1</sup> were assigned to the stretching vibrations of C-F bonds. The peaks due to the stretching vibration of N-H around 1550 cm<sup>-1</sup> were small in spite of the strong absorption in the IR spectra.

An attention was focused on the signs of a couplet assigned to C=O vibrations. According to the theoretical calculation, its signs are dependent on the conformation of the >CH(NH)COmoiety. The previous results on the CD<sub>3</sub>CN and CD<sub>3</sub>CN/C<sub>6</sub>F<sub>6</sub> gels formed by RR-CF7 indicated that the gelator molecule took a conformation with two anti-parallel intermolecular hydrogen bonds, if the couplet showed the positive to negative (±) signs from high to low wavenumber.26 Instead, if the same

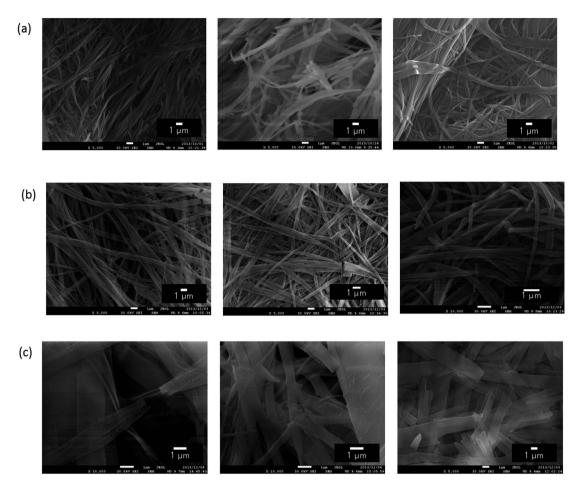


Fig. 2 The SEM images of the dried samples of  $C_6F_6$  gels. Left; RR-CFn, middle; SS-CFn, right; racemic-CFn. (a) CF8 (b) CF9 (c) CF10.

couplet showed the negative to positive  $(\pm)$  signs, it took a conformation with one intermolecular and one intramolecular hydrogen bonds. On the basis of this diagnosis, CF9 took a conformation with two anti-parallel hydrogen bonds, while CF7 and CF8 took a conformation with one intermolecular and one intramolecular hydrogen bonds. In other words, the elongation of a single  $-\text{CF}_2-$  unit resulted in the drastic change of the stacking modes of gelators in fibrils. The effect might be caused by the steric constraint arising from the stacking structures of perfluoroalkyl chains. Comparing the VCD results with the tendency for gelation (Table 1), the high stability of a gel formed by enantiopure CF9 was correlated with the formation of stable two-antiparallel hydrogen bonds in fibrils.

Another attention was paid to the multiplet regions due to the stretching vibration of C–F bonds. The VCD activity of the region reflected the helical conformation of perfluorinated groups. According to the previous theoretical calculation, it was deduced that the positive or negative sign of the strongest peak in the multiplet band around  $1200~\rm cm^{-1}$  represented the rightor left-handed helicity of the perfluorinated chain. On the basis, *RR*-CF7, *RR*-CF8 and *RR*-CF9 had their perfluorinated chains left-, left- and right-handed in  $C_6F_6$  solvent, respectively. Most probably the helicity was determined by the interaction of

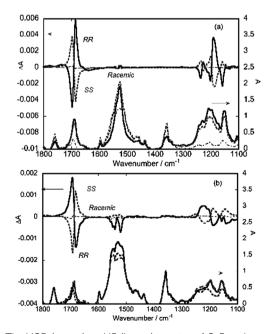


Fig. 3 The VCD (upper) and IR (lower) spectra of  $C_6F_6$  gels containing enantiopure or racemic (a) CF8 (37.5 g  $L^{-1}$ ) and (b) CF9 (7.5 g  $L^{-1}$ ).

the hydrogen atom in the -NH-C=O moiety with the fluorine atom in the perfluorinated chain.

#### Single crystal X-ray analyses

A single crystal was obtained successfully in case of RR-CF4 and racemic-CF4 alone among the present series of gelator molecules. Fig. 4 shows the results of the X-ray crystal analyses of RR-CF4. Molecules were stacked forming a molecular array along the a-axis, in which their cyclohexyl rings were in parallel. In the array, molecules are connected by two anti-parallel intermolecular hydrogen bonds at >C=O and >NH groups (204.0 pm). This mode of aggregation was in accord with the prediction from the VCD spectra of the solid on the basis of the sign of couplet assigned to C=O stretching. Since the VCD spectra of the gels gave the same signals, the same connection was thought to exist in fibrils. In the crystal, the distance of fluorine in the neighboring arrays was shorter than sum of the van der Waals radii of the two fluorine (272.3 pm). It was uncertain, however, whether such an interaction existed in gel fibrils. The sequence of fluorine atoms represented slightly left-handed helical winding along a perfluorinated butyl chain.

By contrast, in the case of racemic-CF4, cyclohexyl ring and perfluoroalkyl moiety were stacked alternately (Fig. 5). The main

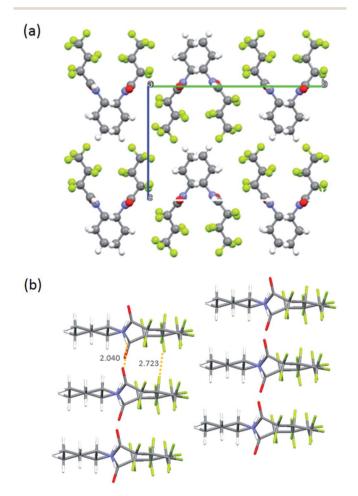


Fig. 4 The molecular structure and packing in a single crystal of RR-CF4.

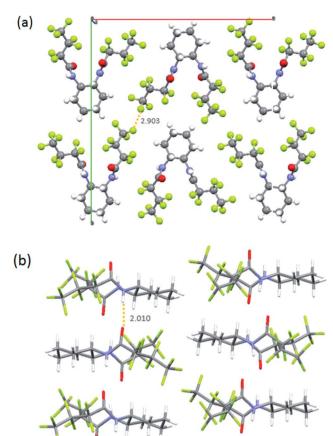


Fig. 5 The molecular structure and packing in a single crystal of racemic-CF4.

factor of this array is two anti-parallel intermolecular hydrogen bonds among RR- or SS-enantiomers at >C=O and >NH groups (201.0 pm). One of the perfluoroalkyl groups is bent. The bent conformation of side chain was also observed in our previous terminally-brominated gel.33 The fluorine in the neighboring molecules do not interact with each other, but fluorine atoms of cater-corner molecules are slightly contacted (290.3 pm).

### Molecular stacking models for enantiopure or racemic gelators

As summarized in Fig. 1, gelation ability was affected by the length of perfluorinated chains in the different fashion between the racemic and enantiomeric gelators. For racemic CF7-CF10, gelation ability was little dependent on the chain length, while it changed drastically for enantiomeric ones. The features were in contrast with what was reported for non-fluorinated analogous gelators (denoted as Cn). Using benzene as a solvent, for example, only enantiopure Cn's formed a gel, while racemic ones much less stable gels than pure enantiomers. 17,34 As for the effect of the chain length, the CGC values decreased monotonously from C8 to C12. It should be emphasized that no gelation occurred for a series of Cn (n = 7-12) for  $C_6F_6$  due to low solubility.

(a) (b) (RR ) (SS ) (RR ) (SS ) (RR ) (SS ) (SS

**RSC Advances** 

Fig. 6 The molecular models: (a) enantiopure-CFs, (b) racemic-CFs.

NH-CO interaction

The above features suggested that the stacking interaction among perfluorinated chains has a main factor to bring about chirality effects on gelation. According to the VCD analyses, the stable aggregation mode for enantiopure CF9 was achieved by the formation of two anti-parallel intermolecular hydrogen bonds (Fig. 6(a)). The same connection was confirmed to exist in the single crystal of CF4. Since a single array was estimated to have a radius of  $\geq 2$  nm, the thin fibrils with a radius of  $\geq 2$   $\mu$ m, which were observed in the SEM images contained more than ten such arrays. For enantiopure CF7 and CF8, the molecules formed a single intermolecular hydrogen bond. Thus they might form a weaker array. In both cases, however, the outer surface of the array possessed the region of perfluorinated chains. It is speculated therefore that the odd-even effect observed for the gelation ability of enantiopure CFn's (Fig. 1) appeared when the array was bundle to a thin fibril.

In contrast, *RR*- or *SS*-enantiomers formed a homochiral pair and oriented in a head-and-tail way in crystal structure and each array consisted of the opposite enantiomers arranged in an alternative way through the two-antiparallel intermolecular hydrogen bonds. It is proposed that the aggregation of the array to form a thinner fibril is achieved by the interdigitation of perfluorinated chains. Under such an aggregation mode, no contact of the end groups of perfluorinated chains would appear, leading to the absence of odd–even effect.

It should be emphasized that the aim of the above stacking model was to rationalize the difference of gelation behavior between racemic and enantiomeric gelators. It is intended to present no speculative details of fibril structures but simply demonstrates the possible connectivity of the gelator molecules. Presently an experimental support is now under progress by finding any periodic structure that depends on molecular chirality such as neutron diffraction or small angle X-ray diffraction measurements.

# Experimental

#### Synthesis and characterization of gelators

**Materials.** All commercially available solvents and reagents for synthesis and analysis were used as received without further purification. Benzotrifluoride (>98%) was obtained from Kanto Chemical Co. Inc. Perfluorobenzen (>99%) was obtained from Aldrich. (1*R*,2*R*)-, (1*S*,2*S*)- and racemic-1,2-diaminocyclohexane (>98%) and tetradecafluorohexane (>96%) were obtained from Tokyo Kasei, Ltd. Perfluoroalkanoys chlorides were synthesized according to previous report.<sup>35</sup>

Characterization methods.  $^1\text{H}$  NMR,  $^{13}\text{C}$  NMR and  $^{19}\text{F}$  NMR were measured on a JEOL GSX-400 spectrometer (400 MHz for  $^1\text{H}$ , 100.5 MHz for  $^{13}\text{C}$ , and 376.2 MHz for  $^{19}\text{F}$ ). All chemical shifts ( $\delta$ ) are reported on parts per million downfield of acetonitrile for  $^1\text{H}$  NMR ( $\delta=1.96$ ) and  $^{13}\text{C}$  NMR ( $\delta=118.26$ ) and trichlorofluoromethane for  $^{19}\text{F}$  NMR ( $\delta=0.0$ ) were used as internal standard for CD $_3$ CN solutions. ESI mass spectra were measured on a Thermo Scientific Exactive mass spectrometer. Optical rotations were measured on a JASCO P-2200 polarimeter at room temperature, using the sodium D line.

**General procedure.** To a solution of 1,2-diaminocyclohexane (0.31 mmol) in dry THF (3 ml) were added  $\rm Et_3N$  (0.93 mmol, 3.0 eq.) and perfluoroalkanoyl chloride (0.93 mmol, 3.0 eq.) at 0 °C, and the mixture was stirred for 1 hour. The resulting mixture was filtrated and the residue was washed with water. Chemical data of **CF7** and **CF8** were previously reported.  $^{13,14}$ 

trans-N,N'-Perfluorobutanoyl-1,2-diaminocyclohexane (CF4). (1R,2R)-CF4 [ $\alpha$ ]<sub>D</sub><sup>27</sup> 35.63 (c 0.19, THF), (1S,2S)-CF4 [ $\alpha$ ]<sub>D</sub><sup>28</sup> -37.49 (c 0.19, THF); <sup>1</sup>H NMR (400 MHz, CD<sub>3</sub>CN)  $\delta$  7.64 (2H, m, NHCO), 3.87 (2H, m, CH<sub>2</sub>CHNH), 1.78 (4H, m, cyclohexyl), 1.47 (2H, m, cyclohexyl), 1.34 (2H, m, cyclohexyl); <sup>13</sup>C NMR (126 MHz, CD<sub>3</sub>CN)  $\delta$  52.3 (2C), 30.0 (2C), 23.3 (2C); <sup>19</sup>F NMR (376 MHz, CD<sub>3</sub>CN)  $\delta$  -80.3 (6F), -119.9 (4F), -126.5 (4F); HRMS (ESI $^-$ ) C<sub>14</sub>H<sub>11</sub>O<sub>2</sub>N<sub>2</sub>F<sub>14</sub> [M - H] (calcd 505.0597, found 505.0578).

*trans-N,N*'-Perfluoropentanoyl-1,2-diaminocyclohexane (CF5). (1R,2R)-CF5 [ $\alpha$ ]<sub>D</sub><sup>27</sup> 35.91 (c 0.20, THF), (1S,2S)-CF5 [ $\alpha$ ]<sub>D</sub><sup>27</sup> -34.64 (c 0.19, THF); <sup>1</sup>H NMR (400 MHz, CD<sub>3</sub>CN)  $\delta$  7.63 (2H, m, NHCO), 3.86 (2H, m, CH<sub>2</sub>CHNH), 1.77 (4H, m, cyclohexyl), 1.45 (2H, m, cyclohexyl), 1.32 (2H, m, cyclohexyl); <sup>13</sup>C NMR (126 MHz, CD<sub>3</sub>CN)  $\delta$  52.8 (2C), 30.8 (2C), 23.7 (2C); <sup>19</sup>F NMR (376 MHz, CD<sub>3</sub>CN)  $\delta$  -81.8 (6F), -120.4 (4F), -124.1 (4F), -126.5 (4F); HRMS (ESI<sup>-</sup>) C<sub>16</sub>H<sub>11</sub>O<sub>2</sub>N<sub>2</sub>F<sub>18</sub> [M - H] (calcd 605.0533, found 605.0524).

trans-N,N'-Perfluorohexanoyl-1,2-diaminocyclohexane (CF6). (1R,2R)-CF6 [ $\alpha$ ]<sub>D</sub><sup>28</sup> 20.17 (c 0.19, THF), (1S,2S)-CF6 [ $\alpha$ ]<sub>D</sub><sup>28</sup> -22.40 (c 0.19, THF); <sup>1</sup>H NMR (400 MHz, CD<sub>3</sub>CN)  $\delta$  7.65 (2H, m, NHCO), 3.86 (2H, m, CH<sub>2</sub>CHNH), 1.75 (4H, m, cyclohexyl), 1.45 (2H, m, cyclohexyl), 1.33 (2H, m, cyclohexyl); <sup>13</sup>C NMR (126 MHz, CD<sub>3</sub>CN)  $\delta$  52.8 (2C), 30.8 (2C), 23.8 (2C); <sup>19</sup>F NMR (376 MHz, CD<sub>3</sub>CN)  $\delta$  -81.5 (6F), -120.2 (4F), -123.1 (4F), -123.3 (4F), -126.7 (4F); HRMS (ESI<sup>-</sup>) C<sub>18</sub>H<sub>11</sub>O<sub>2</sub>N<sub>2</sub>F<sub>22</sub> [M - H] (calcd 705.0469, found 705.0461).

*trans-N,N'*-Perfluorononanoyl-1,2-diaminocyclohexane (CF9). (1R,2R)-CF9 [ $\alpha$ ]<sub>D</sub><sup>27</sup> 19.492 (c 0.19, THF), (1S,2S)-CF9 [ $\alpha$ ]<sub>D</sub><sup>27</sup> -23.841 (c 0.19, THF); <sup>1</sup>H NMR (400 MHz, CD<sub>3</sub>CN)  $\delta$  7.64 (2H, m, N*H*CO), 3.86 (2H, m, CH<sub>2</sub>C*H*NH), 1.76 (4H, m, cyclohexyl), 1.47 (2H, m, cyclohexyl), 1.33 (2H, m, cyclohexyl); <sup>13</sup>C NMR (126 MHz, CD<sub>3</sub>CN)  $\delta$  52.5 (2C), 30.9 (2C), 23.6 (2C); <sup>19</sup>F NMR (376 MHz, CD<sub>3</sub>CN)  $\delta$  -81.6 (6F), -119.7 (4F), -122.1 (4F), -122.5 (8F), -123.1 (4F), -123.7 (4F), -126.6 (4F); HRMS (ESI<sup>-</sup>) C<sub>24</sub>H<sub>11</sub>O<sub>2</sub>N<sub>2</sub>F<sub>34</sub> [M - H] (calcd 1005.0278, found 1105.0273).

*trans-N,N'*-Perfluorodecanoyl-1,2-diaminocyclohexane (CF10). (1R,2R)-CF10 [ $\alpha$ ]<sub>D</sub><sup>28</sup> 13.69 (c 0.19, THF), (1S,2S)-CF10 [ $\alpha$ ]<sub>D</sub><sup>28</sup> −16.53 (c 0.25, THF); <sup>1</sup>H NMR (400 MHz, CD<sub>3</sub>CN)  $\delta$  7.64 (2H, m, NHCO), 3.86 (2H, m, CH<sub>2</sub>CHNH), 1.76 (4H, m, cyclohexyl), 1.47 (2H, m, cyclohexyl), 1.33 (2H, m, cyclohexyl); <sup>13</sup>C NMR (126 MHz, CD<sub>3</sub>CN)  $\delta$  52.4 (2C), 30.7 (2C), 23.5 (2C); <sup>19</sup>F

Paper RSC Advances

NMR (376 MHz, CD<sub>3</sub>CN)  $\delta$  –81.6 (6F), –119.8 (4F), –122.2 (4F), –122.5 (12F), –123.2 (4F), –123.7 (4F), –126.7 (4F); HRMS (ESI<sup>-</sup>) C<sub>26</sub>H<sub>11</sub>O<sub>2</sub>N<sub>2</sub>F<sub>38</sub> [M – H] (calcd 1105.0214, found 1105.0211).

#### Measurements

SEM observation was performed with a S-3100H (Hitachi, Japan). A gel was prepared at the concentration little above CGC. A gel sample was deposited onto a silicon wafer. It was freezedried after being dried under air. The samples were coated with platinum for the measurements.

VCD spectra were measured using a spectrometer PRESTO-S-2007 (JASCO, Japan). The detector was a liquid nitrogen cooled MCT infrared detector equipped with ZnSe windows. A gel was sandwiched between two  $\text{CaF}_2$  plates with a 50  $\mu m$  spacer at the critical concentration. No dichroic effect was observed when the samples were rotated with respect to an incident light.

# Conclusions

The gelation of  $C_6F_6$  was compared for a series of low-molecular gelators with the perfluorinated chains of various length. Notably gelation was achieved by the racemic form of the perfluorinated molecules. The stacking models for racemic and enantiopure gelators are proposed to explain the difference of their gelation ability.

# Acknowledgements

Thanks are due to Ms Mika Sasaki (Ochanomizu University) for the syntheses of gelators. Thanks are also due to Ms Miwa Ochi and Prof. Sho Shirakata (Ehime University) for obtaining SEM images. This work has been financially supported by the MEXT KAKENHI Grant-in-Aid for Exploratory Research Number 26620068.

# Notes and references

- 1 M.-O. M. Piepenbrock, G. O. Lloyd, N. Clarke and J. W. Steed, *Chem. Rev.*, 2010, **110**, 1960–2004.
- 2 A. Ajayaghosh and V. K. Praveen, *Acc. Chem. Res.*, 2007, **40**, 644–656.
- 3 Low Molecular Mass Gelators Design, Self-Assembly, Function, ed. F. Fages, Springer, Berling, Heidlberg, 2005.
- 4 R. Oda, I. Huc, S. J. Candau and F. C. MacKintosh, *Nature*, 1999, **399**, 566–569.
- 5 P. Terech and R. G. Weiss, Chem. Rev., 1997, 97, 3133-3160.
- 6 T. Tachibana, T. Mori and K. Hori, *Nature*, 1979, 278, 578–579.
- 7 J. A. Gladysz, D. P. Curran and I. T. Horvath, *Handbook of Fluorous Chemistry*, Wiley-VCH, Weinheim, 2004.
- 8 Q. Wei, C. Schlaich, S. Prévost, A. Schulz, C. Böttcher, M. Gradzielski, Z. Qi, R. Haag and C. A. Schalley, *Adv. Mater.*, 2014, **26**, 7358–7364.

- 9 E. Faggi, R. M. Sebastian and A. Vallribera, *Tetrahedron*, 2010, 66, 5190–5195.
- 10 M. Yamanaka, K. Sada, M. Miyata, H. Hanabusa and N. Nakano, *Chem. Commun.*, 2006, 2248–2250.
- 11 M. George, S. L. Snyder, P. Terech and G. Weiss, *Langmuir*, 2005, **21**, 9970–9977.
- 12 J. Loiseau, M. Lescanne, A. Colin, F. Fages, J. Verlhac and J. Vincent, *Tetrahedron*, 2002, **58**, 4049–4052.
- 13 P. Terech, V. Rodriguez, J. D. Barnes and G. B. McKenna, *Langmuir*, 1995, **10**, 3406–3410.
- 14 J. Höpken, C. Pugh, W. Richtering and M. Möller, *Makromol. Chem.*, 1988, **189**, 911–925.
- 15 P. Terech, C. J. Glinka and R. G. Weiss, *J. Am. Chem. Soc.*, 2003, **125**, 10275–11028.
- 16 J. G. M. E. Bakkari, C. Belin, C. Margottin, P. Godard, J.-L. Pozzo and J.-M. Vincent, *Chem. Commun.*, 2009, 5133– 5124
- 17 K. Hanabusa, M. Yamada, M. Kimura and H. Shirai, *Angew. Chem.*, *Int. Ed.*, 1996, 35, 1949–1951.
- 18 K. Kohno, K. Morimoto, N. Manabe, T. Yajima and A. Yamagishi, *Chem. Commun.*, 2012, **48**, 3860–3862.
- 19 H. Sato, T. Yajima and A. Yamagishi, *Chem. Commun.*, 2011, 47, 3736–3738.
- 20 W. R. W. Welch, J. Kubelka and T. A. Keiderling, *J. Phys. Chem. B*, 2013, **117**, 10343–10358.
- 21 T. J. Measey and R. Schweitzer-Stenner, *J. Am. Chem. Soc.*, 2011, **133**, 1066–1076.
- 22 D. Kurouski, R. A. Lombardi, R. K. Dukor, I. K. Lednev and L. A. Nafie, *Chem. Commun.*, 2010, 46, 7154–7156.
- 23 T. Weymuth, C. R. Jacob and M. Reiher, *J. Phys. Chem. B*, 2010, **114**, 10649–10660.
- 24 V. Setnička, J. Nový, S. Böhm, N. Sreenivasachary, M. Urbanová and K. Volka, *Langmuir*, 2008, 24, 7520–7521.
- 25 G. Yang and Y. Xu, *Phys. Chem. Chem. Phys.*, 2008, **10**, 6787–6795.
- 26 H. Sato, T. Yajima and A. Yamagishi, RSC Adv., 2014, 4, 25867–25870.
- 27 J. Sadlej, J. C. Dobrowolski and J. E. Rode, *Chem. Soc. Rev.*, 2010, **39**, 1478–1488.
- 28 P. J. Stephens, J. Phys. Chem., 1985, 89, 748-752.
- 29 H. Sato, T. Yajima and A. Yamagishi, *Chirality*, 2015, DOI: 10.1002/chir.22482.
- 30 L. A. Nafie, T. A. Keiderling and P. J. Stephens, *J. Am. Chem. Soc.*, 1976, **98**, 2715–2723.
- 31 K. Monde, N. Miura, M. Hashimoto, T. Taniguchi and T. Inabe, *J. Am. Chem. Soc.*, 2006, **128**, 6000–6001.
- 32 K. Monde, T. Taniguchi, N. Miura and S.-I. Nishimura, *J. Am. Chem. Soc.*, 2004, **126**, 9496–9497.
- 33 H. Sato, E. Nogami, T. Yajima and A. Yamagishi, *RSC Adv.*, 2014, 4, 1659–1665.
- 34 H. Sato, T. Nakae, K. Morimoto and K. Tamura, *Org. Biomol. Chem.*, 2012, **10**, 1581–1586.
- 35 T. Yui, S. Fujii, K. Matsubara, R. Sasai, H. Tachibana, H. Yoshida, K. Takagi and H. Inoue, *Langmuir*, 2013, **29**, 10705–10712.