



Efficient conversion of D-mannitol into 1,2:5,6-diacetonide with Aquivion-H as a recyclable catalyst

Cristiano Bolchi^{*}, Rebecca Appiani, Gabriella Roda, Valentina Bertolini, Sebastiano Arnoldi, Marco Pallavicini

Dipartimento di Scienze Farmaceutiche, Università Degli Studi di Milano, via Mangiagalli 25, Milano, 20133, Italy

ARTICLE INFO

Keywords:

D-mannitol
Aquivion-H
1,2:5,6-di-O-isopropylidene-D-mannitol
2,2-Dimethoxypropane
Acetonides

ABSTRACT

Heterogeneous solid catalysis by the commercially available perfluorosulfonic ionomer Aquivion-H allowed 1,2:5,6-diacetonide of D-mannitol (**1**), immediate precursor of important unichiral C3-synthons, to be efficiently obtained from D-mannitol and 2,2-dimethoxypropane in DMF at room temperature. The 1,2-monoacetonide, whose intermediate formation is the rate-limiting step, could be almost completely converted into **1** with limited concurrent transformation of **1** into triacetonides. In line with recent literature reports, these results indicate that heterogeneous catalysis by Aquivion-H surpasses the performances of homogeneous acidic catalysis assuring, presumably for its peculiar morphology, a higher product selectivity. Easy recovery at the end of the reaction and recyclability are additional advantages of this solid acid catalyst.

1. Introduction

Conversion into cyclic acetals and ketals is one of the most common methods to protect 1,2-diols and, among these, one of the most studied and applied procedure is the acetonation of the two terminal diols of the natural hexa-alcohol D-mannitol to 1,2:5,6-di-O-isopropylidene-D-mannitol (**1**). Thanks to the identical S configuration of C(2) and C(5), oxidative cleavage of unprotected central diol of **1** affords, with 100% atom economy, two molecules of (R)-2,3-O-isopropylidene-glyceraldehyde (**2**) [1] and, upon reduction, of (S)-1,2-O-isopropylidene-glycerol (**3**) [2,3], two of the most important C3-synthons within the chiral pool (Fig. 1). Apart from their predictable wide use in the synthesis of the numerous molecules including the mono-, di- or trisubstituted glycerol framework, **2** and **3** are useful blocks to build other chiral linear molecules [4] and chiral cyclic systems. Examples of the latter are hexahydroindenes [5] benzomorpholines [6], benzodioxanes [7–11], dihydropyrroles [12], dihydrooxazines [12], dioxanes [13,14], pyridodioxanes [15,16], 2-oxazolidinones [17], spirobisdioxanes [18], and spirobisoxathianes [18].

The first satisfactory method of acetonation of mannitol to the diacetonide **1** was developed in the decade between the thirties and the forties by Baer by using acetone and more than stoichiometric zinc chloride at room temperature [19]. The procedure, which involves a laborious removal of the large amount of zinc chloride, affords the

desired 1,2:5,6 diacetonide, after crystallization from dibutyl ether, in 42% yield. In more recent years, a significant improvement of the method yield (82%) was reported by avoiding any heating treatment during the reaction work up and the product purification [20,21].

In the meantime, namely in the eighties and in the nineties, the 1,2:5,6 diacetonation of D-mannitol was deeply investigated [22–24]. With the analytical support of gas chromatography and of ¹³C NMR spectroscopy, the monitoring of the Baer's method and of some newly developed procedures highlighted the major concern of any preparation of **1**. This is to limit the formation of triacetonides and competing diacetonides, primarily 1,2:4,6- and secondarily 1,2:3,6-di-O-isopropylidene-D-mannitol, while maximizing consumption of D-mannitol and of the 1,2-monoacetal, whose initial formation is the rate-determining step because of the very poor solubility of D-mannitol in non-aqueous solvents [22,23] (Fig. 2). Such studies, based on GC analyses of the reaction mixtures at different times, converged on identifying the acetone/zinc chloride procedure by Baer [19,25,26] and the transacetonation with 2,2-dimethoxypropane (2.4 equiv) and catalytic tin(II) chloride in 1,2-dimethoxyethane successively developed by Chittenden [27–29] as the two methods capable of achieving, respectively, the maximal 60 and 55% conversion of D-mannitol into **1**. After 16–24 h at room temperature, the former procedure yields minimal quantities of triacetonides and other diacetonides but leaving behind almost 30% residual mannitol and 1,2-diacetonide. In 2–3 h at reflux,

^{*} Corresponding author.

E-mail address: cristiano.bolchi@unimi.it (C. Bolchi).

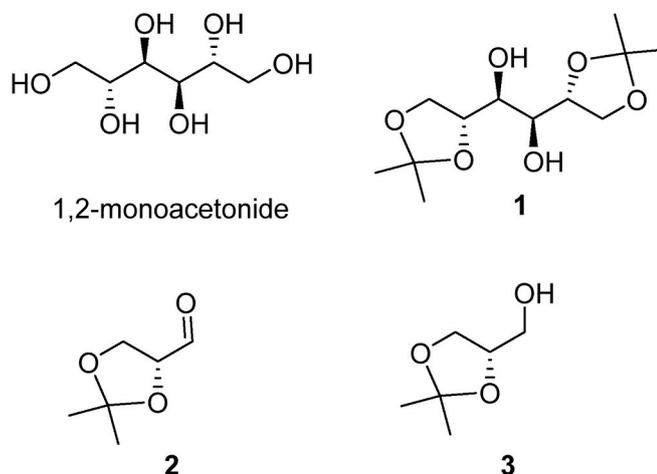


Fig. 1. D-mannitol and its most important acetonide derivatives.

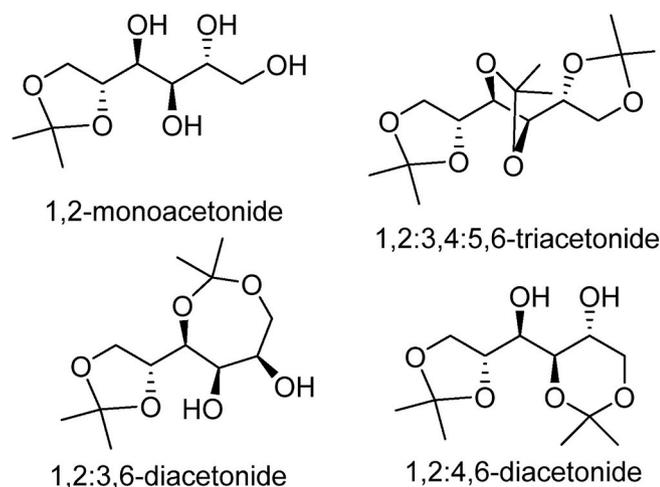


Fig. 2. Main secondary products in the conversion of D-mannitol to the 1,2:5,6 diacetonide (1).

the latter achieves a similar yield converting almost all mannitol and 1, 2-diacetonide but producing more than 30% of triacetonides and other undesired diacetonides. Furthermore, the same studies showed that a third procedure, based on the treatment of D-mannitol with two equivalents of 2-methoxypropene and catalytic *p*-toluenesulfonic acid in DMF at 0 °C, affords **1** with 36% yield and not with 90% yield as previously claimed [30]. However, it is to be noted that this latter procedure interestingly differs from the two previous ones: the products mixture is richer in diacetals (72%), represented by **1**, 1,2:4,6- and 1,2:3,6-di-*O*-isopropylidene-D-mannitol in 3:2:1 ratio, while triacetals are practically absent and the quantities of monoacetonides and unreacted mannitol are modest. The use of catalytic *p*-toluenesulfonic acid was proposed also in conjunction with 2,2-dimethoxypropane (2.5 equiv) or acetone (4.9 equiv) in DMSO claiming a 62% and 77% yield of **1** respectively [31,32].

Although the efficiency of the *p*-toluenesulfonic acid catalyzed conversion of D-mannitol into **1** with 2-methoxypropene or 2,2-dimethoxypropane in polar aprotic solvents is questionable in some respects, we were interested in developing a procedure for the preparation of **1** preferring the catalytic use of an acid, in particular of a sulfonic acid, to stoichiometric zinc chloride. In terms of sustainability, the catalytic approach is superior and, in the present case, an additional attractive feature could be a heterogeneous catalysis with the recyclable solid catalyst we intended to use. This was Aquivion-H (Fig. 3), a

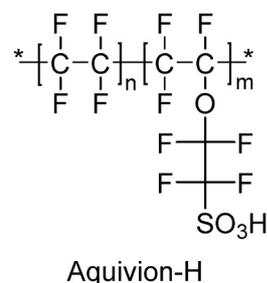


Fig. 3. Chemical structure of Aquivion-H (R-SO₃H: equivalent weight 870 g/eq).

commercially available perfluorosulfonic ionomer (Aquivion PW87S), possessing superacid character, used to prepare polymer electrolyte membranes [33], whose iron-salt we have recently reported as an efficient recyclable catalyst of one-pot reductive aminations [34,35]. Furthermore, in the reported polyols acetonidations utilizing DMF and *p*-TsOH, such as the one mentioned above of D-mannitol with 2-methoxypropene [22,30], or in those of pentoses with 2,2-dimethoxypropane [36], the reaction seems more directable to mono-, di- or three-acetonidation by adjusting reaction parameters, such as temperature, time, and quantity of the acetalating agent, anyway without leaving starting material unreacted. The same is not feasible when working with solvents, such as acetone or dimethoxyethane, in which, unlike in DMF, mannitol is insoluble at all [37,38]. In these solvents, complete consumption of mannitol necessarily results in high percentages of triacetonides.


2. Results and discussion

Given the above considerations, we developed the here reported procedure of conversion of D-mannitol into **1** by treatment with 2,2-dimethoxypropane in DMF in the presence of catalytic Aquivion-H at room temperature for 16 h (Scheme 1). The catalyst was used in 2.8% mol of H⁺ relative to mannitol, namely 133 mg per gram of substrate, since stabilized powdered Aquivion-H PW87S has, insofar as sulfonic acid (R-SO₃H), a nominal equivalent weight of 870 g/eq. The acetalating agent, 2,2-dimethoxypropane, was used in 4:1 M ratio to mannitol, namely 2.7 ml per gram of substrate, while the solvent DMF in 5:1 v/w to mannitol, namely 5 ml per gram of substrate.

The reactions were initially performed on 1 g of mannitol. After 16 h vigorous stirring, the reaction mixture was filtered to remove the catalyst. The filtrate was concentrated under vacuum at 40 °C. The resultant solid was triturated in cyclohexane (15 ml) and recovered by filtration to give **1** in 76% yield. At the end of the first catalytic cycle, Aquivion-H was washed with acetonitrile and then dried under vacuum. Aquivion-H was then recycled for five times without appreciable variation in its catalytic performances (Fig. 4).

The reactions were successively performed on 10 g of mannitol by the same protocol without difficulties and yield decrease.

Based on the previously mentioned literature investigations, pointing out how complex mixtures of mono- and poly-acetonides can form from mannitol, we carefully analyzed both the crude resulting from DMF removal and final **1** obtained by trituration in cyclohexane. Besides routinary melting point and ¹H NMR determinations, we relied on ¹³C NMR and on GC analyses of the acetylated derivatives. The spectroscopic analysis clearly distinguishes among dioxolane, 1,3-dioxane and



Scheme 1. Preparation of **1** from D-mannitol.

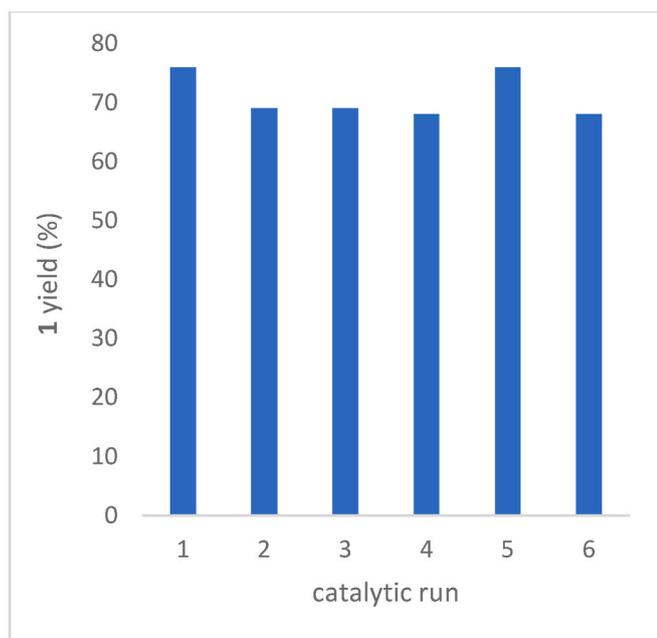


Fig. 4. Recycling of Aquivion-H: 1 yield of the first cycle and of the subsequent five recycles.

1,3-dioxepane substructures thanks to the different shifts of the dimethylated acetal carbon thus revealing the undesired 4,6-acetonidation (1,3-dioxane) and 3,6-acetonidation (1,3-dioxepane) [23]. The GC analysis elutes, in the order, the triacetones, the diacetyl derivatives of the diacetones, the tetraacetyl derivatives of the monoacetones and, finally, the peracetylated mannitol and furthermore it can separate the different isomers within each group. GC analyses of the crudes from three consecutive reactions revealed that triacetones made up less than 10% of the crude solid resultant from removal of the catalyst and DMF, while the 1,2-monoacetone was present in traces and mannitol was absent. The remainder consisted of a largely preponderant product, namely the desired diacetone 1. Consistently, ^1H NMR spectrum of the crudes appeared like that of a unitary product (See the ^1H NMR spectrum of crude 1 and that of pure 1 reported in Supplementary Information). Indeed, the revealing signals, namely those for the hydroxylated methines and for the geminal methyls, were relatively clean. ^{13}C NMR spectrum showed only one signal for the dimethylated acetal carbons, positioned at 109.4 ppm and imputable to the desired acetonidation of vicinal diols to dioxolane rings. Furthermore, it is noteworthy that the main impurity of the crudes was represented by less polar triacetones and not by the highly polar 1,2-monoacetone. This fact allowed us to avoid the purification of 1 by the usual crystallization from di-*n*-butyl or diisopropyl ether. Simple trituration of the crudes in more acceptable solvents, such as cyclohexane or cyclohexane and 'green ether' (CPME, TAME, MeTHF), recently employed by us in the esterification of amino acids [39,40], was enough to remove the minority by-products, namely the triacetones, which were dissolved leaving 1 as a white solid with >98% GC purity. Indeed, when we halved the catalyst amount, the main impurity became the 1,2-monoacetone and, as expectable, trituration of the crude in cyclohexane did not remove it but enriched 1 in it. Therefore, it was necessary to wash an ethyl acetate solution of the crude with water first and only then to triturate the solid resultant from ethyl acetate removal in cyclohexane.

These results indicate that, in a polar aprotic solvent and under the selected conditions, the heterogeneous catalysis by Aquivion-H can efficiently promote diacetoneidation of mannitol with almost complete consumption of the starting material and of the intermediate monoacetone and minimal formation of triacetones. Such an output is in line with those of the reported homogeneous catalysis by *p*-TsOH in DMF

or in DMSO, but here, the preferential formation of diacetones over the other acetals is more pronounced and what is more with a much larger prevalence of the desired diacetone 1.

We think that a key role in determining the efficiency (high conversion into diacetones) and the selectivity (high yield of the diacetone 1) of the procedure is the combination of a polar aprotic solvent with a heterogeneous solid catalyst such as Aquivion-H. In less polar aprotic solvents, such as acetonitrile, glyme, ethyl acetate or acetone, the Aquivion-H catalyzed acetonidation led to triacetals as the main products, as indicated by the almost exclusive presence of singlets imputable to the geminal methyls of the 1,2:3,4:5,6 triacetone in the most upfield region of the ^1H NMR spectra of the crudes and by the concomitant absence, at lower field, of the diagnostic signals for 1, namely those of the two hydroxylated methines. On the other side, DMF, in which the solubility of mannitol at room temperature is low but not null as in the above less polar solvents, can ensure a supply of dissolved substrate proportioned to the turnover frequency of the catalysts, which is, as desirable, lower than that of soluble acids such as *p*-TsOH or H_2SO_4 . In this heterogeneous catalysis, other key aspects able of modulating the reactivity of the species involved are the more difficult accessibility to the catalytic sites by the reactants, reasonably varying with their acetonidation extent, and the amphiphilic nature of the polymer Aquivion-H favouring the reactivity of a highly hydrophilic substrate, such as mannitol, in a non-aqueous environment. The synergy of these factors allows a fine control of the reaction and tunes the reaction selectivity. Evaluation of the individual weight of such factors would imply further ad hoc investigations. However, our statements are supported by the negative or less positive results obtained replacing Aquivion-H with soluble acids or DMF with solvents unable to dissolve mannitol.

The present procedure of mannitol diacetoneidation catalyzed by Aquivion-H places itself beside the recently reported Aquivion catalyzed acetalizations of sugars with fatty alcohols to give amphiphilic alkyl glycosides [41–43], surfactants of great interest for many desirable intrinsic properties. There, acetalization reaction was between hydrophilic carbonyl compounds (glucose, cellulose) and a hydrophobic alcohol (*n*-dodecanol). Here, on the contrary, a highly hydrophilic alcohol (mannitol) reacts with a hydrophobic acetalating agent (2,2-dimethoxypropane). In both cases, due to its amphiphilic nature, Aquivion-H proves to be able to efficiently catalyze the reaction between substrates of very different polarity while showing, because of its structured catalytic sites, good selectivity for a single product inside a large series of candidate products. Among a dozen of mono-, di- and triacetones, Aquivion-H selectively catalyzes the formation of the desired 1,2:5,6 diacetone although in the presence of exceeding acetalating agent for moderately long time at room temperature, maintaining such a performance unaltered through several recycles.

3. Experimental

D-Mannitol (1 g, 5.49 mmol), Aquivion-H (133 mg, 0.153 mmol), 2,2-dimethoxypropane (2.7 ml, 22.0 mmol) and 5 ml of dimethylformamide were introduced into a round bottom flask under inert atmosphere. The reaction mixture was vigorously stirred for 16 h at room temperature. Afterward the suspension was filtered to remove the catalyst and the filtrate was concentrated under vacuum to obtain a white solid crude that was trituated in cyclohexane (15 ml). 1 was recovered by filtration as a white solid in 76% yield (1.09 g): mp = 120.3–121.6 °C; $[\alpha]_{\text{D}}^{25} = +2.6$ (c 1, EtOH). ^1H NMR (CDCl_3) δ 4.19 (q, $J = 6.2$ Hz, 2H), 4.12 (dd, $J = 8.4$ Hz and 6.4 Hz, 2H), 3.97 (dd, $J = 8.4$ Hz and 5.6 Hz, 2H), 3.75 (t, $J = 6.6$ Hz, 2H), 2.59 (d, $J = 6.6$ Hz, 2H), 1.42 (s, 6H), 1.36 (s, 6H). ^{13}C NMR (CDCl_3) δ 109.4, 76.3, 71.2, 66.7, 26.7, 25.2. GC analysis of the diacetylated derivative showed >98% purity. The catalyst removed from the reaction mixture was rinsed with acetonitrile, dried under vacuum, and recycled for five times.

GC analyses were conducted on samples acetylated by treatment

with pyridine and acetic anhydride overnight at room temperature with a Thermo Fisher Trace gas chromatograph using a fused silica capillary column DB-5MS UI (30 m × 0.25 mm) (Agilent); temperature, 5 °C/min from 180 to 280 °C; carrier gas, helium 1.0 ml/min; detector: FID. Under these conditions, the R_t of 1,2:3,4:5,6-triacetal, diacetylated **1**, tetraacetylated 1,2-diacetal and peracetylated mannitol were 3.80, 5.80, 7.49 and 9.55 min, respectively. Their peaks were identified by peak-matching with authentic samples obtained by acetylation of mannitol and of the acetals, in turn isolated from reaction crudes by chromatography on silica gel and identified by comparison of their ^1H NMR spectra with those reported in the literature.

Funding

The study was funded by Università degli Studi of Milan.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Appendix ASupplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.carres.2020.108229>.

References

- K.C. Babu, G. Ramadasu, L. Gangaiah, G. Madhusudhan, K. Mukkanti, A new route for the synthesis of (R)-glyceraldehyde: a key chiral building block, *Indian J. Chem. B* 49B (2010) 260–263.
- M. Pallavicini, E. Valoti, L. Villa, O. Piccolo, Synthesis of (R)- and (S)-isopropylidene glycerol, *Tetrahedron: Asymmetry* 5 (1994) 5–8.
- M. Pallavicini, E. Valoti, L. Villa, O. Piccolo, Resolution of amines with isopropylidene glycerol, *Tetrahedron: Asymmetry* 7 (1997) 1069–1073.
- N. Tahiri, P. Fodran, D. Jayaraman, J. Buter, M.D. Witte, T.A. Ocampo, D. B. Moody, I. Van Rhijn, A.J. Minnaard, Total synthesis of a mycolic acid from *Mycobacterium tuberculosis*, *Angew. Chem. Int. Ed.* 39 (2020) 7555–7560.
- I. Loke, G. Bentzinger, J. Holz, A. Raja, A. Bhasin, F. Sasse, A. Köhn, R. Schobert, S. Laschat, Synthesis of the AB ring system of clifednamide utilizing Claisen rearrangement and Diels-Alder reaction as key steps, *Org. Biomol. Chem.* 14 (2016) 884–894.
- E.K. Jung, L.I. Pilkington, D. Barker, Enantioselective synthesis of 2,3-disubstituted benzomorpholines: analogues of lignan natural products, *J. Org. Chem.* 81 (2016) 12012–12022.
- C. Bolchi, F. Bavo, R. Appiani, G. Roda, M. Pallavicini, 1,4-Benzodioxane, an evergreen, versatile scaffold in medicinal chemistry: a review of its recent applications in drug design, *Eur. J. Med. Chem.* 200 (2020) 112419.
- C. Bolchi, E. Valoti, V. Straniero, P. Ruggeri, M. Pallavicini, From 2-aminomethyl-1,4-benzodioxane enantiomers to unichiral 2-cyano- and 2-carbonyl-substituted benzodioxanes via dichloroamine, *J. Org. Chem.* 79 (2014) 6732–6737.
- L. Fumagalli, M. Pallavicini, R. Budriesi, M. Gobbi, V. Straniero, M. Zagami, G. Chiodini, C. Bolchi, A. Chiarini, M. Micucci, E. Valoti, Affinity and activity profiling of unichiral 8-substituted 1,4-benzodioxane analogues of WB4101 reveals a potent and selective α_{1B} -adrenoceptor antagonist, *Eur. J. Med. Chem.* 58 (2012) 184–191.
- V. Straniero, M. Pallavicini, G. Chiodini, P. Ruggeri, L. Fumagalli, C. Bolchi, A. Corsini, N. Ferri, C. Ricci, E. Valoti, Farnesyltransferase inhibitors: CAAX mimetics based on different biaryl scaffolds, *Bioorg. Med. Chem. Lett.* 24 (2014) 2924–2927.
- M. Pallavicini, C. Bolchi, M. Binda, A. Cilia, F. Clementi, R. Ferrara, L. Fumagalli, C. Gotti, M. Moretti, A. Pedretti, G. Vistoli, E. Valoti, 5-(2-Pyrrolidinyl)oxazolidinones and 2-(2-pyrrolidinyl)benzodioxanes: synthesis of all the stereoisomers and $\alpha\beta 2$ nicotinic affinity, *Bioorg. Med. Chem. Lett.* 19 (2009) 854–859.
- R.L. Knight, F.J. Leeper, Synthesis of and asymmetric induction by chiral bicyclic thiazolium salts, *Tetrahedron Lett.* 38 (1997) 3611–3614.
- R.I. Duclos, A. Makriyannis, Syntheses of all four stereoisomers which are conformationally constrained 1,4-dioxanyl analogs of the antineoplastic ether lipid ET-18-OCH₃, *J. Org. Chem.* 57 (1992) 6156–6163.
- S. Roscales, A.G. Csáky, Trifluoroacetic anhydride promoted tandem conjugate addition of boronic acids/acetals ring opening, *Org. Lett.* 14 (2012) 1187–1189.
- C. Bolchi, M. Pallavicini, L. Fumagalli, B. Moroni, C. Rusconi, E. Valoti, Univocal syntheses of 2- and 3-hydroxymethyl-2,3-dihydro[1,4]dioxino[2,3-b]pyridine enantiomers, *Tetrahedron: Asymmetry* 16 (2005) 3380–3384.
- C. Bolchi, M. Pallavicini, C. Rusconi, L. Diomedea, N. Ferri, A. Corsini, L. Fumagalli, A. Pedretti, G. Vistoli, E. Valoti, Peptidomimetic inhibitors of farnesyltransferase with high in vitro activity and significant cellular potency, *Bioorg. Med. Chem. Lett.* 17 (2007) 6192–6196.
- C.K. Babu, R. Vysabhatter, K.S.V. Srinivas, S. Nigam, G. Madhusudhan, K. Mukkanti, Asymmetric synthesis of (4S,5S)-2-oxo-4-phenyloxazolidine-5-carboxylic acid using a 1,2-addition of PhMgBr to an N-sulfinimine derived from (R)-glyceraldehyde acetonide and (S)-t-BSA, *Tetrahedron: Asymmetry* 21 (2010) 2619–2624.
- M. Goubert, I. Canet, M.E. Sinibaldi, A flexible route to new spirodioxanes, oxathianes and morpholines, *Tetrahedron* 65 (2009) 4182–4189.
- E. Baer, 1,2,5,6-Diacetone d-mannitol and 1,2,5,6-diacetone l-mannitol, *J. Am. Chem. Soc.* 67 (1945) 338–339.
- E.S. De Alvarenga, V.M.T. Carneiro, F.O. Silvério, W.A. Saliba, A high yield synthesis of 1,2:5,6-di-O-isopropylidene-d-mannitol, *J. Chil. Chem. Soc.* 51 (2006) 986–988.
- P. Bentler, N. Erdeljac, K. Bussmann, M. Ahlqvist, L. Knerr, K. Bergander, C. G. Daniliuc, R. Gilmour, Stereocontrolled synthesis of tetrafluoropentanol: multivincinal fluorinated alkane units for drug discovery, *Org. Lett.* 21 (2019) 7741–7745.
- J. Kuszmann, E. Tomori, I. Meerwald, The synthesis of 1,2:5,6-di-O-isopropylidene-d-mannitol: a comparative study, *Carbohydr. Res.* 128 (1984) 87–99.
- J. Kuszmann, E. Tomori, P. Dvortsák, 1,2:4,6- and 1,2:3,6-Di-O-isopropylidene-d-mannitol, *Carbohydr. Res.* 132 (1984) 178–183.
- D.M. Clode, Carbohydrate cyclic acetal formation and migration, *Chem. Rev.* 79 (1979) 491–513.
- C. Morpain, B. Nasser, B. Laude, N. Latruffe, Improved preparation of di-O-isopropylidene-1,2:5,6-d-mannitol, *Org. Prep. Proced. Int.* 22 (1990) 540–543.
- R.M. Archer, S.F. Royer, W. Mahy, C.L. Winn, M.J. Danson, S.D. Bull, Syntheses of 2-keto-3-deoxy-D-xylofuranose and 2-keto-3-deoxy-L-arabinofuranose as stereochemical probes for demonstrating the metabolic promiscuity of *Sulfolobus solfataricus* towards D-xylose and L-arabinose, *Chem. Eur. J.* 19 (2013) 2895–2902.
- G.J.F. Chittenden, An improved, simplified synthesis of 1,2:5,6-di-O-isopropylidene-d-mannitol, *Carbohydr. Res.* 84 (1980) 350–352.
- G.J.F. Chittenden, Isopropylideneation of d-mannitol under neutral conditions, *Carbohydr. Res.* 87 (1980) 219–226.
- C.R. Schmid, J.D. Bryant, M. Dowlatzadeh, J.L. Phillips, D.E. Prather, R.D. Schantz, N.L. Sear, C.S. Vianco, 2,3-O-Isopropylidene-d-glyceraldehyde in high chemical and optical purity: observations on the development of a practical bulk process, *J. Org. Chem.* 56 (1991) 4056–4058.
- J.L. Debost, J. Gelas, D. Horton, Selective preparation of mono- and diacetals of d-mannitol, *J. Org. Chem.* 48 (1983) 1381–1382.
- R.W. Kierstead, A. Faraone, F. Mennona, J. Mullin, R.W. Guthrie, H. Crowley, B. Simko, L.C. Blaber, β_1 -Selective Adrenoceptor antagonists. 1. Synthesis and β -adrenergic blocking activity of a series of binary (aryloxy)propanolamines, *J. Med. Chem.* 26 (1983) 1561–1569.
- R. de S. Martins, M.P. Pereira, P.P. de Castro, F.I. Bombonato, Design and preparation of a novel prolinamide-based organocatalyst for the solvent-free asymmetric aldol reaction, *Tetrahedron* 76 (2020), 130855.
- Solvay Specialty Polymers SpA. https://www.sintef.no/globalassets/upload/material_kjemi/energikonvertering-og-materialer/bilder/merlo-fuel-cell-science-technology-berlin-11-12-april-2012.pdf.
- V. Airolodi, O. Piccolo, G. Roda, R. Appiani, F. Bavo, R. Tassini, S. Paganelli, S. Arnoldi, M. Pallavicini, C. Bolchi, Efficient one-pot reductive aminations of carbonyl compounds with aquivion-Fe as a recyclable catalyst and sodium borohydride, *Eur. J. Org. Chem.* (2020) 162–168.
- F. Bavo, M. Pallavicini, C. Gotti, R. Appiani, M. Moretti, S.F. Colombo, S. Pucci, P. Viani, R. Budriesi, M. Renzi, S. Fucile, C. Bolchi, Modifications at C(5) of 2-(2-pyrrolidinyl)-substituted 1,4-benzodioxane elicit potent $\alpha\beta 2$ nAChR partial agonism with high selectivity over the $\alpha\beta 4$ subtype, *J. Med. Chem.* 63 (24) (2020) 15668–15692.
- M. Kiso, A. Hasegawa, Acetonation of some pentoses with 2,2-dimethoxypropane-N,N-dimethylformamide-p-toluenesulfonic acid, *Carbohydr. Res.* 52 (1976) 95–101.
- M.A. Peña, Y. Daali, J. Barra, P. Bustamante, Partial solubility parameters of lactose, mannitol and saccharose using the modified extended Hansen method and evaporation light scattering detection, *Chem. Pharm. Bull.* 48 (2000) 179–183.
- A. Jouyban, in: A. In Handbook of Solubility Data for Pharmaceuticals, Taylor and Francis, NW, 2010, pp. 69–202.
- C. Bolchi, F. Bavo, M. Pallavicini, One-step preparation of enantiopure l- or d-amino acid benzyl esters avoiding the use of banned solvents, *Amino Acids* 49 (2017) 965–974.
- C. Bolchi, F. Bavo, L. Regazzoni, M. Pallavicini, Preparation of enantiopure methionine, arginine, tryptophan, and proline benzyl esters in green ethers by Fischer-Speier reaction, *Amino Acids* 50 (2018) 1261–1268.
- W. Fang, Z. Fan, H. Shi, S. Wang, W. Shen, H. Xu, J.M. Glacens, F. De Campo, A. Liebens, M. Pera-Titus, Aquivion®-carbon composites via hydrothermal carbonization: amphiphilic catalyst for solvent-free biphasic acetalization, *Mater. Chem.* 4 (2016) 4380–4385.
- A. Karam, K. De Oliveira Vigier, S. Marinkovic, B. Estrine, C. Oldani, F. Jérôme, Conversion of cellulose into amphiphilic alkyl glycosides catalyzed by aquivion, a perfluorosulfonic acid polymer, *ChemSusChem* 10 (2017) 3604–3610.
- A. Karam, K. De Oliveira Vigier, S. Marinkovic, B. Estrine, C. Oldani, F. Jérôme, High catalytic performance of aquivion PFSA, a reusable solid perfluorosulfonic acid polymer, in the biphasic glycosylation of glucose with fatty alcohols, *ACS Catal.* 7 (2017) 2990–2997.