


RSC Advances



This article can be cited before page numbers have been issued, to do this please use: C. Qin, C. Peng, H. Xie, Z. K. Zhao and M. Bao, *RSC Adv.*, 2015, DOI: 10.1039/C5RA05667E.

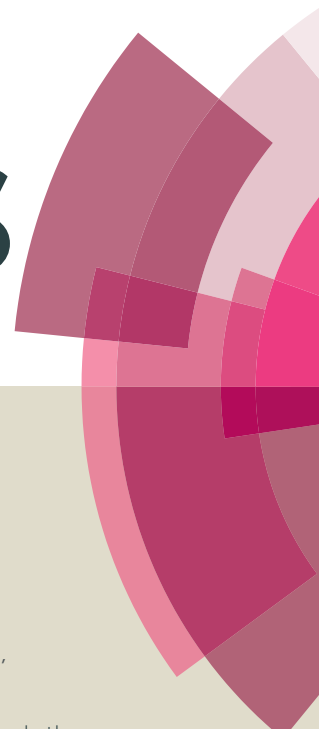

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Journal Name

COMMUNICATION

Cellulosic Poly(ionic liquid)s: Synthesis, Characterization and its Application in the cycloaddition of CO₂ to Epoxide†

Qin Chen,^{a,b} Chang Peng,^a Haibo Xie,^{*a} Zongbao Kent Zhao^{*a} and Ming Bao^bReceived 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Cellulosic poly(ionic liquid)s (PILs) were prepared *via* nucleophilic substitution of chlorinated cellulose by 1-methyl-imidazole and their structure and thermal properties have been fully characterized; the cellulosic PILs were found as green, efficient and recyclable catalysts for the cycloaddition of CO₂ to epoxides under solvent-free conditions.

Ionic liquids (ILs) are molten salts at relatively low temperatures and exhibit a series of unique properties comparing with molecular solvents and materials, which make them interesting as new solvents, catalysts and functional materials¹⁻³. The introduction of ILs moiety into polymers results in a new family of polymeric materials, poly(ionic liquid)s (PILs), with particular properties and interesting applications⁴⁻⁷. For example, considering the catalytic performance of ionic liquids moiety, PILs could be used as efficient heterogeneous catalysts with enhanced recyclability, such as cyclic addition of epoxides with CO₂ to prepare cyclic carbonates⁸⁻¹⁰.

Up to now great efforts have been devoted to synthesize PILs and two distinctive strategies have been developed: (1) polymerization of polymerizable ILs monomers, (2) post-modification of existing polymers⁵. Generally, the polymerizable ILs monomers containing (meth)acryloyl^{11, 12}, styrenic¹³ or vinyl¹⁴ groups can be employed to synthesize PILs *via* traditional polymerization technologies. PILs with special polymeric backbones can be achieved by post-modification of either of synthetic polymers or biopolymers¹⁵⁻¹⁷. Usually, a chloromethyl is introduced onto the synthetic polymers firstly, followed by an alkylation of Lewis organic bases and anion exchange reaction to obtain the designable PILs^{18, 19}.

Compared with those synthetic polymers, the use of biopolymers as backbone of PILs is anticipated to provide


advantages of natural abundance, low cost, nontoxicity, biocompatibility and biodegradability²⁰. The preparation of biopolymers-based PILs is mainly depended on the chemical reactions of its hydroxyl groups. For example, the cellulose-based PILs (quaternized cellulose) have been synthesized *via* etherification reaction and widely used in various fields for a long time, such as environmental protection, water treatment, textile dyeing industry^{17, 21} and gene transfection²². Among the etherification reagents, the 3-chloro-2-hydroxypropyl trimethylammonium chloride (CHTAC) has been the most preferred one²²⁻²⁴. The etherification reaction is usually carried out under aqueous alkaline conditions, and excess amount of sodium hydroxide is usually required to achieve satisfactory modification efficiency. Additionally, the etherification protocol also suffers from drawbacks such as side reaction, low modification efficiency, and low structural diversity^{25, 26}. Another choice of biopolymer as a backbone of PILs is chitosan due to its active functional groups, including hydroxyl groups and amino groups. For example, chitosan-based PILs have been prepared *via* a direct alkylation of amino group, which were successfully used in green catalysis²⁷⁻²⁹. He L. N. et al. prepared chitosan supported PILs via the reaction between chitosan and CHTAC.³⁰ Park D. W. proposed another method in which the quaternization is occurred on the primary amine on chitosan rather than anchoring a prebuilt quaternized group onto chitosan.^{31, 32} Dupont et al. demonstrated that imidazolium-based ILs were great candidates for the formation and stabilization of metal nanoparticles.^{3, 33, 34} Thereby it is still incentive to develop more facile route to prepare cellulosic PILs, especially with the imidazolium group

^aState Key Laboratory of Fine Chemicals, Dalian University of Technology, Dalian 116023, PR China.


^bDalian National Laboratory for Clean Energy; Dalian Institute of Chemical Physics, CAS, Dalian 116023, PR China; E-mail: hbxie@dicp.ac.cn, zhaozb@dicp.ac.cn

† Electronic Supplementary Information (ESI) available: Experimental details and some characterization of cellulosic PILs. See DOI: 10.1039/x0xx00000x

A: The common protocol for the synthesis of imidazolium ionic liquids



B: The new protocol for the preparation of cellulosic PILs precursor by chlorinated cellulose

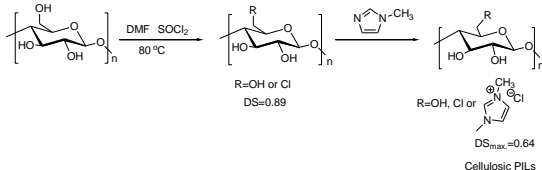

Scheme 1. Facile preparation of cellulosic PILs by using chlorinated cellulose and 1-methyl-imidazole.

Inspired by the commonly used protocol for the preparation of imidazolium ILs (Scheme 1), herein, we report a facile protocol for the preparation of cellulosic PILs, cellulose anchored 1-methyl-imidazolium chloride ([Cellmim][Cl]), *via* alkylation reaction between chlorinated cellulose and 1-methyl-imidazole. The as-prepared cellulosic PILs were applied in the cycloaddition of CO₂ to epoxides under solvent-free conditions as a proof and concept application.

Cellulose was chemically modified with SOCl₂ to obtain chlorinated cellulose (6-chloro-6-deoxycellulose, CDC) with a DS of 0.89 preferentially on C-6 position, which was in accordance with previous publications^{35, 36}. Compared with other classes of ionic liquids the imidazolium-based ionic liquids are one of the most important families of ionic liquids due to their outstanding properties¹. We started the study with 1-methyl-imidazole to prepare the [Cellmim][Cl] both without solvent and in DMSO or 1-alkyl-3-methyl-imidazolium chloride (AmimCl). The degree of substitution (DS) of the [Cellmim][Cl] was calculated according to elemental analysis results of nitrogen content and the reaction efficiency (RE) was calculated from the DS of CDC and the [Cellmim][Cl]. It was found that the alkylation reaction could proceed smoothly at 100 °C, and [Cellmim][Cl] with a DS of 0.56 was obtained in 24 h when excess 1-methyl-imidazole was used as a reagent and solvent (Table 1, entry 3). Further prolonging the reaction time to 48 h, a maximal DS of 0.64 was achieved (Table 1, entry 4). Correspondingly, the RE of the chloromethyl on cellulose was 71.9%. Although the DS increased significantly, the yield did not change notably, which suggested that degradation of the chlorinated cellulose occurred during the reaction. The reaction temperature has a great affect on the reaction, which was evidenced by the DS significantly decreased to 0.37 and 0.14 when the temperature was decreased to 90 °C and 80 °C in 24 h, respectively (Table 1, entries 1, 2). It was also found that the reaction started in heterogeneous conditions and then became highly swollen gel-like state with high viscosity, which confirmed the successful alkylation reaction. In order to decrease the viscosity of the reaction mixture, DMSO and AmimCl were used as solvents for the alkylation reaction under identical conditions. It was interesting to find that the reaction mixture was also heterogeneous at the beginning in the case of DMSO, but became homogeneous in shorter time. Although higher yields were obtained in this case, the [Cellmim][Cl] only have moderate DS of 0.35 and 0.42 at 90 °C

and 100 °C, respectively (Table 1, entries 5, 6), which were lower than those obtained under neat conditions (Table 1, entries 2, 3). The results suggest that the use of DMSO as solvent cannot promote the alkylation reaction, but can suppress the degradation of CDC. In the case of AmimCl, the reaction was performed under homogeneous condition as the ionic liquids were good solvents to CDC; surprisingly, the product with lower DS of 0.3 was obtained, which were similar to the amination of cellulose³⁵. It seems that the stronger ionic strength of ionic liquids suppressed the alkylation reaction although a homogeneous state was sustained all the time.

Table 1. Preparation of [Cellmim][Cl] under various conditions

Entry	Solvent	T °C	t h	N %	DS	Yield %	RE %
1	none	80	24	2.049	0.14	79.3	15.7
2	none	90	24	5.003	0.37	89.6	41.1
3	none	100	24	6.976	0.56	83.5	62.1
4	none	100	48	7.752	0.64	84.5	71.9
5	DMSO ^b	90	72	4.751	0.35	97.5	39.3
6	DMSO ^b	100	24	5.517	0.42	89.2	47.2
7	AmimCl ^c	90	24	4.176	0.30	84.4	33.7

^a0.5 mL 1-methyl imidazole, 0.5 g CDC, ^b0.5 mL DMSO; ^c12.5 g AmimCl;

The solubility of [Cellmim][Cl] with different DS values in conventional solvents was also studied (Table S1). Their solubility mostly depends on the DS values and the samples with DS>0.37 are soluble in water; the sample with a DS of 0.14 only can be swollen by water, but is soluble in DMSO. It is also interesting to find that the samples with DS<0.4 are soluble in DMSO; while the samples with DS>0.4 can be only swollen by DMSO, thus achieving a gel-like solution with enhanced viscosity. It is worthy to mention that the good solubility of the [Cellmim][Cl] in water and DMSO will provide great opportunities to prepare functional composites materials with other functional components through solution processing and homogeneous catalysis.

The successful preparation of chlorinated cellulose and [Cellmim][Cl] was confirmed by comparative CP/MAS ¹³C NMR spectra as shown in Figure 1. The spectrum of pure cellulose show typical peaks for its six carbons in the monomer unit. The downfield peak at 104.7 ppm is assigned to C-1 since C-1 is bonded to two oxygen atoms. The peak at 88.6 ppm is assigned to C-4 which is connected to only one oxygen and is responsible for β-1,4-glucoside bonds. The chemical shift at 74.7 and 72.0 ppm are classified to C-2, C-3 and C-5 because they are all secondary carbons attached to -CH or -OH group. The peak of C-6 appears at 65.0 ppm, which is a primary carbon connected to -OH and -CH₂ groups. The partial substitution of the -OH by chloride at C-6 resulted in a significant change of the chemical shift of C-6 from 65.0 to 44.8 ppm. The substitution only resulted in slight changes

the chemical shifts of C-1 from 104.7 to 103.7 ppm, of C-4 from 88.6 to 83.9 ppm, while no notable affect on the chemical shifts of C-2, C-3 and C-5 was observed. These results confirm the successful preparation of chlorinated cellulose in this study³⁷.

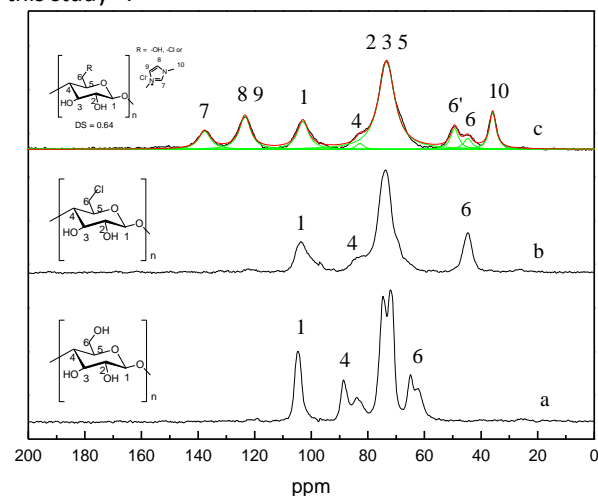


Fig. 1 CP/MAS ^{13}C NMR spectra of cellulose (a), CDC (b, DS=0.89) and [Cellmim][Cl]_{DS=0.64} (c).

With the covalent bonding the 1-methyl-imidazolium chloride moiety onto cellulose, new signals at 35.9 (C-10), 123.2 (C-8, 9), and 137.6 (C-7) appeared, assigning to the imidazolium ionic liquids moiety, and the reaction resulted in a change in the chemical shift of C-6 from 44.8 to 50.3 ppm, and no obvious affect on the chemical shifts of C1-C5 carbons. A signal of chloromethyl carbon were still detected in the spectra of [Cellmim][Cl]_{DS=0.64}, indicating the presence of chloromethyl residual, which was in accordance with the fact that the DS of ionic liquids moiety is lower than the DS of chlorinated cellulose. We further applied the multi-peaks analysis using Lorentzian method in Origin software to separate the overlapped peaks (Fig. 1-c, C6, C6') and calculate the corresponding areas. By compare the areas of the separated peaks, the DS value of methyl imidazolium chloride and chloride is estimated to be 0.64 and 0.36, respectively. The results are in good accordance with the elemental analysis. The structure of [Cellmim][Cl]_{DS=0.64} was further confirmed by HSQC in D₂O (Fig. S1), and the assignments was summarized in Table S2. The results are in accordance with that of solid state ^{13}C NMR.

The successful chemical modification of cellulose was also confirmed by FTIR analysis (Fig 2). In comparison with the spectrum of raw cellulose, two new bands at 752 and 723 cm^{-1} appeared in the spectrum of the chlorinated cellulose, which were corresponded to stretching vibration of the C-Cl bond. In association with the appearance of the new bands, the bands from 1500 to 1200 cm^{-1} decreased owing to the substitution of the hydroxyl group on C-6³⁷. In contrast, new characteristic bands centered at 1577, 1114, and 1065 cm^{-1} corresponded to the imidazolium moiety appeared in the spectrum of [Cellmim][Cl]_{DS=0.64}³⁸, and the intensity of the band centered at 3400 cm^{-1} increased due to the hydrophilic property of the 1-methyl-imidazolium chloride moiety.

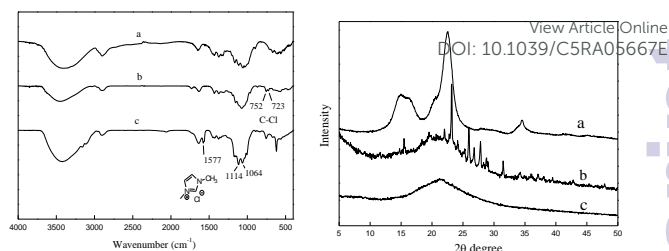


Fig. 2 FTIR and X-ray diffraction patterns of cellulose (a), CDC (b, DS=0.89) and [Cellmim][Cl]_{DS=0.64} (c).

The changes of the molecular-level aggregation structure of the polymer arose by the chemical modifications could be followed by X-ray diffraction technology. The X-ray diffraction pattern of raw cellulose shows three distinctive peaks corresponding to 101, 002 and 040 planes which are characteristic of microcrystalline cellulose (Fig. 2)³⁵. In contrast the chlorinated cellulose exhibits new crystal peaks but with lower intensity, different from those observed for raw cellulose, which indicate that new assembly is formed via the bonded chlorine atoms and remaining hydroxyl groups^{35, 37}. The decreased crystallinity of chlorinated cellulose will be very interesting mainly when subsequent modification are intended such as anchoring a 1-methyl-imidazolium moiety to the backbone. For the [Cellmim][Cl]_{DS=0.64}, as shown in Figure 2, a drastic decrease in crystallinity was observed in comparison with the raw cellulose and CDC. These data suggest that the cellulosic PILs have an amorphous structure, and the newly anchored groups do not establish an ordered assembly.

Further thermogravimetric analysis of cellulose, CDC and [Cellmim][Cl]_{DS=0.64} were shown in Figure 3. Both of cellulose derivatives exhibited inferior thermal stability to the raw cellulose, as illustrated in thermogravimetric curves. Cellulose can remain stable up to 300 °C and shows only one decomposing process from 300 to 380 °C with a mass loss of 92% owing to the pyrolytic degradation of the carbon skeleton. The onset degradation temperature of CDC and [Cellmim][Cl]_{DS=0.64} is 266 and 220 °C, respectively, and their mass loss even after 600 °C is estimated to be 83% and 71%, respectively. The lower degradation temperature was attributed to the destroyed crystalline structure and the different chemical structures. In addition, both CDC and [Cellmim][Cl]_{DS=0.64} gave two stage of decomposition behavior. For CDC the first mass loss between 150 and 250 °C is caused

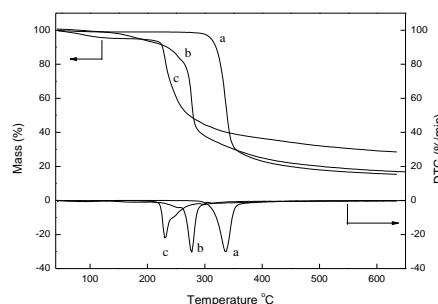


Fig. 3 TGA-DTG curves of cellulose (a), CDC (b, DS=0.89) and [Cellmim][Cl]_{DS=0.64} (c).

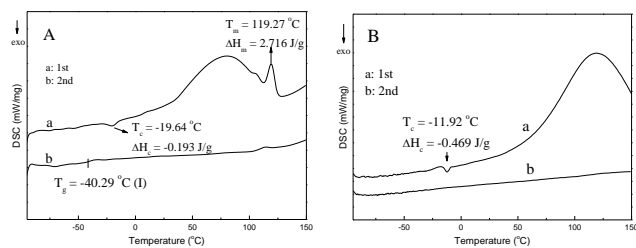


Fig. 4 DSC curve of CDC (DS=0.89, A) and [Cellmim][Cl]_{DS=0.64} (B). a: first heating cycle, b: second heating cycle.

by the cleavage of C-Cl bond and the condensation of hydroxyl groups on C-2 and C-3. The second stage from 250 °C is corresponding to the depolymerization of cellulose polymeric chain^{39, 40}. The degradation behavior of [Cellmim][Cl]_{DS=0.64} is similar to that of CDC, with the initial mass loss from 220 to 280 °C which can be interpreted as losing of the immobilized imidazolium group on cellulose backbone together with the condensation of hydroxyl groups on C-2 and C-3. The second step is also correlated with the loss of cellulose fiber.

The thermal properties of the as-prepared cellulose derivatives were further investigated by differential scanning calorimetry. The CDC exhibits typical crystal structure with melting peak at 119.27 °C and the corresponding enthalpy is 2.716 J/g from the first heating cycle (Fig. 4 A). Additionally, the crystallization temperature (T_c) appeared at -19.64 °C with ΔH_c value of -0.193 J/g. The glass transition temperature was observed from the second heating cycle at -40.29 °C. On the other hand, the [Cellmim][Cl]_{DS=0.64} was found to be amorphous but the obvious glass transition stage was not observed in neither first nor second heating curve (Fig. 4 B). The T_c of [Cellmim][Cl]_{DS=0.64} appeared at -11.92 °C with ΔH_c value of -0.469 J/g from the first heating cycle.

The design and preparation of PILs have been demonstrated to broaden the properties and applications of ionic liquids, which have been reviewed in recent comprehensive reviews^{4, 5, 7, 41}. With the new cellulosic PILs ([Cellmim][Cl]) in hand, it is reasonable to conjecture that its physical and chemical properties can be tuned *via* the freedom combination of this cellulosic poly(cation) and anions due to the designable nature of the anchored 1-methyl-imidazolium chloride moiety⁴²⁻⁴⁴. The direct use of PILs as catalysts or as the supports for catalytic active species in various catalytic reactions has been widely investigated⁷⁻¹⁰. Among the various reactions catalyzed by PILs, one of the most concerned topics is the synthesis of cyclic carbonates *via* its addition reaction of CO₂ and epoxides^{8-10, 27, 42}. Therefore, the reaction was also selected as a proof and concept application of the [Cellmim][Cl]_{DS=0.64} to demonstrate its potential. To our delight, the catalytic activity varied with the halide anion (Table 2), and iodide exhibited the highest yield while chloride showed the lowest yield in the cycloaddition of CO₂ to propylene oxide. The difference may be ascribed to the different nucleophilicity and leaving ability of the halide anions, which is in accordance with the trend in previous studies⁴⁵. The catalytic system could also be extended to the reactions of different epoxides with

Table 2. Cycloaddition of CO₂ with different epoxides catalyzed by [Cellmim][X]^a

DOI: 10.1039/C5RA05667E

Entry	Catalysts	Epoxide	Product	Yield% ^b
1	[Cellmim][Cl] _{DS=0.64}			44.2
2	[Cellmim][Br] _{DS=0.64}			68.7
3	[Cellmim][I] _{DS=0.64}			80.4
4 ^c	[Cellmim][I] _{DS=0.64}			95.1
5	[Cellmim][Br] _{DS=0.64}			87.4
6	[Cellmim][I] _{DS=0.64}			88.7
7	[Cellmim][I] _{DS=0.64}			95.3
8	[Cellmim][I] _{DS=0.64}			91.7

^a Reaction conditions: epoxides 20 mmol, 5 mol% Cellulosic PILs, CO₂ pressure 2 MPa, 120 °C 6 h; ^b isolated yield; ^c 150 °C

CO₂, and good isolated yields of cyclic-carbonates were achieved.

The reusability of the [Cellmim][I]_{DS=0.64} catalyst was studied in the cycloaddition of glycidyl phenyl ether and CO₂. The catalyst could be separated by washing with ethyl acetate, filtered and then dried under vacuum. The recovered catalyst was directly employed for the cycloaddition under identical conditions. The catalyst remained active up to 5 runs without remarkable decrease in yield demonstrating high reusability of the catalyst (Fig. 5). Further analysis of the recovered catalyst by FTIR, ¹H NMR and TGA were performed towards a better understanding of the potential structural changes on the catalyst during the reusability study, and the comparative results were shown in Figure S2 to S4. The structural information from the ¹H NMR and FTIR spectra of the recovered catalyst demonstrated that the chemical bonded imidazolium moiety was stable during the reaction, and the structure remained unchanged after 5 cycles, which determined its stable catalytic activity during the reusability study. The TGA result (Figure S4) showed that the onset temperature of recovered catalyst remained unchanged but the residual weight at 650 °C decreased from 38.9% to 31.0%. The possible reason for this is still unclear at the early stage of the study.

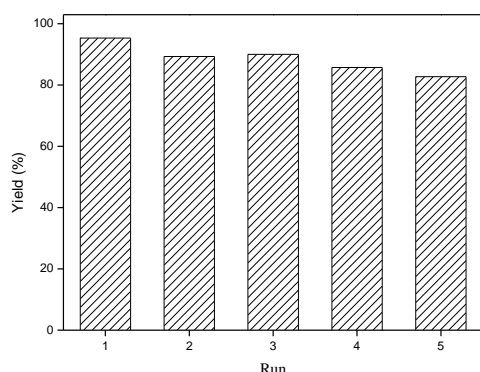


Fig. 5. Reusability of [Cellmim][I]_{DS=0.64}. Reaction conditions: glycidyl phenyl ether (20 mmol), [Cellmim][I]_{DS=0.64} (5 mmol%), 120 °C, 2 MPa, 6 h.

In summary, the chemical modification of cellulose with SOCl₂ produced CDC with a DS of 0.89, which was successfully used as alkylation reagent for 1-methyl-imidazole to synthesize cellulosic PILs with tunable substitution degrees. The structural and thermal properties of the cellulosic PILs were studied by various technologies, and they were ready for the preparation of novel cellulosic functional materials. As a proof and concept application, the as-prepared cellulosic PILs were used as green, efficient and recyclable catalysts for the cycloaddition of CO₂ to epoxides under solvent-free conditions. Further work in this area will focus on the design and application the derivative functional materials by taking the advantages of cellulose and ionic liquids moieties.

Acknowledgements

This work was supported by Natural Science Foundation of China (no. 21002101).

Notes and references

- N. V. Plechkova and K. R. Seddon, *Chem. Soc. Rev.*, 2008, 37, 123-150.
- T. Torimoto, T. Tsuda, K.-i. Okazaki and S. Kuwabata, *Adv. Mater.*, 2010, 22, 1196-1221.
- J. Dupont and J. D. Scholten, *Chem. Soc. Rev.*, 2010, 39, 1780-1804.
- J. Yuan, D. Mecerreyes and M. Antonietti, *Prog. Polym. Sci.*, 2013, 38, 1009-1036.
- J. Yuan and M. Antonietti, *Polymer*, 2011, 52, 1469-1482.
- B. Xin and J. Hao, *Chem. Soc. Rev.*, 2014, 43, 7171-7187.
- P. Zhang, T. Wu and B. Han, *Adv. Mater.*, 2014, 26, 6810-6827.
- S. Ghazali-Esfahani, H. Song, E. Paunescu, F. D. Bobbink, H. Liu, Z. Fei, G. Laurenczy, M. Bagherzadeh, N. Yan and P. J. Dyson, *Green Chem.*, 2013, 15, 1584-1589.
- T.-Y. Shi, J.-Q. Wang, J. Sun, M.-H. Wang, W.-G. Cheng and S.-J. Zhang, *RSC ADV.*, 2013, 3, 3726-3732.
- Y. Xie, Z. Zhang, T. Jiang, J. He, B. Han, T. Wu and K. Ding, *Angew. Chem. Int. Edit.*, 2007, 46, 7255-7258.
- J. Huang, C.-a. Tao, Q. An, W. Zhang, Y. Wu, X. Li, D. Shen and G. Li, *Chem. Commun.*, 2010, 46, 967-969.
- F. Yan and J. Texter, *Chem. Commun.*, 2006, 2696-2698.
- J. E. Bara, C. J. Gabriel, E. S. Hatakeyama, T. K. Carlisle, S. Lessmann, R. D. Noble and D. L. Gin, *J. Membr. Sci.*, 2008, 321, 3-7.
- R. Marcilla, J. Alberto Blazquez, J. Rodriguez, J. A. Pomposo and D. Mecerreyes, *J. Polym. Sci., Part A: Polym. Chem.*, 2004, 42, 208-212.
- W. Zhang, H. Wang, J. Han and Z. Song, *Appl. Surf. Sci.*, 2012, 258, 6158-6168.
- B. Motos-Perez, J. Roeser, A. Thomas and P. Hesemann, *Appl. Organomet. Chem.*, 2013, 27, 290-299.
- M. M. Kamel, M. M. El Zawahry, N. S. E. Ahmed and F. Abdelghaffar, *Ind. Crop. Prod.*, 2011, 34, 1410-1417.
- J. Wang, S. Li and S. Zhang, *Macromolecules*, 2010, 43, 3890-3896.
- B. Lin, H. Dong, Y. Li, Z. Si, F. Gu and F. Yan, *Chem. Mater.*, 2013, 25, 1858-1867.
- Z. Schnepf, *Angew. Chem. Int. Edit.*, 2013, 52, 1096-1108.
- S. Acharya, N. Abidi, R. Rajbhandari and F. Meulewaeter, *Cellulose*, 2014, 21, 4693-4706.
- Y. Song, Y. Sun, X. Zhang, J. Zhou and L. Zhang, *Biomacromolecules*, 2008, 9, 2259-2264.
- T. S. De Vries, D. R. Davies, M. C. Miller and W. A. Cynecki, *Ind. Eng. Chem. Res.*, 2014, 53, 9686-9694.
- M. Hashem, P. Hauser and B. Smith, *Text. Res. J.*, 2003, 73, 1017-1023.
- H. S. Seong and S. W. Ko, *J. Soc. Dyers Colour.*, 1998, 114, 124-129.
- K. R. Roshan, T. Jose, A. C. Kathalikkattil, D. W. Kim, B. Kim and D. W. Park, *Appl. Catal., A*, 2013, 467, 17-25.
- J. Baudoux, K. Perrigaud, P.-J. Madec, A.-C. Gaumont and I. Dez, *Green Chem.*, 2007, 9, 1346-1351.
- N. Clousier, A. Filippi, E. Borré, E. Guibal, C. Crévisy, F. Caiji, M. Mauduit, I. Dez and A.-C. Gaumont, *ChemSusChem*, 2014, 7, 1040-1045.
- J. Sun, J. Wang, W. Cheng, J. Zhang, X. Li, S. Zhang and Y. She, *Green Chem.*, 2012, 14, 654-660.
- Y. Zhao, J.-S. Tian, X.-H. Qi, Z.-N. Han, Y.-Y. Zhuang and L.-N. He, *J. Mol. Catal. A: Chem.*, 2007, 271, 284-289.
- J. Tharun, Y. Hwang, R. Roshan, S. Ahn, A. C. Kathalikkattil and D.-W. Park, *Catalysis Science & Technology*, 2012, 2, 1674-1680.
- J. Tharun, D. W. Kim, R. Roshan, Y. Hwang and D. W. Park, *Catal. Commun.*, 2013, 31, 62-65.
- J. Dupont, G. S. Fonseca, A. P. Umpierre, P. F. P. Fichtner and S. R. Teixeira, *J. Am. Chem. Soc.*, 2002, 124, 4228-4229.
- P. Migowski, G. Machado, S. R. Teixeira, M. C. M. Alves, J. Morais, A. Traverse and J. Dupont, *Phys. Chem. Chem. Phys.*, 2007, 9, 4814-4821.
- E. C. da Silva Filho, S. A. A. Santana, J. C. P. Melo, F. J. V. E. Oliveira and C. Airoidi, *J. Therm. Anal. Calorim.*, 2010, 100, 315-321.
- T. Tashiro and Y. Shimura, *J. Appl. Polym. Sci.*, 1982, 27, 747-756.
- E. C. Silva Filho, L. C. B. Lima, F. C. Silva, K. S. Sousa, M. G. Fonseca and S. A. A. Santana, *Carbohydr. Polym.*, 2013, 92, 1203-1210.
- J. Sun, W. Cheng, W. Fan, Y. Wang, Z. Meng and S. Zhang, *Catal. Today*, 2009, 148, 361-367.
- N. Kasuya, T. Suzuki and A. Sawatari, *J. Wood Sci.*, 1999, 47, 161-163.
- E. C. da Silva Filho, J. C. P. de Melo and C. Airoidi, *Carbohydr. Res.*, 2006, 341, 2842-2850.
- O. Green, S. Grubjesic, S. Lee and M. A. Firestone, *Polym. Rev.*, 2009, 49, 339-360.
- S. Soll, Q. Zhao, J. Weber and J. Yuan, *Chem. Mater.*, 2013, 25, 3003-3010.
- Z.-L. Xie, X. Huang and A. Taubert, *Adv. Funct. Mater.*, 2014, 24, 2837-2843.
- J. Guo, L. Qiu, Z. Deng and F. Yan, *Poly. Chem-UK*, 2013, 1, 1309-1312.

COMMUNICATION

Journal Name


45 L. Han, S.-W. Park and D.-W. Park, *Energ. Environ. Sci.*, 2009, 2, 1286-1292.

View Article Online
DOI: 10.1039/C5RA05667E

RSC Advances Accepted Manuscript

Published on 08 May 2015. Downloaded by Freie Universitaet Berlin on 13/05/2015 17:33:45.

Graphical Abstract

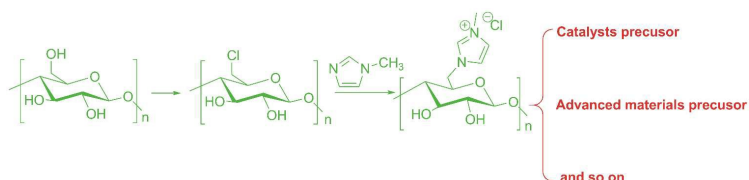Cellulosic Poly(ionic liquid)s: Synthesis, Characterization and its Application in the cycloaddition of CO₂ to Epoxides

Cellulosic poly(ionic liquid)s (PILs) were prepared *via* nucleophilic substitution of chlorinated cellulose by 1-methyl-imidazole and their structure and thermal properties have been fully characterized, which were ready for the preparation of novel green cellulosic catalytic and functional materials.