

Steric activation of chelate catalysts: efficient polyketone catalysts based on four-membered palladium(II) diphosphine chelates

Stephen J. Dossett,^{*a} Amy Gillon,^b A. Guy Orpen,^b James S. Fleming,^b Paul G. Pringle,^{*b} Duncan F. Wass^a and Matthew D. Jones^a

^a BP, Chertsey Road, Sunbury-on-Thames, Middlesex, UK TW16 7LN

^b School of Chemistry, University of Bristol, Cantock's Close, Bristol, UK BS8 1TS.


E-mail: paul.pringle@bristol.ac.uk

Received (in Cambridge, UK) 18th December 2000, Accepted 6th February 2001


First published as an Advance Article on the web 26th March 2001

Palladium(II) complexes of ligands of the type Ar₂PCH₂-PAR₂ and Ar₂PN(Me)PAR₂ (Ar = *ortho*-substituted phenyl group) are very efficient catalysts for copolymerisation of CO and C₂H₄.

The perfectly alternating polyketone made by palladium(II)-catalysed copolymerisation of CO and alkenes [eqn. (1)] has




numerous potential applications.¹ Several types of palladium(II) chelates have been reported to be catalysts^{1,2} but diphosphine chelates outperform all others in terms of activity and selectivity. Drent *et al.*¹ have shown that the CO/C₂H₄ copolymerisation catalytic activity of palladium(II) complexes of diphosphines of the type Ar₂P(CH₂)_nPAR₂ is a sensitive function of the backbone chain length, *n*, and the aryl group, Ar.

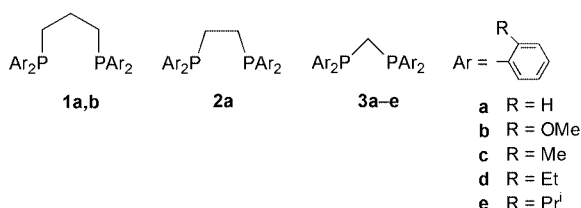

Thus it was shown that the 6-membered chelate derived from **1a** was an order of magnitude more active than the 5-membered analogue from **2a** and that the 4-membered chelate from **3a** was essentially inactive. It was also disclosed that the complex of **1b**, containing *ortho*-methoxy substituents, gave a polymer of significantly greater molecular weight than that obtained with

the complexes of unsubstituted ligand **1a**.³ The catalyst sensitivity to chelate ring size might be rationalised in terms of bite angle effects.⁴ However, we show here that the activity of 4-membered Pd–P–C–P chelates is dramatically increased by the presence of bulky *ortho* substituents on the aryl groups and that polymerisation rates comparable to, or even exceeding, the best commercial catalysts are obtained with 4-membered Pd–P–N–P chelates.^{5,6}

The diphosphine ligands **3b–e** were made from bis(dichlorophosphino)methane⁷ according to eqn. (2) and fully



characterised. The catalysts were tested for the production of ethene/propene/CO terpolymer over a 3 h period at 50 barg and 70 °C in dichloromethane using tris(pentafluorophenyl)borane promoter. In Table 1, the polymer yield is a measure of the productivity of the catalysts over 3 h. The polymerisation rate and catalyst half-life, as determined by fitting first order curves to the cumulative gas uptake profiles, are also given in Table 1. The borane activation method was reported recently and involves the transfer of a pentafluorophenyl group from boron to palladium to form a cationic Pd–C₆F₅ complex which is the catalytically active species.⁶ The catalysts were formed by the reaction of palladium acetate and ligand *in situ* or using pre-formed palladium acetate complexes. The results obtained in terms of rate and productivity are the same (within the accuracy of our measurements) for both of these methods, indicating that the same catalytic species is formed in both cases (see Table 1, entries 3 and 4).

Polydispersities are consistently around the value of 2, as expected for a single site catalyst, and monomer incorpora-


Table 1 Copolymerisation of CO and C₂H₄ results

Entry	Ligand ^a	Yield/g	Rate ^b / g Pd ^{−1} h ^{−1}	Half-life ^b / min	<i>M</i> _w	<i>M</i> _n	PDI	C ₃ H ₆ incorp. (%)
1	3a^d	0.2	^c	^c	58 000	24 000	2.4	6.0
2	3b^d	1.5	1 029	44	81 000	31 000	2.6	6.0
3	3c^d	2.8	2 020	38	78 000	42 000	1.9	6.6
4	3c^d	3.0	2 185	35	71 000	42 000	1.7	6.3
5	3d^d	5.0	2 776	53	98 000	50 000	2.0	6.5
6	3e^d	25.1	9 396	165	278 000	107 000	2.6	5.0
7	3e^e	0.3	^c	^c	17 000	13 000	1.3	7.1
8	5a	0.4	^c	^c	^f	^f	^f	^f
9	5b	12.0	4 800	160	103 000	43 000	2.4	3.6 ^g
10	5c	7.7	3 454	144	282 000	113 000	2.5	3.6 ^g
11	5d	10.4	4 029	152	639 000	179 000	3.6	3.7 ^g
12	5e	17.0	11 517	134	888 000	355 000	2.5	3.7 ^g
13	5e^e	0.2	^c	^c	20 000	9 300	2.1	4.9 ^g

^a Polymerisation conditions: 50 barg C₂H₄/CO, 20.0 g C₃H₆, CH₂Cl₂ diluent, 70 °C for 3 h using B(C₆F₅)₃ promoter (0.2 mmol). Catalyst solution formed *in situ* with Pd(OAc)₂ (0.01 mmol) and ligand (0.01 mmol). ^b Determined by fitting first order curve to cumulative gas uptake profile. ^c Rate too low to be determined. ^d Conditions as above, except [Pd(OAc)₂(ligand)] (0.01 mmol) complex was pre-formed. ^e Conditions as above, except methanol diluent and HBF₄·OMe₂ promoter (0.05 mmol). ^f Only oligomeric products were formed. ^g 12.0 g Propene used.

tion is largely unaffected by ligand structure. However, other aspects of the polymerisations are very sensitive to the structure of the ligand. Generally, polymerisation rate, catalyst stability and polymer molecular weight all increase with increasing steric bulk of the aryl *ortho* substituent (entries 1–6). These effects are very pronounced with the *o*-isopropylphenyl derivative **3e** (entry 6) where, compared with the *o*-ethylphenyl derivative **3d** (entry 5), the productivity has increased 5-fold and the molecular weight has doubled. Polymerisation under the methanolic conditions described by Drent¹ gave only a very low rate (entry 7), showing the importance of the activation method used. Indeed, even dp_{pm} (**3a**) produces polymer under our conditions, albeit in very low yield (entry 1). Derivative **3b** (entry 2), bearing polar methoxy substituents, gives some improvement over the performance of **3a**; however, productivity is less than one third that of the sterically similar *ortho* ethyl compound **3d**.


The correlation between the steric bulk of the *ortho* substituents and the catalytic performance of the 4-membered chelates led us to investigate further the source of this steric activation by carrying out solid state and solution structural studies of model chelates of general structure **4** (M = Pd, X = Cl, OAc; M = Pt, X = Cl). Most enlightening to the catalysis

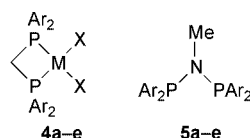

discussed here is the structure of the chelate complex **4e** (M = Pt, X = Cl), a model for the very active catalyst system derived from **3e**. The crystal structure of **4e** was determined (as its dichloromethane solvate) and is shown in Fig. 1.† It shows a flat 4-membered chelate ring with, as a consequence, isoclinal aryl groups, two of which have *ortho*-isopropyl groups orientated so as to block the axial sites at the metal. The NMR spectra for **4e** show that this species is fluxional. The ³¹P NMR spectrum of **4e** in CDCl₃ at +20 °C is a singlet at –64.5 ppm [¹J(PtP), 3130 Hz] but this signal broadens as the temperature is lowered and at –60 °C, there appears to be a 1 : 1 mixture of two species which give rise to an AB pattern [δ_A –65.4, ¹J(PtP_A) 3045 Hz, δ_B –66.1, ¹J(PtP_B) 3337 Hz, ¹J(P_AP_B) 48 Hz] and a singlet [δ_C –68.4, ¹J(PtP) 3195 Hz]. The ¹H NMR signals for the isopropyl groups of **4e** are broad at ambient temperatures and at –60 °C this signal is resolved into overlapping complex multiplets. The ¹H and ³¹P NMR spectra for the parent dp_{pm} complex **4a** (M = Pt, X = Cl) are invariant with temperature and therefore the changes in the NMR spectra with temperature

observed with **4e** are associated with the presence of the bulky *ortho* substituents. Thus we tentatively assign the fluxionality of **4e** to interconversion of symmetrical and unsymmetrical rotamers arising from restricted rotation around the aryl–P bond.

The success of bulky diarylphosphinomethane ligands prompted us to investigate other one-atom backbone diphosphines in which similar steric effects may be observed. Amino-bridged diphosphines offered such a suitably versatile ligand architecture. Although the chemistry of the simple ligands based on this structural motif has been studied,⁸ the synthesis of bulky derivatives **5b–e** and their use in catalysis has not been explored. The methylamino-bridged diphosphines (**5a–e**) were made according to eqn. (3) and fully characterised.



The palladium(II) complexes of ligands **5a–e** were tested for polymerisation activity as before (entries 8–13) and the results largely parallel those obtained with (**3a–e**). Thus, polymerisation rate, catalyst stability and polymer molecular weight all increase with increasing steric bulk of the aryl *ortho* substituent (entries 8–13) and methanolic conditions give only very low activity (entry 13). In this case, the *ortho*-methoxy derivative **5b** (entry 9) shows comparable productivity to the ethyl derivative **5d**, albeit to give a lower molecular weight material. The N₁-backbone chelates are consistently superior to their C₁-backbone analogues and the polymerisation rate of the most active catalyst in this family, **5e**, exceeds that of even dp_{ppp} (**1a**) under our conditions.⁶ The molecular weight of the polymer produced by this system is also extremely high compared with other polyketone catalysts.^{1,3,6}

Our studies have shown that 4-membered palladium(II) diphosphine chelates, hitherto considered to be inefficient polyketone catalysts, are in fact very active when sterically demanding derivatives are used.

Notes and references

† Crystal data for **4b**·CH₂Cl₂: C₃₈H₄₈Cl₄P₂Pt, *M* = 903.59, monoclinic, space group *P*₂₁/*c* (no. 14), *a* = 12.942(2), *b* = 12.338(2), *c* = 23.711(7) Å, β = 98.64(2)°, *U* = 3743.1(15) Å³, *Z* = 4, μ = 4.146 mm^{–1}, *T* = 173 K, 8581 unique data, *R*₁ = 0.0220.

CCDC 155957. See <http://www.rsc.org/suppdata/cc/b0/b010063n/> for crystallographic files in .cif or other electronic format.

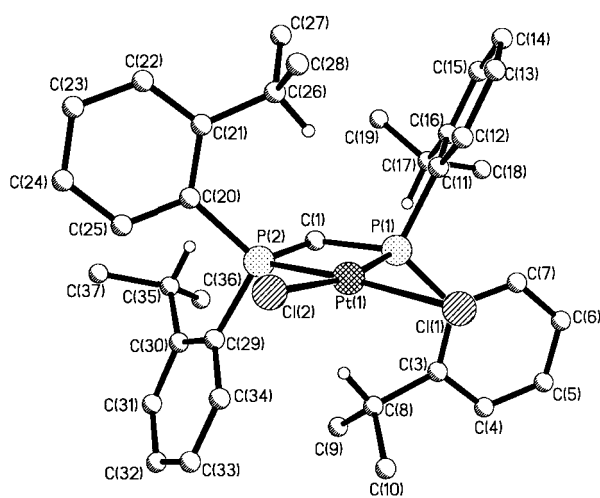


Fig. 1 Molecular structure and numbering scheme for **4b**. All but tertiary isopropyl hydrogen atoms have been omitted for clarity. Important molecular bond lengths (Å) and angles (°): Pt(1)–P(1) 2.2301(9), Pt(1)–P(2) 2.2202(9), Pt(1)–Cl(1) 2.3627(9), Pt(1)–Cl(2) 2.3465(9); P(1)–Pt(1)–P(2) 75.96(3), P(1)–C(1)–P(2) 94.54(13).

- 1 E. Drent and P. H. M. Budzelaar, *Chem. Rev.*, 1996, **96**, 663 and references therein; E. Drent, J. A. M. vanBroekhoven and P. H. M. Budzelaar, *Recl. Trav. Chim.*, 1996, **115**, 263; W. P. Mul, H. Oosterbeek, G. A. Beitel, G. J. Kramer and E. Drent, *Angew. Chem., Int. Ed.*, 2000, **39**, 1848; E. Drent, *Eur. Pat. Appl.*, 1984, EP121965 (to Shell).
- 2 S. Doherty, G. R. Eastham, R. P. Toozee, T. H. Scanlan, D. Williams, M. R. J. Elsegood and W. Clegg, *Organometallics*, 1999, **18**, 3558; B. Milani and G. Mestroni, *Comments on Inorg. Chem.*, 1999, **20**, 301; K. Nozaki, T. Hiyama, S. Kacker and I. T. Horvath, *Organometallics*, 2000, **19**, 2031; C. Gambs, S. Chaloupka, G. Consiglio and A. Togni, *Angew. Chem., Int. Ed.*, 2000, **39**, 2486; K. Vrieze, J. H. Groen, J. G. P. Delis, C. J. Elsevier and P. W. N. M. vanLeeuwen, *New. J. Chem.*, 1997, **21**, 807.
- 3 J. A. M. van Broekhoven and R. L. Wife, *Eur. Pat. Appl.*, 1988, EP257663 (to Shell).
- 4 P. W. N. M. van Leeuwen and P. Diekes, *J. Chem. Soc., Dalton Trans.*, 1999, 1519.
- 5 For first disclosure of these catalysts see: S. J. Dossett, *World Pat. Appl.*, 1997, 97/37765 (to BP Chemicals); S. J. Dossett, *World Pat. Appl.*, 2000, 00/06299 (to BP Chemicals); S. J. Dossett, J. S. Fleming and P. G. Pringle, *World Pat. Appl.*, 2000, 00/03803 (to BP Chemicals).
- 6 G. K. Barlow, J. D. Boyle, N. A. Cooley, T. Ghaffar and D. F. Wass, *Organometallics*, 2000, **19**, 1470 and references therein.
- 7 S. Heitkamp, H. Sommer and O. Stelzer, *Inorg. Synth.*, 1989, **27**, 120.
- 8 M. S. Balakrishna, V. Sreenivasa Reddy, S. S. Krishnamurthy, J. F. Nixon and J. C. T. R. Burkett, *Coord. Chem. Rev.*, 1994, **129**, 1.