



Cite this: *Green Chem.*, 2019, **21**, 6606

Received 6th September 2019,
Accepted 18th November 2019

DOI: 10.1039/c9gc03131f

rsc.li/greenchem

Triphenylamine based conjugated microporous polymers for selective photoreduction of CO₂ to CO under visible light†

Chunhui Dai,^{†a} Lixiang Zhong,^{†b} Xuezhong Gong,^b Lei Zeng,^b Can Xue,^b Shuzhou Li^{*b} and Bin Liu^{*a}

Organic π -conjugated polymers (CPs) have been intensively explored for a variety of critical photocatalytic applications in the past few years. Nevertheless, CPs for efficient CO₂ photoreduction have been rarely reported, which is mainly due to the lack of suitable polymers with sufficient solar light harvesting ability, appropriate energy level alignment and good activity and selectivity in multi-electron-transfer photoreduction of CO₂ reaction. We report here the rational design and synthesis of two novel triphenylamine (TPA) based conjugated microporous polymers (CMPs), which can efficiently catalyze the reduction of CO₂ to CO using water vapor as an electron donor under ambient conditions without adding any co-catalyst. Nearly 100% selectivity and a high CO production rate of 37.15 $\mu\text{mol h}^{-1} \text{g}^{-1}$ are obtained for OXD-TPA, which is significantly better than that for BP-TPA (0.9 $\mu\text{mol h}^{-1} \text{g}^{-1}$) as a result of co-monomer change from biphenyl to 2,5-diphenyl-1,3,4-oxadiazole. This difference could be mainly ascribed to the synergistic effect of a decreased optical band gap, improved interface charge transfer and increased CO₂ uptake for OXD-TPA. This contribution is expected to spur further interest in the rational design of porous conjugated polymers for CO₂ photoreduction.

For the past few decades, artificial photocatalysis has been well established as a sustainable technology for CO₂ conversion into carbonaceous chemical fuels such as CO, CH₃OH, CH₄, *etc.*^{1–6} The technology is particularly appealing as it not only holds great promise to handle environmental issue caused by excess CO₂ release, but also provides fuels for energy supply. However, high energy input is required for CO₂ transformation owing to its remarkable stability with the dissociation energy of C=O bond up to 750 kJ mol^{−1},⁶ which

makes it difficult to develop efficient photocatalysts. Since the pioneering report of heterogeneous CO₂ photoreduction using TiO₂ as the catalyst,⁷ numerous inorganic semiconductors have been under active exploration. However, most inorganic photocatalysts suffer from limited tunability, potential heavy metal toxicity and wide band gap,^{7–10} which hinder their practical applications and thus require the exploration of alternatives.

Conjugated microporous polymers (CMPs), a subclass of structurally diverse polymeric materials, have many advantages such as permanent porosity, large surface area, strong visible light activity, facile synthesis, tunable optoelectronic properties, and high chemical and thermal stability, making them attractive candidates for a range of applications, such as gas sequestration and separation,^{11–15} heterogeneous catalytic reaction,^{16–20} sensing,^{21,22} and energy storage and conversion.^{23–27} Recent studies have revealed that porous conjugated polymers (CPs) are promising photocatalysts for CO₂ reduction and their photocatalytic activities could be effectively enhanced by rational molecular design. For instance, Liu *et al.* reported photocatalytic CO₂ reduction using a series of pyrene-based porous CPs in a CO₂-saturated ionic liquid, which yielded CO with a rate of 47.37 $\mu\text{mol h}^{-1} \text{g}^{-1}$ and reaction selectivity reached 98.3% (>420 nm).²⁸ By copolymerization between 2,4,6-triphenyl-1,3,5-triazine and different comonomers, the charge separation of the resulting polymers could be improved to give a maximum CO production rate of 18.2 $\mu\text{mol h}^{-1} \text{g}^{-1}$ with 81.6% selectivity in the presence of CoCl₂ and dipyrindyl as the co-catalysts.²⁹ Crystalline covalent organic framework (COF) based CO₂-reduction photocatalysts were reported by Huang *et al.*, in which Re(bpy)(CO)₃Cl was incorporated into the 2D COF to reduce CO₂ using triethanolamine as a sacrificial agent and 98% selectivity was obtained.³⁰ Despite this exciting progress, these CO₂ reduction reactions were carried out in CO₂-saturated liquid media, which required the use of organic electron donors, co-catalysts or ionic liquids, adding cost and complexity. Moreover, the limited solubility of CO₂ in liquid media is unfavorable for

^aDepartment of Chemical and Biomolecular Engineering, National University of Singapore, 4 Engineering Drive 4, Singapore 117585, Singapore. E-mail: cheliub@nus.edu.sg

^bSchool of Materials Science and Engineering, Nanyang Technological University, 50 Nanyang Avenue, Singapore 639798, Singapore. E-mail: liz@ntu.edu.sg

†Electronic supplementary information (ESI) available: Experimental methods and supporting figures. See DOI: 10.1039/c9gc03131f

‡These authors contributed equally to this work.

achieving high reaction efficiency. By contrast, the reduction reaction performed on a gas–solid interface relies on CO₂ chemisorption and activation by the photocatalysts, which eliminates the need for liquid media. This simple and environmentally-friendly approach uses only a trace amount of water vapor as the electron donor, which significantly inhibits the competing process of water reduction and favors the selectivity of CO₂ reduction.^{1,3} However, to the best of our knowledge, the exploration of efficient polymers for CO₂ reduction on a gas–solid system remains a great challenge.³¹ Very recently, Eosin Y-based conjugated porous polymers were developed for CO₂ photoreduction, which resulted in a CO production rate of 33 $\mu\text{mol h}^{-1} \text{g}^{-1}$ with 92% selectivity.³¹ To achieve better photocatalytic performance, new polymers and useful molecular design strategies to reveal the critical parameters that control their photoactivities are highly desirable.

In this study, we present two specially designed CMPs as visible-light-active photocatalysts for the reduction of CO₂ to CO only in the presence of water vapor under ambient conditions. The polymer structures are shown in Scheme 1. Triphenylamine (TPA) based CMPs were developed owing to their inherent advantages of high surface area for effective CO₂ absorption, facile preparation, and fine optimization of energy levels.^{32,33} The optical band gaps of the as-prepared CMPs could be tuned from 2.38 to 2.22 eV by replacing biphenyl (BP) with 2,5-diphenyl-1,3,4-oxadiazole (OXD). More importantly, the CO production rate could be enhanced to 37.15 $\mu\text{mol h}^{-1} \text{g}^{-1}$ with $\sim 100\%$ selectivity under visible light irradiation ($>420 \text{ nm}$). In addition, we provide a comprehensive understanding of the photocatalytic activity of polymers by complementary experimental and computational studies, which is critical for future development of conjugated polymers for CO₂ photoreduction.

The synthetic details and characterization of the monomers and conjugated microporous polymers are given in the ESI.† Tris(4-ethynylphenyl)amine was prepared by the Pd(II)-catalyzed coupling of tris(4-bromophenyl)amine and ethynyltrimethylsilane and subsequent deprotection promoted by K₂CO₃.³⁴ Starting from 4-bromobenzoyl chloride, 2,5-bis(4-bro-

mophenyl)-1,3,4-oxadiazole was obtained in three high yielding steps as depicted in Scheme S1.† A condensation reaction between 4-bromobenzoyl chloride and hydrazine hydrate afforded 1,2-bis(4-bromobenzoyl)hydrazide, followed by cyclodehydration to give 2,5-bis(4-bromophenyl)-1,3,4-oxadiazole in 71% yield.³⁵ BP-TPA and OXD-TPA were synthesized from tris(4-ethynylphenyl)amine with 4,4'-dibromodiphenyl and 2,5-diphenyl-1,3,4-oxadiazole, respectively, by the Sonogashira coupling reaction in an Et₃N/DMF (1:1, v/v) mixture with Pd(PPh₃)₄ and CuI as catalysts. The resulting product was successively washed with water, acetone and methanol followed by Soxhlet extraction (THF and then CH₂Cl₂). BP-TPA and OXD-TPA are insoluble in all common solvents such as DMF, THF and CH₂Cl₂. The structural characterization of the two polymers was studied by solid-state ¹³C NMR spectroscopy, FT-IR spectroscopy, and elemental analysis. Both polymers show aromatic peaks at 120–150 ppm and peaks at $\sim 91 \text{ ppm}$ for quaternary alkynes (Fig. S1 and S2†), consistent with the CMPs synthesized by the Sonogashira polymerization.³⁴ In addition, the peak at 163 ppm in the NMR spectrum of OXD-TPA is ascribed to the carbon atom of oxadiazole. Fourier-transform infrared (FT-IR) spectra analysis confirmed the alkynyl linker of the two polymers by the evidence of stretching vibrations of triple bonds appearing around 2200 cm^{-1} (Fig. S3†). BP-TPA and OXD-TPA show similarly spherical morphologies revealed by scanning electron microscopy (SEM) measurement (Fig. S4†). Negligible Pd residual was detected in both polymer networks and the content is 0.34% for BP-TPA and 0.54% for OXD-TPA, respectively. The powder X-ray diffraction (PXRD) patterns demonstrated that both polymers exhibited broad diffraction peaks with low intensities in the wide region, indicative of their amorphous nature (Fig. S6†). Thermal gravimetric analysis (TGA) demonstrated their excellent thermostability with 5% weight loss for BP-TPA and OXD-TPA observed at 463 °C and 412 °C, respectively (Fig. S7†).

The porosity of BP-TPA and OXD-TPA was evaluated by N₂ sorption isotherm measurements at 77 K. As shown in Fig. 1a, both polymer networks give rise to type I isotherms and exhibit a steep increase in the low relative pressure regions (<0.01) due to their microporosity. The apparent BET surface area of BP-TPA is 512 $\text{m}^2 \text{g}^{-1}$, which is lower than that of OXD-TPA (686 $\text{m}^2 \text{g}^{-1}$).



Scheme 1 Chemical structures of the conjugated microporous polymers for CO₂ photoreduction in this study.

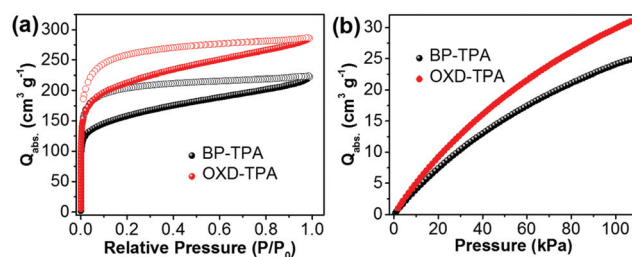


Fig. 1 (a) N₂ sorption isotherm curves of the polymers obtained at 77 K. (b) CO₂ adsorption isotherm curves of the polymers at 298 K.

Both polymers have similar pore size distributions with pore widths at about 1.1, 1.5 and 2.7 nm, respectively (Fig. S5†). The CO₂ uptake capacities of the two polymers at 298 K were evaluated by CO₂ adsorption isotherms. OXD-TPA exhibited a higher volumetric CO₂ uptake than BP-TPA (Fig. 1b). In particular, the difference of CO₂ uptake became more distinct with increasing pressure. At $P = 100$ kPa, the CO₂ uptake capacities of BP-TPA and OXD-TPA were 24.1 and 30.3 cm³ g⁻¹, respectively. The enhanced CO₂ absorbing ability of OXD-TPA compared to BP-TPA is attributed to its higher BET surface area and the dipole-induced electrostatic interactions between the N or O atoms of the oxadiazole unit and the C atoms of CO₂.^{36–38}

The UV/vis diffuse reflectance spectra (DRS) and photoluminescence spectra of BP-TPA and OXD-TPA are displayed in Fig. 2a. OXD-TPA with extended π -conjugation shows broader absorption than BP-TPA. Accordingly, the optical band gaps estimated from the absorption onset of the DRS spectra are 2.38 eV for BP-TPA and 2.22 eV for OXD-TPA. Upon excitation at 380 nm, BP-TPA exhibits emission centered at 562 nm, which is slightly blue-shifted to 557 nm for OXD-TPA. Notably, the emission of OXD-TPA is significantly stronger than that of BP-TPA. This is largely due to the twisted conformation between phenyl and oxadiazole in 2,5-diphenyl-1,3,4-oxadiazole, which interrupts the π -conjugation and molecular stacking, thus blue-shifts the emission and enhances the fluorescence intensity.^{39,40} In addition, time-resolved photoluminescence decay spectra demonstrated a slightly longer fluorescence lifetime of 0.82 ns for OXD-TPA than that of BP-TPA (0.61 ns) (Fig. S8†). The LUMO levels of polymers were evaluated using cyclic voltammetry (Fig. S9†). Both exhibited well-defined reversible reduction waves with the LUMO levels of -0.41 V (vs. NHE) for BP-TPA and -0.44 V (vs. NHE) for

Table 1 Optical and electrochemical properties, BET surface area and CO₂ uptake data of the polymers

| Polymers | E_g^a (eV) | $E_{\text{red, onset}}^b$ (V) | LUMO/ HOMO ^c (V, vs. NHE) | S_{BET} (m ² g ⁻¹) | CO ₂ uptake ^d (cm ³ g ⁻¹) |
|----------|-----------------|-------------------------------|--|---|---|
| BP-TPA | 2.38 | -1.04 | -0.41/1.97 | 2.38 | 24.1 |
| OXD-TPA | 2.22 | -1.07 | -0.44/1.78 | 2.22 | 30.3 |

^a Estimated from the UV/vis diffuse reflectance spectra onset ($E_g = 1240/\lambda_{\text{onset}}$). ^b Versus Fc/Fc⁺ in acetonitrile solution, 50 mV s⁻¹ scan rate. ^c $E_{\text{NHE}} = E_{\text{Fc/Fc}^+} + 0.63$ V, $E_{\text{HOMO}} = E_{\text{LUMO}} - E_g$, opt. ^d At $P = 100$ kPa.

OXD-TPA (Table 1). Accordingly, the HOMO levels of BP-TPA and OXD-TPA were calculated to be 1.97 V and 1.78 V, respectively. The energy band structures of both polymers are well positioned for the reduction of CO₂ to CO, indicating that they are thermodynamically capable of generating CO from CO₂ photoreduction under light irradiation (Fig. 2b).⁴¹ Photoelectrochemical measurements were conducted to compare the photogenerated charge carrier transport of the two polymers. As shown in Fig. 2c, the Nyquist plot of OXD-TPA exhibits a smaller diameter of the semicircular than that of BP-TPA, revealing a decrease of the charge-transfer resistance by replacing biphenyl with 2,5-diphenyl-1,3,4-oxadiazole. The improved photoinduced charge transport can be further supported by an increased transit photocurrent response of OXD-TPA as shown in Fig. 2d, which reveals a visible-light photocurrent of ~ 2 $\mu\text{A cm}^{-2}$ for OXD-TPA and ~ 0.5 $\mu\text{A cm}^{-2}$ for BP-TPA.

The CO₂ photoreduction reactions over the as-synthesized polymers were carried out in the presence of CO₂ and water vapor under ambient conditions. Interestingly, CO was detected as the only reductive product in the photocatalytic system (Fig. S10b†). As shown in Fig. 3a, after the four-hour irradiation of visible light (>420 nm), OXD-TPA produced 148.6 $\mu\text{mol g}^{-1}$ CO, which is much more than that by BP-TPA (3.6 $\mu\text{mol g}^{-1}$). At 420 nm, the quantum efficiencies are about 0% and 0.19% for BP-TPA and OXD-TPA (Fig. S19†), respectively. To the best of our knowledge, the photocatalytic activity of OXD-TPA (37.15 $\mu\text{mol h}^{-1} \text{g}^{-1}$) is much better than that of commonly used g-C₃N₄ and many newly reported CPs under similar conditions (Table S1†).



Fig. 2 (a) UV/vis diffuse reflectance spectra (solid line) and photoluminescence (PL) spectra (dashed lines; $\lambda_{\text{ex}} = 380$ nm) of BP-TPA and OXD-TPA in the solid state. (b) Energy levels of BP-TPA and OXD-TPA relative to the potentials of CO₂ reduction to CO and water oxidation, respectively, vs. the NHE at pH = 0. (c) EIS Nyquist plots and (d) periodic transient photocurrent response of polymer electrodes in 0.5 M Na₂SO₄ aqueous solution.

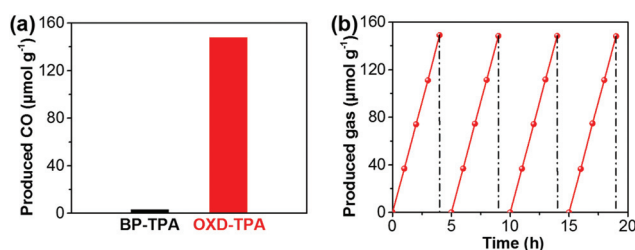


Fig. 3 (a) CO production from the photocatalytic CO₂ reduction over BP-TPA and OXD-TPA after 4 h irradiation (>420 nm). Reaction conditions: 15 mg polymer, CO₂ (1.0 atm), water vapor, room temperature. (b) Time course of photocatalytic CO₂ reduction over OXD-TPA.

To confirm the photocatalytic process, we have performed a series of control experiments. No reductive products were detected under dark conditions. Upon replacing CO₂ with N₂, only a trace amount of CO could be detected, indicating that CO₂ is the reductive agent in the system. When no H₂O is added to the reaction system, negligible CO could be measured, which suggests that H₂O plays an important role as an electron donor. Notably, H₂ and other carbonaceous products, such as CH₄, HCHO, HCOOH, and CH₃OH were not found in our tests, demonstrating that the separated electrons on the surface of the polymer network are almost exclusively used for CO₂ reduction to CO and ~100% selectivity was obtained for OXD-TPA in the photocatalytic reaction.

To study the source of generated CO during the photocatalytic process, an isotopic experiment with ¹³CO₂ (Fig. S11†) was conducted under the same reaction conditions (>420 nm). When ¹²CO₂ was replaced by ¹³CO₂ in the reactor, a gas product with a retention time of 4.026 min was detected, which was different from that of ¹²CO at 3.958 min (Fig. S10b and c†). In addition, after adding concentrated NaOH aqueous solution into the reactor to remove unreacted ¹³CO₂, the gas sample was subsequently analyzed by MS spectrometry and a peak at *m/z* = 29 was found (Fig. S12†), which was assigned to ¹³CO. This peak was not due to the fragmentation of ¹³CO₂ during the MS analysis as the unreacted ¹³CO₂ was completely removed prior to the analysis. Based on all these results, it could be concluded that CO originated from the reduction of CO₂ on OXD-TPA.

The photocatalytic CO₂ reduction stability and recyclability of OXD-TPA was evaluated by four cyclic testing (4 h-irradiation in each run). The photocatalytic reactor was treated under vacuum and then refilled with the mixture of CO₂ and water vapor after each run. Steady CO production is observed over four runs (Fig. 3b). After the photocatalysis experiments, the recycled polymer did not show any significant structural changes (Fig. S13–S15†), indicating that OXD-TPA is highly stable during the photocatalytic process.

DFT calculations were performed to understand the electronic properties of both polymers. The optimized structures are shown in Fig. S16.† The excited electrons for both BP-TPA and OXD-TPA are distributed all over the backbone, whereas the excited holes are mainly localized in TPA due to its strong electron-donating feature (Fig. S17a and S17b†). Moreover, compared to the BP moiety, the more electronegative OXD moiety impairs the density of excited electrons within the TPA part, which decreases the overlap between the excited electrons and holes in OXD-TPA as compared to that of BP-TPA, indicating less recombination of photogenerated charges in OXD-TPA.

We further studied the adsorption energy of COOH*, which is proposed to be the intermediate for CO₂ reduction to CO, on different positions of BP-TPA and OXD-TPA (Fig. 4a and b), and the corresponding adsorption energies are shown in Fig. 4c. The most stable configurations of COOH* are shown in the insert of Fig. 4c and Fig. S17c.† The most stable adsorbed COOH* has similar configurations but the adsorp-

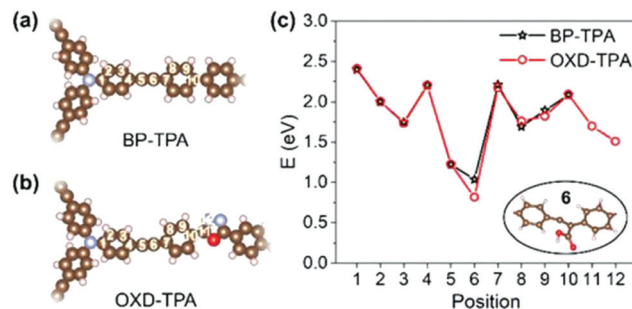


Fig. 4 Different adsorption sites on (a) BP-TPA and (b) OXD-TPA, and (c) the corresponding adsorption energies for COOH*.

tion is ~0.2 eV more stable on OXD-TPA, which facilitates the reduction of CO₂.

DFT calculations revealed that the band gaps for BP-TPA and OXD-TPA are 2.47 and 2.38 eV, respectively, which are in agreement with the optical bandgaps obtained in our experiments (2.38 eV for BP-TPA and 2.22 eV for OXD-TPA as shown in Table 1). Notably, the theoretically predicted HOMOs and LUMOs for BP-TPA and OXD-TPA are depicted in Fig. S18a.† The HOMO potential of BP-TPA (0.79 V) is approximate to the one required for water oxidation (0.82 V, neutral conditions), while it is 0.27 V more positive for OXD-TPA. The LUMO potentials of both BP-TPA (−1.68 V) and OXD-TPA (−1.31 V) are much more negative than the reduction potential of CO₂ to CO (−0.53 V). The results reinforced the sufficient redox ability of the two polymers to trigger the photocatalytic reactions in our system. The possible CO₂ photoreduction process for the polymers is described as follows: the CO₂ gas can be absorbed and activated by the porous polymers. Upon the illumination of visible light, the photogenerated electrons (e[−]) could migrate from the LUMO levels to the HOMO levels of the polymer. Subsequently, the absorbed CO₂ captures electrons on the polymer surface, forming CO and H₂O (CO₂ + 2H⁺ + 2e[−] → CO + H₂O), while the photoinduced holes were utilized for oxidizing water to generate oxygen and hydrogen ions *via* the half-reaction (2H₂O + 4h⁺ → O₂ + 4H⁺) (Fig. S18b†). The low water concentration in the reaction system could efficiently inhibit the competitive reaction to give H₂, CH₃OH, CH₄, *etc.* This is beneficial for the high selectivity of polymers. The much better photocatalytic performance of OXD-TPA could be attributed to its smaller band gap, increased dissociation of photogenerated excitons, and more stable COOH*.

Conclusions

In conclusion, we present the rational design of two novel tri-phenylamine based CMPs for CO₂ photoreduction to CO under visible light irradiation. The CO production rate could be significantly enhanced from 0.9 to 37.15 μmol h^{−1} g^{−1} (>420 nm) with ~100% selectivity, which is much better than the newly reported CPs in similar photocatalytic systems (Table S1†). The enhancement in the photocatalytic activity of

polymers resulting from molecular tuning was fully investigated by experiments and theoretical calculations. Accordingly, we expect that this study will stimulate research interest in designing stable and highly efficient conjugated polymers for CO₂ photoreduction.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We are grateful for financial support from the Singapore National Research Foundation (R279-000-444-281 and R279-000-483-281), the National University of Singapore (R279-000-482-133), the Singapore MOE AcRF-Tier1 (2018-T1-001-072, RG 9/18) and MOE AcRF-Tier2 (MOE2016-T2-2-056).

Notes and references

- J. L. White, M. F. Baruch, J. E. Pander, Y. Hu, I. C. Fortmeyer, J. E. Park, T. Zhang, K. Liao, J. Gu, Y. Yan, T. W. Shaw, E. Abelev and A. B. Bocarsly, *Chem. Rev.*, 2015, **115**, 12888.
- M. Marszewski, S. Cao, J. Yu and M. Jaroniec, *Mater. Horiz.*, 2015, **2**, 261.
- K. Li, B. Peng and T. Peng, *ACS Catal.*, 2016, **6**, 7485.
- R. Shi, G. I. N. Waterhouse and T. Zhang, *Sol. RRL*, 2017, **1**, 1700126.
- J. Ran, M. Jaroniec and S.-Z. Qiao, *Adv. Mater.*, 2018, **30**, 1704649.
- Z. Sun, N. Talreja, H. Tao, J. Texter, M. Muhler, J. Strunk and J. Chen, *Angew. Chem., Int. Ed.*, 2018, **57**, 7610.
- T. Inoue, A. Fujishima, S. Konishi and K. Honda, *Nature*, 1979, **277**, 637.
- A. Dhakshinamoorthy, S. Navalon, A. Corma and H. Garcia, *Energy Environ. Sci.*, 2012, **5**, 9217.
- S. N. Habisreutinger, L. Schmidt-Mende and J. K. Stolarczyk, *Angew. Chem., Int. Ed.*, 2013, **52**, 7372.
- K. Li, B. Peng and T. Peng, *ACS Catal.*, 2016, **6**, 7485.
- A. Li, R. F. Lu, Y. Wang, X. Wang, K. L. Han and W. Q. Deng, *Angew. Chem., Int. Ed.*, 2010, **49**, 3330.
- R. Dawson, E. Stockel, J. R. Holst, D. J. Adams and A. I. Cooper, *Energy Environ. Sci.*, 2011, **4**, 4239.
- Q. Chen, M. Luo, P. Hammershøj, D. Zhou, Y. Han, B. W. Laursen, C.-G. Yan and B.-H. Han, *J. Am. Chem. Soc.*, 2012, **134**, 6084.
- Y. H. Xu, S. B. Jin, H. Xu, A. Nagai and D. L. Jiang, *Chem. Soc. Rev.*, 2013, **42**, 8012.
- Y. Yuan, H. Huang, L. Chen and Y. Chen, *Macromolecules*, 2017, **50**, 4993.
- L. Chen, Y. Yang, Z. Guo and D. Jiang, *Adv. Mater.*, 2011, **23**, 3149.
- K. Zhang, D. Kopetzki, P. H. Seeberger, M. Antonietti and F. Vilela, *Angew. Chem., Int. Ed.*, 2013, **52**, 1432.
- Z. J. Wang, S. Ghasimi, K. Landfester and K. A. I. Zhang, *Adv. Mater.*, 2015, **27**, 6265.
- Y.-B. Zhou, Y.-Q. Wang, L.-C. Ning, Z.-C. Ding, W.-L. Wang, C.-K. Ding, R.-H. Li, J.-J. Chen, X. Lu, Y.-J. Ding and Z.-P. Zhan, *J. Am. Chem. Soc.*, 2017, **139**, 3966.
- R. Li, J. Byun, W. Huang, C. Ayed, L. Wang and K. A. I. Zhang, *ACS Catal.*, 2018, **8**, 4735.
- X. Liu, Y. Xu and D. Jiang, *J. Am. Chem. Soc.*, 2012, **134**, 8738.
- C. Gu, N. Huang, J. Gao, F. Xu, Y. Xu and D. Jiang, *Angew. Chem., Int. Ed.*, 2014, **53**, 4850.
- Y. Kou, Y. Xu, Z. Guo and D. Jiang, *Angew. Chem., Int. Ed.*, 2011, **50**, 8753.
- F. Vilela, K. Zhang and M. Antonietti, *Energy Environ. Sci.*, 2012, **5**, 7819.
- C. Gu, N. Huang, Y. Chen, L. Qin, H. Xu, S. Zhang, F. Li, Y. Ma and D. Jiang, *Angew. Chem., Int. Ed.*, 2015, **54**, 13594.
- C. Zhang, Y. He, P. Mu, X. Wang, Q. He, Y. Chen, J. Zeng, F. Wang, Y. Xu and J.-X. Jiang, *Adv. Funct. Mater.*, 2018, **28**, 1705432.
- J. Zhu, C. Yang, C. Lu, F. Zhang and Z. Yuan, *Acc. Chem. Res.*, 2018, **51**, 3191.
- Y. Chen, G. Ji, S. Guo, B. Yu, Y. Zhao, Y. Wu, H. Zhang, Z. Liu, B. Han and Z. Liu, *Green Chem.*, 2017, **19**, 5777.
- C. Yang, W. Huang, L. C. da Silva, K. A. I. Zhang and X. Wang, *Chem. – Eur. J.*, 2018, **24**, 17454.
- S. Yang, W. Hu, X. Zhang, P. He, B. Pattengale, C. Liu, M. Cendejas, I. Hermans, X. Zhang, J. Zhang and J. Huang, *J. Am. Chem. Soc.*, 2018, **140**, 14614.
- X. Yu, Z. Yang, B. Qiu, S. Guo, P. Yang, B. Yu, H. Zhang, Y. Zhao, X. Yang, B. Han and Z. Liu, *Angew. Chem., Int. Ed.*, 2019, **58**, 632.
- T. Geng, Z. Zhu, W. Zhang and Y. Wang, *J. Mater. Chem. A*, 2017, **5**, 7612.
- Z. Chen, W. Li, Y. Dai, N. Xu, C. Su, J. Liu and C. Zhang, *Electrochim. Acta*, 2018, **286**, 187.
- Z. Xie, Y. Wei, X. Zhao, Y. Li, S. Ding and L. Chen, *Mater. Chem. Front.*, 2017, **1**, 867.
- W.-Y. Wong and Y.-H. Guo, *J. Mol. Struct.*, 2008, **890**, 150.
- M. Saleh, H. M. Lee, K. C. Kemp and K. S. Kim, *ACS Appl. Mater. Interfaces*, 2014, **6**, 7325.
- S. Hug, L. Stegbauer, H. Oh, M. Hirscher and B. V. Lotsch, *Chem. Mater.*, 2015, **27**, 8001.
- K. Yuan, C. Liu, L. Zong, G. Yu, S. Cheng, J. Wang, Z. Weng and X. Jian, *ACS Appl. Mater. Interfaces*, 2017, **9**, 13201.
- C. Wang, L.-O. Pålsson, A. S. Batsanov and M. R. Bryce, *J. Am. Chem. Soc.*, 2006, **128**, 3789.
- Y. Tao, Q. Wang, C. Yang, C. Zhong, K. Zhang, J. Qin and D. Ma, *Adv. Funct. Mater.*, 2010, **20**, 304.
- W. Fan, Q. Zhang and Y. Wang, *Phys. Chem. Chem. Phys.*, 2013, **15**, 2632.