

Synthesis and Characterization of CeO₂ Nanoparticles via Solution Combustion Method for Photocatalytic and Antibacterial Activity Studies

Thammadihalli Nanjundaiah Ravishankar,^[a] Thippeswamy Ramakrishnappa,^{*,[a]} Ganganagappa Nagaraju,^{*,[b]} and Hanumanaika Rajanaika^[c]

CeO₂ nanoparticles have been proven to be competent photocatalysts for environmental applications because of their strong redox ability, nontoxicity, long-term stability, and low cost. We have synthesized CeO₂ nanoparticles via solution combustion method using ceric ammonium nitrate as an oxidizer and ethylenediaminetetraacetic acid (EDTA) as fuel at 450 °C. These nanoparticles exhibit good photocatalytic degradation and antibacterial activity. The obtained product was characterized by various techniques. X-ray diffraction data confirms a cerianite structure: a cubic phase CeO₂ having crystallite size of 35 nm. The infrared spectrum shows a strong band below 700 cm⁻¹ due to the Ce–O–Ce stretching vibrations.

The UV/Vis spectrum shows maximum absorption at 302 nm. The photoluminescence spectrum shows characteristic peaks of CeO₂ nanoparticles. Scanning electron microscopy (SEM) images clearly show the presence of a porous network with a lot of voids. From transmission electron microscopy (TEM) images, it is clear that the particles are almost spherical, and the average size of the nanoparticles is found to be 42 nm. CeO₂ nanoparticles exhibit photocatalytic activity against trypan blue at pH 10 in UV light, and the reaction follows pseudo first-order kinetics. Finally, CeO₂ nanoparticles also reduce Cr^{VI} to Cr^{III} and show antibacterial activity against *Pseudomonas aeruginosa*.

1. Introduction

CeO₂ nanoparticles are interesting due to their wide variety of applications in polishing agents, sunscreens, solid electrolytes, solar cells, fuel cells, phosphorescent/luminescent materials, photocatalysis, sensors, oxygen pumps, and metallurgy.^[1] These applications take advantage of cerium's high thermodynamic affinity for oxygen and sulfur, its potential redox chemistry involving Ce^{III}/Ce^{IV} and the unique and useful absorption/excitation energy bands associated with its electronic structure.^[2] Cerium is a lanthanide series rare earth element and exists as a free metal or oscillates between the Ce^{III} and Ce^{IV} oxidation states. Nanoceria (cerium oxide nanoparticles) also hop between Ce^{III} and Ce^{IV} valence states and they contain oxygen vacancies that allow the nanoparticles to act as regenerative catalysts.^[3]

Dyes from textile, paper, and other industries are prime examples of environmental contaminants. Nowadays, the presence of pollutant organic dyes in wastewater has become a serious problem.^[4,5] Among these dyes, trypan blue is one of the most widely used dye in these industries. Trypan blue, an azo dye reported as a carcinogen,^[6] creates several environmental problems by releasing highly toxic molecules into bodies of water. It has a highly stable complex structure. Thus, there is a need for an efficient and economical method for the degradation of such highly photostable compounds.^[7,8,9] Various techniques available for the complete removal of toxic dyes present in wastewater can be subdivided into four main groups: 1) physical techniques, 2) chemical/photocatalytic degradation of dyes, 3) electrochemical techniques, and 4) biological processes.^[10] Among these methods, photocatalytic degradation of dyes using UV light is one of the most prominent techniques because the reactions are carried out under ambient conditions that are cost-effective and simple.^[11,12] Various photocatalysts like TiO₂, ZnO, WO₃, CeO₂, and ZrO₂ nanoparticles are used for degradation of organic dyes.^[13,14] Out of these catalysts, CeO₂ nanoparticles have been proven to be competent photocatalysts for environmental applications because of their strong redox ability, nontoxicity, long-term stability, and low cost.^[15] Various methods available to prepare CeO₂ nanoparticles include hydrothermal, solvothermal, coprecipitation, sol-gel, solution combustion, and sonochemical methods.^[16,17] Solution combustion synthesis has an edge over other methods as it is considered simple, instantaneous, single-step, and energy saving.^[18] Here we report the synthesis of CeO₂ nano-

[a] T. N. Ravishankar, T. Ramakrishnappa
Centre for Nano and Material Sciences, Jain University
Jakkasandra, Kanakapura (India)
E-mail: t.ramakrishnappa@jainuniversity.ac.in

[b] G. Nagaraju
Department of Chemistry, Siddaganga Institute of Technology
Tumkur, Karnataka (India)
E-mail: nagarajugn@rediffmail.com

[c] H. Rajanaika
Department of Studies and Research in Environmental Science
Tumkur University, Tumkur, Karnataka (India)

© 2014 The Authors. Published by Wiley-VCH Verlag GmbH & Co. KGaA. This is an open access article under the terms of the Creative Commons Attribution-NonCommercial License, which permits use, distribution and reproduction in any medium, provided the original work is properly cited and is not used for commercial purposes.

particles using ceric ammonium nitrate as an oxidizer and ethylenediaminetetraacetic acid (EDTA) as a fuel for the first time. EDTA is used as fuel because it is nontoxic, cheap, and rich in carbon, nitrogen, hydrogen, and oxygen which are released as their corresponding oxides during combustion. The release of these gases leads to the formation of highly porous CeO₂ nanoparticles with a greater surface area. This paper focuses on the applications of these CeO₂ nanoparticles in the photo-degradation of trypan blue, antimicrobial activity, and reduction of Cr^{VI} to Cr^{III}.

2. Results and Discussion

2.1 X-ray diffraction

Figure 1a shows the X-ray diffraction (XRD) pattern of CeO₂ nanoparticles synthesized by solution combustion method. XRD was used to check the purity and crystallinity of the nanocrystals. All the diffraction peaks of CeO₂ are indexed to cerianite-(Ce): syn structure with cubic phase, lattice points $a=b=c=5.41134\text{ \AA}$, space group: Fm-3m (no. 225) and Joint Committee on Powder Diffraction Standards (JCPDS) no. 34-394.

The crystallite size calculated from the most intense peaks ($2\theta=28.5^\circ$) by the Scherrer formula was found to be 35 nm.

2.2 Fourier transform infrared (FTIR) and UV/Vis spectroscopy

The FTIR spectrum (Figure 1b) shows a band at $\sim 3480\text{ cm}^{-1}$ which can be indexed to water molecules. The bands from $1200\text{--}2000\text{ cm}^{-1}$ are due to organic moieties. The spectrum exhibits strong bands below 700 cm^{-1} due to the Ce–O–Ce stretching vibrations.

The UV/Vis spectrum of CeO₂ nanoparticles (Figure 1c) shows a maximum absorption at 302 nm corresponding to the band gap of 4.1 eV, which was blue shifted compared to that of bulk material. The optical properties are strongly dependent on the particle size. The origin of blue shift may be due to size effects.^[19]

2.3 Photoluminescence (PL) study

Figure 1d shows the PL spectrum of CeO₂ nanoparticles with an excitation wavelength of 350 nm. It mainly consists of five emission bands: a strong blue emission band at 426 nm (2.9 eV), a strong blue band at 441 nm (2.8 eV), a blue band at

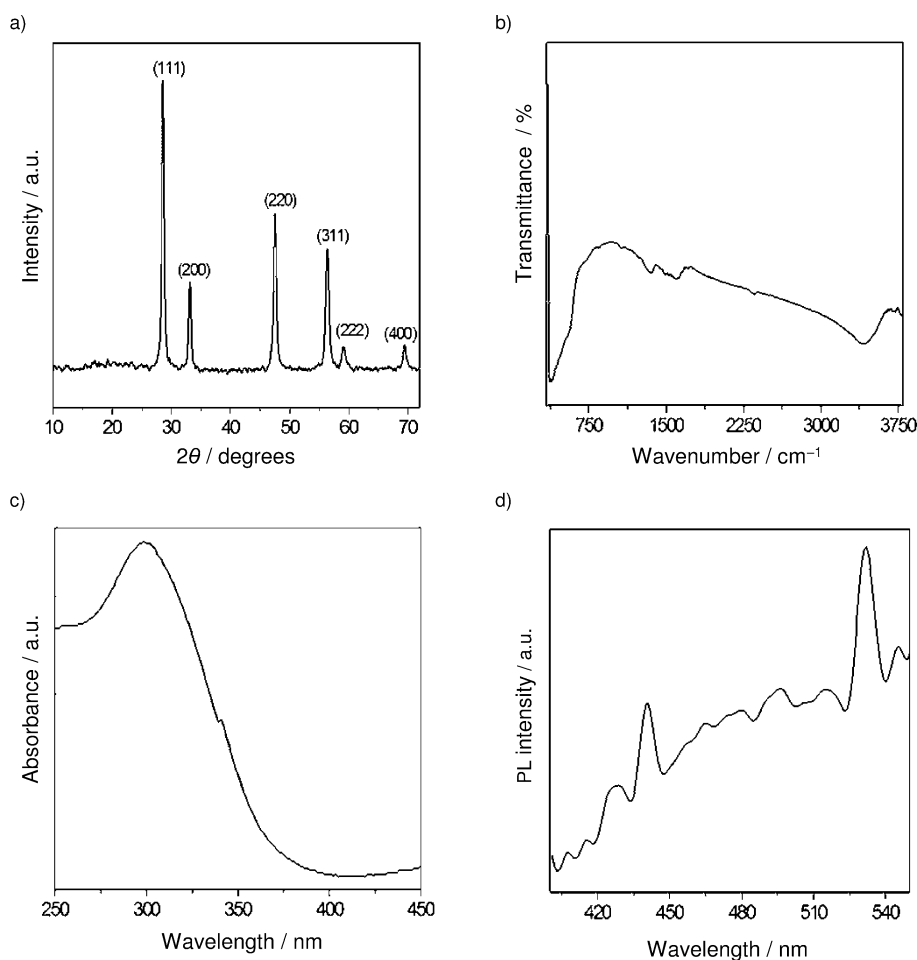


Figure 1. Characterization of CeO₂ nanoparticles prepared via solution combustion method. a) Powder XRD pattern; b) FTIR spectrum; c) UV/Vis spectrum; d) Photoluminescence (PL) spectrum.

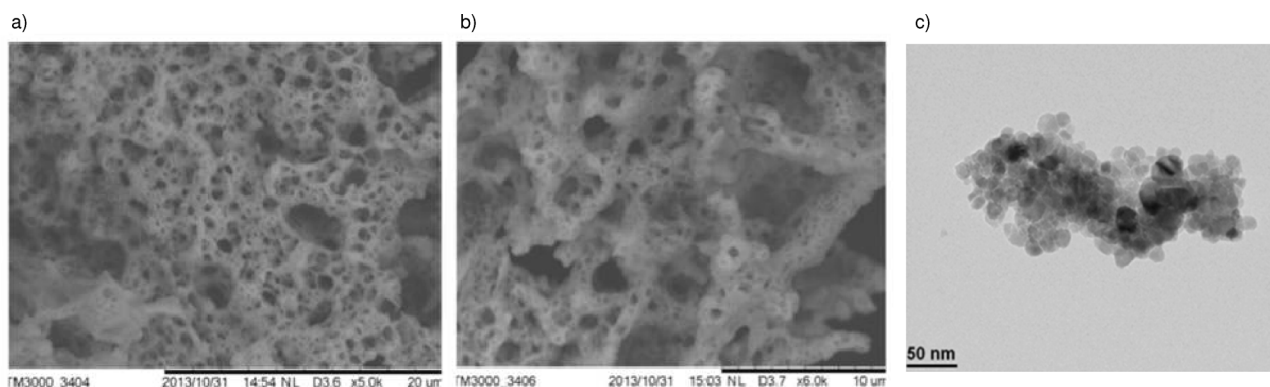


Figure 2. Microscopy images of CeO₂ nanoparticles prepared via solution combustion method. a) SEM image (Scale bar: 20 μm); b) SEM image (Scale bar: 10 μm.); c) TEM image.

466 nm (2.7 eV), a strong blue-green band at 481 nm (2.6 eV), and a green band at 532 nm (2.33 eV). Our results are consistent with that reported for CeO₂ in literature.^[20] Strong emission peaks at 414 nm and 422 nm are observed for CeO₂ nanoparticles. Maensiri et al.^[21] reported a blue band at approximately 443 nm, along with a green band at 529 nm. The blue shift of the PL peak depends on the size of CeO₂ nanoparticles. This phenomenon has been explained by charge transitions from the 4f band to the valence band of the CeO₂ nanoparticles.^[22] In addition, it is well known that the band gap energy between the 4f band, and the valence band of CeO₂ nanoparticles varies from 3.0 to 3.38 eV. It depends on the particle size of CeO₂ nanoparticles and it can be determined from the calculation of the electronic structure of CeO₂.^[23] Therefore, the emission in our CeO₂ samples could be due to the transition from the Ce 4f band to the O 2p band (valence band) in CeO₂. The broad PL band ranging from 410 to 540 nm could be the result of defects, including oxygen vacancies in the crystal with electronic energy levels below the 4f band.^[24] This is confirmed by the enhanced absorption tail below 3 eV in nonstoichiometric CeO₂ that was previously observed and attributed to the presence of oxygen vacancies.^[25]

2.4 Scanning electron microscopy (SEM) and transmission electron microscopy (TEM)

Figures 2a–b show the SEM images of CeO₂ nanoparticles synthesized by the solution combustion method. This type of porous network with lot of voids is typical of combustion-synthesized powders due to escaping gases. The TEM image (Figure 2c) shows that the particles are almost spherical in shape, and the average nanoparticle size is found to be 42 nm. This result resembles the crystallite size calculated using Scherer's formula.

2.5 Surface area and pore diameter

Figure 3 shows the N₂ adsorption–desorption isotherms along with the Barret–Joyner–Halenda (BJH) pore size distribution plot of CeO₂ nanoparticles, and it exhibits a typical IUPAC type

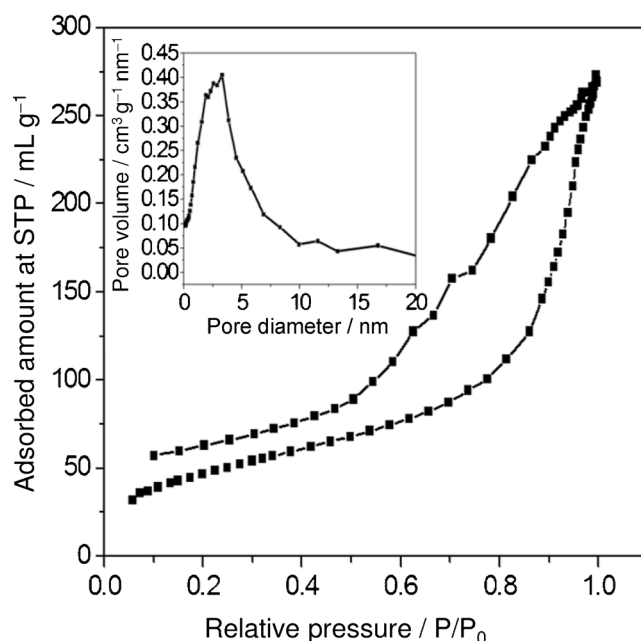


Figure 3. N₂ gas adsorption–desorption isotherm of CeO₂ nanoparticles. Figure insert: pore diameter of CeO₂ nanoparticles prepared via solution combustion method.

IV pattern with the presence of a hysteresis loop. The Brunauer–Emmett–Teller (BET) surface area analysis was found to be 163.5 m² g^{−1} which is higher than the reported values. Ching and co-workers synthesized CeO₂ nanoparticles through the self-assembly of functionalized nanoparticles in a liquid-crystal phase and reported a surface area of 125 m² g^{−1}.^[26] Pan and co-workers explained that the BET surface area greatly influences the catalytic activity. They have also reported the BET surface area of CeO₂ nanorods, nanoparticles, and nanotubes as 52.5, 37.2, and 80.1 m² g^{−1} respectively.^[27] Fang and co-workers reported the BET surface area of bulk CeO₂ (5.67 m² g^{−1}), CeO₂ nanoparticles (30.33 m² g^{−1}), and CeO₂ nanotubes (83.15 m² g^{−1}).^[28] Based on the BJH equation, the main pore size of our CeO₂ nanoparticles is 2.9 nm, as given in the inset of Figure 3.

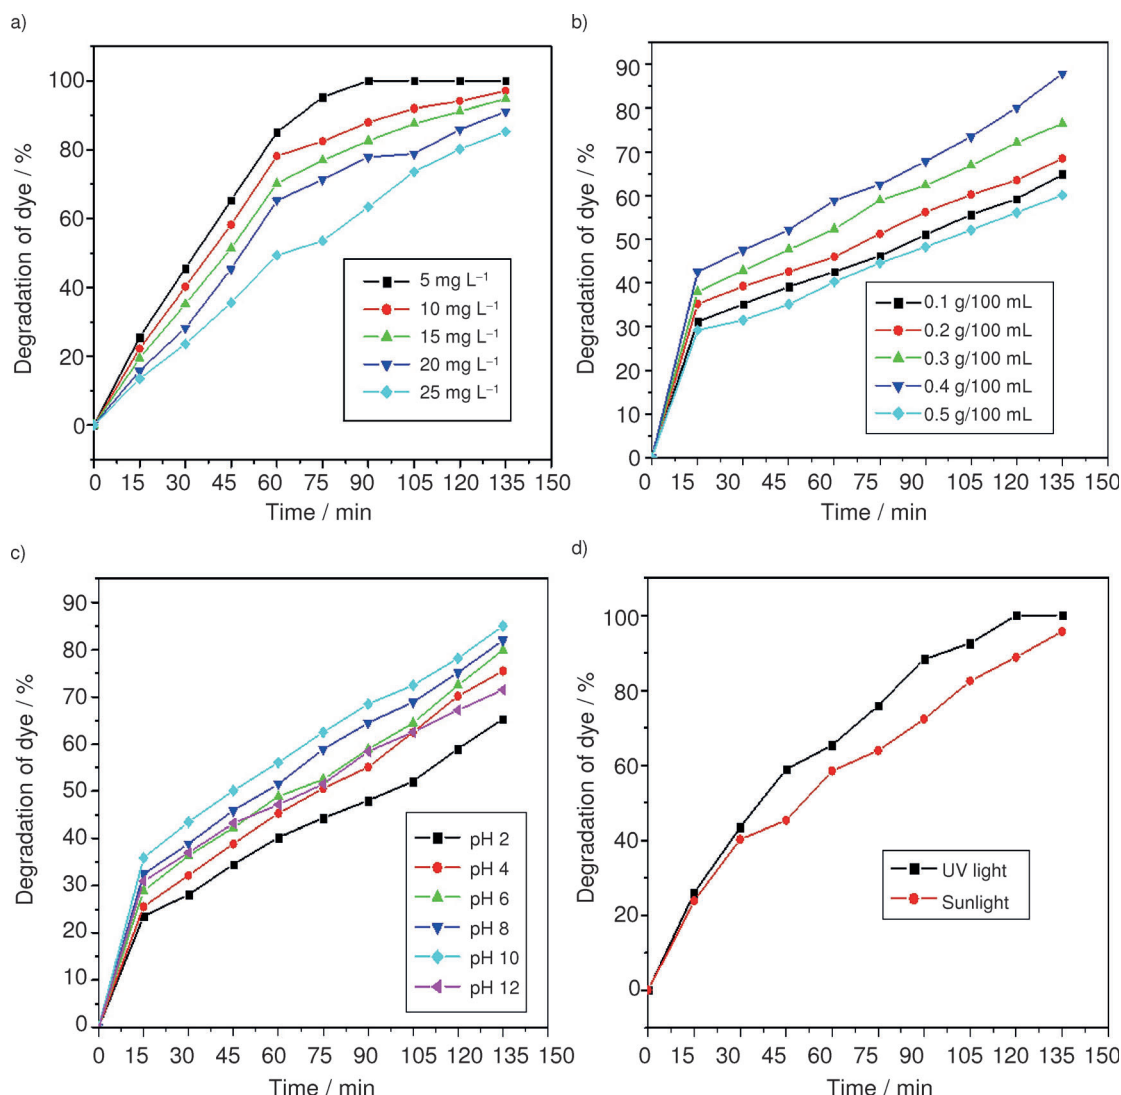


Figure 4. Effect of a) dye concentration, b) catalytic load, c) pH, and d) light source on the photocatalytic activity of CeO₂ nanoparticles.

2.6 Photocatalytic Activity of CeO₂ nanoparticles in UV light

2.6.1 Effect of dye concentration

Figure 4a shows the effect of dye concentration on the photocatalytic activity of CeO₂ nanoparticles. The experimental concentration range of trypan blue was 5–25 mg L⁻¹. Catalytic load was maintained at 0.4 g and pH 10. As the dye concentration increases, the time taken for complete degradation of the dye also increases. When the dye concentration is smaller, many active sites in the photocatalyst lie vacant; hence the slurry remains almost clear, enabling light penetration. Light penetration helps in photodegradation. With an increase in the dye concentration, the active sites get occupied by the dye molecules, and this trend continues until all the sites are fully filled which occurs at a specified optimum concentration. Beyond this concentration, the slurry gets turbid, preventing light penetration resulting in decreased degradation.

2.6.2 Effect of catalyst load




The effect of catalyst load on the photocatalytic degradation of the dye is as shown in Figure 4b. In order to determine the optimal dosage of the catalyst; the catalytic load was varied from 0.1 to 0.5 g/100 mL. The optimal load was found to be 0.4 g/100 mL. Above the optimal load, the turbidity of the slurry increases, light penetration decreases, and thus the availability of hydroxides and superoxides becomes minimal; hence, photocatalytic activity also decreases.

2.6.3 Effect of pH

Figure 4c shows the effect of pH on the photocatalytic degradation of trypan blue. From the figure, it is clear that the photocatalytic process strongly depends on the pH of the dye solution.^[29] The pH of the solution is adjusted by the addition of either 0.1 M NaOH or 0.1 M H₂SO₄. The degradation efficiency is higher in basic than in acidic conditions. This observation agrees well with the reported studies.^[30] The variation of pH

alters the surface properties of CeO_2 , and, in turn, the dissociation of the dye molecules. At pH 10, perhydroxyl radicals (HO_2^\cdot) are formed, leading to the formation of hydrogen peroxide which gives rise to a number of hydroxyl radicals (HO^\cdot).^[30] The highest photocatalytic degradation observed in the case of CeO_2 is at pH 10.

The mechanism of formation of possible radicals is as given below:



2.6.4 Effect of light source on photocatalytic activity

Figure 4d shows the effect of light sources on photocatalytic degradation. Two different light sources are used, namely, sunlight and UV light. From the figure, it is clear that photocatalytic degradation of the dye is greater in UV light than in sunlight. This is due to the fact that UV light has a higher intensity (lower wavelength or higher energy), so it can easily penetrate the slurry, resulting in the formation of more radicals which in turn increases the rate of photocatalytic degradation of the azo dye.

2.6.5 Effect of recyclability of CeO_2 for photocatalytic degradation

Figure 5 shows the effect of recyclability of CeO_2 in the photocatalytic degradation of trypan blue. One of today's key industrial wastewater treatment strategies focuses on the development of green technologies. CeO_2 recycling can be seen as a good practice for sustainable industrial waste treatment. Consequently, it is necessary to demonstrate whether the catalyst can be reused after rounds of photocatalytic treatment. The nanoparticles were recycled for consecutive use in the trypan blue degradation process, which was repeated up to three times. The photocatalytic reaction was carried out at a constant dye concentration (5 mg L^{-1}) and catalytic load (0.4 g/100 mL of CeO_2). These studies indicate that the rate of photodegradation of CeO_2 in the first cycle is higher than the subsequent cycles; this could be due to the aggregation and

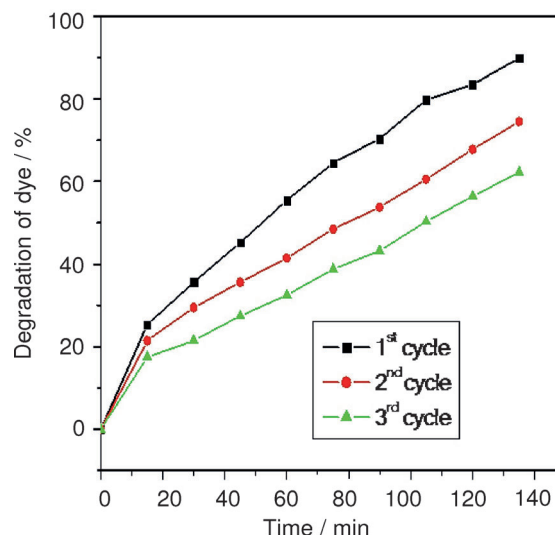


Figure 5. Effect of recyclability of CeO_2 on photocatalytic activity.

sedimentation of the dye around CeO_2 resulting in decreased activity.^[31]

2.6.6 Comparative study of photocatalytic degradation using bulk CeO_2 and nanoparticles

Comparative studies related to the photocatalytic degradation of trypan blue using our prepared CeO_2 nanoparticles and commercially procured bulk CeO_2 are shown in Figure 6. The photocatalytic reaction was carried out at a constant dye concentration (2 mg L^{-1}) and catalytic load (0.2 g/100 mL of CeO_2). From this experiment, it is clear that the photocatalytic activity shown by our CeO_2 nanoparticles is much better than for bulk CeO_2 . This is because size and surface area play major roles in photocatalytic activity.^[26]

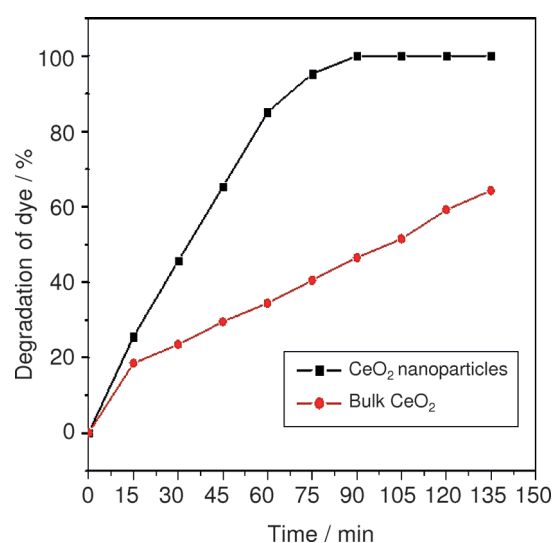


Figure 6. Comparison of the photocatalytic degradation of trypan blue by CeO_2 nanoparticles and bulk CeO_2 .

2.6.7 Kinetics of photocatalytic degradation

The plot of $1 + \log(\text{optical density (O.D.)})$ versus irradiation time is a straight line, as shown in Figure 7. This suggests that the bleaching of dye by CeO_2 follows a pseudo first-order rate law. The rate constant was found to be $3.52 \times 10^{-5} \text{ s}^{-1}$ and was calculated as follows: K (rate constant) = $2.303 \times \text{slope}$, with the following conditions: dye concentration = 10 mg L^{-1} , catalytic dosage = 0.4 g/100 mL , pH 10. The data obtained for the kinetics experiment are shown in Table 1.

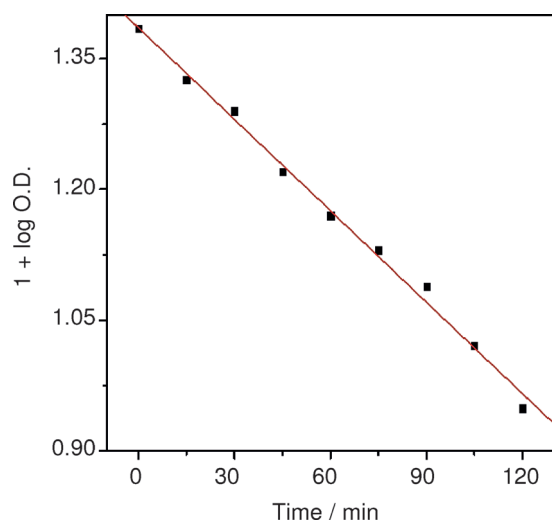


Figure 7. Kinetics of the photocatalytic degradation of trypan blue by CeO_2 nanoparticles.

Table 1. Kinetics of trypan blue dye degradation by CeO_2 . ^[a]		
Time [min]	O.D.	$1 + \log(\text{O.D.})$
0	2.43	1.39
15	2.12	1.33
30	1.95	1.29
45	1.69	1.22
60	1.48	1.17
75	1.35	1.13
90	1.23	1.09
105	1.05	1.03
120	0.89	0.95

[a] Dye concentration = 10 mg L^{-1} , catalytic dosage = 0.4 g/100 mL , pH 10. Measurement of optical density of dye solution at 592 nm.

2.6.8 Reduction of Cr^{VI} to Cr^{III} using CeO_2 nanoparticles

Compared to Cr^{III} , Cr^{VI} is more toxic, leads to adverse effects in the human system, and may cause cancer.^[32] It cannot be directly decomposed by microbes in the environment.^[33] The removal of Cr^{VI} from the environment via chemical or physical adsorption has been previously reported.^[34] The transformation of Cr^{VI} to Cr^{III} decreases its toxicity.^[35] Here we report the photocatalytic degradation of $\text{K}_2\text{Cr}_2\text{O}_7$ ($1 \times 10^{-3} \text{ M}$, pH 3.5) by CeO_2 nanoparticles (0.2 g) upon treatment with UV light for 105 min.



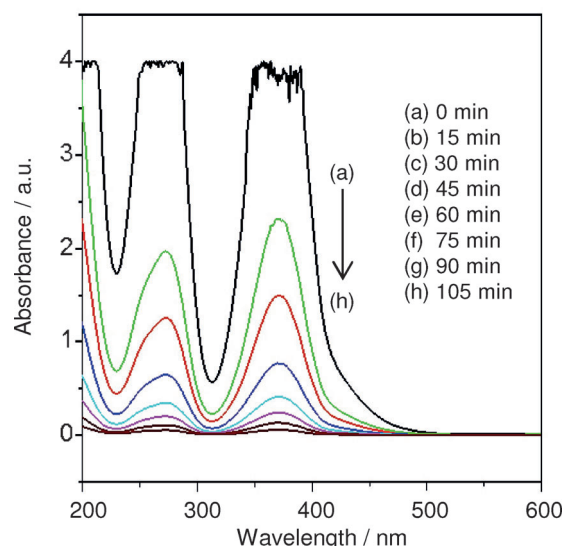


Figure 8. Photochemical reduction of Cr^{VI} to Cr^{III} using CeO_2 nanoparticles.

Degradation was monitored by measuring the sample's absorbance at 372 nm and 273 nm, which decreases gradually, indicating the successful reduction of Cr^{VI} to Cr^{III} as shown in Figure 8.

The possible mechanism of the reduction of Cr^{VI} to Cr^{III} using CeO_2 nanoparticles is shown below.



2.6.9. Detection of hydroxyl radicals

Hydroxyl radicals (HO^\bullet) have been proven to be the major active species during the photocatalytic degradation reaction. The amount of HO^\bullet can be detected by photoluminescence (PL). The rate of formation of HO^\bullet during the photocatalytic degradation reaction could be detected by using a simple, rapid, sensitive PL technique by using coumarin as a standard probe. Coumarin reacts with HO^\bullet to produce highly fluorescent 7-hydroxycoumarin at a signal of $\sim 495 \text{ nm}$ as shown in Figure 9. In this method, catalyst (0.1 g) was dispersed in coumarin taken (50 mL of 10^{-3} M) in a borosil trough. Before irradiation the solution was allowed to attain adsorption-desorption equilibrium. This solution was irradiated with UV light with an intensity of 125 W m^{-2} .^[36] Every 15 min, aliquots were drawn, and the PL intensity was measured at 456 nm. The intensity increased linearly with the irradiation time which indicates that the formation of HO^\bullet at the surface of CeO_2 was proportional to the irradiation time.^[37]

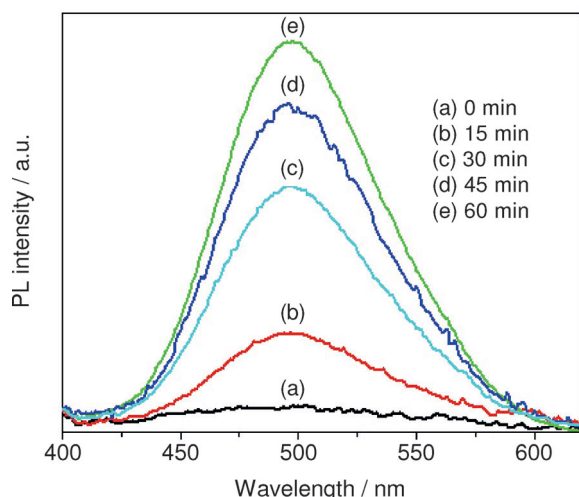


Figure 9. Phospholuminescence (PL) spectra for the detection of hydroxyl radicals.

2.7. Antibacterial activity of CeO₂ nanoparticles

2.7.1 Agar well diffusion method

The stock solution of CeO₂ nanoparticles was prepared by dispersing 2000 µg L⁻¹ in sterile water and making further dilutions. Ciprofloxacin (500 µg L⁻¹ in sterile water) was used as positive control and only sterile water was used as negative control.

CeO₂ nanoparticles were screened using the agar well diffusion method on two different bacterial pathogens: *Pseudomonas aeruginosa* and *Staphylococcus aureus*. We maintained the positive standard's concentration at 10 µg/50 mL, while varying that of CeO₂ nanoparticles from 500 µg/50 mL to 1000 µg/50 mL for both bacterial pathogens. The obtained experimental data (Table 2) clearly show that, as the concentration of CeO₂ nanoparticles increases, the zone of inhibition also increases in the case of *P. aeruginosa*. The other bacterial pathogen, *S. aureus*, did not show a zone of inhibition due to the incomplete dissolution of the compound (Figure 10).

2.7.2 Broth dilution method

In the broth dilution method it is clear that CeO₂ nanoparticles show antibacterial activity towards *P. aeruginosa* (Figure 11). The nanoparticles did not show any activity towards *S. aureus* when they were incubated for 24 h. A possible mechanism is that the nanoparticles facilitate the formation of free radicals

Table 2. Antibacterial activity of CeO ₂ nanoparticles towards <i>P. aeruginosa</i> and <i>S. aureus</i> .			
Group	Treatment	Zone of inhibition (diameter) [mm]	
		<i>P. aeruginosa</i>	<i>S. aureus</i>
I	Ciprofloxacin (10 µg/50 µL)	14.17 ± 0.17	13.17 ± 0.44
II	CeO ₂ (500 µg/50 µL)	3.33 ± 0.33 ^[**]	Not seen
III	CeO ₂ (750 µg/50 µL)	3.57 ± 0.17 ^[*]	Not seen
IV	CeO ₂ (1000 µg/50 µL)	4.50 ± 0.29 ^[**]	Not seen

Values represent the mean ± S.E. for *n* = 3 replicates. [*] *p* < 0.05, [^{**}] *p* < 0.01 as compared with the control group.

that interact with bacteria, resulting in the degradation of the bacterial cell wall and eventual extermination.^[38]

3. Conclusions

This paper reports the synthesis and characterization of CeO₂ nanoparticles via solution combustion method using EDTA as a fuel for the first time. XRD experiments confirm that the obtained product is cerianite, cubic phase CeO₂ with crystallite size 35 nm. FTIR spectrum shows a strong band below 700 cm⁻¹ due to the Ce–O–Ce stretching vibration. The UV/Vis spectrum shows a maximum absorption band at 302 nm. The PL spectrum shows characteristic peaks of CeO₂ nanoparticles. SEM images clearly show a porous network with lots of voids, while TEM images indicate spherical particles; the size of the nanoparticles are found to be 42 nm. BET surface area and pore diameter are found to be 163.5 m² g⁻¹ and 2.9 nm respectively. We have observed that CeO₂ nanoparticles show significant photocatalytic activity leading to the degradation of trypan blue which follows pseudo first-order kinetics. CeO₂ nanoparticles exhibit antibacterial activity against *P. aeruginosa*

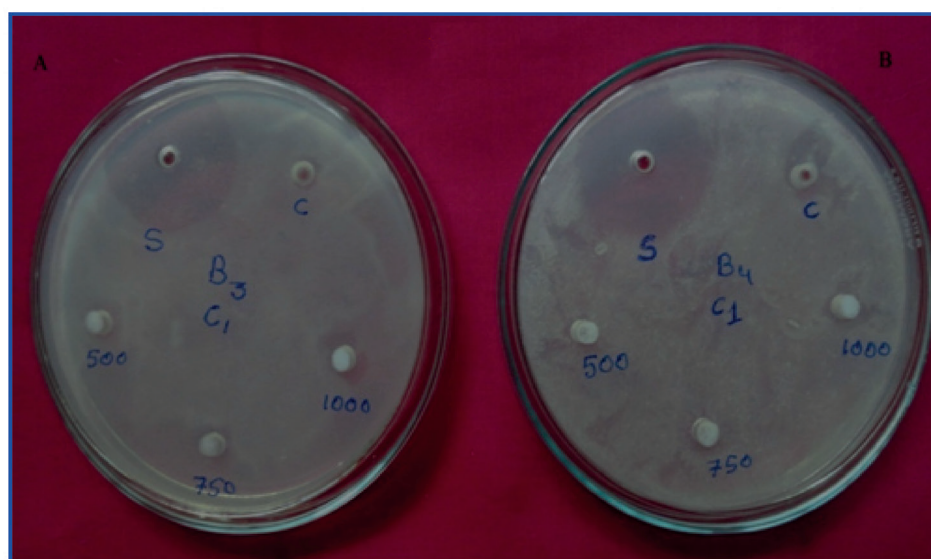


Figure 10. Antibacterial activity of CeO₂ nanoparticles using the agar well diffusion method. A) *P. aeruginosa* with CeO₂ (500, 750, and 1000 µg per 50 µL in well), s: Ciprofloxacin (standard, positive control), c: water (negative control); B) *S. aureus* with CeO₂ (500, 750, and 1000 µg per 50 µL in well).

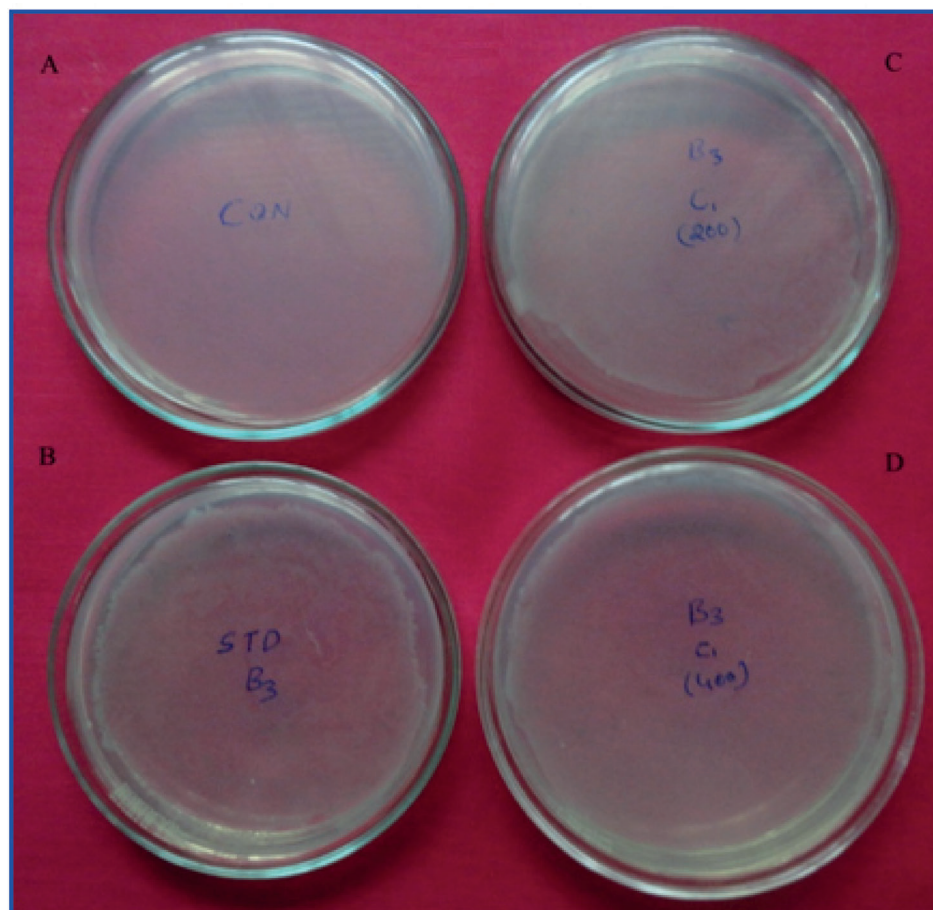



Figure 11. Antibacterial activity of CeO_2 nanoparticles using the broth dilution method. *P. aeruginosa* treated with A) water (negative control); B) Ciprofloxacin (positive control); C) $200 \mu\text{g mL}^{-1}$ CeO_2 ; D) $400 \mu\text{g mL}^{-1}$ CeO_2 nanoparticles.

in both agar well diffusion and broth dilution methods, and it also actively reduces Cr^{VI} to Cr^{III} in UV light at pH 3.5.

4. Experimental Section

4.1. Materials. All the chemicals used for synthesis were of analytical grade. Chemicals like $(\text{NH}_4)_2\text{Ce}(\text{NO}_3)_6$ and EDTA disodium salt were purchased from Merck, India and were used without further purification. Distilled water was used throughout the experiments.

4.2. Preparation of CeO_2 nanoparticles. $(\text{NH}_4)_2\text{Ce}(\text{NO}_3)_6$ and EDTA disodium salt was used as an oxidizer and fuel respectively. To remove the Na^+ ions, EDTA disodium salt (10 mL of 1 M solution) was treated with HCl (5 mL of 2 M), and the reaction is as shown in

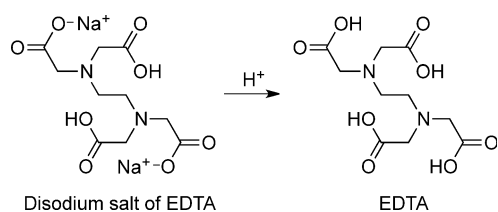

Scheme 1. Conversion of disodium salt of EDTA to pure EDTA.

Scheme 1. The obtained precipitate of EDTA was washed several times with water to remove Na^+ ions present and dried at 80°C for 1 h. The dried EDTA was used as a fuel for the preparation of CeO_2 nanoparticles.

Stoichiometric amounts (1:1) of the oxidizer (2 g) and fuel (0.8 g) were taken in a trough, 10 mL distilled water was added, and the mixture was stirred for 10 min. The homogeneous redox solution was preheated and dehydrated on a hot plate at 150°C . After dehydration, a gel formed, and this was introduced into a preheated muffle furnace maintained at 450°C . Smoldering-type combustion took place, and within 3–4 min, the reaction proceeded to completion, forming nanocrystalline CeO_2 .

4.3. Characterization. Powder XRD data was recorded on an X'pert PRO PANalytical X-ray diffractometer (PANalytical, Almelo, The Netherlands) with graphite-monochromatized $\text{Cu-K}\alpha$ (1.5418 \AA) radiation. The FTIR spectrum of the sample was collected using an Alpha-P IR spectrometer (Bruker, Billerica, USA). The absorption spectrum and reduction spectrum of Cr^{VI} to Cr^{III} were measured on a Lambda-750 UV/Vis spectrometer (PerkinElmer, Waltham, USA). The PL spectrum was measured using

an RF-5301PC spectrofluorophotometer (Shimadzu, Kyoto, Japan). The BET surface area, that is, N_2 adsorption–desorption measurements of the samples were measured using a Tristar II surface area and porosity instrument (Micromeritics, Norcross, USA). The surface morphology was examined using an Ultra 55 SEM (Carl Zeiss, Jena, Germany). TEM was performed on a JEM 1200 Ex microscope (Jeol, Tokyo, Japan) operating at 100 kV.

4.4. Photocatalytic degradation of dye. Photocatalytic experiments were carried out in a $150 \times 75 \text{ mm}$ batch reactor in the month of August 2013 between 12–3 PM, in sunlight (750 W m^{-2} intensity) and in UV light (125 W m^{-2} intensity). An aqueous suspension was prepared by adding a known amount of CeO_2 nanoparticles (0.1–0.5 g) to a given concentration of trypan blue dye solution ($5\text{--}25 \text{ mg L}^{-1}$ in 100 mL). The pH of the solution was adjusted by addition of either 0.1 M NaOH or 0.1 M H_2SO_4 . During the photocatalytic experiments, the slurry was stirred for uniform exposure to light sources. A known volume of the exposed solution (10 mL) was withdrawn at specific intervals of time (15 min), centrifuged (2000 rpm, 15 min) to remove the photocatalyst, and assessed for extent of degradation using a spectrophotometer at 592 nm. Various parameters like effect of nanoparticle concentration, catalytic load, irradiation time, pH, nature of light, and recyclability were also examined. After the completion of the photocatalytic degradation, the catalyst was removed by centrifugation (2000 rpm, 15 min), washed with water, and dried in an air oven at

100 °C for 2 h. This oven-dried catalyst was used for another round of degradation. This procedure was repeated twice, and degradation efficiency was tested each time.

4.5. Antibacterial activity by agar well diffusion method. Antibacterial activity was screened by agar well diffusion method^[39] for bacterial pathogens (*P. aeruginosa* NCIM-2242 and *S. aureus* NCIM-5022). These strains were purchased from National Chemical Laboratory (NCL), Pune, India. Nutrient agar plates were swabbed using sterile L-shaped glass rods with mature broth cultures of the respective bacterial strains incubated for 24 h. By using a sterile cork borer, 6 mm wells were made into the each Petri dish. Various concentrations of CeO₂ in sterile water (500, 750, and 1000 µg L⁻¹ per well,) were used to assess the activity of CeO₂ nanoparticles. Water (negative control) and Ciprofloxacin (positive control, Hi Media, Mumbai, India) were added into the wells by using sterile micropipettes. All the plates were simultaneously incubated at 37 °C for 24 h. After the incubation period, the diameter of the inhibition zones of each well was measured. Each sample was tested in triplicate, and the average values were calculated to determine antibacterial activity.

4.6. Antibacterial activity by broth dilution method. Two concentrations of CeO₂ (200 and 400 µg L⁻¹) were screened for two bacterial strains, namely *P. aeruginosa* NCIM-2242 and *S. aureus* NCIM-5022. In this method, the nanoparticles were dispersed in sterile water to get two different concentrations of the sample solutions. Then, these sample solutions were added into sterile tubes containing nutrient broth. The bacterial suspension (0.1 mL of ~108 CFU/mL) was added into each tube. In addition, positive control tubes, containing same amount of bacteria and nutrient broth, and negative control tubes, containing only nutrient broth, were also prepared. All the tubes were incubated in a reciprocal shaker with a shaking speed of about 200 rpm min⁻¹ at 37 °C for 24 h. The minimum inhibition concentration (MIC) was defined as the minimum concentration at which there is no visible change in the turbidity of the medium. To evaluate the bactericidal efficacy of the samples, each of the bacterial solutions (0.025 mL) with samples (200 and 400 µg L⁻¹) was taken and plated in sterile nutrient agar plates. Then the plates were incubated at 37 °C for another 24 h, and the number of bacterial colonies was counted. The bactericidal rate (K) could be calculated according to Equation 16, where A and B are the number of bacterial colonies corresponding to the positive control group and the sample group, respectively.^[40]

$$K = (A - B)/B \times 100 \% \quad (16)$$

Acknowledgements

T. N. Ravishankar wishes to acknowledge Jain University, India for financial support to carry out the research.

Keywords: antibacterial · cerium oxide · nanoparticles · photocatalysis · solution combustion

- [1] T. Masui, H. Hirai, N. Imanaka, G. Adachi, T. Sakata, H. Mori, *J. Mater. Sci. Lett.* **2002**, 21, 489–491.
[2] W. Lin, Y.-w. Huang, X.-D. Zhou, Y. Ma, *Int. J. Toxicol.* **2006**, 25, 451–457.

- [3] M. C. Arnold, A. R. Badireddy, M. R. Wiesher, R. T. Giulia, J. N. Meyer, *Arch. Environ. Contam. Toxicol.* **2013**, 65, 224–233.
[4] N. Zhang, R. Ciriminna, M. Pagliaro, Y. J. Xu, *Chem. Soc. Rev.* **2014**, 43, 5276–5287.
[5] N. Zhang, Y. J. Xu, *Nanoscale* **2012**, 4, 5792–5813.
[6] L. D. Benefield, F. Judkins, B. L. Weand, *Process Chemistry for Water and Wastewater Treatment*, Prentice-Hall, New Jersey, **1982**, pp. 365–404.
[7] W. Chu, *J. Water. Res.* **2001**, 35, 3147–3152.
[8] M. Q. Yang, Y. J. Xu, *Phys. Chem. Chem. Phys.* **2013**, 15, 19102–19118.
[9] B. Weng, S. Liu, Z. R. Tang, Y. J. Xu, *RSC Adv.* **2014**, 4, 12685–12700.
[10] H. Bader, V. Sturzenegger, J. Hoigné, *J. Water. Res.* **1988**, 22, 1109–1115.
[11] A. Fujishima, N. R. Tata, A. T. Donald, *J. Photochem. Photobiol. C* **2000**, 1, 1–21.
[12] Y. Zhang, Z. R. Tang, X. Fu, Y. J. Xu, *ACS Nano* **2010**, 4, 7303–7314.
[13] N. Zhang, M. Q. Yang, Z. R. Tang, Y. J. Xu, *ACS Nano* **2014**, 8, 623–633.
[14] P. V. Kamat, *Chem. Rev.* **1993**, 93, 267–300.
[15] J. P. Nair, E. Wachtel, I. Lubomirsky, J. Fleig, J. Maier, *Adv. Mater.* **2003**, 15, 2077–2081.
[16] N. Zhang, S. Liu, Y. J. Xu, *Nanoscale* **2012**, 4, 2227–2238.
[17] X. Pan, M. Q. Yang, X. Fu, N. Zhang, Y. J. Xu, *Nanoscale* **2013**, 5, 3601–3614.
[18] B. M. Nagabhushana, R. P. Sreekanth, K. P. Ramesh, C. Shivakumara, G. T. Chandrappa, *J. Mater. Res. Bull.* **2006**, 41, 1735–1746.
[19] V. Ramakrishna, P. Rima, K. M. Apurba, *Nanomater. Nanotechnol.* **2012**, 2, 8:2012.
[20] S. Sathyamurthy, K. J. Leonard, R. T. Dabestani, M. P. Paranthaman, *Nanotechnology* **2005**, 16, 1960.
[21] S. Maensiri, C. Marsingboon, P. Loakul, W. Jareonboon, V. Promarak, P. L. Anderson, *Cryst. Growth Des.* **2007**, 7, 950–955.
[22] F. Gao, G. H. Li, J. H. Zhang, F. G. Qin, Z. Y. Yao, Z. K. Liu, Z. G. Wang, L. Y. Lin, *Chin. Phys. Lett.* **2001**, 18, 443.
[23] A. H. Morshed, M. E. Moussa, S. M. Bedair, R. Leonard, S. X. Liu, N. E. Masry, *Appl. Phys. Lett.* **1997**, 70, 1647–1650.
[24] F. Marabelli, P. Wachter, *Phys. Rev. B* **1987**, 36, 1238–1243.
[25] D. D. Koelling, A. M. Boring, J. H. Wood, *Solid State Commun.* **1983**, 47, 227–232.
[26] J.-Y. Chane-Ching, F. Cobo, D. Aubert, H. G. Harvey, M. Airiau, A. Corma, *Chem. Eur. J.* **2005**, 11, 979–987.
[27] C. Pan, D. Zhang, L. Shi, *J. Solid State Chem.* **2008**, 181, 1298–1306.
[28] J. Fang, Z. Cao, D. Zhang, X. Shen, W. Ding, L. Shi, *J. Rare Earths* **2008**, 26, 153–157.
[29] T. K. Ghorai, *Open. J. Phys. Chem.* **2011**, 1, 28–36.
[30] G. Nagaraju, T. N. Ravishankar, K. Manjunatha, S. Sarkar, H. Nagabhushana, R. Goncalves, R. J. Dupont, *Mater. Lett.* **2013**, 109, 27–30.
[31] E. M. Saggiaro, A. S. Oliveira, T. Pavesi, C. G. Maia, *Molecules* **2011**, 16, 10370–10374.
[32] G. M. Ganea, P. E. Kolic, B. Zahab, I. M. Warner, *Anal. Chem.* **2011**, 83, 2576–2581.
[33] C. E. Barrera-Díaz, V. Lugo-Lugo, B. Bilyeu, *J. Hazard. Mater.* **2012**, 223–224, 1–12.
[34] T. W. Speir, H. A. Kettles, A. Parshotam, *Soil. Bio Biochem.* **1995**, 27, 801–810.
[35] S. J. Park, B. J. Park, S. K. Ryu, *Carbon* **1999**, 37, 1223–1226.
[36] G. Nagaraju, K. Manjunath, T. N. Ravishankar, B. S. Ravikumar, H. Nagabhushan, G. Ebeling, *J. Mater. Sci.* **2013**, 48, 8420–8426.
[37] I. T. Liu, M. H. Hon, L. G. Teoh, *J. Electron. Mater.* **2013**, 42, 2536–2541.
[38] Y. Kuang, X. He, Z. Zhang, Y. Li, H. Zhang, Y. Ma, Z. Wu, Z. Chai, *J. Nano-sci. Nanotechnol.* **2011**, 11, 4103–4108.
[39] R. Gokulakrishnan, S. Ravikumar, R. Anandha, *Asian Pac. J. Trop. Dis.* **2012**, 2, 411–413.
[40] X.-D. Zhou, W. Huebner, H. U. Anderson, *Appl. Phys. Lett.* **2002**, 80, 3814.

Received: August 26, 2014
Revised: November 14, 2014
Published online on ■■■ ■■, 0000

FULL PAPERS


T. N. Ravishankar, T. Ramakrishnappa,*
G. Nagaraju,* H. Rajanaika

■■ – ■■

**Synthesis and Characterization of
CeO₂ Nanoparticles via Solution
Combustion Method for
Photocatalytic and Antibacterial
Activity Studies**

CeO₂ nanoparticles

Photocatalytic degradation of dyes
Antibacterial activity
Detoxification (Cr^{VI} → Cr^{III})

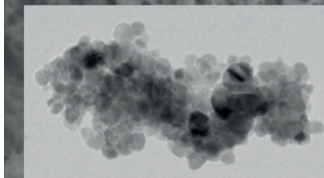

Nanoparticles for the environment:

CeO₂ nanoparticles are competent photocatalysts for environmental applications because of their strong redox ability, nontoxicity, stability, and low cost. We synthesized CeO₂ nanoparticles using a solution combustion method. These show photocatalytic activity in the degradation of trypan blue (a typical pollutant dye), antibacterial activity against *Pseudomonas aeruginosa*, and detoxifying activity as shown in the reduction of Cr^{VI} to Cr^{III}.