



Pergamon

Tetrahedron: Asymmetry 9 (1998) 2019–2022

TETRAHEDRON:
ASYMMETRY

Heterogeneous asymmetric epoxidation of *cis*-allylic alcohols: use of polymer-supported Ti(IV)-catalyst

Jaana K. Karjalainen,^a Osmo E. O. Hormi^{a,*} and David C. Sherrington^b

^aDepartment of Chemistry, University of Oulu, PO Box 333, FIN-90570 Oulu, Finland

^bDepartment of Pure and Applied Chemistry, University of Strathclyde, Thomas Graham Building, 295 Cathedral Street, Glasgow, G1 1XL, Scotland, UK

Received 8 April 1998; accepted 12 May 1998

Abstract

Heterogeneous asymmetric epoxidation of *cis*-allylic alcohols with titanium isopropoxide and *tert*-butyl hydroperoxide has been achieved using a branched/crosslinked poly(tartrate ester) ligand. The enantioselectivities and chemical yields obtained are at least comparable to low molecular weight tartrate ligands. © 1998 Published by Elsevier Science Ltd. All rights reserved.

The asymmetric epoxidation of alkenes is central to many of the recent developments in the stereoselective synthesis of chiral molecules.¹ Our earlier studies have established the advantages of using a polymer-supported Ti(IV)-catalyst in the epoxidation of *trans*-allylic alcohols.^{2–4} In line with our continuing interest in this area, we have now undertaken the investigation of the epoxidation of *cis*-allylic alcohols.


Allylic alcohols having a *cis*-3-substituent are typically the most sluggish of allylic alcohols to be epoxidised.⁵ Using the conventional low molecular weight Sharpless tartrate–titanium isopropoxide system these *cis*-allylic alcohols give variable enantiofacial selectivity.⁶ Nevertheless, asymmetric epoxidation of these substrates is effective and in most cases the enantiomeric purity is at least 80%.

The numerous attractive features of a polymer-supported asymmetric organic synthesis are well recognised. For example the isolation of the chiral product, free of the chiral catalyst or auxiliary, is simplified. In addition many successful chiral catalytic systems are moisture or air-sensitive organometallic species and polymer-supported analogues can be used and be recovered more easily without exposure to water and/or air.⁷

We have previously reported on the synthesis of branched/crosslinked poly(tartrate ester)s and have studied the use of these optically active poly(tartrate ester) ligands in asymmetric epoxidations of *trans*-allylic alcohols with titanium tetrakisopropoxide and *tert*-butyl hydroperoxide.^{3,4} In the present paper

* Corresponding author. E-mail: Osmo.Hormi@oulu.fi

The branched/crosslinked polyester **3** was prepared by condensation polymerisation of L-(+)-tartaric acid and 1,8-octanediol as shown in Scheme 1.³ The degree of branching/crosslinking was determined as described before by ¹H NMR.⁴ We have previously pointed out that a high level of branching/crosslinking of the polymer ligand inhibits the enantioselective epoxidation of *trans*-allylic alcohols.⁴ Accordingly we have now used poly(tartrate ester)s having a degree of branching of 10%, 14% and \gg 15% in epoxidations of *cis*-allylic alcohols.

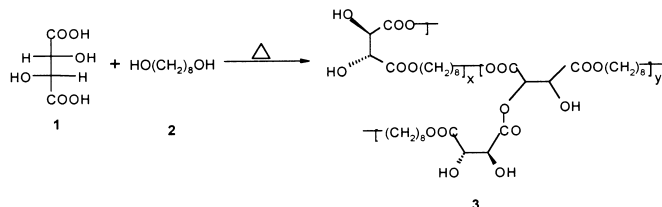

In summary, we have demonstrated that using polymer-supported Sharpless catalyst in the asymmetric epoxidation of *cis*-allylic alcohols the results obtained are comparable with, or better than, those achieved by using the optimised conventional low molecular weight ligand. The enantioselectivities obtained vary

Table 1

Comparison of DMT and polyester **3** prepared from L-(+)-tartaric acid in the asymmetric epoxidation of *cis*-2-allylic alcohols with TBHP (2 equiv.) and Ti(OPrⁱ)₄ in CH₂Cl₂ at –20°C¹²

Entry	R	Ligand [(%), branching / crosslinking] ^a	Molar ratio substrate:Ti:tartrate	Reaction time (days)	Epoxide yield (%) ^b	Ee ^c (%)
1	C ₂ H ₅	3 (10 %)	100:100:200	7	51	86
2	C ₂ H ₅	3 (>> 15 %)	100:100:200	6	42	48
3	C ₂ H ₅	DMT	100:10:14	7	57	78
4	C ₃ H ₇	3 (10 %)	100:200:400	6	48	80
5	C ₃ H ₇	3 (14 %)	100:200:400	21	29	75 ^d
6	C ₃ H ₇	DMT	100:50:100	13	54	38 ^e
7	PhCH ₂ OCH ₂	3 (10 %)	100:100:200	7	20	66 ^f
8	PhCH ₂ OCH ₂	3 (10 %)	100:200:400	6	18 ^g	68
9	PhCH ₂ OCH ₂	3 (>> 15 %)	100:100:200	6	20 ^g	38
10	PhCH ₂ OCH ₂	DMT	100:10:14	7	38	60

^aDMT = L-(+)-dimethyl tartrate. ^bFrom GC analysis with internal standard dodecane correcting for response factors. ^cDetermined by ¹H NMR analysis of the derived MTPA ester in benzene-d₆. ^dDetermined also by chiral HPLC analysis (Chiralpak AS, RI-detection, 9:1 hexane/isopropanol, flow rate 0.5 ml/min): 75 ee%. ^eEe% determined by chiral HPLC analysis (Chiralpak AS, RI-detection, 9:1 hexane/isopropanol, flow rate 0.5 ml/min). ^fDetermined by chiral HPLC analysis (Chiralpak AS, RI-detection, 9:1 hexane/isopropanol, flow rate 0.5 ml/min). Determined also by ¹H NMR analysis of the derived MTPA ester in benzene-d₆: 62 ee%. ^gIsolated yield.

from 66–86% with reasonable chemical yields (up to 57%) using the polymer ligand having a degree of branching of 10%–14%. The crosslinked polymer ligand resulted in remarkably lower enantioselectivity (38–48% ee) with reasonable chemical yields. A large excess of polymer-supported catalyst can be used to improve reaction rates while avoiding added complications in the work-up.

It could also be interesting to investigate the circulation of the polymeric catalyst but, so far, we have made no thorough study to reuse the catalyst.

Acknowledgements

JKK acknowledges financial support from the Neste Oy Foundation, Finland which made this work possible.

References

1. Rossiter, B. E. *Asymmetric Synthesis*, Academic Press, Orlando, FL, 1985, Vol.5, 193–246.
2. Canali, L.; Karjalainen, J. K.; Hormi, O.; Sherrington, D. C. *J. Chem. Soc., Chem. Comm.* **1997**, 123–124.
3. Karjalainen, J. K.; Hormi, O.; Sherrington, D. C. *Molecules*, **1998**, 3, 51–59.
4. Karjalainen, J. K.; Hormi, O.; Sherrington, D. C. *Accepted for publication in Tetrahedron: Asymmetry*.

5. Johnson, R. A.; Sharpless, K. B. In *Catalytic Asymmetric Synthesis*; Ed. Ojima, I., VCH Publishers, Inc., 1993; pp. 103–158.
6. Gao, Y.; Hanson, R. M.; Klunder, J. M.; Ko, S. Y.; Masamune, H.; Sharpless, K. B. *J. Am. Chem. Soc.* **1987**, *109*, 5765–5780.
7. Hodge, P. Polymer-supported Asymmetric Organic Synthesis in *Innovation and Perspectives in Solid Phase Synthesis*; Ed. R. Epton; SPCC UK, 1990; pp. 273–292.
8. Baker, R.; Swain, C. J.; Head, J. C. *J. Chem. Soc., Chem. Comm.* **1986**, 874.
9. (a) Mori, K.; Nakazono, Y. *Tetrahedron*, **1986**, *42*(23), 6459. (b) Nicolaou, K. C., Webber, S. E. *J. Chem. Soc., Chem. Comm.* **1985**, 297.
10. Katsuki, T.; Lee, A. W. M.; Ma, V. S. *J. Org. Chem.* **1982**, *47*(7), 1373.
11. The esters used conventionally in Sharpless epoxidations are dimethyl, diethyl and diisopropyl tartrates, and, with a few subtle exceptions, all are equally effective at inducing asymmetry. See for example Johnson, R. A.; Sharpless, K. B. In *Comprehensive Organic Synthesis*, Vol. 7, Eds. Trost, B. M., Fleming, I., Ley, S. V. Pergamon Press, Oxford 1991, pp. 389–436.
12. *General procedure for asymmetric epoxidation*: The literature procedure for the epoxidation of allylic alcohols was followed with modifications. An oven-dried three-necked round-bottomed flask equipped with a magnetic stirbar, nitrogen inlet, septum and bubbler was charged with 4 Å powdered, activated molecular sieves, polymer-ligand **3** and dry CH₂Cl₂. The flask was cooled to –20°C and Ti(O-*i*-Pr)₄ (via syringe) was added dropwise with stirring. The reaction mixture was stirred at –20°C and after about one hour, 2 equiv. of TBHP in *iso*-octane was added with a syringe at a moderate rate. The resulting mixture was stirred at –20°C for at least one hour. The substrate (dissolved in dry CH₂Cl₂) was added dropwise with a syringe, being careful to maintain the reaction temperature between –15°C and –20°C. The mixture was stirred for an additional 3–12 hours at –15°C to –20°C. The reaction mixture was stored in a freezer for approximately one week. The reaction was monitored by gas chromatography (GC) using dodecane as an internal standard. The polymer was filtered and the reaction mixture washed thoroughly with CH₂Cl₂. Workup was then performed. The crude product was purified by flash-chromatography (eluent: petrol ether (40°C–60°C):diethyl ether=1:1) and analysed by ¹H NMR, GC and HRMS. All compounds showed satisfactory spectroscopic and analytical data. The enantioselectivity of the epoxide was measured by ¹H NMR analysis of the derived MTPA ester in benzene-*d*₆ or by HPLC using a chiral Chiralpak AS 25 cm×0.46 cm column together with a Chiralpak AS 5 cm×0.46 cm pre-column (RI-detection, eluent: n-hexane:isopropanol=9:1, flow rate: 0.5 ml/min).