

# Synthesis and Properties of New Optically Active $\gamma$ -Lactones as Chiral Dopants for Ferroelectric Liquid Crystals

Tetsuo Kusumoto,<sup>a</sup> Akiko Nakayama,<sup>a</sup> Ken-ichi Sato,<sup>a</sup> Kiyoharu Nishide,<sup>a</sup> Tamejiro Hiyama,<sup>a</sup> Sadao Takehara,<sup>b</sup> Tadao Shoji,<sup>b</sup> Masashi Osawa,<sup>b</sup> Takeshi Kuriyama,<sup>b</sup> Kayoko Nakamura<sup>b</sup> and Toru Fujisawa<sup>b</sup>

<sup>a</sup> Sagami Chemical Research Center, 4-4-1 Nishiohnuma, Sagamihara, Kanagawa 229, Japan

<sup>b</sup> Central Research Laboratories, Dainippon Ink and Chemicals, Inc., 631 Sakado, Sakura, Chiba 285, Japan


Optically active  $\alpha$ -aryl- $\gamma$ -alkyl- $\gamma$ -lactones were synthesized through the reaction of chiral 1,2-epoxyalkanes with the carbanion derived from 4-methoxyphenylacetonitrile or 4-methoxyphenylacetic acid and shown to be good chiral dopants for ferroelectric liquid crystals.

It has recently been suggested that thin cells containing ferroelectric liquid crystals (FLCs) can be applied to high-speed switching devices.<sup>1</sup> The switching time depends on the magnitude of spontaneous polarization ( $P_s$ ) and viscosity of the FLCs. The FLC materials are usually prepared by mixing chiral dopants possessing large  $P_s$  values with achiral smectic C ( $S_C$ ) host liquid crystal mixtures having low viscosity. For chiral dopants various optically active compounds have been designed. In particular, we have proposed chiral dopants containing a chiral centre connected directly both to a core aromatic ring and to a polar group and have shown that these actually exhibit large  $P_s$  values.<sup>2-5</sup> Examples are compounds with the structure  $ArCHMeCO_2R$ .<sup>2</sup> To improve the  $P_s$  values further, we have designed FLCs having an optically active lactone ring, e.g. **1** and **2**, wherein two polar groups  $C=O$  and  $C-O-C$  are disposed so that each dipole is fixed in a nearly parallel direction. In addition, free rotation of the lactone ring is apparently more restricted than it is in  $ArCHMeCO_2R$  because this ring is directly connected to the core aromatic ring. We report herein the synthesis of compounds **1** which are indeed found to be superior chiral dopants.


The chiral  $\gamma$ -lactone **1a** was prepared according to the route shown in Scheme 1. The carbanion of 4-methoxyphenylaceto-

nitrile **3** was allowed to react with (*R*)-1,2-epoxyoctane to give **4** as a *ca.* 1:1 mixture of diastereoisomers (70% yield). Hydrolysis of the cyano group using KOH in diethylene glycol followed by esterification with thionyl chloride afforded lactones **5a** (52%) and **5b** (44%). The diastereoisomers were easily separated by silica gel column chromatography. Alternatively, **5a** and **5b** were available by the reaction of (*R*)-1,2-epoxyoctane with the dianion of 4-methoxyacetic acid **6** and subsequent lactonization (45 and 48% yield respectively). Selective demethylation of **5a** was effected with EtSH- $AlCl_3$ <sup>6</sup> to give the phenol derivative **7** (90% yield) which was esterified with 4-octyloxybenzoyl chloride to give **1a** (70% yield). Compounds **1b** and **1c** were synthesized similarly. Lactone **1e** was obtained from (*S*)-propylene oxide in a similar manner, whereas **1d** was prepared using a chiral epichlorohydrin. The cyano epoxide **8** (77% yield, *ca.* 1:1 diastereoisomer mixtures), obtained through the reaction of (*R*)-epichlorohydrin with the carbanion of **3**, was allowed to react with propylmagnesium bromide in the presence of CuI to give **9** in 59% yield. This cyano alcohol was converted into **1d** as described above.

Although compounds **1a-1e** did not exhibit a chiral smectic C phase ( $S_C^*$ ), they were employed as chiral dopants for

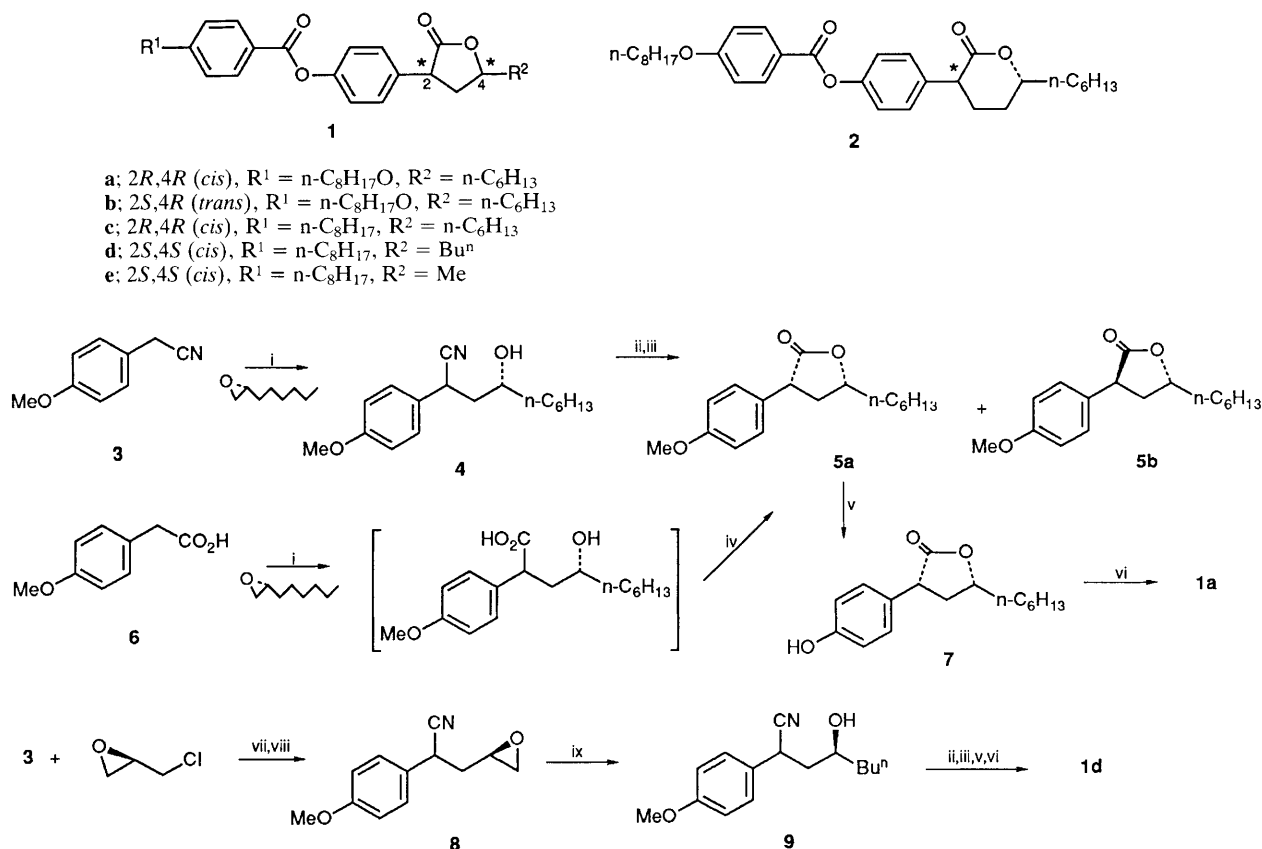

**Scheme 1** Reagents: i, Bu<sup>n</sup>Li; ii, KOH; iii, SOCl<sub>2</sub>; iv, *p*-MeC<sub>6</sub>H<sub>4</sub>SO<sub>3</sub>H; v, EtSH, AlCl<sub>3</sub> or Me<sub>2</sub>S, AlCl<sub>3</sub>; vi, *p*-n-C<sub>8</sub>H<sub>17</sub>OC<sub>6</sub>H<sub>4</sub>COCl, pyridine; vii, Bu<sup>n</sup>Li; viii, NaH; ix, Pr<sup>n</sup>MgBr, CuI

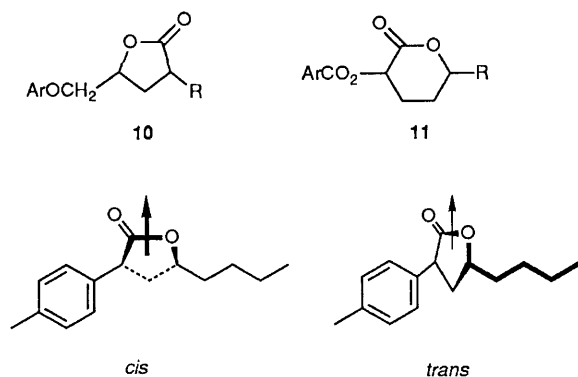

achiral smectic C liquid crystals. Thus, each was added to a host liquid crystals mixture A.<sup>†</sup> The electrooptical properties of the resulting mixtures are listed in Table 1. The mixture containing 2 wt% *cis*-lactone **1a** showed a very large  $P_s$  value (4.5 nC cm<sup>-2</sup>), a short response time (162 μs) and tilt angle (25°). Use of 4 wt% of **1a** resulted in a large enhancement of  $P_s$  and decrease of the response time: 12.7 nC cm<sup>-2</sup> and 98 μs respectively. These  $P_s$  values are apparently larger than that for the acyclic model ArCHMeCO<sub>2</sub>R and can be estimated to be comparable or slightly superior to  $P_s$  values of the related lactones **10**<sup>7,8</sup> and **11**.<sup>9</sup> Noteworthy is the fact that the *trans*-lactone **1b** showed a very small  $P_s$  value whereas the *cis*-lactones **1a** and **1c–1e** exhibited large values. This observation may be ascribed to the conformation of the lactones: the dipole moment of the *cis*-lactones is apparently arranged perpendicular to the axis of the core and alkyl chains, whereas that of the *trans*-lactone is nearly parallel to the planes of the core and alkyl side chain.<sup>‡</sup> The former conformation is particularly important for high  $P_s$  to be realized, as discussed for **10**.<sup>8</sup> The nature of the group R<sup>1</sup> (octyloxy or octyl) did not influence  $P_s$  **1a** vs. **1c**, but a short R<sup>2</sup> lowered  $P_s$  somewhat (**1c** vs. **1d** or **1e**). The sign of the  $P_s$  is decisively correlated with the chirality of the lactone ring: (*R,R*), (+); (*S,S*), (–).

In contrast to γ-butyrolactones **1**, δ-valerolactones **2** showed very small  $P_s$  values.<sup>10</sup> Thus, the conformational

<sup>†</sup> The host liquid crystal mixture A consists of 2-(4-nonyloxyphenyl)-5-heptylpyrimidine (30 wt%), 2-(4-octyloxyphenyl)-5-octylpyrimidine (20 wt%), 2-(4-decyloxyphenyl)-5-octylpyrimidine (30 wt%), and 2-(4-octyloxyphenyl)-5-nonylpyrimidine (20 wt%). The phase transition temperatures (*T*/°C) of the host A were Cr 13 S<sub>C</sub>H56 S<sub>A</sub> 65 N 70 I.

<sup>‡</sup> This conformation was suggested by molecular mechanics calculations (MM2 and MOPAC).

**Table 1** Electrooptical properties of the chiral dopant **1** in host liquid crystal mixture A at 25 °C<sup>a</sup>

Chiral dopant (wt%)	$P_s^b$ /nC cm <sup>-2</sup>	Response time <sup>c</sup> /μs	Tilt angle/°
<b>1a</b> (2)	+4.5	162	25
(4)	+12.7 <sup>d</sup>	98	24
<b>1b</b> (10)	— <sup>e</sup>	891	14
<b>1c</b> (2)	+4.4	153	26
<b>1d</b> (2)	–4.2	169	24
<b>1e</b> (2)	–4.1	171	23

<sup>a</sup> The liquid crystal mixture was sealed in a polyimide rubbing cell of about 2 μm thickness, and a square wave of 10 V<sub>p-p</sub>/μm was applied to the cell. <sup>b</sup>  $P_s$  was measured by the triangular wave method. <sup>c</sup> Change of transmittance (from 0 to 90%) of light was observed. <sup>d</sup> Extrapolation to 100 wt% gives a value > 300 nC cm<sup>-2</sup> (probably around 1000 nC cm<sup>-2</sup>). <sup>e</sup> Too small to be measured.

rigidity of the lactone ring seems to be essential for high  $P_s$  values. The lactone ring system may thus be considered to be a new chiral core which introduces chirality to the whole molecule in a way different from the chiral centre(s) in alkyl side chains.

Received, 14th November 1990; Com. 0/05115B

## References

- N. A. Clark and S. T. Lagerwall, *Appl. Phys. Lett.*, 1980, **36**, 899.
- T. Kusumoto, T. Ueda, T. Hiyama, S. Takehara, T. Shoji, M. Osawa, T. Kuriyama, K. Nakamura and S. Fujisawa, *Chem. Lett.*, 1990, 523.
- K. Nishide, A. Nakayama, T. Kusumoto, T. Hiyama, S. Takehara, T. Shoji, M. Osawa, T. Kuriyama, K. Nakamura and T. Fujisawa, *Chem. Lett.*, 1990, 623.
- T. Kusumoto, T. Hanamoto, T. Hiyama, S. Takehara, T. Shoji, M. Osawa, T. Kuriyama, K. Nakamura and T. Fujisawa, *Chem. Lett.*, 1990, 1615.
- T. Kusumoto, T. Hanamoto, K. Sato, T. Hiyama, S. Takehara, T. Shoji, M. Osawa, T. Kuriyama, K. Nakamura and T. Fujisawa, *Tetrahedron Lett.*, 1990, **31**, 5343.
- K. Fuji and M. Node, *Yuki Gosei Kagaku Kyokaishi*, 1984, **42**, 193.
- M. Kodon, T. Kuratate, F. Funada, K. Awane, K. Sakaguchi, Y. Shiomi and T. Kitamura, *Jpn. J. Appl. Phys.*, 1990, **29**, L981.
- Similar discussion: M. Kodon, T. Kuratate, F. Funada, K. Awane, K. Sakaguchi and Y. Shiomi, *Mol. Cryst. Liq. Cryst. Lett.*, 1990, **7**, 79.
- J. Nakauchi, M. Uematsu, K. Sakashita, Y. Kageyama, S. Hayashi, T. Ikemoto and K. Mori, *Jpn. J. Appl. Phys.*, 1989, **28**, L1258.
- To be published in due course.