



Free-radical chain generation of ketene during the synthesis of liquid crystalline aromatic polyesters

Mihaela C. Stuparu, Juhua Xu, H. K. Hall Jr. *

C. S. Marvel Laboratories, Department of Chemistry, The University of Arizona, Tucson, AZ 85721, United States

ARTICLE INFO

Article history:

Received 2 July 2009

Revised 26 August 2009

Accepted 27 August 2009

Available online 2 September 2009

ABSTRACT


At the high temperatures used for the preparation of liquid crystalline aromatic polyesters (LCPs), ketene cleavage occurred from acetoxyarenes. Ketene is known to oligomerize to colored oligomers which may be responsible for an undesirable yellow color in LCPs. Thermolysis of the model compound *p*-acetoxybenzoate gave ketene oligomers and methyl *p*-hydroxybenzoate, which oligomerized. A free-radical chain reaction mechanism for ketene formation was demonstrated by the reaction of tributyltin hydride with haloacetoxyarenes.

© 2009 Elsevier Ltd. All rights reserved.

1. Introduction

This study explored the possibility of ketene formation and oligomerization contributing to the yellowing observed during aromatic main chain liquid crystal polymer (LCP) synthesis.^{1,2} Such yellowing limits potential LCP uses as optical materials. In earlier LCP work, it was shown that at high polymerization tem-


perature some of the mixed anhydride intermediates thermolyze to ketene and aromatic carboxylic acid; a nitrogen sweep carried ketene out of the reaction to a trap where its occurrence was demonstrated by the reaction with aniline to form acetanilide (**3**).³ If the ketene is left in the reaction, it can oligomerize; and polyketene is variously described as ranging from yellow⁴ to dark brown-black.⁵

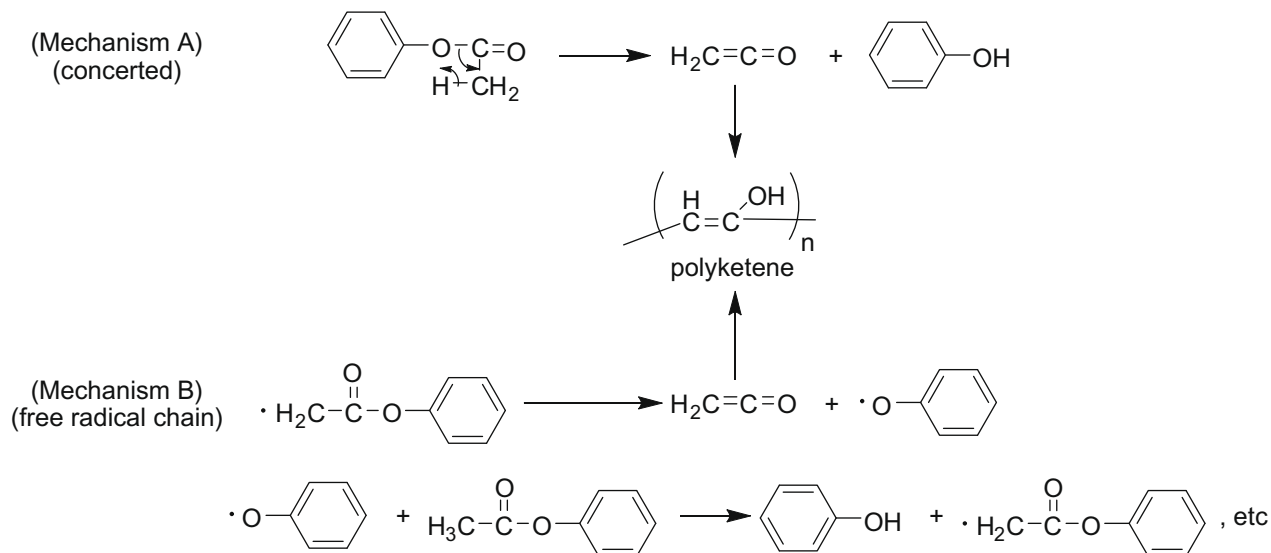


Scheme 1.

* Corresponding author. Tel.: +1 520 621 6325; fax: +1 520 621 8407.

E-mail address: hkh@u.arizona.edu (H.K. Hall Jr.).

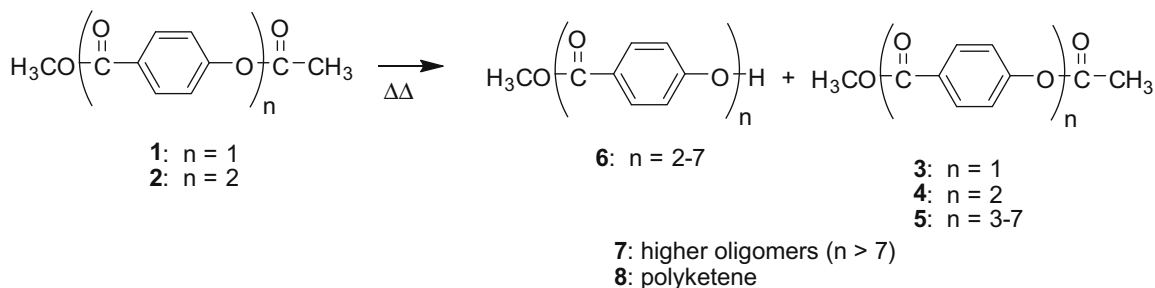

Scheme 2.

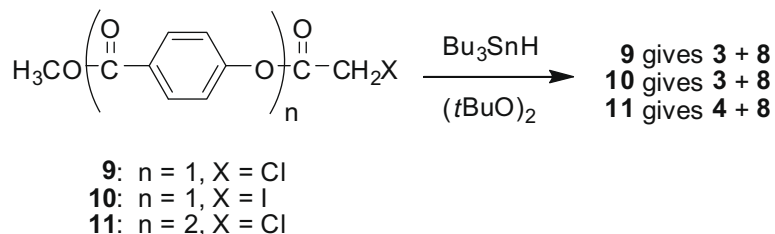

Scheme 3.

The mechanistic question arises: Is this ketene formation a concerted electrocyclic reaction (Scheme 1, A) or a free-radical chain reaction (Scheme 1, B). The literature^{6–11} supports either mechanism.

2. Reactions in the absence of free-radical generators (Scheme 2)

Heating either model acetoxyarene **1** or **2** at 280–320 °C for 20 min gave a dark yellow reaction mixture. The mixtures were analyzed by GC–MS. Isolation of low molecular weight products was done by flash column chromatography. Higher oligomers were detected using ESI–MS techniques. An intractable residue, soluble only in pentafluorophenol, presumably a mixture of higher molecular weight oligoesters, was also formed. The yellow component of **8** was highly polar, requiring methanol for elution but it could not be more closely characterized. These results are explained by thermal cleavage of **1** or **2** to hydroxyesters **3** and **4** which can undergo intermolecular methanolysis to form **3–5**.

3. Reactions in the presence of free-radical generators (Scheme 3)

Hydrogen abstraction was achieved by heating **1** with di-*t*-butyl peroxide at 150 °C under argon gave a mixture of **3** and polar yellow material **8**, along with unreacted **1**. More decisively, halogen abstraction was achieved by heating the halo compounds **9–11** with tributyltin hydride in the presence of di-*t*-butyl peroxide which converted them to **3** and **4** in virtually quantitative yields.

4. Conclusions

At high temperature polymerization used in LCP synthesis, model compounds **1** and **2** cleave to ketene and two sets of *p*-oxybenzoyl oligomers. To decide whether the cleavage mechanism was either a concerted or a free-radical chain, the feasibility of the latter mode was demonstrated at lower temperatures. The postulated chain-carrying acyloxy radical was generated by either hydrogen or halogen abstraction and shown to readily lose ketene.

Acknowledgements

We thank Solvay Advanced Polymers for support, Mr. Jeffrey Robertson for the thermolysis of **6**, Dr. Ian W. Jones, and Professor R. B. Bates for assistance.

References and notes

- Yoon, H. N.; Charbonneau, L. F.; Calundann, G. W. *Synthesis Processing and Properties of Thermotropic Liquid Crystal Polymers. Advanced Materials*, Weinheim, Wiley-VCH, 1992; Vol. 4, pp 206–213.
- Negi, Y. S.; Goyal, R. K. *Int. J. Plastics Tech.* **2003**, 7, 99–118 [CAN 142:23533r].
- Han, X.; Williams, P. A.; Padias, A. B.; Hall, H. K., Jr.; Sung, H. N.; Linstid, H. C.; Lee, C. *Macromolecules* **1996**, 29, 8313.
- Yamashita, Takeya, Japan Tokyo Koho [CAN 78 31587].
- Khemani, K. C.; Wudl, F. *J. Am. Chem. Soc.* **1989**, 111, 9124–9125.
- Nishida, S.; Imai, T.; Tsuji, T. *Chem. Lett.* **1974**, 11, 1303–1304.
- Barefoot, A. C.; Carroll, F. A. *J. Chem. Soc., Chem. Commun.* **1974**, 9, 357.
- Kaspar, M.; Prochazka, M. *Collect. Czech. Chem. Commun.* **1974**, 39, 3124–3130.
- (a) Ghibaudi, E.; Colussi, A. J. *J. Chem. Soc., Chem. Commun.* **1984**, 7, 433–434; (b) Ghibaudi, E.; Colussi, A. J. *Int. J. Chem. Kinet.* **1984**, 16, 1575–1583.
- Taylor, R. J. *J. Chem. Soc., Perkin Trans. 2* **1988**, 2, 1839.
- Chihara, T.; Kaniguchi, S. *Chem. Lett.* **2002**, 1, 70–71.