

Communication

The Anionic Ring-Opening Polymerization of N-(tolylsulfonyl)azetidines to Produce Linear Poly(trimethylenimine) and Closed-System Block Copolymers

Louis Reisman, Elizabeth A Rowe, Enrique M. Jackson,
Christian Thomas, Tomekia Simeon, and Paul A Rupar

J. Am. Chem. Soc., **Just Accepted Manuscript** • DOI: 10.1021/jacs.8b10326 • Publication Date (Web): 08 Nov 2018

Downloaded from <http://pubs.acs.org> on November 8, 2018

Just Accepted

"Just Accepted" manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides "Just Accepted" as a service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. "Just Accepted" manuscripts appear in full in PDF format accompanied by an HTML abstract. "Just Accepted" manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are citable by the Digital Object Identifier (DOI®). "Just Accepted" is an optional service offered to authors. Therefore, the "Just Accepted" Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the "Just Accepted" Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these "Just Accepted" manuscripts.



ACS Publications

is published by the American Chemical Society, 1155 Sixteenth Street N.W., Washington, DC 20036

Published by American Chemical Society. Copyright © American Chemical Society. However, no copyright claim is made to original U.S. Government works, or works produced by employees of any Commonwealth realm Crown government in the course of their duties.

The Anionic Ring-Opening Polymerization of *N*-(*p*-tolylsulfonyl)azetidines to Produce Linear Poly(trimethylenimine) and Closed-System Block Copolymers

Louis Reisman,¹ Elizabeth A. Rowe,¹ Enrique M. Jackson,² Christian Thomas,² Tomekia Simone,³ and Paul A. Rupar^{1*}

¹Department of Chemistry and Biochemistry, The University of Alabama, Tuscaloosa, Alabama 35487-0336, United States

²Materials Test Branch, NASA Marshall Space Flight Center, Martin Rd SW, Huntsville, Alabama, 35808, United States

³Dillard University, Department of Chemistry, 2601 Gentilly Blvd, New Orleans, LA, 70122, United States

Supporting Information Placeholder


ABSTRACT: The anionic ring-opening copolymerization of *N*-(*p*-tolylsulfonyl)azetidine (**pTsAzet**) and *N*-(*o*-tolylsulfonyl)azetidine (**oTsAzet**) produces poly(*p*TsAzet-*co*-*o*TsAzet) as a statistical copolymer. The **pTsAzet/oTsAzet** copolymerization is living and allows for the synthesis of poly(sulfonylazetidine) of target molecular weights with narrow dispersities. ¹H NMR spectroscopy was used to monitor the kinetics of the polymerization and estimate the monomer reactivity ratios. It was found that the reactivity ratios for **oTsAzet** and **pTsAzet** are 1.66 and 0.60, respectively. The tosyl groups of p(*p*TsAzet-*co*-*o*TsAzet) were reductively removed to produce linear poly(trimethylenimine) (LPTMI). This represents the first route to LPTMI of controlled molecular weight and low dispersity. Finally, the slow kinetics of the sulfonylazetidine polymerization facilitated the synthesis of a block copolymer without requiring the sequential addition of monomer. Specifically, **pTsAzet**, **oTsAzet**, and (*N*-*p*-toluenesulfonyl-2-methylaziridine) (**pTsMAz**) were combined in solution. **pTsMAz** selectively polymerizes to form the first block at moderate temperature. After consumption of **pTsMAz**, the temperature was increased to copolymerize **pTsAzet** and **oTsAzet** and produce the block copolymer p(*p*TsMAz)-*b*-p(*p*TsAzet-*co*-*o*TsAzet).

Despite the structural similarities between cyclic imines and cyclic oxides, their polymerizations are very different. For example, ethylene oxide can be polymerized by both cationic ring-opening polymerization (CROP)¹ and anionic ring-opening polymerization (AROP)²⁻³ to produce a linear polymer with high degrees of control. In contrast, aziridine can only be polymerized by CROP to produce a hyperbranched polymer.⁴⁻⁸ This has led to the development of indirect routes to linear polyimines, the most prominent being the polymerization of oxazolines, despite the difficulties in this approach.⁵ However, controlled routes to polyimines continue to be highly sought after due to their use in high value applications (i.e. antimicrobial and antifouling coatings,⁹ chelation and polymer-assisted deposition,¹⁰ CO₂ capture,¹¹ and non-viral gene transfection⁵).

Poly(trimethylenimine) (PTMI) [-CH₂CH₂CH₂NH-] is among the least studied of the simple polyimines. This is due to the complexity of azetidine polymerization which exclusively forms

hyperbranched PTMI (BPTMI, Scheme 1, TOP).^{4, 7-8, 12-17} Initial work on linear PTMI (LPTMI) was reported by Kobayashi.¹⁸ Recently, Jones utilized this oxazine based route to LPTMI and showed that its CO₂ capture ability is superior to linear polyethylenimine (LPEI) [-CH₂CH₂NH-].¹⁹ However, to date, there are no known routes to LPTMI that have demonstrated control over molecular weight and dispersity.


Inspired by recent breakthroughs in the AROPs of *N*-sulfonyl aziridines²⁰⁻³³ as a way to access linear polyimines,³⁴⁻³⁶ we recently reported on the AROP of *N*-(methanesulfonyl)azetidine (**MsAzet**) (Scheme 1, bottom).³⁷ The polymerization kinetics of **MsAzet** were notably slower than *N*-sulfonylaziridines, and, surprisingly, the resulting p(**MsAzet**) had a branched structure. The branching, which arose due to transfer to the methanesulfonyl groups during polymerization, precluded **MsAzet** as a precursor to LPTMI. However, the fact that AROP of **MsAzet** did occur, suggests that a suitable *N*-sulfonylazetidine could be used to form a linear polymer and provide a controlled route to LPTMI.

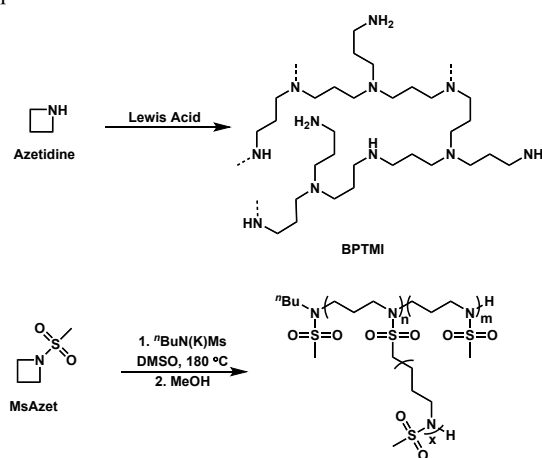

Scheme 1. (TOP) CROP of azetidine to produce BPTMI.⁷ (BOTTOM) AROP of **MsAzet**.³⁷

We turned our attention to the polymerization of *N*-(tolylsulfonyl)azetidines as their protons are less likely to be activated under the polymerization conditions. We initially attempted to use AROP to convert *N*-(*p*-tolylsulfonyl)azetidine

(*p*TsAzet) and *N*-(*o*-tolylsulfonyl)azetidine (*o*TsAzet) to the corresponding homopolymers, however, both monomers only formed low molecular weight homooligomers. The poor solubility of *p*-(*N*-(tolylsulfonyl)azetidine) homopolymers is not completely unexpected as related poly(*N*-sulfonylaziridine) homopolymers are often similarly insoluble.^{26, 34}

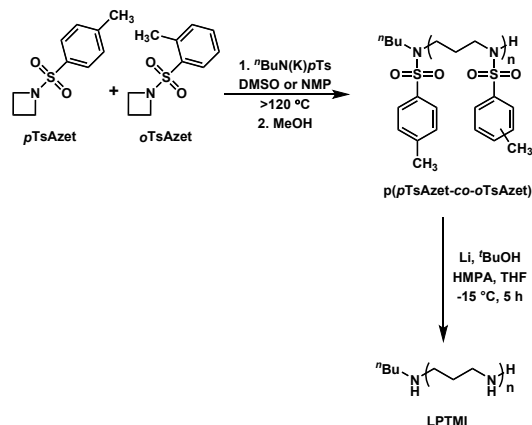

Scheme 2. Polymerization of TsAzet monomers to soluble *p*(*p*TsAzet-*co*-*o*TsAzet) and transformation to LPTMI.

We next attempted the copolymerization of the two *N*-(tolylsulfonyl)azetidine monomers (Scheme 2). This was motivated by prior work showing that the solubility of poly(*N*-sulfonylaziridine) random copolymers are greatly improved compared to the corresponding homopolymers.³⁴ Copolymerization of *p*TsAzet with *o*TsAzet in a 1:1 ratio produced *p*(*p*TsAzet-*co*-*o*TsAzet), which is soluble in DMF, DMSO, NMP and HMPA. The weakly basic nature of the propagating anion²⁴ allows this copolymerization to proceed in NMP without any apparent reaction with NMP. For the polymerizations performed in DMSO, small amounts of transfer to solvent is likely occurring,³⁷⁻³⁸ although we were unable to observe and quantify this. DMF was also a suitable solvent for the AROP of sulfonyl azetidines.

The polymerization kinetics of the AROP of *N*-(tolylsulfonyl)azetidines in DMSO_{d6} were studied by real-time ¹H NMR spectroscopy.^{27, 29, 37} The plot of natural log of total monomer concentration with respect to time is linear, suggesting it is first order with respect to total monomer concentration and that the number of active chain ends remains constant during the polymerization (Figure S1 and Table S2).³⁹ Compositional drift was observed during the course of the copolymerization, with *o*TsAzet being incorporated at a faster rate (Figure S3). The monomer reactivity ratios were estimated using Lynd's non-terminal model.⁴⁰ This model assumes that the identity of the active chain end does not impact subsequent monomer additions, which is usually a valid assumption in ionic polymerizations.⁴¹⁻⁴² Lynd's non-terminal model is attractive as it allows determination of reactivity ratios through the observation of a single copolymerization. This model calculated the reactivity ratios to be 1.66 and 0.60 for *o*TsAzet and *p*TsAzet, respectively, at 180 °C (Table S2).⁴³ We also determined the reactivity ratios for *o*TsAzet and *p*TsAzet by the Kelen-Tüdös method and there were found to be similar (Figure S4 and Table S3).⁴⁴

In order to determine the possibility of controlling the AROP of the *N*-(tolylsulfonyl)azetidines, a series of copolymerizations were performed where the monomers to initiator ratio was varied (the ratio of the monomers was kept 1:1). The *D_p*, as measured by ¹H NMR spectroscopic end-group analysis closely matched the theoretical values (Table S4) and the plot of *M_n* vs monomer: initiator was linear (Figure 1). All SEC traces are monomodal with narrow *Đ* (Figure S20 and Table S4) and a decrease in retention time was observed with increasing monomer to initiator ratio.

MALDI-TOF mass spectrometric (MS) analysis of the polymers revealed signals consistent with each polymer chain containing the ⁿBu(N)Ts initiator (Figure S22). Additionally, upon complete consumption of the monomers, additional equivalents of monomers could be added to the reaction mixture, and chain extension was observed (Figure S21). This data shows that, as with sulfonylaziridines, the copolymerization of *p*TsAzet and *o*TsAzet appears to be living and controlled.

WAXS data revealed that *p*(*p*TsAzet-*co*-*o*TsAzet) was crystalline, but the crystalline peaks are distinct from those of the *p*(*p*TsAzet) and *p*(*o*TsAzet) homooligomers (Figure S28). This suggests that *p*(*p*TsAzet-*co*-*o*TsAzet) does not have blocky domains. DSC presents a well-defined *T_g* of 68 °C and *T_m* of 140 °C and TGA reveals a *T_d* of 360 °C (Table S5, entry 6). The difference between the *T_m* of the copolymer and the homooligomers (213 and 190 °C for *p*TsAzet and *o*TsAzet homooligomers, respectively, Table S5) further suggests an absence of blocky segments.

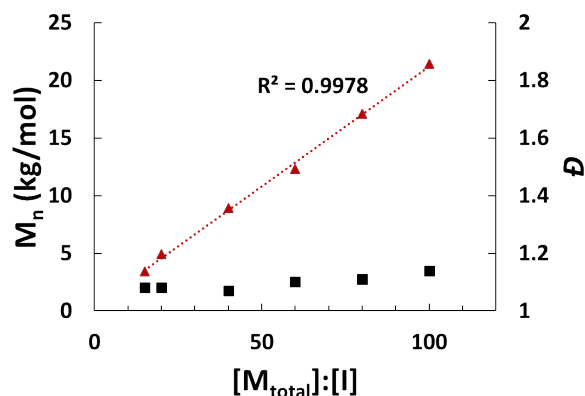



Figure 1. *M_n* determined by ¹H NMR end-group analysis vs [*M_{total}*]:[*I*] (▲). Dispersity vs [*M_{total}*]:[*I*] (■).

In order to convert *p*(*p*TsAzet-*co*-*o*TsAzet) into LPTMI, the tosyl groups were removed using Li (Scheme 2).^{34, 45} ¹H NMR spectra (Figure S17) of the resulting polymer was consistent with the formation of LPTMI.¹⁹ MS was used to confirm that chain scission had not occurred during the deprotection. MALDI-TOF mass spectrum of LPTMI (Figure S24) derived from low molecular weight *p*(*p*TsAzet-*co*-*o*TsAzet)₁₅ revealed a *D_p* = 14.8 with *Đ* = 1.04. The observed MALDI-TOF MS data of LPTMI implies that no chain scission is occurring during the removal of the tosyl groups.

Lastly, we set out to produce block copolymers utilizing *N*-(tolylsulfonyl)azetidine monomers, as this would provide a route to novel polyimine block copolymers. Since *p*TsAzet and *o*TsAzet do not polymerize at temperatures < 100 °C, we proposed that a third monomer, which polymerizes at lower temperatures, could do so in the presence of the sulfonyl azetidines, and allow for a closed-system block copolymer synthesis in which all monomers are present at initiation. After this first monomer is consumed, the reaction mixture could then be heated to higher temperature to facilitate the copolymerization of the azetidines.

We chose to create a block copolymer using *N*-(*p*-tolylsulfonyl)-2-methylaziridine (*p*TsMAz) as *p*TsMAz readily polymerizes at lower temperatures and its propagating chain end could likely initiate the *N*-(tolylsulfonyl)azetidines. To accomplish the block copolymer polymerization, *p*TsMAz, *p*TsAzet, *o*TsAzet and ⁿBuN(K)pTs were dissolved in DMSO_{d6} (Scheme 3). The reaction mixture was heated to 50 °C for 4 h, during which time *p*TsMAz was consumed (Figure 2A). Next, the reaction mixture was heated to 180 °C to polymerize the second block, resulting in the formation

of the desired block copolymer $p(pTsMAz)_{20}-b-p(pTsAzet-co-oTsAzet)_{40}$.

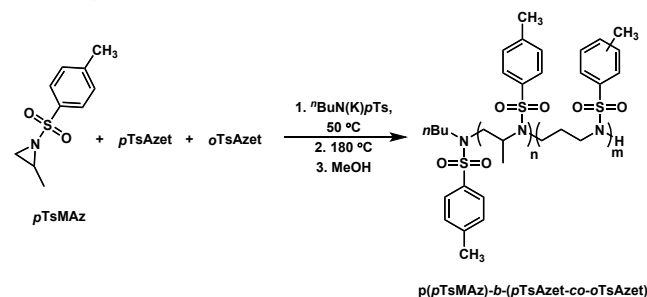

Scheme 3. Block copolymerization of $pTsMAz$ with $oTsAzet$ and $pTsAzet$ to produce $p(pTsMAz)-b-p(pTsAzet-co-oTsAzet)$.

Monitoring the polymerization by 1H NMR showed no evidence of sulfonylazetidine consumption at lower temperature (Figure 2A). As such, the resulting block copolymer is believed to have a sharp transition between the two domains, with no region of sulfonylaziridine and sulfonylazetidines mixing. In addition, the SEC trace of the resulting polymer showed no evidence of lower molecular weight $p(pTsMAz)$ homopolymer (Figure 2B). Subsequent sulfonyl group removal of this block copolymer would allow for the synthesis of a LPPI-*b*-LPTMI block copolymer.

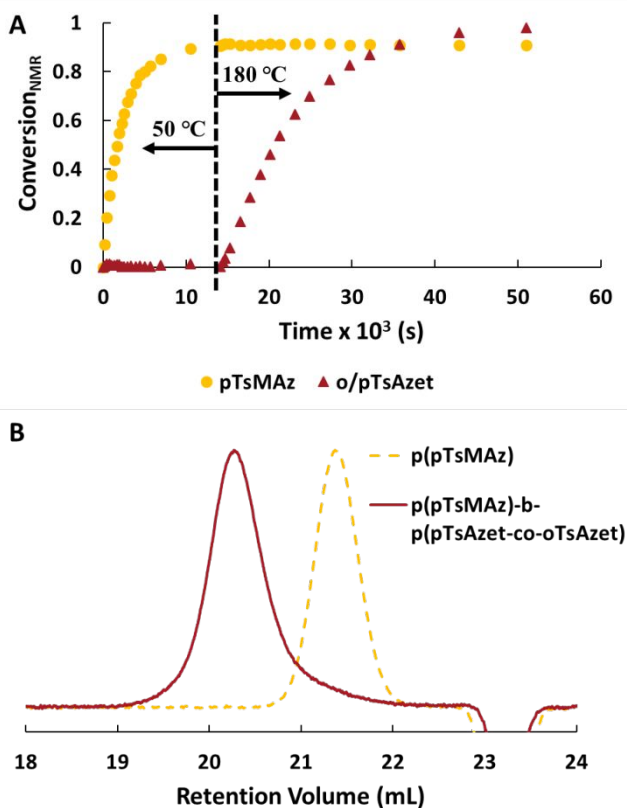


Figure 2. (A) Plot of conversion vs. time for the copolymerization of $pTsMAz$, $pTsAzet$ and $oTsAzet$ in $DMSO_d6$ to produce $p(pTsMAz)_{20}-b-p(pTsAzet-co-oTsAzet)_{40}$. The reaction is kept at 50 °C for 4 h, then 180 °C for 10.25 h. The NMR measured conversion of $pTsMAz$ appears to not reach 100% due to signal overlap between the monomer and polymer resonances in 1H NMR spectra of the reaction mixture as the polymer signal grows in intensity. (B) SEC trace of $p(pTsMAz)_{20}$ prior to block copolymer chain extension (---). SEC trace of $p(pTsMAz)_{20}-b-p(pTsAzet-co-oTsAzet)_{80}$ (—). Block copolymerization to produce $p(pTsMAz)_{20}-b-p(pTsAzet-co-oTsAzet)_{80}$ was performed with

$[pTsMAz]:[oTsAzet]:[pTsAzet]:[I]$ of 20:40:40:1 in NMP at 70 °C for 12 h, then 205 °C for 16 h.

This ability to produce block copolymers in a closed-system provides a solution to a common issue with the synthesis of block copolymers, especially high-performance block copolymer materials. Traditionally, upon addition of the second monomer, there is often a small amount of chain termination which leads to the presence of homopolymer impurity.⁴⁶ This homopolymer impurity can affect the properties of the block copolymer material. This problem can be mitigated by the use of strenuous purifications, as well as high vacuum and break-seal techniques.⁴⁷⁻⁵⁰ Recently, Sumerlin reported block copolymers by RAFT polymerization synthesized in a closed system where individual monomers were segregated in the reaction mixture by temporarily freezing one monomer in a high melting point solvent.⁵¹ More recently, Wurm has utilized a similar closed-system to synthesize $p(pTsMAz)$ -PEO block copolymers, although there is some gradient in the transition between the blocks.⁵²

In conclusion, we have shown that the copolymerization of $pTsAzet$ with $oTsAzet$ produces a soluble, statistical copolymer, $p(pTsAzet-co-oTsAzet)$, and reported the kinetics of the polymerization as well as the reactivity ratios of the two monomers in the copolymerization. The polymerization is living and controlled and can be converted to LPTMI. This allows, for the first time, the synthesis of LPTMI by a controlled, living anionic ring-opening polymerization, an important finding due to the potential high value of this polymer in non-viral gene transfection; studies have shown that the length of the carbon spacer between the nitrogens (i.e. ethyl vs propyl) influences nucleotide binding.⁵³ Additionally, the high barrier to ring-opening of *N*-sulfonylazetidines can be exploited to produce block copolymers in a closed-system process.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website. Experimental procedures, NMR spectra, MALDI-TOF mass spectra, SEC, WAXS, kinetic and compositional drift data, and thermal analysis plots. (PDF).

Unprocessed, experimental data can be found online via Open Science Framework at DOI: [osf.io/pfje6](https://doi.org/10.26434/chemrxiv-2023-pfje6)

AUTHOR INFORMATION

Corresponding Author

*E-mail: parupar@ua.edu

Notes

The authors declare no competing financial interests.

ACKNOWLEDGMENT

We thank the ACS-Petroleum Research Fund (55075-DNI7), the Department of Education-GAANN (P200A150329), NASA (80MSFC18M0041), and the University of Alabama (UA) for financial support. We thank NSF (CHE-1726812) from the Major Research Instrumentation (MRI) program for purchase of the MALDI/TOF-TOF mass spectrometer. We thank Prof. Vincent Scalfani (UA) for his assistance with the Open Science Framework, Prof. Jared Allred (UA) for helpful discussions in determining experimental parameters for and interpreting WAXS data, and Prof. Patrick Frantom (UA) for helpful discussions on kinetics.

REFERENCES

1. Penczek S.; Kubisa P.; Matyjaszewski K. Oxiranes. In *Cationic Ring-Opening Polymerization*; Advances in Polymer Science; Springer: Berlin, Heidelberg, Germany, 1985; Vol. 68/69, pp 52-65.
2. Gee, G.; Higginson, W. C. E.; Merrall, G. T. 267. Polymerisation of epoxides. Part II. The polymerisation of ethylene oxide by sodium alkoxides. *J. Chem. Soc.* **1959**, 0, 1345-1352.
3. Gee, G.; Higginson, W. C. E.; Levesley, P.; Taylor, K. J. 266. Polymerisation of epoxides. Part I. Some kinetic aspects of the addition of alcohols to epoxides catalysed by sodium alkoxides. *J. Chem. Soc.* **1959**, 0, 1338-1344.
4. Goethals, E. J.; Schacht, E. H.; Bruggeman, P.; Bossaer, P. Cationic Polymerization of Cyclic Amines. In *Ring-Opening Polymerization*, American Chemical Society, 1977; Vol. 59, pp 1-12.
5. Jager, M.; Schubert, S.; Ochrimenko, S.; Fischer, D.; Schubert, U. S. Branched and linear poly(ethylene imine)-based conjugates: synthetic modification, characterization, and application. *Chem. Soc. Rev.* **2012**, 41, 4755-67.
6. Kobayashi, S. Ethylenimine polymers. *Prog. Polym. Sci.* **1990**, 15, 751-823.
7. Schacht, E. H.; Goethals, E. J. Cationic polymerization of cyclic amines. 3. Polymerization of azetidine. *Makromol. Chem.* **1974**, 175, 3447-3459.
8. Sarazen, M. L.; Jones, C. W. Insights into Azetidine Polymerization for the Preparation of Poly(propylenimine)-Based CO₂ Adsorbents. *Macromolecules*. **2017**, 50, 9135-9143.
9. Dhende, V. P.; Samanta, S.; Jones, D. M.; Hardin, I. R.; Locklin, J. One-Step Photochemical Synthesis of Permanent, Nonleaching, Ultrathin Antimicrobial Coatings for Textiles and Plastics. *ACS Appl. Mater. Interfaces*. **2011**, 3, 2830-2837.
10. Zou, G. F.; Zhao, J.; Luo, H. M.; McCleskey, T. M.; Burrell, A. K.; Jia, Q. X. Polymer-assisted-deposition: a chemical solution route for a wide range of materials. *Chem. Soc. Rev.* **2013**, 42, 439-449.
11. Hicks, J. C.; Drese, J. H.; Fauth, D. J.; Gray, M. L.; Qi, G.; Jones, C. W. Designing Adsorbents for CO₂ Capture from Flue Gas-Hyperbranched Aminosilicas Capable of Capturing CO₂ Reversibly. *J. Am. Chem. Soc.* **2008**, 130, 2902-2903.
12. Goethals, E. J.; Schacht, E. H.; Bogaert, Y. E.; Ali, S. I.; Tezuka, Y. The Polymerization of Azetidines and Azetidine Derivatives. *Polym. J.* **1980**, 12, 571-581.
13. Hashimoto, S.; Yamashita, T. Ring-Opening Polymerization of 1-Benzylazetidine. *J. Macromol. Sci., Part A*. **1986**, 23, 295-304.
14. Hashimoto, S.; Yamashita, T.; Hino, J. Ring-Opening Polymerization of 1-Substituted Azetidine. I. Polymerization of 1-[beta]-Cyanoethylazetidine with Cationic Initiators. *Polym. J.* **1977**, 9, 19-22.
15. Lavagnino, E. R.; Chauvette, R. R.; Cannon, W. N.; Kornfeld, E. C. Conidine—Synthesis, Polymerization and Derivatives. *J. Am. Chem. Soc.* **1960**, 82, 2609-2613.
16. Oike, H.; Washizuka, M.; Tezuka, Y. Cationic ring-opening polymerization of N-phenylazetidine. *Macromol. Chem. Phys.* **2000**, 201, 1673-1678.
17. Schacht, E. H.; Goethals, E. J. Cationic polymerization of cyclic imines. I. 1,3,3-trimethylazetidine. *Makromol. Chem.* **1973**, 167, 155-169.
18. Saegusa, T.; Nagura, Y.; Kobayashi, S. Isomerization Polymerization of 1,3-Oxazine. I. Polymerization of Unsubstituted 5,6-Dihydro-4H-1,3-oxazine Giving Poly(N-formyltrimethylenimine) and Its Alkaline Hydrolysis of Poly(trimethylenimine). *Macromolecules*. **1973**, 6, 495-498.
19. Pang, S. H.; Lively, R. P.; Jones, C. W. Oxidatively-Stable Linear Poly(propylenimine)-Containing Adsorbents for CO₂ Capture from Ultradilute Streams. *ChemSusChem*. **2018**, 11, 2628-2637.
20. Bakkali-Hassani, C.; Coutouly, C.; Gleede, T.; Vignolle, J.; Wurm, F. R.; Carlotti, S.; Taton, D. Selective Initiation from Unprotected Aminoalcohols for the N-Heterocyclic Carbene-Organocatalyzed Ring-Opening Polymerization of 2-Methyl-N-tosyl Aziridine: Telechelic and Block Copolymer Synthesis. *Macromolecules*. **2018**, 51, 2533-2541.
21. Bakkali-Hassani, C.; Rieger, E.; Vignolle, J.; Wurm, F. R.; Carlotti, S.; Taton, D. The organocatalytic ring-opening polymerization of N-tosyl aziridines by an N-heterocyclic carbene. *Chem. Commun.* **2016**, 52, 9719-9722.
22. Bakkali-Hassani, C.; Rieger, E.; Vignolle, J.; Wurm, F. R.; Carlotti, S.; Taton, D. Expanding the scope of N-heterocyclic carbene-organocatalyzed ring-opening polymerization of N-tosyl aziridines using functional and non-activated amine initiators. *Eur. Polym. J.* **2017**, 95, 746-755.
23. Gleede, T.; Rieger, E.; Homann-Müller, T.; Wurm, F. R. 4-Styrenesulfonyl-(2-methyl)aziridine: The First Bivalent Aziridine-Monomer for Anionic and Radical Polymerization. *Macromol. Chem. Phys.* **2018**, 219, 1700145.
24. Gleede, T.; Rieger, E.; Liu, L.; Bakkali-Hassani, C.; Wagner, M.; Carlotti, S.; Taton, D.; Andrienko, D.; Wurm, F. R. Alcohol- and Water-Tolerant Living Anionic Polymerization of Aziridines. *Macromolecules*. **2018**, 51, 5713-5719.
25. Homann-Müller, T.; Rieger, E.; Alkan, A.; Wurm, F. R. N-Ferrocenylsulfonyl-2-methylaziridine: the first ferrocene monomer for the anionic (co)polymerization of aziridines. *Polym. Chem.* **2016**, 7, 5501-5506.
26. Mbarushimana, P. C.; Liang, Q.; Allred, J. M.; Rupar, P. A. Polymerizations of Nitrophenylsulfonyl-Activated Aziridines. *Macromolecules*. **2018**, 51, 977-983.
27. Rieger, E.; Alkan, A.; Manhart, A.; Wagner, M.; Wurm, F. R. Sequence-Controlled Polymers via Simultaneous Living Anionic Copolymerization of Competing Monomers. *Macromol. Rapid Commun.* **2016**, 37, 833-839.
28. Rieger, E.; Blankenburg, J.; Grune, E.; Wagner, M.; Landfester, K.; Wurm, F. R. Controlling the Polymer Microstructure in Anionic Polymerization by Compartmentalization. *Angew. Chem., Int. Ed. Engl.* **2017**, 57, 2483-2487.
29. Rieger, E.; Gleede, T.; Weber, K.; Manhart, A.; Wagner, M.; Wurm, F. R. The living anionic polymerization of activated aziridines: a systematic study of reaction conditions and kinetics. *Polym. Chem.* **2017**, 8, 2824-2832.
30. Rieger, E.; Manhart, A.; Wurm, F. R. Multihydroxy Polyamines by Living Anionic Polymerization of Aziridines. *ACS Macro Lett.* **2016**, 5, 195-198.
31. Thomi, L.; Wurm, F. R. Aziridine Termination of Living Anionic Polymerization. *Macromol. Rapid Commun.* **2014**, 35, 585-589.
32. Thomi, L.; Wurm, F. R. Living Anionic Polymerization of Functional Aziridines. *Macromol. Symp.* **2015**, 349, 51-56.
33. Wang, X.; Liu, Y.; Li, Z.; Wang, H.; Gebru, H.; Chen, S.; Zhu, H.; Wei, F.; Guo, K. Organocatalyzed Anionic Ring-Opening Polymerizations of N-Sulfonyl Aziridines with Organic Superbases. *ACS Macro Lett.* **2017**, 6, 1331-1336.
34. Reisman, L.; Mbarushimana, C. P.; Cassidy, S. J.; Rupar, P. A. Living Anionic Copolymerization of 1-(Alkylsulfonyl)aziridines to Form Poly(sulfonylaziridine) and Linear Poly(ethylenimine). *ACS Macro Lett.* **2016**, 5, 1137-1140.
35. Rieger, E.; Gleede, T.; Manhart, A.; Lamla, M.; Wurm, F. R. Microwave-Assisted Desulfonylation of Polysulfonamides toward Polypropylenimine. *ACS Macro Lett.* **2018**, 7, 598-603.

36. Stewart, I. C.; Lee, C. C.; Bergman, R. G.; Toste, F. D. Living Ring-Opening Polymerization of N-Sulfonylaziridines: Synthesis of High Molecular Weight Linear Polyamines. *J. Am. Chem. Soc.* **2005**, *127*, 17616-17617.
37. Reisman, L.; Rowe, E. A.; Liang, Q.; Rupar, P. A. The anionic ring-opening polymerization of N-(methanesulfonyl)azetidene. *Polym. Chem.* **2018**, *9*, 1618-1625.
38. Price, C. C. Polyethers. *Acc. Chem. Res.* **1974**, *7*, 294-301.
39. See the discussion on kinetics located in the supporting information for a more detailed explanation.
40. Beckingham, B. S.; Sanoja, G. E.; Lynd, N. A. Simple and Accurate Determination of Reactivity Ratios Using a Nonterminal Model of Chain Copolymerization. *Macromolecules.* **2015**, *48*, 6922-6930.
41. Lee, B. F.; Wolffs, M.; Delaney, K. T.; Sprafke, J. K.; Leibfarth, F. A.; Hawker, C. J.; Lynd, N. A. Reactivity Ratios and Mechanistic Insight for Anionic Ring-Opening Copolymerization of Epoxides. *Macromolecules.* **2012**, *45*, 3722-3731.
42. Zhang, W.; Allgaier, J.; Zorn, R.; Willbold, S. Determination of the Compositional Profile for Tapered Copolymers of Ethylene Oxide and 1,2-Butylene Oxide by In-situ-NMR. *Macromolecules.* **2013**, *46*, 3931-3938.
43. As a control, to confirm that the growing chain end's affect is negligible, the kinetics of the copolymerization were studied using a different monomer feed ratio (70:30, ***oTsAzet:pTsAzet***) (Figure S3). The reactivity ratios, in this case were found to be 1.60 and 0.62 for ***oTsAzet*** and ***pTsAzet***, respectively.
44. Kelen, T.; Tüdös, F. Analysis of the Linear Methods for Determining Copolymerization Reactivity Ratios. I. A New Improved Linear Graphic Method. *J. Macromol. Sci.: Part A – Chem.* **1975**, *9*, 1-27.
45. Cuvigny, T.; Larchevêque, M. Clivage réducteur des sulfonamides et des sulfonates par les métaux alcalins dissous dans le hmp. *J. Organomet. Chem.* **1974**, *64*, 315-321.
46. Matyjaszewski, K.; Shipp, D. A.; McMurtry, G. P.; Gaynor, S. G.; Pakula, T. Simple and effective one-pot synthesis of (meth)acrylic block copolymers through atom transfer radical polymerization. *J. Polym. Sci., Part A: Polym. Chem.* **2000**, *38*, 2023-2031.
47. Ratkanthwar, K.; Hadjichristidis, N.; Mays, J. High Vacuum Techniques for Anionic Polymerization. In *Anionic Polymerization: Principles, Practice, Strength, Consequences and Applications*, Hadjichristidis, N.; Hirao, A., Eds. Springer: Tokyo, Japan, 2015; pp 19-59.
48. Lu, W.; Huang, C.; Hong, K.; Kang, N.-G.; Mays, J. W. Poly(1-adamantyl acrylate): Living Anionic Polymerization, Block Copolymerization, and Thermal Properties. *Macromolecules.* **2016**, *49*, 9406-9414.
49. Wang, W.; Schlegel, R.; White, B. T.; Williams, K.; Voyloy, D.; Steren, C. A.; Goodwin, A.; Coughlin, E. B.; Gido, S.; Beiner, M.; Hong, K.; Kang, N.-G.; Mays, J. High Temperature Thermoplastic Elastomers Synthesized by Living Anionic Polymerization in Hydrocarbon Solvent at Room Temperature. *Macromolecules.* **2016**, *49*, 2646-2655.
50. Nikos, H.; Hermis, I.; Stergios, P.; Marinos, P. Anionic polymerization: High vacuum techniques. *J. Polym. Sci., Part A: Polym. Chem.* **2000**, *38*, 3211-3234.
51. Carmean, R. N.; Figg, C. A.; Becker, T. E.; Sumerlin, B. S. Closed-System One-Pot Block Copolymerization by Temperature-Modulated Monomer Segregation. *Angew. Chem., Int. Ed. Engl.* **2016**, *55*, 8624-8629.
52. Gleede, T.; Rieger, E.; Blankenburg, J.; Klein, K.; Wurm, F. R. Fast Access to Amphiphilic Multiblock Architectures by the Anionic Copolymerization of Aziridines and Ethylene Oxide. *J. Am. Chem. Soc.* **2018**, *140*, 13407-13412.
53. Wiebke, F.; Blandine, B.; Sylvain, P.; Marta, K.; Ioanna, A.; Andrea, J.; Michael, G.; Rainer, H. Synthesis of Linear Polyamines with Different Amine Spacings and their Ability to Form dsDNA/siRNA Complexes Suitable for Transfection. *Macromol. Biosci.* **2010**, *10*, 1073-1083.

Table of Contents artwork:

