

Chemical Science

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: C. Han, Z. Tang, J. Liu, S. Jin and Y. Xu, *Chem. Sci.*, 2019, DOI: 10.1039/C8SC05813J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Efficient photoredox conversion of alcohol to aldehyde and H₂ by heterointerface engineering of bimetal-semiconductor hybrids†

Chuang Han,^{ab} Zi-Rong Tang,^b Junxue Liu,^c Shengye Jin,^{*c} and Yi-Jun Xu^{*ab}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Controllable and precise design of bimetal- or multimetal-semiconductor nanostructures with efficient light absorption, charge separation and utilization is strongly desired for photoredox catalysis applications in solar energy conversion. Taking advantage of Au nanorods, Pt nanoparticles, and CdS as plasmonic metal, nonplasmonic co-catalyst and semiconductor respectively, we report a steerable approach to engineer the heterointerface of bimetal-semiconductor hybrids. We show that the ingredient composition and spatial distribution between bimetal and semiconductor significantly influence the redox catalytic activity. The CdS deposited anisotropic Pt-tipped Au nanorods, which features the improved light absorption, structure-enhanced electric field distribution and spatially regulated multichannel charge transfer, shows distinctly higher photoactivity than blank CdS and other metal-CdS hybrids for simultaneous H₂ and value-added aldehyde production from one redox cycle.

Introduction

Harvesting solar energy to drive artificial photosynthesis for the production of value-added chemicals and renewable energy is a promising strategy to solve the growing worldwide energy crisis.^{1–5} However, the solar-to-chemical conversion efficiency of semiconductor is often limited by their finite light absorption and/or slow charge separation rates and reaction kinetics.^{6–10} Integrating different functional materials into a single hybrid structure with precise design holds great promise for constructing efficient composite photocatalysts owing to the synergistic properties induced by the interactions between these components in an integrative ensemble.^{5, 11–16}

Bimetallic nanostructures, coupling surface plasmon resonance (SPR, **Scheme S1**) functionality with efficient co-catalytic effect, could be an ideal candidate to simultaneously modulate the photoabsorption and steer the multichannel charge separation/transfer and reaction kinetics of semiconductor.^{17–21} The design of effective bimetal-semiconductor composite photocatalysts requires the rational understanding of structural design principle, because the randomly hybridizing counterparts would often shield the SPR intensity and local electric field of plasmonic metal or weaken the net photoabsorption of semiconductor.^{22–25} In addition,

recent research has predominantly focused on charge separation and transfer mainly occurring at the plasmonic metal domains (*i.e.*, SPR-induced sensitization effect),^{25–27} and the quantum efficiency over such systems is still relatively low in contrast to those by semiconductor photoexcitation. To obtain a high photocatalytic activity, the structural design of special composite catalysts to synergistically utilize SPR enhancement mechanism and band-gap photoexcitation of semiconductor is desirable.^{28, 29} However, thus far, it is still unclear how the composition and structural arrangement of plasmonic-nonplasmonic bimetal hybrids comprehensively affect their interactions with semiconductor and the subsequent band alignment, charge transfer dynamics, local electric field distribution and redox catalysis performance.

Herein, we report a controllable way to design bimetal-semiconductor hybrids with different heterointerfaces for progressively improved redox catalysis conversion of alcohol to H₂ and aldehyde under visible-near-infrared (Vis-NIR) light irradiation. Au nanorods (NRs) and Pt nanoparticles (NPs) are promising metallic nanocrystals platform for fabricating metal-semiconductor hybrids due to their tunable longitudinal-SPR absorption in the near-infrared (NIR) region and high efficiency for catalysis proton reduction reaction, respectively.^{13, 30–34} In this regard, we chose Au NRs and Pt NPs to form the plasmonic bimetal component. CdS, a well-known visible (Vis) light responsive photocatalyst with a direct band-gap of around 2.4 eV,^{8, 35–38} is chosen as the semiconductor component. Integrating co-catalytic factor with semiconductor photoexcitation and SPR resonance modes in different optical response region by rational assembly of nonplasmonic Pt NPs and semiconductor on CdS on the surface of Au NRs, can provide the spatial transfer multichannel for electrons and boost the local electric field, promoting the generation and

^a State Key Laboratory of Photocatalysis on Energy and Environment, College of Chemistry, Fuzhou University, Fuzhou, 350116, China. E-mail: yjxu@fzu.edu.cn

^b College of Chemistry, New Campus, Fuzhou University, Fuzhou, 350116, China.

^c State Key Laboratory of Molecular Reaction Dynamics, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian, Liaoning, 116023, China. E-mail: sjin@dicp.ac.cn.

† Electronic Supplementary Information (ESI) available: Additional characterizations and discussions, 13 figures and 3 tables. See DOI: 10.1039/x0xx00000x




migration of electron-hole charge carriers. As a result, the CdS deposited anisotropic Pt-tipped Au NRs (Au-Pt@CdS), which features the multiple metal-semiconductor and metal-metal heterojunctions, exhibits distinctly higher photoactivity than blank CdS and other metal-CdS hybrids counterparts for photocatalytic conversion of alcohol to aldehyde and H₂ by simultaneous utilization of photogenerated holes and electrons in one redox cycle. Resorting to electric field simulations, transient absorption spectroscopy and multiple control experiments, it is demonstrated that the redox photoactivity is highly dependent on the ingredient composition and spatial distribution of metal component because they play a significant role in affecting multiple electron transfer pathways and local electric field enhancement.

Results and discussion

The fabrication process is based on progressively seed-mediated growth, as illustrated in **Scheme 1**. The stronger interaction between the cetyltrimethylammonium bromide (CTAB) surface-capping molecules and the side facets of Au NRs results in the higher packed density of CTAB at the sides than that at the ends of Au NRs.^{24, 25} By taking advantage of this anisotropic surface structure, Pt NPs were firstly selectively deposited on the tips of Au NRs seeds for preparation of anisotropic Pt-tipped Au NRs (Au-Pt). The spatial distribution of Pt on the Au NRs surface depends on the surface-capping molecules. Pt-covered Au NRs (Au@Pt) can be synthesized by decreasing the concentration of CTAB molecules. The Au-based NRs were subsequently used as seeds for assembly of semiconductor CdS *via* a facile and controllable refluxing process. It should be noticed that our synthesis reaction is performed at low temperature (85 °C) and in the absence of metal ion sources (*e.g.*, Ag⁺ or Cu²⁺) as a "bridge" between Au NRs and CdS to achieve the heterogrowth,^{39, 40} which can prevent the Au NRs from undesired reshaping in the wet-chemistry growth process.

The samples obtained in each growth stage were characterized using scanning electron microscopy (SEM) and transmission electron microscopy (TEM) analysis. The average

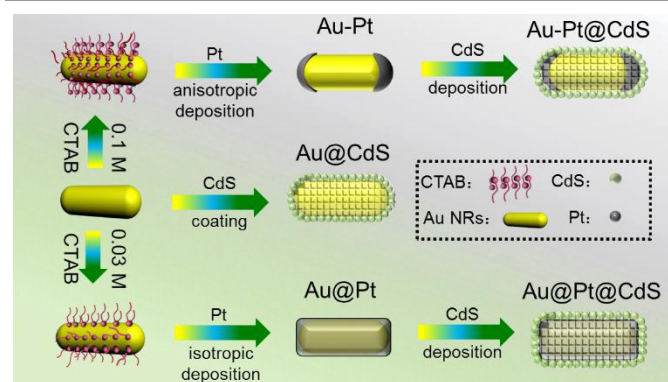

Scheme 1 Schematic flowchart illustrating the controllable preparation of CdS deposited Pt-tipped Au NRs (Au-Pt@CdS), CdS deposited Au NRs (Au@CdS) and CdS deposited Pt-covered Au NRs (Au@Pt@CdS).

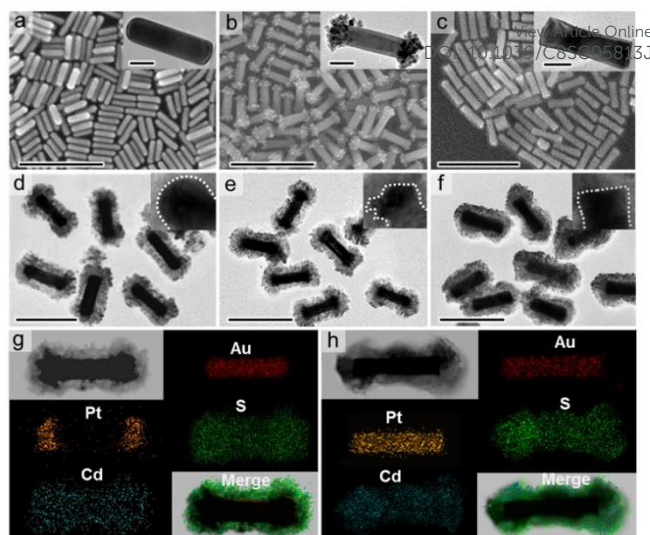


Fig. 1 SEM images of (a) Au NRs, (b) Au-Pt, and (c) Au@Pt, scale bar, 200 nm. The insets of (a-c) show TEM images of corresponding samples, scale bar, 20 nm. TEM images of (d) Au@CdS, (e) Au-Pt@CdS and (f) Au@Pt@CdS, scale bar, 200 nm. Elemental mapping results of (g) Au-Pt@CdS and (h) Au@Pt@CdS.

diameter and length of original Au NRs are 29.0 and 92.5 nm, respectively (**Fig. 1a** and **Fig. S1**). After the growth of Pt onto the tips of Au NRs, the smooth ends of Au NRs become gibbous, while the surface at the side of Au NRs remains almost unchanged (**Fig. 1b** and **Fig. S2**). The average diameter at the middle of Au-Pt NRs is 29.1 nm, and the average length is increased to 114.0 nm. These results suggest that Pt tends to anisotropically deposit at the two ends of Au NRs. **Fig. 1c** and **Fig. S3** show the morphology of Au@Pt with an average diameter of 33.2 nm and length of 107.9 nm, which are enclosed by the Pt shell.

The morphology information of CdS deposited Au NRs (Au@CdS), CdS deposited Pt-tipped Au NRs (Au-Pt@CdS) and CdS deposited Pt-covered Au NRs (Au@Pt@CdS) are disclosed in **Fig. 1d-f** and **Fig. S4**. No noticeable structural deformation of Au-based seeds can be discerned after depositing CdS nanoshells, which should benefit from the mild reaction process at a low temperature. For Au@CdS, we can clearly see from **Fig. 1d** and **Fig. S4a-c** that the Au NRs core with hemispherical ends are coated with a loose and porous CdS semiconductor layer in thicknesses of 15–20 nm. TEM images of Au-Pt@CdS (**Fig. 1e**) and Au@Pt@CdS (**Fig. 1f**) indicate their similar overall shape to Au@CdS. However, the bimetal cores in Au-Pt@CdS and Au@Pt@CdS respectively show the convex (**Fig. S4d-f**) and bar-like (**Fig. S4g-i**) shape. Elemental mapping analysis on Au-Pt@CdS (**Fig. 1g**) discloses that the Pt is located at the ends of Au NRs, further confirming the tip-coated morphology of Au-Pt core in Au-Pt@CdS. Elemental mapping study for Au@Pt@CdS indicates the layers of Pt and CdS shells are both isotropically deposited on the entire surface of Au NRs (**Fig. 1h**). The morphology of blank CdS was also analyzed (**Fig. S5**), suggesting that blank CdS are composed of tiny NPs.

X-ray diffraction (XRD) patterns of blank CdS and metal-CdS hybrids are shown in **Fig. 2a**, in which the diffraction peaks of hexagonal phases CdS (JCPDS, No. 41-1049) and cubic phases



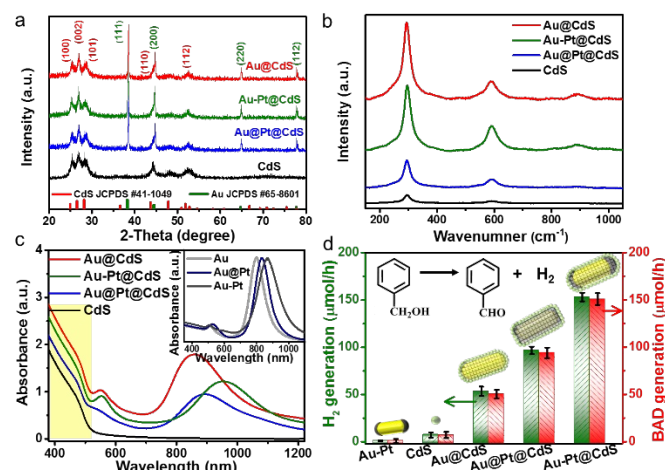


Fig. 2 (a) XRD patterns, (b) Raman spectra and (c) absorption spectra of CdS and metal-CdS hybrids. The inset of (c) shows the normalized absorption spectra of Au, Au@Pt and Au-Pt for comparison. (d) H₂ and benzaldehyde (BAD) generation rate in the photocatalytic conversion of benzyl alcohol (BA) under Vis-NIR light ($\lambda > 420$ nm) irradiation over Au-Pt, CdS and metal-CdS hybrids. The insets of (d) show the formula for photocatalytic conversion of BA and the corresponding structural models of the samples.

Au (JCPDS, No. 65-8601) can be well identified. The characteristic diffraction peaks of Pt are hardly observed due to their relatively low content in the composites.⁴¹ Raman spectra, as displayed in **Fig. 2b**, show that blank CdS exhibits the Raman signals at 299 cm⁻¹, 597 cm⁻¹ and 890 cm⁻¹, which are identified as characteristic peaks of the longitudinal optical (LO) phonons of CdS phase.⁴² In comparison with CdS, all of these peaks are significantly intensified for CdS deposited metal hybrids, suggesting an enhanced light-matter interaction due to the strong electric field enhancement near the surface of plasmonic Au-based NRs.⁴²

The evolution of optical absorption spectra along with the structural variation of the samples is displayed in **Fig. 2c**. The raw Au NRs have two SPR absorption bands centered at 510 and 800 nm, which are respectively assigned to transverse-SPR (T-SPR) and longitudinal-SPR (L-SPR) photoabsorption (inset of **Fig. 2c**). After Pt is deposited on Au NRs, the L-SPR band red-shifts to 833 and 865 nm for Au@Pt and Au-Pt, respectively. In addition, the T-SPR band of Au@Pt slightly red-shifts to 527 nm, while almost no change occurs for that of Au-Pt, which is probably due to the selective deposition of Pt onto the tips of Au NRs for the Au-Pt sample.²⁴ Both the T-SPR and L-SPR band are further red-shifted after the semiconductor CdS is grown onto Au@Pt and Au-Pt, resulting from the increase of surrounding dielectric constant.^{31, 43} The blank CdS and metal-CdS hybrids disclose the similar optical absorption threshold located at 520 nm, which is corresponding to the optical band-gap of about 2.4 eV in pristine CdS semiconductor. However, the absorption of metal-CdS hybrids is higher than that of blank CdS throughout the whole Vis to NIR region due to the contribution from the SPR absorption of Au-based NRs.^{36, 43}

We tested the samples as dual-function photocatalysts for conversion of benzyl alcohol (BA) to H₂ and benzaldehyde (BAD) under Vis-NIR light ($\lambda > 420$ nm, **Fig. S6**) irradiation. We initially studied the effects of different components proportion

on the photoactivity and determined the sample with optimal photoactivity, as shown in **Fig. S7a-c**. The direct photoactivity comparison with the H₂ and BAD production rates over the samples with the optimal components proportion is shown in **Fig. 2d**. Notably, the molar ratio of reduction product (H₂) and oxidation product (BAD) is calculated to be *ca.* 1.0, suggesting a stoichiometric dehydrogenation reaction. The fine control of the heterointerface of metal-semiconductor composites can result in the progressively optimal photoactivity. Blank Au-Pt and CdS show very low activity for H₂ and BAD production due to the fast recombination of electron-hole pairs.^{11, 12, 20, 31} For binary Au@CdS, the H₂ evolution rate is enhanced to 53.2 μmol h⁻¹. After coupling co-catalyst Pt with Au@CdS, the H₂ evolution rates over ternary Au@Pt@CdS and Au-Pt@CdS reach to 96.6 μmol h⁻¹ and 153.0 μmol h⁻¹, respectively, which are about 13.4 and 21.2 times as high as that over blank CdS (7.2 μmol h⁻¹). Notably, the anisotropic Au-Pt@CdS exhibits higher H₂ and BAD production rates than Au@CdS and Au@Pt@CdS, implying that the photoactivity enhancement of bimetal-semiconductor composites is not only dependent on the ingredient composition, but also affected by the spatial distribution of metal components. For comparison, we also investigated the photoactivity of CdS supported Au-Pt NRs (Au-Pt/CdS, **Fig. S7d**) and the result shows that the photoactivity of such supported Au-Pt/CdS is much lower than that of Au-Pt@CdS, which manifests that the core-shell configuration can strengthen the interfacial contact between metal and semiconductor CdS, thereby facilitating the charge carriers separation and transfer across the interfacial domain and consequently boosting the photoactivity.

The photoactivity enhancement and general applicability of Au-Pt@CdS were further investigated by conversion of other aromatic alcohols (R-PhCH₂OH, R = OCH₃, CH₃, Cl and OH) with different substituent groups. By taking the unsubstituted BA (**Fig. 2d**) as reference, **Fig. S8a-d** indicate that the H₂ and aldehydes production rates are enhanced by electron-donating substituents (R = OCH₃ and CH₃) and retarded by electron-withdrawing groups (R = Cl and OH) for all photocatalysts. The Au-Pt@CdS displays higher photoactivity than blank CdS and other metal-CdS hybrids for conversion of these alcohols. In addition, the photocatalytic performance of Au-Pt@CdS is either comparable or superior to other similar coupled reaction systems for simultaneous H₂ and value-added chemicals production (**Table S1**).

Fig. 3a shows the long-term photocatalytic performance of the Au-Pt@CdS toward conversion of BA under Vis-NIR light irradiation. After 5 h of irradiation, the conversion of BA is about 80.1% and the selectivity for BAD reaches 94.0%. The H₂ and BAD production rates display no obvious decrease during four successive runs within 20 h. In addition, the morphology, composition and crystalline structure of Au-Pt@CdS after recycling photocatalytic reactions are similar to the fresh sample (**Fig. S9**). These results indicate the good stability of Au-Pt@CdS in our photocatalytic reaction conditions. To understand the roles respectively played by semiconductor and metal components of Au-Pt@CdS in the photoactivity enhancement, we performed the wavelength-dependent



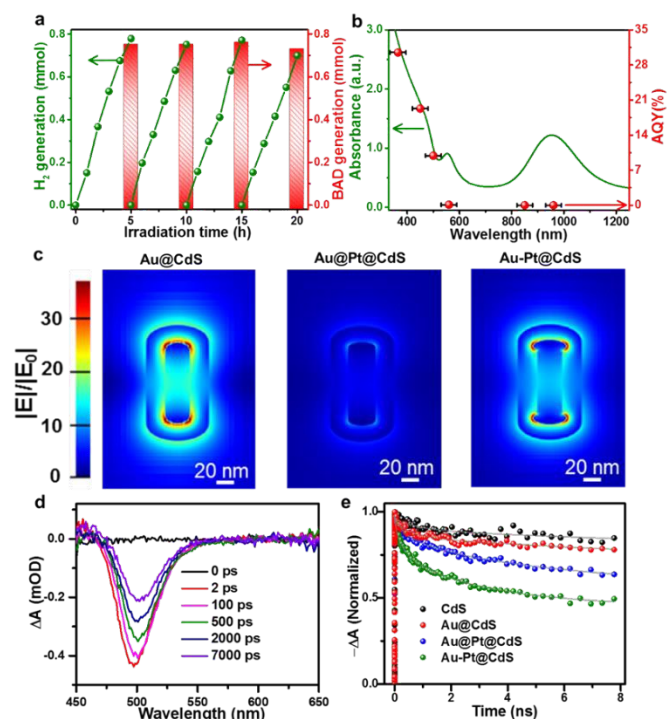


Fig. 3 (a) Long-term photocatalytic conversion of BA using Au-Pt@CdS under Vis-NIR light ($\lambda > 420$ nm) irradiation. (b) Absorption spectra of Au-Pt@CdS and apparent quantum yield efficiency (AQY) of hydrogen evolution from BA under different monochromatic lights. Error bars refer to the wavelength range of the incident light. (c) Local electric field distributions of metal-CdS hybrids at L-SPR excitation calculated by finite-difference time-domain method. (d) Transient absorption (TA) spectra of Au-Pt@CdS with time delays after 370 nm excitation. (e) Comparison of the exciton bleach recovery kinetics for CdS and metal-CdS hybrids probed at 503 nm and their corresponding fits.

experiment. As shown in **Fig. 3b**, the action spectrum of apparent quantum yield efficiency (AQY) is in agreement with the band-gap absorption of CdS component. This result reveals that the photocatalytic conversion of BA to produce BAD and H₂ proceeds through the light absorption by semiconductor CdS component instead of SPR excitation of Au-Pt bimetal.^{24,44} Therefore, it is crucial to explore what is the specific role of plasmonic Au and nonplasmonic Pt in improving the photoactivity of semiconductor CdS, and what kind of contribution of the SPR excitation is associated with bimetallic Au-Pt in influencing charge carriers separation photogenerated from CdS in Au-Pt@CdS.

Since electric field distribution and intensity are related to the SPR enhancement,^{25,45,46} we simulated the electric field ($|E|/|E_0|$) distribution around different metal-CdS hybrids, aiming to ascertain the region of electric field enhancement upon SPR excitation and its possible contribution to the photoactivity enhancement. As shown in **Fig. 3c**, differing from strong electric field distribution at both ends of binary Au@CdS, the ternary Au@Pt@CdS sample exhibits weak electric field enhancement. When the continuous Pt shell encapping the entire surface of Au NRs in Au@Pt@CdS is replaced by discrete Pt selectively tipped onto the two ends of Au NRs in Au-Pt@CdS, the electric field enhancement around the surface of Au-Pt@CdS is greatly boosted. The weakest electric field enhancement of Au@Pt@CdS could be ascribed

to the plasmon-induced electrons transfer from Au to Pt and the serious plasmon damping effect of the continuous Pt shell.^{23-25,36}

According to the simulation result, the maximum value of electric field enhancement at the outside surface of CdS for Au@CdS, Au-Pt@CdS and Au@Pt@CdS are about 15, 13 and 5, respectively. The enhanced electric field can improve the light harvesting ability of the catalyst, and increase the generation and separation rate of electron-hole pairs near the surface of the semiconductor material.⁴⁵⁻⁴⁷ However, the trend in electric field enhancement (i.e., Au@CdS > Au-Pt@CdS >> Au@Pt@CdS) is inconsistent with that of photoactivity (i.e., Au-Pt@CdS > Au@Pt@CdS > Au@CdS). This indicates that in addition to the effect of electric field enhancement factor on the photoactivity of metal-semiconductor hybrids, other factors should be simultaneously considered to account for the difference in photoactivity enhancement.

We then investigated charge transfer dynamics in CdS and metal-CdS hybrids by using ultrafast transient absorption (TA) spectroscopy. Upon 370 nm excitation, a negative absorption peak at about 500 nm corresponding to the ground state bleach (GSB) signal of CdS component is formed due to the band-filling by photoinduced electrons and holes (**Fig. 3d** and **Fig. S10**). The recovery kinetics of this GSB reflects the charge dissipating processes by recombination and/or charge transfer (**Fig. 3e**). In blank CdS, the recovery kinetics originates from the recombination of electrons and holes and possible charge trapping process into defects.^{15,48} In the presence of metal nanostructures, the kinetics become significantly faster. We attribute this observation to the photoinduced electrons transfer from CdS to the metal ingredient, as reported in similar semiconductor-metal composites.^{11,29,49} In order to quantitatively determine the electrons transfer rate, the recovery kinetics were fitted by a biexponential function and the electrons transfer rates were estimated by comparing the charge transfer rate constant (k_{ct} , see **Equation S1-3** and **Table S2**).⁵⁰ In comparison with blank CdS, the charge transfer rate over binary Au@CdS is increased, which indicates an electrons transfer channel from CdS to Au because the work function of Au (5.10 eV) is larger than that of CdS (4.20 eV).^{51,52} After the Pt NPs (with work function of 5.40 eV) are deposited on Au NRs, the k_{ct} of both Au@Pt@CdS and Au-Pt@CdS are further enhanced. The highest k_{ct} value for Au-Pt@CdS signifies that the Au-Pt bimetal nanostructure is more effective than Au@Pt in facilitating the photoexcited charge transfer in the photocatalytic system, due to the additional interfacial electrons transfer channels from CdS to Au and to Pt guaranteed by the direct contact and matched band alignment among three components (**Fig. S11**).^{51,52}

To study the effect of SPR excitation on photoactivity enhancement, we performed wavelength-control experiment over Au-Pt@CdS under selective photoexcitation of plasmonic Au-Pt component (**Fig. S12a**).^{31,53} It is seen from **Fig. S12b** that the Au-Pt@CdS hybrids show only trace photoactivity under SPR excitation alone, indicating the effect of hot electrons injection from Au-Pt to CdS on the photoactivity is negligible. When we used the photon energy at 570 nm to excite the T-SPR of Au-Pt@CdS in TA measurement, the sample shows no



signal corresponding to excitation and relaxation kinetics (Fig. S12c), which further confirms the absence of hot electrons transfer process. Thus, the SPR enhancement mechanisms should be interpreted in terms of electric field effect.⁴⁵ In addition, control experiments under selective photoexcitation of CdS or simultaneous photoexcitation of CdS and Au-Pt (Fig. S13a) disclose that the Au-Pt@CdS exhibits enhanced photoactivity as compared to bare CdS under both irradiation conditions, and the photoactivity enhancement is more prominent under simultaneous photoexcitation of CdS and Au-Pt component (Fig. S13b). We also prepared nonplasmonic Pt-loaded CdS (Pt-CdS) through the well-reported photodeposition method.^{44, 54} The photocatalytic activity of nonplasmonic Pt-CdS is much lower than that of plasmonic Au-Pt@CdS under Vis-NIR light irradiation (Fig. S13c).

The above joint results signify that the promoted photoactivity of Au-Pt@CdS is induced by the synergistic coupling of the band-gap photoexcitation of semiconductor CdS with the electric field enhancement and the electrons sink effect of Au-Pt bimetal, as depicted in Fig. 4a.^{55, 56} Specifically, when Au-Pt@CdS ternary heterostructure is illuminated by Vis-NIR light ($\lambda > 420$ nm), CdS component can harvest short-wavelength visible light ($420 \text{ nm} < \lambda < 520 \text{ nm}$), yielding electron-hole charge carriers (e^-h^+). Meanwhile, the SPR excitation of plasmonic Au-Pt bimetal by longer-wavelength light irradiation provides extra electric field enhancement to improve the photoabsorption, and promote the generation and separation of electron-hole pairs in CdS.^{45, 46, 57} Subsequently, the photogenerated electrons transfer from the conduction band (CB) of CdS to the component of anisotropic Au-Pt bimetal. The protons (H^+) diffuse through the loose and porous CdS thin layer and react with electrons to generate H_2 .^{35, 58, 59} The holes retained in the valence band (VB) of CdS can selectively oxidize alcohols to aldehydes, which is the overall activity-limiting step in the redox cycle.^{44, 60} The photogenerated electrons and holes are spatially separated, significantly reducing the recombination probability, which lead to greatly improved photoactivity of Au-Pt@CdS.

The investigation of photoelectrochemical (PEC) process can further reveal the picture of electron transfer and the underlying photoactivity enhancement mechanism. As shown in Fig. 4b, transient photocurrent responses of different samples under chopped Vis-NIR light illumination indicate that the construction of bimetal-semiconductor hybrids is conducive to enhancing the photocurrent of semiconductor CdS, which follows the same order as the photoactivity: Au-Pt@CdS > Au@Pt@CdS > Au@CdS > CdS. This result indicates a more effective separation of electron-hole pairs over Au-Pt@CdS than other electrode samples.^{9, 35, 61, 62} The Au-Pt@CdS and Au@Pt@CdS consist of the same hetero-components, but the anisotropic Au-Pt@CdS exhibits higher photocurrent and photoactivity than isotropic Au@Pt@CdS under Vis-NIR light illumination. This suggests that the inappropriate arrangement of plasmonic-nonplasmonic bimetal heterostructure in Au@Pt@CdS leads to the suppression of electric field enhancement and electrons sink effect, as respectively proved

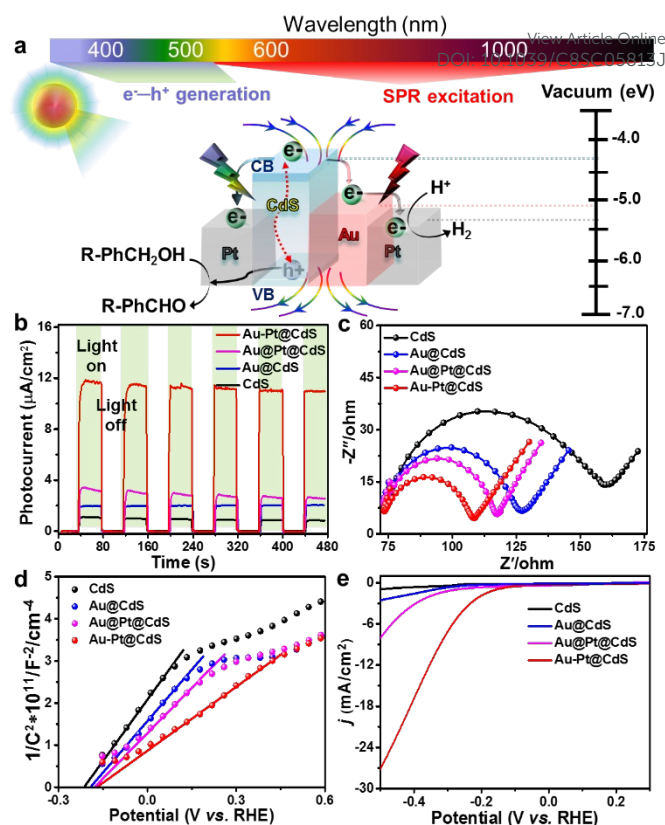


Fig. 4 (a) Schematic illustration of the energy band alignment and SPR-coupled multichannel electrons transfer in Au-Pt@CdS heterostructures. (b) Photocurrent density versus time (I-t) curves, (c) electrochemical impedance spectroscopy (EIS) Nyquist plots and (d) Mott-Schottky plots of CdS and metal-CdS hybrids under Vis-NIR light ($\lambda > 420$ nm) irradiation. (e) Linear sweep voltammetry (LSV) curves of CdS and metal-CdS electrodes.

by the results of electric field simulation (Fig. 3c) and TA characterization (Fig. 3e).^{24, 25}

Electrochemical impedance spectroscopy (EIS, Fig. 4c) and Mott-Schottky (Fig. 4d) analysis were conducted under Vis-NIR light illumination. The arc at middle frequencies of Nyquist plot in Fig. 4c is characteristic of charge transportation resistance.⁶³ Apparently, the diameter of the arc for the Au-Pt@CdS electrode is much smaller than that of CdS, Au@CdS and Au@Pt@CdS, indicating that the resistance of interfacial charge transportation is significantly decreased over Au-Pt@CdS electrode. The Mott-Schottky analysis can be used to provide fundamental insights into the charge carriers density (N_D), which is obtained from the following equation:^{63, 64}

$$N_D = \frac{2}{e\epsilon\epsilon_0} \left(\frac{d\left(\frac{1}{C^2}\right)}{dV} \right)^{-1}$$

Where, C is the capacitance, e is the elementary electronic charge, ϵ_0 is the permittivity in vacuum, and ϵ is the dielectric constant, specifically 8.99 for CdS.⁶³⁻⁶⁵ From the slope in the plot of $1/C^2$ vs. V in Fig. 4d, N_D can be determined by the above equation. A summary of N_D values is given in Table S3. The plot of Au-Pt@CdS electrode shows the smallest slope value among the samples, indicating a much higher N_D than that of CdS, Au@CdS and Au@Pt@CdS. The higher N_D signifies the lower resistance, faster charge transfer rate and consequently the



enhanced PEC and photocatalytic performance. In addition, all plots show the positive slopes, indicating the n-type semiconductor characteristic of CdS.^{63,66} The formed multiple Schottky barrier between n-type CdS semiconductor and Au-Pt bimetal would prevent the electrons from the metal drifting back to the semiconductor.⁶⁷ Based on above results, it can be concluded that Au-Pt can effectively facilitate the generation and transfer of charge carriers from CdS, due to the boosted local electric field and the enriched spatial charge transfer channels. **Fig. 4e** displays the linear sweep voltammetry (LSV) curves of Au-Pt@CdS, Au@Pt@CdS, Au@CdS and CdS electrode without light irradiation, from which it is seen that the addition of nonplasmonic Pt into Au@CdS can obviously enhance the cathodic current density and decrease the overpotential of H₂ production, thus further promoting catalytic efficiency.^{31, 48}

Conclusions

In summary, we have accomplished a controllable design of bimetal-semiconductor hybrids for optimizing the redox photocatalysis performance of alcohol conversion to H₂ and value-added aldehyde for the first time. Experimental results and theoretical analyses indicate that the composition and spatial configurations of metal components have significant influences on photoabsorption, local electric field distribution and photoinduced charge carriers transfer rate in bimetal-semiconductor heterostructures. Compared with blank CdS and other metal-CdS composites, the Au-Pt@CdS exhibits the collective advantages for photoredox catalysis as follows. 1) The unique SPR of Au NRs improves light absorption and induces local electric field enhancement, which can promote the charge carriers generation/migration of CdS. 2) Pt NPs anisotropically located at the tips of Au NRs serve as electrons reservoir and co-catalyst to steer the directional charge flow and facilitate the proton reduction. 3) The intimate and multiple metal-metal and metal-semiconductor heterointerfaces ensures the spatially regulated multichannel electrons transfer and maximized plasmon-exciton interactions. Mechanistic studies demonstrated that the photoactivity of Au-Pt@CdS is driven by the photogenerated charge carriers from semiconductor CdS instead of plasmonic Au-Pt bimetal. It is hoped that this facile strategy for controllable synthesis of bimetal-semiconductor hybrids, as well as the underlying SPR-coupled multichannel electron transfer mechanism illustrated here, could be instructive for further rational design of plasmonic bimetal- or multimetal-semiconductor hybrids toward efficient redox catalysis.

Experimental sections

Chemicals and materials

All chemicals were analytical grade and used without further purification. Hexadecyltrimethylammonium bromide (C₁₉H₄₂NBr, CTAB), silver nitrate (AgNO₃), sodium borohydride (NaBH₄), L-ascorbic Acid (C₆H₈O₆, AA), hydrochloric acid (HCl,

37 wt%) and benzonitrile (C₇H₅F₃, BTF) were purchased from Sigma Aldrich. Benzyl alcohol (C₇H₈O, BA), benzaldehyde (C₇H₆O, BAD) and sodium oleate (C₁₈H₃₃O₂Na, NaOL) were purchased from Aladdin. 4-Methylbenzyl alcohol (C₈H₁₀O), 4-methoxybenzyl alcohol (C₈H₁₀O₂), 4-chlorobenzyl alcohol (C₇H₇ClO), and 4-hydroxybenzyl alcohol (C₇H₈O₂) were supplied by Alfa Aesar. Cadmium acetate (C₄H₆O₄Cd, Cd(Ac)₂), thioacetamide (C₂H₅SN, TAA), chloroauric acid tetrahydrate (HAuCl₄·4H₂O), glycine acid (C₂H₅NO₂, Gly), anhydrous ethanol (C₂H₅OH, EtOH) and chloroplatinic acid hexahydrate (H₂PtCl₆·6H₂O) were obtained from Sinopharm Chemical Reagent Co., Ltd. (Shanghai, China). Deionized water used in the synthesis was obtained from local sources.

Synthesis of Au NRs

The Au NRs were prepared using a seed-mediated growth method.⁶⁸ The seed solution for Au NRs growth was prepared as follows: 5 mL of 0.5 mM HAuCl₄ was mixed with 5 mL of 0.2 M CTAB solution in a 20 mL scintillation vial. 0.6 mL of fresh 0.01 M NaBH₄ was diluted to 1 mL with water and was then injected to the above solution under vigorous stirring (1200 rpm). The solution color changed from yellow to brownish yellow and the stirring was stopped after 2 min. The seed solution was aged at room temperature for 2 h before use. Subsequently, 1.4 g of CTAB and 0.25 g of NaOL were dissolved in 50 mL of warm water (~50 °C) in a 100 mL Erlenmeyer flask. The solution was allowed to cool down to 30 °C and 3.6 mL 4 mM AgNO₃ solution. The mixture was kept undisturbed at 30 °C for 15 min after which 50 mL of 1 mM HAuCl₄ solution was added. The solution became colorless after 90 min of stirring (700 rpm) and 0.3 mL of HCl (37 wt% in water, 12.1 M) was then introduced. After another 15 min of slow stirring at 400 rpm, 0.25 mL of 0.064 M AA was added and the solution was vigorously stirred for 30 s. Finally, 0.4 mL of seed solution was injected into the growth solution. The resultant mixture was stirred for 30 s and left undisturbed at 30 °C for 12 h for NRs growth.

Preparation of Au-Pt

Au-Pt were prepared by using Au NRs as template.²⁴ Briefly, 10 mL of the prepared Au NRs were separated from excess CTAB by centrifugation twice (at 10000 rpm) and redispersed in 0.1 M CTAB solution. Then, 0.568 mL of 0.1 M ascorbic acid was added into 10 mL of as-made Au NRs suspension. 100 µL of 0.01 M H₂PtCl₆·6H₂O and subsequently 0.08 mL of 0.01 M HCl were added to the reaction mixture. The mixture was left undisturbed for 24 h at 30 °C. Pt-covered Au NRs (Au@Pt) were prepared by using Au NRs in 0.03 M CTAB solution as template following the same procedure.

Preparation of Au-Pt@CdS

For the synthesis of Au-Pt@CdS, 10 mL of the as-prepared Au-Pt seeds and 10 mL of aqueous Gly solution (0.2 M) were mixed in a 50 mL vial, and subsequently 300 µL aqueous NaOH solution (2 M) were added to the reaction mixture. The mixture was kept at 30 °C for 30 min without stirring. Next, 200 µL of Cd(Ac)₂ (0.1 M) and TAA (0.1 M) solution were



injected into the above solution drop by drop. The reaction was allowed to proceed at 85 °C under vigorously stirring for 2 h. The suspensions were centrifuged at 12 000 rpm for 10 min and washed with ethanol for three times, and then the precipitations were vacuum dried at 40 °C. Au@CdS, Au@Pt@CdS and blank CdS were also synthesized by the above method, except using the corresponding seeds or blank CTAB (0.1 M) aqueous solution instead of Au-Pt, respectively, in the synthesis process. Au-Pt/CdS sample was prepared by mixing the blank CdS with an appropriate amount of Au-Pt in solution with vigorous stirring for 24 h followed by the wash and dry process similar to Au-Pt@CdS.

Material characterization

The crystal phase properties of the samples were analysed with a Bruker D8 Advance X-ray diffractometer (XRD) using Ni-filtered Cu K α radiation at 40 kV and 40 mA in the 2 θ ranging from 20° to 80° with a scan rate of 0.02° per second. The optical properties of the samples were characterized using the Cary-5000 ultraviolet-visible-near infrared diffuse reflectance spectrophotometer (DRS, Varian Co.). The morphology and elemental distribution of the samples were analysed by field-emission scanning electron microscopy (FESEM) on a FEI Nova NANOSEM 230 spectrophotometer and transmission electron microscopy (TEM), high-resolution TEM (HRTEM) and elements mapping analysis using a JEOL 2100F instrument at an accelerating voltage of 200 kV. Raman spectroscopy was performed on a Renishaw inVia Raman System 1000 with a 532 nm Nd:YAG excitation source at room temperature. X-ray photoelectron spectroscopy (XPS) measurements were performed using a Thermo Scientific ESCA Lab250 spectrometer that consists of a monochromatic Al K α as the X-ray source, a hemispherical analyser, and a sample stage with multiaxial adjustability to obtain the composition on the surface of samples. All of the binding energies were calibrated by the C 1s peak of the surface adventitious carbon at 284.6 eV. The elemental concentrations analysis was performed by an inductively coupled plasma emission spectroscopy instrument (ICP, PerkinElmer Optima 8000). The carriers dynamic were measured by using femtosecond transient absorption spectroscopy (Time-Tech Spectra, femtoTA-100). Part of the 800 nm output pulse from the amplifier was used to pump a TOPAS Optical Parametric Amplifier (OPA) which generates the 370 nm pump beam. The pump pulses were chopped by a synchronized chopper at 500 Hz and the absorbance change was calculated with two adjacent probe pulses (pump-blocked and pump-unblocked), and the pump power was approximately 1 uW. The samples were dispersed in water for all pump-probe characterizations performed under ambient conditions. The photoelectrochemical analysis was carried out in a conventional three-electrode cell using a Pt plate and an Ag/AgCl electrode as the counter electrode and reference electrode, respectively. The electrolyte was 0.2 M Na₂SO₄ aqueous solution containing 0.1 mM BA. The working electrode was prepared on indium-tin oxide (ITO) glass that was cleaned by sonication in ethanol for 30 min and dried at 353 K. The boundary of ITO glass was protected using Scotch

tape. 5 mg of the sample was dispersed in 0.5 mL of *N,N*-dimethylformamide (DMF, supplied by Sinopharm Chemical Reagent Co., Ltd.) by sonication to get slurry. The slurry (20 μ L) was spread onto the pre-treated ITO glass. After air drying, the working electrode was further dried at 393 K for 2 h to improve adhesion. Then, the Scotch tape was unstuck, and the uncoated part of the electrode was isolated with epoxy resin. The exposed area of the working electrode was 0.25 cm². The light irradiation source was a 300 W Xe arc lamp system equipped with a filter to cut off light of wavelength $\lambda < 420$ nm. The cathodic polarization curves were obtained using the linear sweep voltammetry (LSV) technique with a scan rate of 2 mV s⁻¹. The electrochemical impedance spectroscopy (EIS) experiments were conducted on a AUTOLAB M204 workstation.

FDTD simulations

The electric field simulations were carried out by using finite-difference time-domain (FDTD) software package (Lumerical Solutions, Inc.). The refractive indices of CdS, BTF, Au and Pt were taken from previous reported data.^{19, 23, 69} A total-field/scattered field (TFSF) source was used as an incident field into the simulation region, which coincided with wavelength of our experimental irradiation source. Perfectly matched layers (PML) boundary conditions were used in our simulations. The Au NRs are a cylinder with round ends and the size was taken to match their average values. The radius of the cylinder is 14.5 nm and radii of the ends are 8 nm. The total length of the Au NRs is 92.5 nm. All the CdS shell thickness is 20 nm. For the model of Au-Pt@CdS, ellipse Pt spheres with diameters of 14 nm were located at both ends of the Au NRs with a total length of 98 nm. For Au@Pt@CdS, the Pt shell is a cylinder with radius of 2.1 nm and total length of the Au NRs is 107.9 nm.

Photoactivity

The experiments were performed referring to previously reported literatures with some modifications.^{44, 70} In a typical photocatalytic reaction, 2 mL catalyst suspension (1 mg mL⁻¹ in BTF) containing 0.5 M alcohols was placed in a quartz reactor (25 mL) equipped with a magnetic stir bar. The reaction suspension was sonicated for 2 min at room temperature and purged with Ar gas for 30 min. The reactor was then tightly sealed and then stirred for 30 minutes in the dark to achieve an adsorption-desorption equilibrium. A 300 W Xe arc lamp (PLS-SXE 300, Beijing Perfect light Co., Ltd.) with a filter to cut off light of wavelength $\lambda < 420$ nm was used as the irradiation source. The light intensity was fixed at 800 mW cm⁻². The photon flux of incident light was measured using an Optical Power/Energy Meter (Newport 842-PE). The irradiation area is 3.8 cm². During photocatalysis, the suspension was continuously stirred to ensure uniform irradiation. The evolved gases were analysed by gas chromatograph (Shimadzu GC-2014C, MS-5 A column, Ar carrier) equipped with a thermal conductivity detector (TCD). Products in solution were quantified by Agilent Gas Chromatograph (GC-7820) with flame-ionization detector (FID) and identified by gas chromatography-mass spectrometry (GC-MS, Agilent



Technologies, GC6890N, MS 5973). The recycling test for photocatalytic conversion of BA over Au-Pt@CdS was performed as follows. After 5 h reaction under Vis-NIR light irradiation, the suspension was centrifuged and mixed with 2 mL BTF containing 0.5 M BA for continuous test. Conversion of BA and selectivity for BAD were calculated with following equations:⁷¹

$$\text{Conversion (\%)} = \frac{C_0 - C_{\text{BA}}}{C_0} \times 100$$

$$\text{Selectivity (\%)} = \frac{C_{\text{BAD}}}{C_0 - C_{\text{BA}}} \times 100$$

Here C_0 is the initial concentration of BA; C_{BA} and C_{BAD} are the concentrations of the residual BA and the corresponding BAD at a certain time after the catalytic reaction, respectively. The apparent quantum efficiency (AQE) was calculated from the ratio of twice the number of H_2 molecules to the number of incident photons by using the following expression:^{22, 31}

$$\begin{aligned} \text{AQE} &= \frac{2 \times \text{Number of } \text{H}_2 \text{ molecules}}{\text{Number of incident photons}} \times 100\% \\ &= \frac{2 \times M \times N_A \times h \times c}{S \times P \times t \times \lambda} \times 100\% \end{aligned}$$

Where M is the molar amount of H_2 molecules, N_A is Avogadro constant, h is the Planck constant, c is the speed of light, S is the irradiation area, P is the intensity of the irradiation, t is the photoreaction time and λ is the wavelength of the monochromatic light. The power density of different monochromatic light was fixed at $30.0 \text{ mW}\cdot\text{cm}^{-2}$.

Acknowledgements

The support from the National Natural Science Foundation of China (NSFC) (21872029, U1463204, 21173045), the Award Program for Minjiang Scholar Professorship, the Natural Science Foundation (NSF) of Fujian Province for Distinguished Young Investigator Rolling Grant (2017J07002), the Independent Research Project of State Key Laboratory of Photocatalysis on Energy and Environment (NO. 2014A05), and the 1st Program of Fujian Province for Top Creative Young Talents is gratefully acknowledged.

Notes and references


- J. C. Colmenares and R. Luque, *Chem. Soc. Rev.*, 2014, **43**, 765-778.
- M.-Q. Yang, N. Zhang, M. Pagliaro and Y.-J. Xu, *Chem. Soc. Rev.*, 2014, **43**, 8240-8254.
- G. Xie, K. Zhang, B. Guo, Q. Liu, L. Fang and J. R. Gong, *Adv. Mater.*, 2013, **25**, 3820-3839.
- N. Zhang, C. Han, Y.-J. Xu, J. J. Foley IV, D. Zhang, J. Codrington, S. K. Gray and Y. Sun, *Nature Photon.*, 2016, **10**, 473-482.
- Z. Yin, J. Guo, S. Lin, Y. Zhu, H. Ke, Y. Zheng and Z. Tang, *Sci. Adv.*, 2017, **3**, e1701162.
- W. Jiang, S. Bai, L. Wang, X. Wang, L. Yang, Y. Li, D. Liu, X. Wang, Z. Li, J. Jiang and Y. Xiong, *Small*, 2016, **12**, 1640-1648.
- M.-Q. Yang, M. Gao, M. Hong and G. W. Ho, *Adv. Mater.*, 2018, **30**, 1802894. DOI: 10.1039/C8SC05813J
- J. Chen, X.-J. Wu, L. Yin, B. Li, X. Hong, Z. Fan, B. Chen, C. Xue and H. Zhang, *Angew. Chem. Int. Ed.*, 2015, **54**, 1210-1214.
- C. Han, S.-H. Li, Z.-R. Tang and Y.-J. Xu, *Chem. Sci.*, 2018, **9**, 8914-8922.
- F. Xie, Y. Zhang, X. He, H. Li, X. Qiu, W. Zhou, S. Huo and Z. Tang, *J. Mater. Chem. A*, 2018, **6**, 13236-13243.
- W.-T. Chen, T.-T. Yang and Y.-J. Hsu, *Chem. Mater.*, 2008, **20**, 7204-7206.
- S. Han, L. Hu, N. Gao, A. A. Al-Ghamdi and X. Fang, *Adv. Funct. Mater.*, 2014, **24**, 3725-3733.
- J. D. Xiao, L. Han, J. Luo, S. H. Yu and H. L. Jiang, *Angew. Chem. Int. Ed.*, 2018, **57**, 1103-1107.
- X. Liu, J. Iocozzia, Y. Wang, X. Cui, Y. Chen, S. Zhao, Z. Li and Z. Lin, *Energy Environ. Sci.*, 2017, **10**, 402-434.
- H.-Q. Xu, S. Yang, X. Ma, J. Huang and H.-L. Jiang, *ACS Catal.*, 2018, **8**, 11615-11621.
- N. Zhang, C. Han, X. Fu and Y.-J. Xu, *Chem*, 2018, **4**, 1832-1861.
- L. Zhang, Z. Xie and J. Gong, *Chem. Soc. Rev.*, 2016, **45**, 3916-3934.
- H. Huang, L. Zhang, Z. Lv, R. Long, C. Zhang, Y. Lin, K. Wei, C. Wang, L. Chen, Z.-Y. Li, Q. Zhang, Y. Luo and Y. Xiong, *J. Am. Chem. Soc.*, 2016, **138**, 6822-6828.
- Z. Zheng, T. Tachikawa and T. Majima, *J. Am. Chem. Soc.*, 2014, **137**, 948-957.
- Y. Yin, Y. Yang, L. Zhang, Y. Li, Z. Li, W. Lei, Y. Ma and Z. Huang, *RSC Adv.*, 2017, **7**, 36923-36928.
- S.-F. Hung, Y.-C. Yu, N.-T. Suen, G.-Q. Tzeng, C.-W. Tung, Y.-Y. Hsu, C.-S. Hsu, C.-K. Chang, T.-S. Chan, H.-S. Sheu, J.-F. Lee and H. M. Chen, *Chem. Commun.*, 2016, **52**, 1567-1570.
- Q. Li, B. Guo, J. Yu, J. Ran, B. Zhang, H. Yan and J. R. Gong, *J. Am. Chem. Soc.*, 2011, **133**, 10878-10884.
- M. Grzelczak, J. Pérez-Juste, F. J. García de Abajo and L. M. Liz-Marzán, *J. Phys. Chem. C*, 2007, **111**, 6183-6188.
- Z. Zheng, T. Tachikawa and T. Majima, *J. Am. Chem. Soc.*, 2014, **136**, 6870-6873.
- J. Guo, Y. Zhang, L. Shi, Y. Zhu, M. F. Mideksa, K. Hou, W. Zhao, D. Wang, M. Zhao, X. Zhang, J. Lv, J. Zhang, X. Wang and Z. Tang, *J. Am. Chem. Soc.*, 2017, **139**, 17964-17972.
- S. Bai, X. Li, Q. Kong, R. Long, C. Wang, J. Jiang and Y. Xiong, *Adv. Mater.*, 2015, **27**, 3444-3452.
- S.-C. Lin, C.-S. Hsu, S.-Y. Chiu, T.-Y. Liao and H. M. Chen, *J. Am. Chem. Soc.*, 2017, **139**, 2224-2233.
- R. Long, Y. Li, L. Song and Y. J. Xiong, *Small*, 2015, **11**, 3873-3889.
- J. Wu, Z. Zhang, B. Liu, Y. Fang, L. Wang and B. Dong, *Solar RRL*, 2018, **2**, 1800039.
- J. Zhu, Y. Yang, L. Chen, W. Xiao, H. Liu, H. D. Abruña and D. Wang, *Chem. Mater.*, 2018, **30**, 5987-5995.
- C. Han, Q. Quan, H. M. Chen, Y. Sun and Y.-J. Xu, *Small*, 2017, **13**, 1602947.



- 32 X.-J. Wu, J. Chen, C. Tan, Y. Zhu, Y. Han and H. Zhang, *Nature Chem.*, 2016, **8**, 470.
- 33 A. Li, P. Zhang, X. Chang, W. Cai, T. Wang and J. Gong, *Small*, 2015, **11**, 1892-1899.
- 34 A. Li, X. Chang, Z. Huang, C. Li, Y. Wei, L. Zhang, T. Wang and J. Gong, *Angew. Chem. Int. Ed.*, 2016, **55**, 13734-13738.
- 35 X. Ma, K. Zhao, H. Tang, Y. Chen, C. Lu, W. Liu, Y. Gao, H. Zhao and Z. Tang, *Small*, 2014, **10**, 4664-4670.
- 36 L. Ma, K. Chen, F. Nan, J.-H. Wang, D.-J. Yang, L. Zhou and Q.-Q. Wang, *Adv. Funct. Mater.*, 2016, **26**, 6076-6083.
- 37 C. Han, Z. Chen, N. Zhang, J. C. Colmenares and Y.-J. Xu, *Adv. Funct. Mater.*, 2015, **25**, 221-229.
- 38 Y. Hu, X. Gao, L. Yu, Y. Wang, J. Ning, S. Xu and X. W. Lou, *Angew. Chem. Int. Ed.*, 2013, **52**, 5636-5639.
- 39 J. Zhang, Y. Tang, K. Lee and M. Ouyang, *Science*, 2010, **327**, 1634-1638.
- 40 H. Wang, Z. Sun, Q. Lu, F. Zeng and D. Su, *Small*, 2012, **8**, 1167-1172.
- 41 H. Ataee-Esfahani, L. Wang, Y. Nemoto and Y. Yamauchi, *Chem. Mater.*, 2010, **22**, 6310-6318.
- 42 J. S. Suh and J. S. Lee, *Chem. Phys. Lett.*, 1997, **281**, 384-388.
- 43 M. Li, X.-F. Yu, S. Liang, X.-N. Peng, Z.-J. Yang, Y.-L. Wang and Q.-Q. Wang, *Adv. Funct. Mater.*, 2011, **21**, 1788-1794.
- 44 Z. Chai, T.-T. Zeng, Q. Li, L.-Q. Lu, W.-J. Xiao and D. Xu, *J. Am. Chem. Soc.*, 2016, **138**, 10128-10131.
- 45 J. Xu, W.-M. Yang, S.-J. Huang, H. Yin, H. Zhang, P. Radjenovic, Z.-L. Yang, Z.-Q. Tian and J.-F. Li, *Nano Energy*, 2018, **49**, 363-371.
- 46 J.-J. Chen, J. C. S. Wu, P. C. Wu and D. P. Tsai, *J. Phys. Chem. C*, 2012, **116**, 26535-26542.
- 47 H. Gao, P. Zhang, J. Zhao, Y. Zhang, J. Hu and G. Shao, *Appl. Catal. B*, 2017, **210**, 297-305.
- 48 M.-Q. Yang, Y.-J. Xu, W. Lu, K. Zeng, H. Zhu, Q.-H. Xu and G. W. Ho, *Nat. Commun.*, 2017, **8**, 14224.
- 49 Y. Du, B. Chen, Z. Yin, Z. Liu and H. Zhang, *Small*, 2014, **10**, 4727-4734.
- 50 Z. Zhang, Y. Huang, K. Liu, L. Guo, Q. Yuan and B. Dong, *Adv. Mater.*, 2015, **27**, 5906-5914.
- 51 X. Wang, C. Liow, A. Bisht, X. Liu, T. C. Sum, X. Chen and S. Li, *Adv. Mater.*, 2015, **27**, 2207-2214.
- A. Tanaka, K. Nakanishi, R. Hamada, K. Hashimoto and H. Kominami, *ACS Catal.*, 2013, **3**, 1886-1891.
- Y.-C. Pu, G. Wang, K.-D. Chang, Y. Ling, Y.-K. Lin, B. C. Fitzmorris, C.-M. Liu, X. Lu, Y. Tong and J. Z. Zhang, *Nano Lett.*, 2013, **13**, 3817-3823.
- A. Tanaka, K. Hashimoto and H. Kominami, *J. Am. Chem. Soc.*, 2014, **136**, 586-589.
- Z. Zhang, A. Li, S.-W. Cao, M. Bosman, S. Li and C. Xue, *Nanoscale*, 2014, **6**, 5217-5222.
- Y.-H. Chiu, K.-D. Chang and Y.-J. Hsu, *J. Mater. Chem. A*, 2018, **6**, 4286-4296.
- C. Li, P. Wang, Y. Tian, X. Xu, H. Hou, M. Wang, G. Qi and Y. Jin, *ACS Catal.*, 2017, **7**, 5391-5398.
- L. Ma, S. Liang, X.-L. Liu, D.-J. Yang, L. Zhou and Q.-Q. Wang, *Adv. Funct. Mater.*, 2015, **25**, 898-904.
- D. Seo, G. Park and H. Song, *J. Am. Chem. Soc.*, 2012, **134**, 1221-1227.
- S. Meng, X. Ye, J. Zhang, X. Fu and S. Chen, *J. Catal.*, 2018, **367**, 159-170.
- M.-Q. Yang, L. Shen, Y. Lu, S. W. Chee, X. Lu, X. Chi, Z. Chen, Q.-H. Xu, U. Mirsaidov and G. W. Ho, *Angew. Chem. Int. Ed.*, 2018, DOI: 10.1002/anie.201810694.
- M. Wang, X. Pang, D. Zheng, Y. He, L. Sun, C. Lin and Z. Lin, *J. Mater. Chem. A*, 2016, **4**, 7190-7199.
- Z. Xu, Y. Lin, M. Yin, H. Zhang, C. Cheng, L. Lu, X. Xue, H. J. Fan, X. Chen and D. Li, *Adv. Mater. Interfaces*, 2015, **2**, 1500169.
- F.-X. Xiao, J. Miao, H.-Y. Wang, H. Yang, J. Chen and B. Liu, *Nanoscale*, 2014, **6**, 6727-6737.
- G. A. Samara, *Phys. Rev. B*, 1983, **27**, 3494-3505.
- N. Zhang, Y. Zhang, X. Pan, M.-Q. Yang and Y.-J. Xu, *J. Phys. Chem. C*, 2012, **116**, 18023-18031.
- S. Bai, J. Jiang, Q. Zhang and Y. Xiong, *Chem. Soc. Rev.*, 2015, **44**, 2893-2939.
- X. Ye, Y. Gao, J. Chen, D. C. Reifsnyder, C. Zheng and C. B. Murray, *Nano Lett.*, 2013, **13**, 2163-2171.
- M. S. Gomez, J. M. Guerra and F. Vilches, *Appl. Opt.*, 1985, **24**, 1147-1150.
- D. Jiang, X. Chen, Z. Zhang, L. Zhang, Y. Wang, Z. Sun, R. M. Irfan and P. Du, *J. Catal.*, 2018, **357**, 147-153.
- N. Zhang, M.-Q. Yang, Z.-R. Tang and Y.-J. Xu, *ACS Nano*, 2013, **8**, 623-633.



TOC graphic

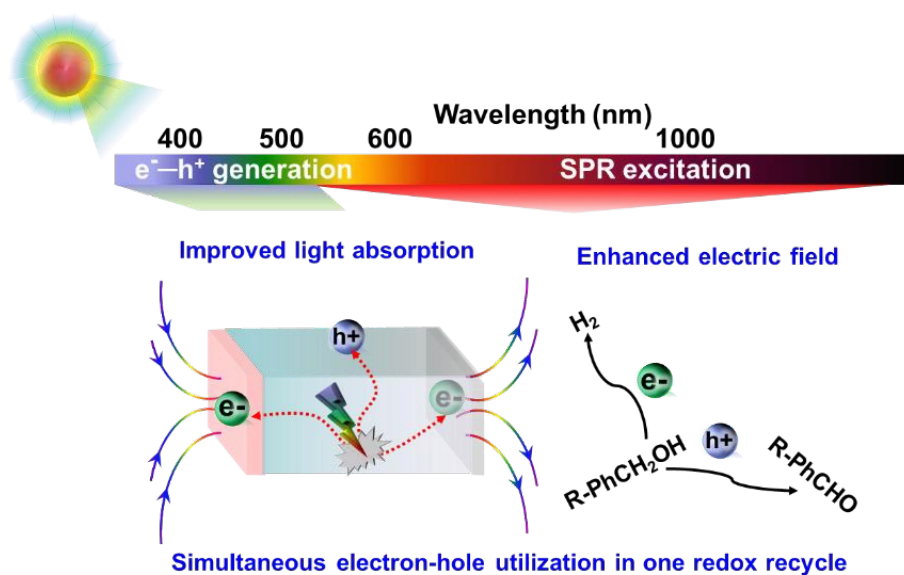View Article Online
DOI: 10.1039/C8SC05813J

An anisotropic bimetal-semiconductor heterostructure with efficient charge carriers generation, transfer and utilization for plasmon-enhanced photoredox catalysis.

