

A Journal of the Gesellschaft Deutscher Chemiker

Angewandte Chemie

GDCh

International Edition

www.angewandte.org

Accepted Article

Title: Heterogeneously-catalyzed aerobic oxidation of methane to a methyl derivative

Authors: Jeroen A. van Bokhoven, Andrea N. Blankenship, Manoj Ravi, and Mark A. Newton

This manuscript has been accepted after peer review and appears as an Accepted Article online prior to editing, proofing, and formal publication of the final Version of Record (VoR). This work is currently citable by using the Digital Object Identifier (DOI) given below. The VoR will be published online in Early View as soon as possible and may be different to this Accepted Article as a result of editing. Readers should obtain the VoR from the journal website shown below when it is published to ensure accuracy of information. The authors are responsible for the content of this Accepted Article.

To be cited as: *Angew. Chem. Int. Ed.* 10.1002/anie.202104153

Link to VoR: <https://doi.org/10.1002/anie.202104153>

RESEARCH ARTICLE

Heterogeneously-catalyzed aerobic oxidation of methane to a methyl derivative

Andrea N. Blankenship,^{[a]†} Manoj Ravi,^{[a]†} Mark A. Newton,^[a] and Jeroen A. van Bokhoven^{*[a][b]}

[a] Ms. A. N. Blankenship, Dr. M. Ravi, Dr. M. A. Newton, Prof. J. A. van Bokhoven
Institute for Chemical and Bioengineering
ETH Zurich

Vladimir-Prelog-Weg 1, 8093 Zurich (Switzerland)
E-mail: jeroen.vanbokhoven@chem.ethz.ch

[b] Prof. J. A. van Bokhoven
Laboratory for Catalysis and Sustainable Chemistry
Paul Scherrer Institute
5232 Villigen (Switzerland)

† Authors contributed equally to the manuscript

Supporting information for this article is given via a link at the end of the document.

Abstract: A promising strategy to break through the selectivity-conversion limit of direct methane conversion to achieve high yields is the protection of methanol via esterification to a more stable methyl ester. In this study, we present a novel aerobic methane-to-methyl-ester approach that utilizes a highly dispersed, cobalt-containing solid catalyst, along with significantly more favorable reaction conditions compared to existing homogeneously-catalyzed approaches (e.g. diluted acid, O₂ oxidant, moderate temperature and pressure). The trifluoroacetic acid medium is diluted (< 25 wt%) with an inert fluorine co-solvent that can be recovered after the separation of the methyl trifluoroacetate via liquid-liquid extraction at ambient conditions. Silica-supported cobalt catalysts are highly active in this system, with competitive yields and turnovers in comparison to known aerobic transition metal-based catalytic systems. This work highlights the need and potential to reinvigorate the development of methane conversion technologies through the innovative application and combination of concepts from across the community.

Introduction

In 2018, it is estimated that nearly 145 billion cubic meters of unused natural gas, a methane-rich by-product of oil extraction, were flared due to the lack of commercial technologies and incentives to bring it to market^[1]. Methane derived from natural gas is a highly abundant resource that is widely used in the production of commodity chemicals and liquid energy carriers, notably methanol^[2]. Although well-established industrial routes for methane utilization exist, these processes generally proceed through an indirect two-step pathway, with syngas as an intermediate product. Consequently, these energy- and capital-intensive processes are rendered economically unviable for methane valorization at small- and mid-scale facilities^[2a, 3], such as remote and decentralized shale oil production sites^[4]. The challenge of developing a more scale-flexible direct methane conversion route has therefore motivated the academic and industrial communities over the previous years^[5].

Many diverse approaches have evolved to address this challenge, including the selective functionalization of the methane C-H bond to form primary oxygenates, such as methanol or other

derivatives, over heterogeneous catalysts^[2b, 4c, 5d, 6]. However, existing approaches to partial oxidation are constrained by a number of limitations, most notably, the selectivity-conversion paradigm arising from the vulnerability of methanol to over-oxidation^[5d, 7]. Comparisons between diverse solid catalyst systems reveal a clear trend of decreasing selectivity to methanol with increasing conversion of methane, a limit that severely restricts achievable yields and necessitates operating conditions that are highly impractical for commercialization^[5d, 7b, 7c, 8]. In order to achieve industrially relevant methane conversion without compromising high selectivity for methanol, it is imperative that methanol is stabilized to prevent over-oxidation^[7b, 7c, 9]. An interesting 'product protection' strategy, demonstrated primarily in homogeneous catalytic systems, is the protection of methanol via esterification to methyl bisulfate^[10] and methyl trifluoroacetate^[11]. These esters are less prone to further oxidation under typical reaction conditions^[7b] and, therefore, offer the possibility to circumvent the selectivity-conversion limit during methane conversion. In later steps, these esters can be hydrolyzed back to methanol, thereby widening the array of potential commercial applications for this chemistry. The translation of this protection strategy to use with a heterogeneous catalyst has been largely unexplored, with the notable exception of Schüth and co-workers who synthesized a highly active solid catalyst based on the homogeneous Periana platinum bipyrimidine complex for the conversion of methane to methyl bisulfate in oleum using a SO₃ oxidant^[6e].

The attractive yields of current methane-to-methyl ester processes notwithstanding, these processes still fall short of potential commercial application. Rather than focusing only on obtaining high product yields, a more holistic consideration of process conditions, cost and handling of reagents, and necessary separations and recycle streams is essential. These factors, which have been rigorously defined by industrial experts in this field^[12], constitute a further set of criteria for commercialization. In particular, several key factors have precluded commercialization of these processes, which include: (i) the homogeneous nature of the catalysis, translating into challenges in product and catalyst recovery; (ii) the use of harsh corrosive acids in an undiluted form, which leads to greater operational hazards and costly equipment materials^[13]; (iii) the use of economically underwhelming oxidants,

RESEARCH ARTICLE

such as potassium persulfate and hydrogen peroxide^[13]; and (iv) the difficulty in hydrolyzing the ester to methanol due to the highly exothermic interaction of water with the reaction mixture, which potentially results in the undesired evaporation of methanol^[14]. A process that demonstrates the breakthrough performance of methane-to-methyl-ester systems, while simultaneously overcoming these conventional challenges has not, to our knowledge, been previously demonstrated.

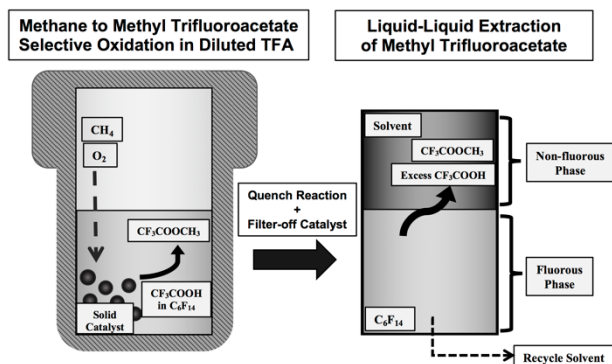


Figure 1. Overview of designed methane-oxidation process and product recovery. The conversion of methane to methyl trifluoroacetate occurs in an autoclave charged with methane, air, solid catalyst, and a solution of TFA in perfluorohexane. After reaction, methyl trifluoroacetate is extracted from the fluorous reaction medium into a non-fluorous solvent.

To address the pressing limitations of direct methane conversion, we propose an approach that combines the heterogeneously-catalyzed partial oxidation of methane with subsequent esterification of the product in a reaction medium of trifluoroacetic acid (TFA) diluted in an inert perfluoroalkane co-solvent. Perfluoroalkanes, such as perfluorohexane, are inert, stable at elevated temperatures^[15], and can exhibit high solubilities for gases^[16]. By diluting TFA to manageable concentrations of below 25 wt% in a non-corrosive and oxidation-resistant perfluoroalkane, a number of improvements are attained, namely: a strongly reduced corrosivity of the reaction medium; improved stability of a heterogeneous catalyst through operation in a milder environment; enhanced recovery of the methyl ester via a simple liquid-liquid extraction with a non-fluorous polar solvent; and improved hydrolysis conditions.

Results and Discussion

Previous studies have shown that a number of homogeneous transition metal catalysts display activity for methane to methyl trifluoroacetate conversion, including copper^[11e], manganese^[11c], and cobalt^[11d]. As a preliminary step, therefore, a variety of transition metals on solid supports were synthesized and screened for activity in a batch reactor system (Figure 1, screening results in Supporting Information). Based on the initial screening, cobalt-containing silica catalysts synthesized via an incipient wetness impregnation (Co/SiO₂-IWI) with an aqueous cobalt nitrate solution showed the most promising activity.

The methyl ester is recovered from the fluorous reaction medium through a facile liquid-liquid extraction with a polar

solvent at room temperature. Acetonitrile-d₃ is an aprotic polar solvent used as the extractant to preserve the product as the methyl ester and directly measure the product concentrations using ¹H NMR. Only residual amounts of the methyl ester remain in the fluorous phase immediately after contact with the deuterated acetonitrile phase as determined through ¹H NMR (Supporting Information, Figures S1 and S2), and therefore the total product yield can be determined from the acetonitrile-d₃ phase after extraction. Substituting water as the non-fluorous extracting solvent could provide opportunities for product separation with enhanced ester hydrolysis conditions compared to processes that rely on undiluted reaction mediums. Importantly, this simple and highly effective product separation method provides a straightforward pathway for recycling the fluorous co-solvent, thereby greatly reducing the overall usage of this component. This unique advantage in product separation and solvent recycle has not been previously described in published methane-to-methyl-ester systems.

Herein, catalysts with cobalt loadings of 0.1 wt%, 0.5 wt%, 1.5 wt%, 5 wt% and 10 wt% were synthesized through an incipient wetness impregnation method (Co/SiO₂-IWI) and studied for the catalytic partial oxidation of methane. Figure 2a illustrates the dependence of the methyl ester productivity on the cobalt loading of the Co/SiO₂-IWI catalysts under the typical reaction conditions. A methyl ester productivity of approximately 250 μmol/g_{cat}·h is obtained with the 0.5 wt% Co/SiO₂-IWI catalysts. Increasing the cobalt content of the catalysts results in only minor changes in the productivity of the methyl ester up to 5 wt% (Figure 2a, blue markers). Cobalt utilization is substantially higher for the low-loaded catalysts, with a maximum of nearly 175 mmol/g_{Co}·h achieved using the 0.1 wt% Co/SiO₂-IWI material, which decreases rapidly with increased cobalt loading (Figure 2a, green markers). The performance of the 10 wt% Co/SiO₂-IWI catalyst is substantially inferior to the catalysts with lower cobalt content in terms of both productivity and cobalt utilization. In combination with the average particle sizes from the corresponding transmission electron microscopy (TEM) images (see Supporting Information), these results suggest that the more active catalysts are those with the higher cobalt dispersions. Consequently, the most efficient utilization of cobalt is realized in the lowest cobalt-loaded cases.

The heterogeneity of the reaction for the Co/SiO₂-IWI materials was confirmed via a hot filtration test and ICP-OES of the reaction medium (Supporting Information, Figure S4). Additional tests demonstrating the necessity of cobalt and molecular oxygen oxidant are summarized in Supporting Information Table S3. To further assess the stability of the Co/SiO₂-IWI catalysts, the catalyst material was recovered after an initial catalytic test and recycled back into the reactor for a second run conducted under the same conditions. Before recycling, some samples underwent a thermal treatment consisting of a calcination to at least 250 °C in static air and are denoted as “reactivated” samples. Samples that did not receive any treatment before the second run are referred to as “spent” samples. The catalytic productivity obtained with the spent 0.5 wt% Co/SiO₂-IWI catalyst after reactivation is comparable to that obtained with the freshly synthesized catalyst (Figure 2b). Without the reactivation step, decreased catalytic activity is observed for this catalyst.

On inspecting the fresh catalysts by TEM, we find large cobalt-containing particles in those with high loadings, and X-ray diffraction (XRD) of these catalysts confirms the presence of

RESEARCH ARTICLE

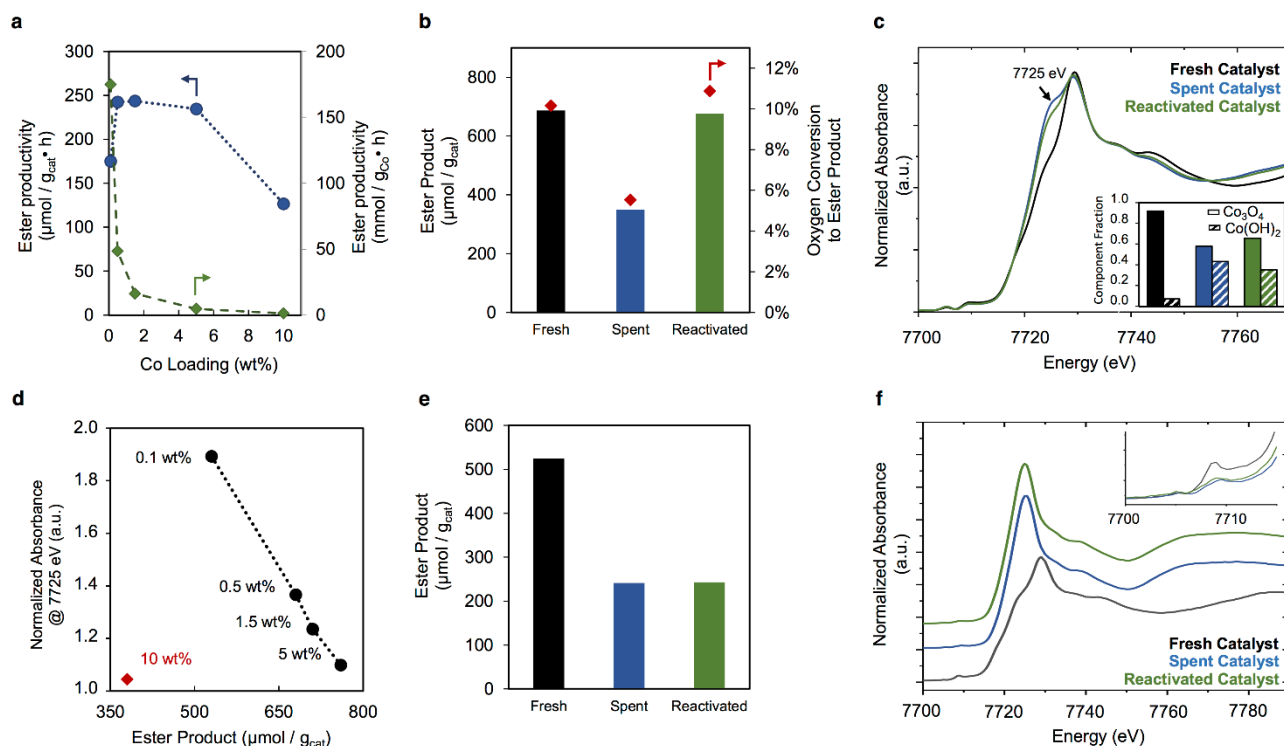


Figure 2. Co/SiO₂-IWI catalytic methane oxidation performance and characterization. (a) Effect of cobalt loading of Co/SiO₂-IWI catalyst on methyl ester productivity in methane-oxidation. Reaction conditions: 100 mg catalyst, 5 bar CH₄, 2 bar air, 7 g of 14 wt% TFA/C₆F₁₄, 215 °C, 3 h; (b) Methyl ester product (bar graph) and ester yield (scatter point) obtained with fresh, spent and reactivated 0.5 wt% Co/SiO₂-IWI catalyst. Reaction conditions: 5 bar CH₄, 2 bar air, 7 g of 14 wt% TFA/C₆F₁₄, 215 °C, 100 mg catalyst, 3 h; (c) Co K-edge XANES of 0.5 wt% Co/SiO₂-IWI series. Inset includes two-component LCA results with the Co₃O₄ and Co(OH)₂ standards; (d) Normalized absorbance of the Co K-edge XANES at 7725 eV for the spent Co/SiO₂-IWI catalysts with respect to corresponding ester product of the catalyst during reaction; (e) Methyl ester product obtained with fresh, spent and reactivated 0.1 wt% Co/SiO₂-IWI catalyst. Reaction conditions: 5 bar CH₄, 2 bar air, 7 g of 14 wt% TFA/C₆F₁₄, 215 °C, 100 mg catalyst, 3 h; (f) Co K-edge XANES of 0.1 wt% Co/SiO₂-IWI series. Inset includes close-up of pre-edge feature.

Co₃O₄ (see Supporting Information). X-ray absorption spectroscopy (XAS) further corroborates the dominance of a spinel Co₃O₄ at each of the weight loadings in the fresh state and suggests the presence of a minority Co^{II}-like fraction, which becomes less significant as the cobalt loading increases (Supporting Information, Figure S9). Figure 2c shows the Co K-edge X-ray absorption near edge structure (XANES) of the 0.5 wt% Co/SiO₂-IWI catalyst in the fresh, spent, and reactivated state. The lower binding energy feature around 7725 eV associated with a Co^{II} component is noticeably more prominent in the spent and reactivated catalysts as compared to the fresh catalysts. Linear combination analysis (LCA) fits to the XANES of these materials (see Supporting Information) suggests that the reactivated catalyst regains more of the Co^{III}/Co^{II} character indicative of the initial spinel structure, but still retains a significant, loading-dependent amount of the character of the second Co(OH)₂-like species (Figure 2c, inset). For the higher-loaded samples, such as the 5 wt% Co/SiO₂-IWI catalyst, the cobalt structure appears to be less perturbed after reaction in the spent catalysts and the structure more closely resembles the initial structure following reactivation (Supporting Information, Figure S11).

In the case of the 0.1 wt% Co/SiO₂-IWI catalysts, both the spent and reactivated catalysts show equivalent ester productivities that are approximately 50% of that obtained from

the fresh catalyst (Figure 2e). Despite the decrease in activity observed after the initial reaction, the spent and reactivated samples still show better cobalt utilization than the higher-loaded catalysts, with cobalt-based ester productivities around 80 mmol/g_{Co}·h (corresponding to approx. 240 μmol/g_{cat} in Fig 2e). From an activity standpoint, the aerobic reactivation protocol does not have a significant effect on the 0.1 wt% catalyst. The XAS of both the spent and reactivated materials, which reveals a strong resemblance between these materials (Figure 2f), supports this observation. The effects of catalysis manifest principally through the development of a shoulder in the XANES, associable with Co^{II} @ 7725 eV in the higher-loaded samples (Figure 2c). There is an explicit linear relationship between the fraction of cobalt associated with the 7725 eV Co^{II} XANES feature and the obtained methyl ester yield over the studied range of cobalt loadings (Figure 2d). The 10 wt% Co/SiO₂-IWI catalyst noticeably deviates from this trend, which likely results from the greatly increased domain size and reduced dispersion due to the formation of very large cobalt particles and agglomerates, as evidenced by TEM and XRD (see Supporting Information). In the case of the 0.1 wt% material, the XANES feature @7725 eV Co^{II} is transformed into a strong peak rather than a shoulder (Figure 2f), and the overall XANES envelopes of 0.1 wt% Co/SiO₂-IWI in the spent and reactivated state are markedly different from those of the higher weight loaded samples.

RESEARCH ARTICLE

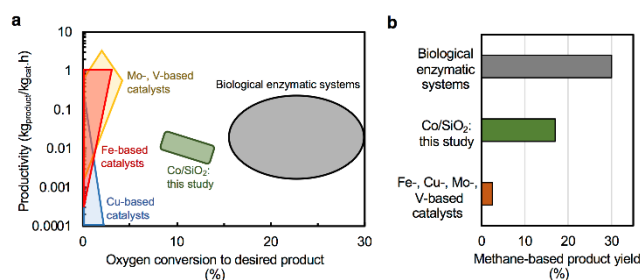



Figure 3. Overview of the performance of different aerobic methane-oxidation approaches. (a) Comparison of the productivity and oxygen-based yields of previously reported methane-oxidation with molecular oxygen approaches; (b) Comparison of the methane-based product yields of various methane-oxidation with molecular oxygen approaches.

The pre-edge feature at ca. 7709 eV is indicative of a fraction of the cobalt that initially exists with the tetrahedral (T_d) symmetry expected from the Co^{II} component of the spinel structure of Co_3O_4 (Figure 2f, inset)^[17]. This feature is removed in the spent catalyst, suggesting the removal T_d symmetry from the 0.1 wt% sample post-reaction. Moreover, the overall shift of the Co K-edge edge position to lower energy further suggests that the

octahedral (O_h) Co^{III} component of the Co_3O_4 , has also been consumed. Analysis of the EXAFS further indicates that a complete structural transformation of the cobalt species present on the 0.1 wt% catalyst from the Co_3O_4 starting phase into a highly dispersed O_h Co^{II} species has occurred (see Supporting Information). The combination of catalytic data with the XAS suggests that the new O_h Co^{II} species can still be associated with activity for methane oxidation. The most active cobalt species across the series of catalysts, therefore, may not be the Co_3O_4 nanoparticles that are predominantly present in the fresh catalysts across the range of loadings, but rather a newly formed species that is best observed in the low-loaded, highly dispersed catalyst materials.

By increasing the liquid hold-up in the reactor and reducing the partial pressure of oxygen, the highest oxygen-based yield of 12% of the theoretical maximum was reached with 1.5 wt% Co/SiO_2 catalyst (Supporting Information, Table S5). Figure 3a ranks the performance of the cobalt-catalyzed process reported herein in comparison to other methane-oxidation approaches that solely use dioxygen as the oxidant based on two important parameters, namely productivity and oxygen conversion to the desired product. This comparison reveals the considerable performance-gap that exists between aerobic heterogeneous

Table 1. A comparison to homogeneous systems for the oxidation of methane to methyl trifluoroacetate.

Entry	Pre-catalyst	Oxidant	P_{methane} [bar]	Reported TO ^[a]	Productivity ^[b] [mol _{ester} mol _{metal} ⁻¹ h ⁻¹]	Ref
1	$Pd(OAc)_2$	$K_2S_2O_8$	20	3.8	0.2	[18]
2		$K_2S_2O_8$	30	30	2.1	[18]
3	$H_5PV_2Mo_{10}O_{40}$	$K_2S_2O_8$	10	128 [c]	6.4 [c]	[19]
4	CuO	$K_2S_2O_8$	5	33	1.9	[11e]
5	$Co(OCOFCF_3)_3$	O_2	20	4	1	[20]
6	$EuCl_3 / Zn$	O_2	10	5.3	5.3	[21]
7	$FeCl_3$	O_2	10	< 0.5	< 0.5	[21]
8	$Pd(OAc)_2/BQ/H_5PMo_{10}V_2O_{40}$	O_2	25	3 – 118 [d]	0.4 – 14.8 [d]	[22]
9	$Co(OAc)_2 \cdot 4H_2O$	O_2	20	13.2	0.6	[23]
10	Mn_2O_3	O_2	7	8.5	2.8	[11c]
11	$[Pd(hfacac)_2]$	H_2O_2	30	39	9.8	[24]
12	$[Cu(hfacac)_2(H_2O)_2]$	H_2O_2	30	13	3.3	[24]
13	$VO(acac)_2$	H_2O_2	50	18.5 [c]	0.8 [c]	[25]
14	$H_4PV_1Mo_{11}O_{40}$	H_2O_2	50	224 [c]	9.3 [c]	[25]
15	0.1% Co/SiO_2 -IWI	O_2	5	31	10.3	This study

[a] [Moles of methyl trifluoroacetate] / [Moles of metal in catalyst] measured over the reported reaction time; [b] Average rate of production based on reported metal/catalyst loading and reaction time; [c] Including methyl acetate as a product; [d] Determined with respect to $Pd(OAc)_2$.

RESEARCH ARTICLE

systems for methane-oxidation. The latter operate aerobically with a NADH electron carrier and are characterized by a highly selective conversion of methane to methanol^[26].

It is clear that high-temperature heterogeneous catalytic approaches using different transition metals typically result in much a poorer selectivity even at lower conversion, and consequently, these systems appear on the very left in Figure 3a. The performance of the Co/SiO₂-IWI catalyst is distinct from these other approaches and advances toward the more efficient bio-enzymatic systems. Furthermore, methanol productivity achieved per gram of the cobalt catalyst is of the same order as that achieved per gram of dry / wet cells in the biological conversion of methane. With the Co/SiO₂-IWI catalyst, a productivity up to 0.03 kg_{methanol}/kg_{cat}·h was attained at low cobalt loadings under low-pressure conditions and a pronounced enhancement is expected on increasing the feed pressure further. The volumetric productivity, or space-time-yield (STY), is an additional metric useful for comparing processes. Although optimization of this parameter was not a focus of this work, volumetric productivity in this case would likely be greatly enhanced through increasing the amount of catalyst in the reactor, increasing methane partial pressures, and targeting the retention of efficient cobalt utilization at higher weight loadings.

In addition to excellent oxygen-based product yields, working at lower partial pressure of methane showed improved selective methane conversion to the methyl ester. Reactions performed with 2.5% methane feed resulted in methane-based ester yields of up to 17% (Supporting Information, Table S4). While the transition metal-based catalysts depicted in Figure 3b reach 2 - 3% methane-based yields at best, biological systems consistently report yields close to 30%^[26]. The high activity of MMO enzymes coupled with the high selectivity in methane conversion and oxygen utilization has proved difficult to replicate in heterogeneous systems. The high activity of the cobalt-based catalyst along with the use of esterification as a 'product protection' strategy enables a performance that is comparable to the bio-enzymatic systems.

Table 1 lists the activity of the Co/SiO₂-IWI catalyst with known homogeneous catalytic systems that oxidize methane to methyl trifluoroacetate. The performance of these systems is compared on the basis of the reported turnovers (TO) over the reaction period and the productivity. We note that the turnovers reported typically represent a lower bound on the amount of product formed per mole of catalyst, since in most cases it appears that the catalyst may not be fully deactivated at the end of the reaction period. The Co/SiO₂-IWI catalyst achieved turnovers of up to 31 and a corresponding productivity of 10.3 mol_{ester} mol_{Co}⁻¹ h⁻¹. This performance is competitive to even homogeneous systems that employ stronger oxidants (K₂S₂O₈, H₂O₂), higher partial pressures of methane, and/or more complex redox cycling schemes. Taken together, Figure 3 and Table 1 illustrate the outstanding catalytic performance of the system that is achieved with an economical oxidant and under reaction conditions that are more favorable than those generally employed in state-of-the-art methane-to-methyl-ester systems.

Conclusion

An improved methane-to-methyl ester process with competitive performance for the selective conversion of methane was

designed by systematically addressing the limitations of conventional systems. The use of a fluorine co-solvent as an acid diluent brought several advantages, notably a milder reaction environment that benefited working in a heterogeneous mode and a facile product and solvent recovery method through a highly-effective extraction with a non-fluorous solvent. The performance of this cobalt-catalyzed process far exceeds other comparable heterogeneous transition metal-based high-temperature catalytic processes, which are generally restricted by much lower methane conversion and product selectivity. Through future work to elucidate the reaction mechanisms, target improvement of the cobalt utilization at high metal loadings, and optimization of process conditions, this novel catalytic approach holds the promise of significant future improvement.

Acknowledgements

This work was supported financially by ETH Zurich and the Swiss National Science Foundation (Grant No. 200021_178943). The authors would also like to acknowledge Dr. Frank Krumeich at ETH Zurich for his work in acquiring the electron microscopy images presented in this work, Prof. Christophe Copéret for helpful discussions, and Dr. Adam Clark at the Swiss Light Source for his expertise and support in acquiring the XAS data, as well as the SuperXAS beamline for the provision of measurement time.

Keywords: Heterogeneous Catalysis • Methyl Ester • Cobalt • Product Protection • Fluorous Solvents


- [1] IEA, IEA, Paris, **2019**.
- [2] a.J. P. Lange, *Catal Today* **2001**, *64*, 3-8; b.C. Hammond, S. Conrad, I. Hermans, *ChemSuschem* **2012**, *5*, 1668-1686; c.M. Blug, J. Leker, L. Plass, A. Günther, in *Methanol: The Basic Chemical and Energy Feedstock of the Future: Asinger's Vision Today* (Eds.: M. Bertau, H. Offermanns, L. Plass, F. Schmidt, H.-J. Wernicke), Springer Berlin Heidelberg, Berlin, Heidelberg, **2014**, pp. 603-618; d.A. I. Olivios-Suarez, A. Szecsenyi, E. J. M. Hensen, J. Ruiz-Martinez, E. A. Pidko, J. Gascon, *Acs Catal* **2016**, *6*, 2965-2981.
- [3] a.J. R. Rostrup-Nielsen, J. Sehested, J. K. Nørskov, *Adv Catal* **2002**, *47*, 65-139; b.P. Tang, Q. J. Zhu, Z. X. Wu, D. Ma, *Energy Environ Sci* **2014**, *7*, 2580-2591; c.I. Dybkjaer, K. Aasberg-Petersen, *Can J Chem Eng* **2016**, *94*, 607-612.
- [4] a.J. P. Lange, *Ind Eng Chem Res* **1997**, *36*, 4282-4290; b.S. Mokhtab, J. Mak, J. V. Valappil, D. A. Wood, *Handbook of liquefied natural gas*, First edition. ed., Elsevier, GPP, Amsterdam, **2014**; c.W. Taifan, J. Baltrusaitis, *Appl Catal B-Environ* **2016**, *198*, 525-547.
- [5] a.B. Hashiguchi, M. M. Konnick, S. M. Bischof, S. J. Gustafson, D. Devarajan, N. Gunsalus, D. H. Ess, R. A. Periana, *Science* **2014**, *343*, 1232-1237; b.V. L. Sushkevich, D. Palagin, M. Ranocchiari, J. A. van Bokhoven, *Science* **2017**, *356*, 523-+; c.J. Shan, M. Li, L. F. Allard, S. Lee, M. Flytzani-Stephanopoulos, *Nature* **2017**, *551*, 605-608; d.M. Ravi, M. Ranocchiari, J. A. van Bokhoven, *Angew Chem Int Edit* **2017**, *56*, 16464-16483; e.J. Xie, R. Jin, A. Li, Y. Bi, Q. Ruan, Y. Deng, Y. Zhang, S. Yao, G. Sankar, D. Ma, J. Tang, *Nature Catalysis* **2018**, *1*, 889-896; f.V. Paunović, P. Hemberger, A. Bodi, N. López, J. Pérez-Ramírez, *Nature Catalysis* **2018**, *1*, 363-370; g.H. J. Kim, J. Huh, Y. W. Kwon, D. Park, Y. Yu, Y. E. Jang, B.-R. Lee, E. Jo, E. J. Lee, Y. Heo, W. Lee, J. Lee, *Nature Catalysis* **2019**, *2*, 342-353; h.M. O. Ross, F. MacMillan, J. Wang, A. Nisthal, T. J. Lawton, B. D. Olafson, S. L. Mayo, A. C. Rosenzweig, B. M. Hoffman, *Science* **2019**, *364*, 566; i.Y. Zhou, L. Zhang, W. Wang, *Nature Communications* **2019**, *10*, 506; j.C. Diaz-Urrutia, T. Ott, *Science* **2019**, *363*, 1326; k.Z. Jin, L. Wang, E. Zuidema, K. Mondal, M. Zhang, J. Zhang, C. Wang, X. Meng, H. Yang, C. Mesters, F.-S. Xiao, *Science* **2020**, *367*, 193; l.S. Bai, F. Liu, B. Huang, F. Li, H. Lin, T. Wu, M. Sun, J. Wu, Q. Shao, Y. Xu, X. Huang, *Nature Communications* **2020**, *11*, 954.
- [6] a.T. Kobayashi, N. Guilhaume, J. Miki, N. Kitamura, M. Haruta, *Catal Today* **1996**, *32*, 171-175; b.R. L. McCormick, G. O. Alptekin, *Catal Today* **2000**, *55*, 269-280; c.C.-B. Wang, R. G. Herman, C.

RESEARCH ARTICLE

- Shi, Q. Sun, J. E. Roberts, *Applied Catalysis A: General* **2003**, 247, 321-333; dY. Li, D. An, Q. Zhang, Y. Wang, *The Journal of Physical Chemistry C* **2008**, 112, 13700-13708; eR. Palkovits, M. Antonietti, P. Kuhn, A. Thomas, F. Schuth, *Angew Chem Int Edit* **2009**, 48, 6909-6912; fK. Narsimhan, K. Iyoki, K. Dinh, Y. Roman-Leshkov, *Acs Central Sci* **2016**, 2, 424-429; gE. V. Kondratenko, T. Poppel, D. Seeburg, V. A. Kondratenko, N. Kalevaru, A. Martin, S. Wohlrab, *Catal Sci Technol* **2017**, 7, 366-381; hE. Tabor, J. Dedeczek, K. Mlekodaj, Z. Sobalik, P. C. Andrikopoulos, S. Sklenak, *Science Advances* **2020**, 6, eaaz9776.
- [7] aB. A. Arndtsen, R. G. Bergman, T. A. Mobley, T. H. Peterson, *Accounts Chem Res* **1995**, 28, 154-162; bM. Ahlquist, R. J. Nielsen, R. A. Periana, W. A. Goddard, *Journal of the American Chemical Society* **2009**, 131, 17110-17115; cA. A. Latimer, A. Kakekhani, A. R. Kulkarni, J. K. Norskov, *Acs Catal* **2018**, 8, 6894-6907.
- [8] J. P. Lange, K. P. de Jong, J. Ansorge, P. J. A. Tijm, in *Studies in Surface Science and Catalysis, Vol. 107* (Eds.: M. de Pontes, R. L. Espinoza, C. P. Nicolaides, J. H. Scholtz, M. S. Scurrrell), Elsevier, **1997**, pp. 81-86.
- [9] Z. R. Jovanovic, J.-P. Lange, M. Ravi, A. J. Knorpp, V. L. Sushkevich, M. A. Newton, D. Palagin, J. A. van Bokhoven, *Journal of Catalysis* **2020**, 385, 238-245.
- [10] aR. A. Periana, D. J. Taube, E. R. Evitt, D. G. Loffler, P. R. Wentreck, G. Voss, T. Masuda, *Science* **1993**, 259, 340-343; bR. A. Periana, D. J. Taube, S. Gamble, H. Taube, T. Satoh, H. Fujii, *Science* **1998**, 280, 560-564; cB. Michalkiewicz, *Kinet Catal+* **2003**, 44, 801-805; dX. Gang, Y. M. Zhu, H. Birch, H. A. Hjuler, N. J. Bjerrum, *Appl Catal a-Gen* **2004**, 261, 91-98; eT. Zimmermann, M. Soorholtz, M. Bilke, F. Schuth, *J Am Chem Soc* **2016**, 138, 12395-12400.
- [11] aL. C. Kao, A. C. Hutson, A. Sen, *J Am Chem Soc* **1991**, 113, 700-701; bM. Muehlhofer, T. Strassner, W. A. Herrmann, *Angew Chem Int Edit* **2002**, 41, 1745-+; cW. S. Chen, J. A. Kocal, T. A. Brandvold, M. L. Bricker, S. R. Bare, R. W. Broach, N. Greenlay, K. Popp, J. T. Walenga, S. S. Yang, J. J. Low, *Catal Today* **2009**, 140, 157-161; dT. Strassner, S. Ahrens, M. Muehlhofer, D. Munz, A. Zeller, *Eur J Inorg Chem* **2013**, 2013, 3659-3663; eM. Ravi, J. A. van Bokhoven, *Chemcatchem* **2018**, 10, 2383-2386.
- [12] aJ. P. Lange, P. J. A. Tijm, *Chemical Engineering Science* **1996**, 51, 2379-2387; bJ. P. Lange, *Catal Sci Technol* **2016**, 6, 4759-4767.
- [13] J.-P. Lange, in *Sustainable Strategies for the Upgrading of Natural Gas: Fundamentals, Challenges, and Opportunities* (Eds.: E. G. Derouane, V. Parmon, F. Lemos, F. Ramôa Ribeiro), Springer Netherlands, Dordrecht, **2005**, pp. 51-83.
- [14] B. Michalkiewicz, K. Kalucki, J. G. Sosnicki, *Journal of Catalysis* **2003**, 215, 14-19.
- [15] W. A. Arnold, T. G. Hartman, J. McQuillen, *J Spacecraft Rockets* **2007**, 44, 94-101.
- [16] J. A. Gladysz, D. P. Curran, I. T. Horváth, *Handbook of fluororous chemistry*, Wiley-VCH, Weinheim, **2004**.
- [17] L. Bai, M. Pravica, Y. Zhao, C. Park, Y. Meng, S. V. Sinogeikin, G. Shen, *J Phys Condens Matter* **2012**, 24, 435401.
- [18] M. Muehlhofer, T. Strassner, W. A. Herrmann, *Angewandte Chemie International Edition* **2002**, 41, 1745-1747.
- [19] D.-g. Piao, K. Inoue, H. Shibasaki, Y. Taniguchi, T. Kitamura, Y. Fujiwara, *Journal of organometallic chemistry* **1999**, 574, 116-120.
- [20] M. N. Vargaftik, I. P. Stolarov, I. I. Moiseev, *J Chem Soc Chem Comm* **1990**, 1049-1050.
- [21] I. Yamanaka, M. Soma, K. Oisuka, *Journal of the Chemical Society, Chemical Communications* **1995**, 21, 2235-2236.
- [22] J. Yuan, L. Wang, Y. Wang, *Industrial & Engineering Chemistry Research* **2011**, 50, 6513-6516.
- [23] T. Strassner, S. Ahrens, M. Muehlhofer, D. Munz, A. Zeller, *European Journal of Inorganic Chemistry* **2013**, 2013, 3659-3663.
- [24] G. Ingrosso, N. Midollini, *Journal of Molecular Catalysis A: Chemical* **2003**, 204, 425-431.
- [25] Y. Seki, J. S. Min, M. Misono, N. Mizuno, *The Journal of Physical Chemistry B* **2000**, 104, 5940-5944.
- [26] aD. Sugimori, M. Takeguchi, I. Okura, *Biotechnol Lett* **1995**, 17, 783-784; bM. Takeguchi, T. Furuto, D. Sugimori, I. Okura, *Appl Biochem Biotech* **1997**, 68, 143-152; cT. Furuto, M. Takeguchi, I. Okura, *J Mol Catal a-Chem* **1999**, 144, 257-261; dC. H. Duan, M. F. Luo, X. H. Xing, *Bioresource Technol* **2011**, 102, 7349-7353.

RESEARCH ARTICLE

Entry for the Table of Contents

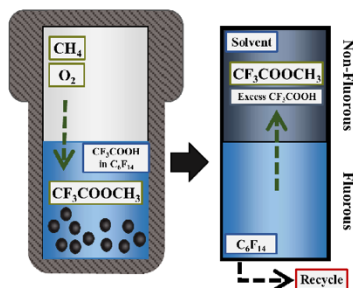

Methane is aerobically converted to an oxidant-resistant methyl ester in high yields with a solid cobalt-containing catalyst at a moderate temperature and pressure. Improved reaction conditions result from the dilution of the trifluoroacetic acid in an inert perfluoroalkane co-solvent. The fluorous character of the solvent enables the facile recovery of the product ester through a simple liquid-liquid extraction with a non-fluorous solvent.