

A Recyclable, Self-Supported Organocatalyst Based on a Poly(N-Heterocyclic Carbene)

Adam B. Powell,[†] Yasuo Suzuki,[‡] Mitsuru Ueda,[‡] Christopher W. Bielawski,[†] and Alan H. Cowley^{*,†}[†]Department of Chemistry and Biochemistry, The University of Texas at Austin, Austin, Texas 78712-0165, United States[‡]Department of Organic and Polymeric Materials, Tokyo Institute of Technology, Tokyo 152-8552, Japan

S Supporting Information

ABSTRACT: We report the synthesis and catalytic activity of a polymeric imidazolium salt. In contrast to the well-known resin-supported N-heterocyclic carbenes (NHCs), the material described herein affords a polymer with NHCs orthogonally positioned along a main chain upon generation in situ. The unique structural characteristics of the corresponding poly(NHC)s enabled the materials to display catalytic activities that were similar or superior to those displayed by monomeric analogues. Moreover, the new catalyst was successfully recovered and reused with minimal loss of performance over several cycles.

Recently, intense interest has emerged in the development of recyclable organocatalysts that may be used to facilitate reactions which typically require transition metals.¹ While resin-supported systems have found success in this regard, the process of attaching the catalyst to the solid support is often low yielding and synthetically challenging.² Furthermore, such heterogeneous systems frequently suffer from swelling and mass transport issues and operate via processes that are distinct from those of their homogeneous counterparts.³ A promising method for overcoming the limitations intrinsic to such approaches is to incorporate an organocatalyst into a soluble, recoverable polymer.⁴ Considering that N-heterocyclic carbenes (NHCs) have been proven to be powerful organocatalysts for promoting a broad range of synthetic transformations,⁵ efforts were directed toward the development of a recyclable polymeric NHC.⁶

As shown in Figure 1, there are two primary classes of polymers which contain NHCs as integral components of the main chains. The first class comprises diametrically opposed, ditopic NHCs attached to electrophiles or transition metals,^{7,8} whereas the second features NHC moieties positioned orthogonally with respect to the polymer backbone, often via metalation.⁹ The unique architectures inherent in the latter increase the likelihood of cooperative or synergistic effects between each repeating unit along the polymer chain and could ultimately result in higher efficiencies compared to monomeric analogues. Moreover, modification of such materials may lead to “self-supported” organocatalysts that are conveniently recycled and reused. Herein, we describe a recyclable poly(NHC) polymer that exhibits superior catalytic activity compared to a monomeric analogue and may be recycled repeatedly with only marginal losses in efficacy.


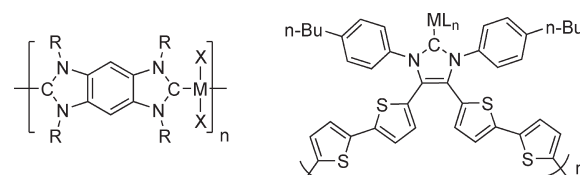


Figure 1. Representative classes of poly(NHC)s.

Scheme 1. Synthesis of Imidazolium Salt 3 and Poly(3) (R = 9,9-Dihexylfluorene)

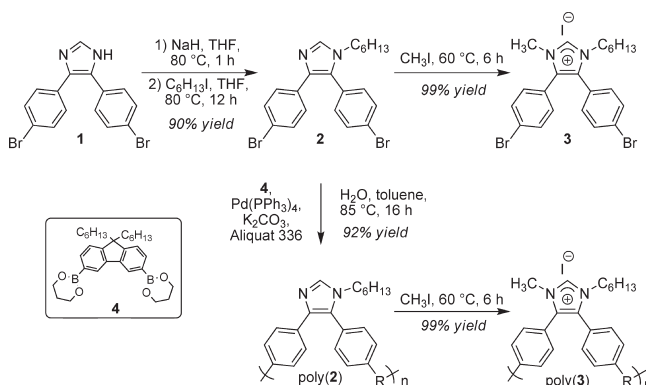


The synthesis of the aforementioned polymer is outlined in Scheme 1. Alkylation of dibromimidazole polymer **1**, which was obtained by treating 4,4-dibromobenzil with paraformaldehyde under acidic conditions,¹⁰ afforded **2** in 90% yield. Palladium catalyzed cross-coupling copolymerization of this monomer with a commercially available fluorenyl boronic acid diester (**4**) was used to obtain poly(**2**) in high yield.¹¹ The polyimidazole exhibited a weight average molecular weight (M_w) of approximately 4500 g/mol, as determined by gel permeation chromatography,¹² and displayed broad ¹H NMR signals, as expected for a high molecular weight polymer. Treatment of **2** or poly(**2**) with iodomethane afforded the monomeric catalyst precursor **3** (which served as a control; see below) or poly(**3**), respectively, in high overall yields. In general, the isolated imidazolium salts were found to be hygroscopic¹³ but stable in air.

With **3** and poly(**3**) in hand, their abilities to catalyze the benzoin condensation were compared.¹⁴ Initial efforts were


Received: January 20, 2011

Published: March 17, 2011

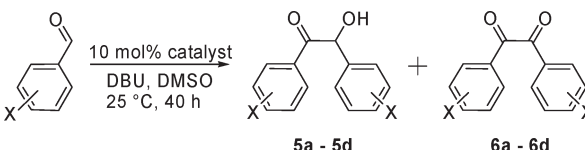Table 1. Selected Data for the Dimerization of Various Substrates Using Monomeric and Polymeric Imidazolium Salts^a


substrate	% yield ^b of benzoin product 5		% yield ^b of benzil product 6	
	with 3	with poly(3)	with 3	with poly(3)
X = H	67	67	0	0
X = <i>m</i> -Br	15	47	6	10
X = <i>p</i> -CF ₃	9	43	2	4
X = <i>p</i> -OCH ₃	29	52	9	9

^aIn a typical experiment, 2.94 mmol of substrate, to mol % of 3 or the repeat unit of poly(3), 15 mol % DBU, and 2.0 mL of dry DMSO were stirred for 40 h at 25 °C under argon. ^bIsolated yield.

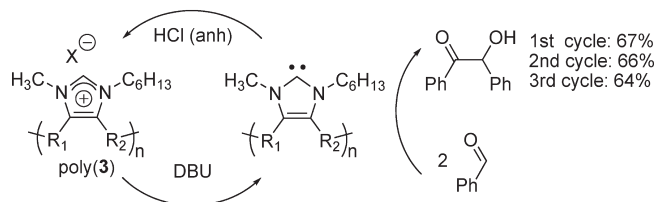Scheme 2. Schematic Representation of the Procedure Used to Recycle and Reuse Poly(3)

directed toward optimizing the reaction conditions, which included catalyst loading, temperature, base (to generate the free NHC in situ), solvent, and time (see Supporting Information). Using optimized conditions (DBU as base, minimal DMSO, room temperature, 40 h), the catalytic activities of 3 and poly(3) were explored using benzaldehyde and a range of functionalized derivatives. As shown in Table 1, the catalytic activity exhibited by poly(3) was similar to that of 3; however, higher yields of products were obtained with the former when electron-rich or -deficient benzaldehydes were employed. As noted above, the enhanced reactivity may be due to a synergistic effect between the catalytically active sites along the polymer backbone.^{15,16} In some cases, the corresponding benzil products were detected in small amounts ($\leq 10\%$), which may be attributed to the mildly oxidizing properties of DMSO.¹⁷

The ability of poly(3) to be recovered and reused was also explored. After stirring a mixture of benzaldehyde, poly(3), DBU, and DMSO under an atmosphere of argon for 40 h, a solution of 4.0 M HCl in dioxane was added. The reaction mixture was stirred for an additional 1 h, after which excess ethyl acetate was added. Subsequent collection of the yellow precipitate via filtration afforded poly(3) in an isolated yield of 92%, as verified by ¹H NMR spectroscopy (the diagnostic imidazolium proton was observed as a broad singlet at $\delta = 9.50$ ppm; DMSO-*d*₆). Benzoin

was also isolated as a product of this reaction in good yield (Scheme 2) upon aqueous workup of the filtrate and further purification by flash column chromatography. This procedure was repeated twice with only a marginal loss in catalytic efficiency per cycle (see Scheme 2).¹⁸ In contrast, the monomeric analogue 3 could not be recovered following the dimerization reaction using an analogous protocol.

In summary, a catalytically active, “self-supported” poly(NHC) precursor was synthesized via methylation following the cross-coupling copolymerization of 2 with a fluorenyl boronic acid diester. The corresponding catalyst was generated in situ and used to facilitate the dimerization of several benzaldehyde derivatives in good yields. The results presented herein not only demonstrate that NHCs can display enhanced catalytic activities upon incorporation into a polymeric framework but also should enable other NHC-based catalysts to be conveniently regenerated and reused.

■ ASSOCIATED CONTENT

Supporting Information. Additional experimental details and spectroscopic data. This material is available free of charge via the Internet at <http://pubs.acs.org>.

■ AUTHOR INFORMATION

Corresponding Author
 cowlley@mail.utexas.edu

■ ACKNOWLEDGMENT

We are grateful to the Robert A. Welch Foundation (Grants F-0003 to A.H.C. and F-1621 to C.W.B.) for their generous support of this work.

■ REFERENCES

- (1) For excellent reviews on using NHC–transition metal complexes to facilitate various catalytic reactions, see: (a) Díez-González, S.; Marion, S. P.; Nolan, S. P. *Chem. Rev.* **2009**, *109*, 3612–3676. (b) Würtz, S.; Glorius, F. *Acc. Chem. Res.* **2008**, *41*, 1523–1533. (c) John, A.; Ghosh, P. *Dalton Trans.* **2010**, *39*, 7183–7206.
- (2) (a) Gruttadauria, M.; Giacalone, F.; Noto, R. *Chem. Soc. Rev.* **2008**, *37*, 1666–1688. (b) Youk, S. H.; Oh, S. H.; Rho, H. S.; Lee, J. E.; Lee, J. W.; Song, C. E. *Chem. Commun.* **2009**, 2220–2222. (c) Heitbaum, M.; Glorius, F.; Escher, I. *Angew. Chem., Int. Ed.* **2006**, *45*, 4732–4762. (d) Parida, K. M.; Singha, S.; Sahoo, P. C. *J. Mol. Catal. A: Chem.* **2010**, *325*, 40–47. (e) Parida, K. M.; Rath, D. *J. Mol. Catal. A: Chem.* **2009**, *310*, 93–100.
- (3) (a) Kristensen, T. E.; Hansen, T. *Eur. J. Org. Chem.* **2010**, 3179–3204. (b) Parida, K. M.; Rath, D.; Dash, S. S. *J. Mol. Catal. A: Chem.* **2010**, *318*, 85–93.
- (4) For examples of recyclable organocatalysts, see: (a) Rodríguez Llansola, F.; Miravet, J. F.; Escuder, B. *Chem. Commun.* **2009**, 7303–7305. (b) Ghosh, S. K.; Zheng, Z.; Ni, B. *Adv. Synth. Catal.* **2010**, *352*, 2378–2382.
- (5) (a) Marion, N.; Díez-González, S.; Nolan, S. P. *Angew. Chem., Int. Ed.* **2007**, *46*, 2988–3000. (b) Enders, D.; Niemeier, O.; Henseler, A. *Chem. Rev.* **2007**, *107*, 5606–5655. (c) Struble, J. R.; Bode, J. W. *Tetrahedron* **2009**, *65*, 4957–4967. (d) Phillips, E. M.; Wadamoto, M.; Roth, H. S.; Ott, A. W.; Scheidt, K. A. *Org. Lett.* **2009**, *11*, 105–108. (e) Kaeobamrung, J.; Kozłowski, M. C.; Bode, J. W. *Proc. Natl. Acad. Sci. U.S.A.* **2010**, *107*, 20661–20665. (f) Moore, J. L.; Rovis, T. *Top. Curr. Chem.* **2010**, *291*, 77–144. (g) Denk, M. K.; Hezarkhani, A.; Zheng, F.-L. *Eur. J. Inorg. Chem.* **2007**, *22*, 3527–5734. (h) Jokić, N. B.; Straubinger, C. S.;

Goh, S. L. M.; Herdtweck, E.; Herrmann, W. A.; Kühn, F. E. *Inorg. Chim. Acta* **2010**, 363, 4181–4188.

(6) For a review of coordination and supramolecular polymers, see: Yang, S. K.; Ambade, A. V.; Weck, M. *Chem. Soc. Rev.* **2011**, 40, 129–137.

(7) For a recent review of main-chain poly(NHC)s, see: Merce, L.; Albrecht, M. *Chem. Soc. Rev.* **2010**, 39, 1903–1902. For examples of main-chain poly(NHCs), see: (a) Guerret, O.; Sole, S.; Gornitzka, H.; Teichert, M.; Trinquier, G.; Bertrand, G. *J. Am. Chem. Soc.* **1997**, 119, 6668–6669. (b) Coady, D. J.; Khramov, D. M.; Norris, B. C.; Tennyson, A. G.; Bielawski, C. W. *Angew. Chem., Int. Ed.* **2009**, 48, 5187–5190. (c) Norris, B. C.; Bielawski, C. W. *Macromolecules* **2010**, 43, 3591–3593. (d) Kamplain, J. W.; Bielawski, C. W. *Chem. Commun.* **2006**, 1727–1729. (e) Boydston, A. J.; Rice, J. D.; Sanderson, M. D.; Dykhno, O. L.; Bielawski, C. W. *Organometallics* **2006**, 25, 6087–6098. (f) Boydston, A. J.; Bielawski, C. W. *Dalton Trans.* **2006**, 34, 4073–4077.

(8) A main-chain poly(NHC) containing Pd has been reported to facilitate Suzuki–Miyaura coupling reactions in aqueous media; see: Karimi, B.; Akhavan, P. F. *Chem. Commun.* **2009**, 3750–3752.

(9) (a) Powell, A. B.; Bielawski, C. W.; Cowley, A. H. *J. Am. Chem. Soc.* **2009**, 131, 18232–18233. (b) Powell, A. B.; Bielawski, C. W.; Cowley, A. H. *J. Am. Chem. Soc.* **2010**, 132, 10184–10194.

(10) Puratchikody, A.; Doble, M. *Bioorg. Med. Chem.* **2007**, 15, 1083–1090.

(11) The molecular weight and polydispersity of poly(**2**) were similar to those found for other polymers prepared by Suzuki polymerization; see: (a) Li, Y.; Li, H.; Xu, B.; Li, Z.; Chen, F.; Feng, D.; Zhang, J.; Tian, W. *Polymer* **2010**, 51, 1786–1795. (b) Shi, W.; Jiang, X.; Zen, W.; Huang, F.; Yang, W.; Liu, R.; Cao, Y. *Macromol. Chem. Phys.* **2009**, 210, 150–160. (c) Jayakannan, M.; van Dongen, J. L. J.; Janssen, R. A. J. *Macromolecules* **2001**, 34, 5386–5393.

(12) Polymer molecular weights are reported relative to polystyrene standards in (0.1 M LiBr) DMF at 40 °C with a flow rate of 1.0 mL/min.

(13) For other examples of main-chain polyimidazolium salts, see: (a) Tennyson, A. G.; Kamplain, J. W.; Bielawski, C. W. *Chem. Commun.* **2009**, 2124–2126. (b) Toba, M.; Nakashima, T.; Kawai, T. *Macromolecules* **2009**, 42, 8068–8075.

(14) For an excellent review of NHC-based organocatalysts, see: Marion, N.; Díez-González, S.; Nolan, S. P. *Angew. Chem., Int. Ed.* **2007**, 46, 2988–3000. For an example of a self-supported, polymeric gel containing thiazolium salts used to facilitate Stetter-type reactions, see: Barrett, A. G. M.; Love, A. C.; Tedeschi, L. *Org. Lett.* **2004**, 6, 3377–3380. For an example of a recyclable triazolium-based ionic liquid used as an organocatalyst, see: Yu, F.; Zhang, R.; Xie, C.; Yu, S. *Tetrahedron* **2010**, 66, 9145–9150. For a recent example of using recyclable polymers containing pendant NHCs to facilitate benzoin condensations, see: Pinaud, J.; Vignolee, J.; Gnanou, Y.; Taton, D. *Macromolecules* **2011** dx.doi.org/10.1021/ma1024285.

(15) Madhavan, N.; Jones, C. W.; Weck, M. *Acc. Chem. Res.* **2008**, 41, 1153–1165.

(16) Dicationic imidazolium salts have been shown to be more effective catalysts than their corresponding monomers; see: Mavis, M. E.; Yolacan, C.; Aydogan, F. *Tetrahedron Lett.* **2010**, 51, 4509–4511.

(17) Shimakawa, Y.; Morikawa, T.; Sakaguchi, S. *Tetrahedron Lett.* **2010**, 51, 1786–1789.

(18) For an example of a recyclable benzoin condensation organocatalyst tethered to polystyrene beads, see: Storey, J. M. D.; Williamson, C. *Tetrahedron Lett.* **2005**, 46, 7337–7339.