



## Mesomorphism dependence on halogenated chalconyl esters in terms of molecular flexibility/rigidity

Vinay S. Sharma & R. B. Patel

To cite this article: Vinay S. Sharma & R. B. Patel (2016) Mesomorphism dependence on halogenated chalconyl esters in terms of molecular flexibility/rigidity, Molecular Crystals and Liquid Crystals, 633:1, 80-90, DOI: [10.1080/15421406.2016.1177887](https://doi.org/10.1080/15421406.2016.1177887)

To link to this article: <http://dx.doi.org/10.1080/15421406.2016.1177887>



Published online: 24 Aug 2016.



Submit your article to this journal [↗](#)



Article views: 10



View related articles [↗](#)



View Crossmark data [↗](#)

## Mesomorphism dependence on halogenated chalconyl esters in terms of molecular flexibility/rigidity

Vinay S. Sharma and R. B. Patel

Chemistry Department, K. K. Shah Jarodwala Maninagar Science College, Gujarat University, Ahmedabad, India

### ABSTRACT

Vinyl carboxy central group containing a novel chalconyl ester homologous series:  $\text{RO.C}_6\text{H}_4.\text{CH}=\text{CH.COO.C}_6\text{H}_4.\text{CH}=\text{CH.CO.C}_6\text{H}_4.\text{I}$  (para) have been synthesized and studied with a view to understand and establish the relation between thermotropic liquid crystalline (LC) behaviors and the molecular structure. Novel chalconyl ester homologous series consists of thirteen homologs ( $\text{C}_1\text{--C}_{18}$ ).  $\text{C}_1\text{--C}_3$  homologs are non-mesogenic,  $\text{C}_4$  homolog is enantiotropic nematogenic and the rest of the homologs ( $\text{C}_5\text{--C}_{18}$ ) are enantiotropically smectogenic plus nematogenic. Phase transition temperatures and textures of LC phase were determined by an optical polarizing microscopy (POM) equipped with a heating stage. Cr-M/I, Sm-N, N-I transition curves in a phase diagram behaved in normal manner. Sm-N and N-I transition curves exhibited odd-even effect from  $\text{C}_4\text{--C}_{10}$  or nearby  $\text{C}_{10}$  homolog. Textures of nematic phase are threaded or Schlieren and that of the smectic phase are of the type smectic A or C. Analytical and spectral data confirms the molecular structure of homologs. Thermal stabilities for smectic and nematic mesophases are 155.0 and 180.7, respectively, and their corresponding mesophaselengths are varied from minimum to maximum at  $17.0^\circ\text{C}\text{--}39.0^\circ\text{C}$  as well as  $15.0^\circ\text{C}\text{--}30.0^\circ\text{C}$ . Thus, it is middle ordered melting type series. The group efficiency orders derived on the basis of smectic and nematic thermal stabilities are as under: Sm:  $-\text{C}_6\text{H}_4.\text{I} > -\text{C}_6\text{H}_4.\text{Cl} > -\text{C}_4\text{H}_3\text{S}$  and N:  $-\text{C}_6\text{H}_4.\text{I} > -\text{C}_6\text{H}_4.\text{Cl} > -\text{C}_4\text{H}_3\text{S}$  from comparative study of structurally similar analogous series

### KEYWORDS

Enantiotropy; liquid crystals; mesophaselength; nematic; smectic

## Introduction

A liquid crystalline (LC) state [1] has proved its ability and importance in the benefit of mankind in the various fields of scientific and technological applications [2–9]. Present investigation on thermotropic LC state have been planned with an aim to understand and establish the effect of molecular structure on LC properties [10–14] of novel substances. Novel substances will be synthesized through homologous series consisting of two or three phenyl rings, one or two central bridges, and two terminal end groups viz.  $-\text{OR}$  and  $-\text{I}$ , the left and right sided polar terminal groups. One of the central groups will be  $-\text{CH}=\text{CH}-\text{CO}-$  which will be bioactive and other will be vinyl carboxylate ester group. Thus, thermotropy which may be useful for LC devices as well as bioactivity may be useful for LC devices and bioactivity which

may be useful for its lyotropic study. Hence dual study of same novel compounds can be facilitated. Present study will include only synthesis, characterization, results and discussion will be interpreted on the basis of molecular rigidity and flexibility [15–17] for thermometric data of novel substances. Number of ester homologous series have been reported till the date [18–25]. Group efficiency order on the basis of thermal stability and the early commencement of mesophase will be derived from comparative study of analogous series.

## Experimental

### Synthesis

4-*n*-alkoxy cinnamic acids (A) were synthesized by the alkylation of 4-hydroxy benzaldehyde to form 4-alkoxy benzaldehyde and further reaction with Malonic acid in pyridine in presence of few drops of piperidine as a catalyst [26],  $\alpha$ -4-Hydroxy phenyl  $\beta$ -4'-iodo benzoyl ethylene (m.p 167°C, yield 76%) (B) was prepared by usual established method [27]. Final product were prepared by the esterification of (A) and (B) [28]. Thus, the ester chalconyl homolog derivatives were filtered, washed with sodium bicarbonate solution followed by distilled water, dried and purified till constant transition temperatures obtained using an optical polarizing microscope equipped with a heating stage. Alkyl halides, EtOH, KOH, Acetone, DCM, 4-Iodo acetophenone, 4-Hydroxy benzaldehyde, dicyclohexyl carbodimide, Dimethyl amino pyridine, Malonic acid etc., required for synthesis were used as received except solvents which were dried and distilled prior to use. The synthetic route to the series is mentioned below as scheme-1

### Characterization


Representative homologs of a series were characterized by elemental analysis, Infrared spectroscopy,  $^1\text{H}$  NMR spectra, IR spectra were recorded on Perkin-Elmer spectrum GX,  $^1\text{H}$  NMR spectra were recorded on Bruker using  $\text{CDCl}_3$  as solvent. Microanalysis was performed on Perkin-Elmer PE 2400 CHN analyzer (Table 1). Transition temperature (Table 4) and LC properties (Textures) were determined using an optical polarizing microscopy equipped with heating stage and digital camera (POM). Texture images of nematic phase were characterized by miscibility method (Table 2), Decomposition temperatures (Table 3) were determined using of Shimadzu DSC 60 differential Scanning Calorimeter with a heating rate of 5–10.0°C  $\text{min}^{-1}$  in air and it was calibrated with indium (156.6°C, 28.45 J  $\text{g}^{-1}$ ) Holland. Thermodynamic quantities enthalpy ( $\Delta H$ ) and entropy ( $\Delta S = \Delta H/T$ ) are qualitatively discussed.

## Analytical data

### IR spectra in $\text{cm}^{-1}$ for hexadecyloxy & octadecyloxy derivatives

**Hexadecyloxy:** 2924 (C-H str. of alkane), 2850 (C-H str. of  $-(\text{CH}_2)_n$  group of  $-\text{OC}_{16}\text{H}_{33}$  group), 1658 (C = O str. of carbonyl carbon of ester), 1600 (C = C str. of alkene), 1448, 1510, 1571 (C = C str. of aromatic ring), 952, 1024 (C-H bending of alkene), 1170 (C-O str. of ether linkage), 1251 (C-O str. of ester group), 1359 (C-H bending of alkene), 648, 570 (C-I str.). IR data confirms the molecular structure.

**Octadecyloxy:** 2916 (C-H str. of alkane), 2870 (C-H str. of  $-(\text{CH}_2)_n$  group of  $-\text{OC}_{18}\text{H}_{37}$  group), 1730 (C = O str. of carbonyl carbon of ester), 1600 (C = C str. of alkene), 1467, 1533,

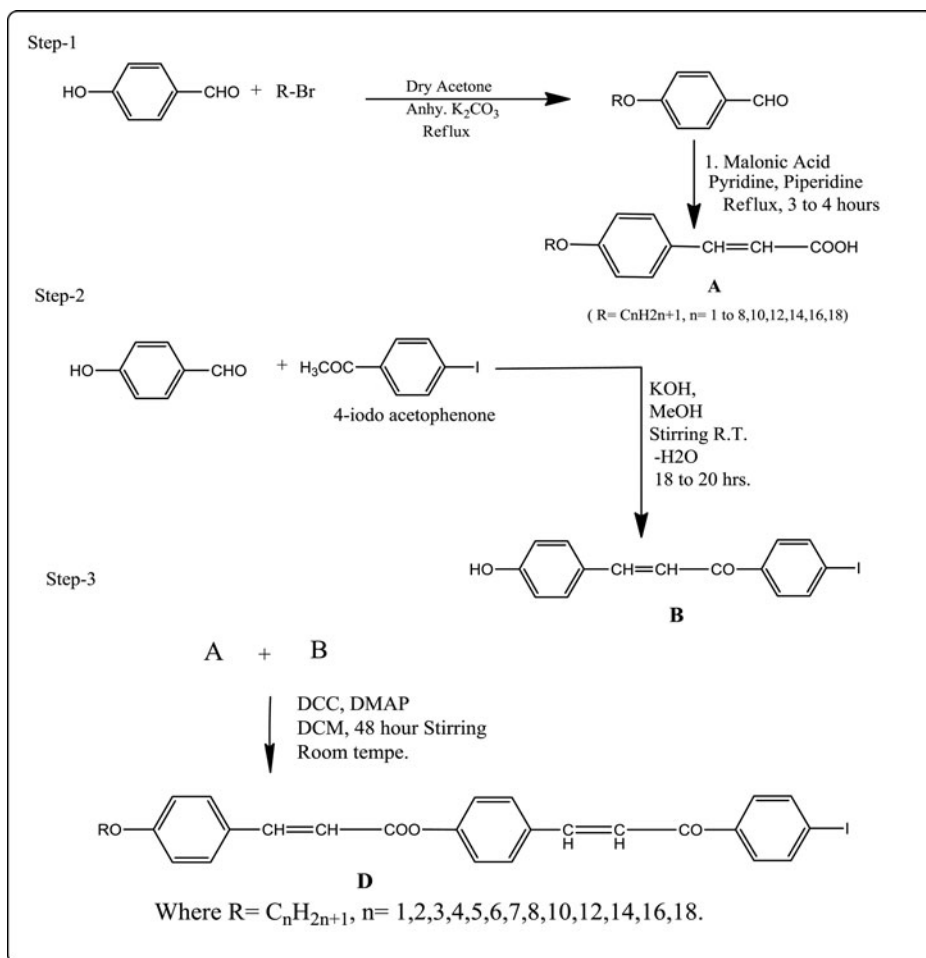

**Scheme 1.** Synthesis route to the series.

**Table 1.** Elemental analysis for (1) hexyloxy (2) heptyloxy (3) decyloxy (4) octadecyloxy derivatives.

Sr. No.	Molecular formula	%Elements found			%Elements calculated		
		C	H	I	C	H	I
1	$C_{30}H_{29}O_4I$	62.41	4.98	21.80	62.50	5.03	21.87
2	$C_{31}H_{31}O_4I$	62.66	5.18	21.20	62.73	5.22	21.24
3	$C_{34}H_{39}O_4I$	64.00	6.08	19.72	64.05	6.12	19.78
4	$C_{42}H_{53}O_4I$	67.39	8.03	16.82	67.46	7.09	16.86

**Table 2.** Texture of nematic phase of  $C_5$ ,  $C_6$ ,  $C_{12}$ ,  $C_{14}$  by miscibility method.

Sr. No.	Homolog	Texture
1	$C_5$	Threaded
2	$C_6$	Threaded
3	$C_{12}$	Schlieren
4	$C_{14}$	Schlieren

**Table 3.** Transition temperature ( $^{\circ}\text{C}$ ) and enthalpy ( $\text{J g}^{-1}$ ) and entropy change ( $\text{J g}^{-1}\text{K}^{-1}$ ) by DSC measurement.

Homologs or Comp.	Transition	Heating scan( $^{\circ}\text{C}$ )	Cooling scan( $^{\circ}\text{C}$ )	$\Delta H$ ( $-\text{Jg}^{-1}$ )	$\Delta H$ ( $\text{Jg}^{-1}$ )	$\Delta S$ ( $\text{J g}^{-1}\text{K}^{-1}$ )	$\Delta S$ ( $\text{J g}^{-1}\text{K}^{-1}$ )
<b>C<sub>4</sub></b>	<b>Cr-SmC</b>	—	—	—	—	—	—
	<b>SmC-N</b>	175	168	8.32	7.21	0.0185	0.0163
	<b>N-I</b>	>180	—	—	—	—	—
<b>C<sub>7</sub></b>	<b>Cr-SmC</b>	122	121	30.30	33.01	0.0767	0.0837
	<b>SmC-N</b>	159	160	6.28	5.97	0.0145	0.0137
	<b>N-I</b>	>170	—	—	—	—	—
<b>C<sub>10</sub></b>	<b>Cr-SmC</b>	134	132	38.54	40.08	0.0946	0.0989
	<b>SmC-N</b>	166	162	7.84	6.62	0.0178	0.0152
	<b>N-I</b>	>180	—	—	—	—	—
<b>C<sub>14</sub></b>	<b>Cr-SmC</b>	116	104	33.56	34.06	0.0862	0.0903
	<b>SmC-N</b>	137	131	5.56	5.40	0.0135	0.0133
	<b>N-I</b>	>145	—	—	—	—	—

1579 ( $\text{C}=\text{C}$  str. of aromatic ring), 1004, 1062 ( $\text{C-H}$  bending of alkene), 1143, 1199 ( $\text{C-O}$  str. of ether linkage), 1251 ( $\text{C-O}$  str. of ester group), 1309 ( $\text{C-H}$  bending of alkene), 690, 570 ( $\text{C-I}$  str.). IR data confirms the molecular structure.


### **<sup>1</sup>HNMR spectra in $\text{CDCl}_3$ in $\delta$ ppm for heptyloxy & octyloxy derivative**

**Heptyloxy:** 0.82 (t, 3H,  $-\text{CH}_3$  of  $-\text{C}_7\text{H}_{15}$ ), 1.29 (t, 4H,  $\text{CH}_3\text{-CH}_2\text{-CH}_2\text{-CH}_2\text{-CH}_2\text{-OC}_7\text{H}_{15}$ ), 1.43 (p, 5H  $-\text{CH}_2\text{-CH}_2\text{-CH}_2\text{-}$  of  $-\text{OC}_7\text{H}_{15}$ ), 1.31 (q, 4H,  $-\text{CH}_2\text{-CH}_3$ ), 1.73(t, 2H,  $-\text{CH}_2\text{-CH}_2\text{-}$  of  $-\text{OC}_7\text{H}_{15}$ ), 4.06(t, 3H,  $-\text{OCH}_2\text{-CH}_2\text{-}$  of  $-\text{OC}_7\text{H}_{15}$ ), 6.51 & 7.59 (d, 2H,  $-\text{CH}=\text{CH}-$ ), 7.2 & 7.74 (4.01 H, middle phenyl ring), 7.65 & 7.97 (4H, third phenyl ring), 6.93 & 7.61 (4H, phenyl ring with alkoxy chain). NMR data confirms the molecular structure.

**Octyloxy:** 0.82 (t, 3H,  $-\text{CH}_3$  of  $-\text{C}_8\text{H}_{17}$ ), 1.75(t, 4H,  $\text{CH}_3\text{-CH}_2\text{-CH}_2\text{-CH}_2\text{-CH}_2\text{-CH}_2\text{-OC}_8\text{H}_{17}$ ), 1.29 (p, 5H  $-\text{CH}_2\text{-CH}_2\text{-CH}_2\text{-}$  of  $-\text{OC}_8\text{H}_{17}$ ), 1.31 (q, 4H,  $-\text{CH}_2\text{-CH}_3$ ), 1.73(t, 2H,  $-\text{CH}_2\text{-CH}_2\text{-}$  of  $-\text{OC}_8\text{H}_{17}$ ), 3.93 (t, 3H,  $-\text{OCH}_2\text{-CH}_2\text{-}$  of  $-\text{OC}_8\text{H}_{17}$ ), 6.51 & 7.59 (d, 2H,  $-\text{CH}=\text{CH}-$ ).

**Table 4.** Transition temperatures in  $^{\circ}\text{C}$  for series 1.  $\alpha$ -4-(4'-n-alkoxycinnamoyloxy) phenyl- $\beta$ -4'-iodo benzoyl ethylenes.

Transition temperatures in $^{\circ}\text{C}$				
Sr.no	R = n-alkyl group			
		Smectic	Nematic	Isotropic
1	C <sub>1</sub>	—	—	210.0
2	C <sub>2</sub>	—	—	208.0
3	C <sub>3</sub>	—	—	218.0
4	C <sub>4</sub>	—	176.0	206.0
5	C <sub>5</sub>	137.0	164.0	194.0
6	C <sub>6</sub>	142.0	159.0	189.0
7	C <sub>7</sub>	128.0	156.0	184.0
8	C <sub>8</sub>	130.0	169.0	188.0
9	C <sub>10</sub>	147.0	177.0	198.0
10	C <sub>12</sub>	139.0	178.0	193.0
11	C <sub>14</sub>	128.0	152.0	171.0
12	C <sub>16</sub>	99.0	122.0	145.0
13	C <sub>18</sub>	96.0	118.0	139.0

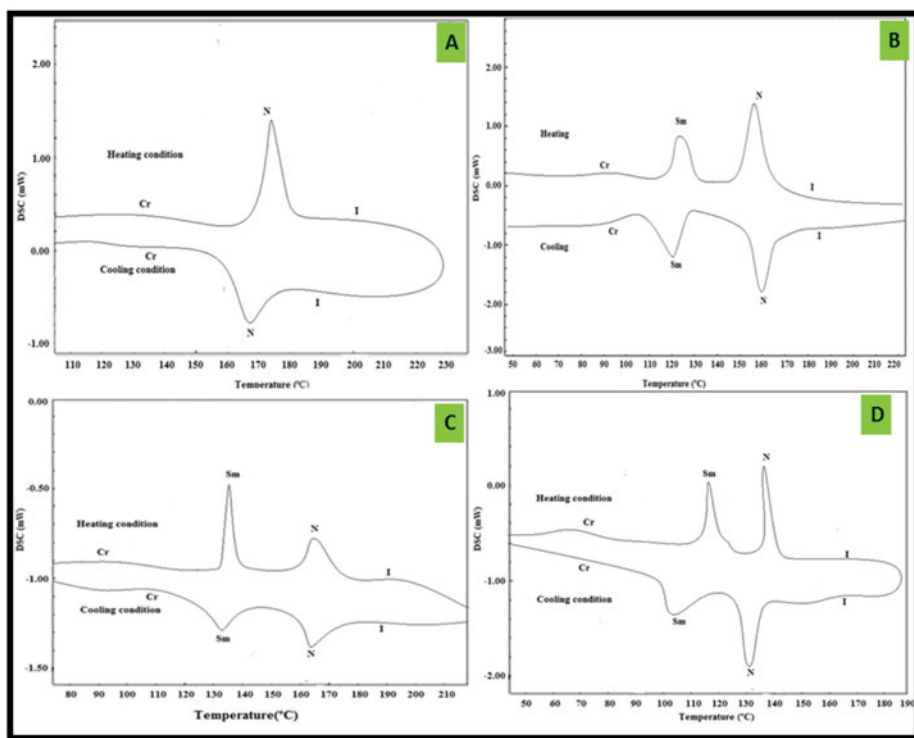


**Figure 1.** DSC measurement **(A)**  $C_4$  homolog at heating condition endothermic peak at  $175^{\circ}\text{C}$ , while at cooled condition peak observed at  $168^{\circ}\text{C}$ . **(B)**  $C_7$  homolog, first endothermic peak at  $122^{\circ}\text{C}$  and second peak at  $159^{\circ}\text{C}$  during heating stage, while in cooling stage two peak trace at  $160^{\circ}\text{C}$  and  $121^{\circ}\text{C}$  enantiotropically. **(C)**  $C_{10}$  homolog, heating condition first endothermic peak observed at  $134^{\circ}\text{C}$  and second endothermic at  $166^{\circ}\text{C}$  and at cooled condition two peaks are obtained at  $162^{\circ}\text{C}$  and  $132^{\circ}\text{C}$ . **(D)**  $C_{14}$  homolog, two endothermic peak observed at  $116^{\circ}\text{C}$  and  $137^{\circ}\text{C}$ , while at cooling stage trace two peaks at  $131^{\circ}\text{C}$  and  $104^{\circ}\text{C}$ .

CH-), 7.21 & 7.74 (4.01 H, middle phenyl ring), 7.56 & 7.97 (4H, third phenyl ring), 6.93 & 7.61 (4H, phenyl ring with alkoxy chain). NMR data confirms the molecular structure.

## Results and discussion

A novel chalconyl ester homologous series of LC (thermotropic) property determined from condensation of dimeric trans cinnamic acids and  $\alpha$ -4-Hydroxy phenyl  $\beta$ -4'-Iodo benzoyl ethylene (m.p  $167^{\circ}\text{C}$  & yield 76%) is synthesized and evaluated their some thermometric data to correlate mesomorphic behaviors and the molecular structure through molecular rigidity and flexibility. Mesomorphism commences from  $C_4$  homolog. All the mesogenic homologs are enantiotropically smectogenic plus nematogenic except  $C_4$  homolog which missed smectogenic character and exhibited only nematic character in enantiotropic manner. Transition temperatures (Table 4) as determined using an optical polarizing microscopy (POM) equipped with heating stage are plotted versus the number of carbon atoms present in  $n$ -alkyl chain 'R' of -OR group. DSC thermogram of  $C_4$ ,  $C_7$ ,  $C_{10}$ ,  $C_{14}$  homologue is shown in Figure 1 during heating and cooling condition. Then, on linking like or related transition points; Cr-M/I, Sm-N and N-I transition curves are obtained, showing phase behaviors of series as shown in Fig. 2. Cr-M/I transition curve adopts a zigzag path of rising and falling with overall descending tendency and behaved in normal manner. Sm-N transition curve initially rises

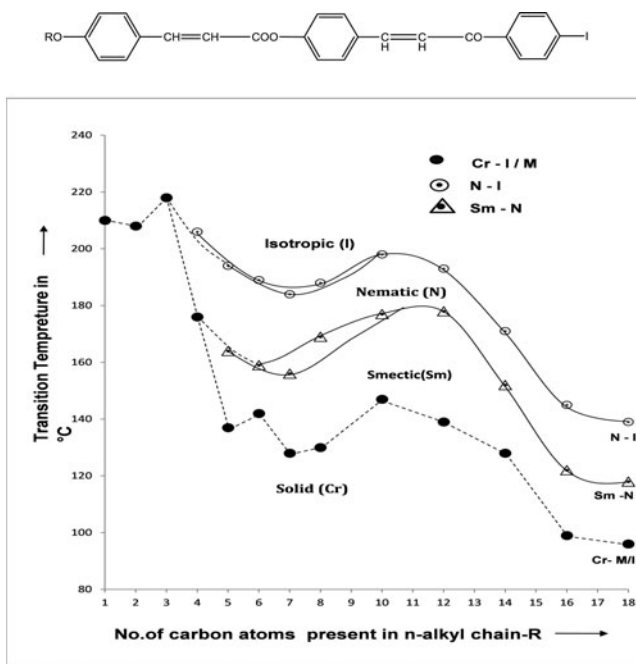


**Figure 2.** Phase behaviors of series.

and then passes through maxima at  $C_{12}$  homolog and descended as series is ascended with exhibition of odd-even effect and behaved in normal manner. N-I transition curve initially descended up to  $C_7$  homolog, ascended up to  $C_{10}$  homolog and then descended up to  $C_{18}$  homolog with exhibition of odd-even effect. Thus, it behaved in normal established manner. Odd-even effect in Sm-N and N-I transition curves appeared up to nearby  $C_{10}$  or exactly at  $C_{10}$  homolog respectively, and then it disappeared for higher homologs of longer *n*-alkyl chain 'R' of -OR group. Thus, alternation and lowering of transition temperature as compared to the corresponding trans *n*-alkoxy cinnamic acids are observed for present novel homologous series. Transition curves for smectic and nematic are extrapolated to nonsmectogen  $C_4$  and nonmesogen  $C_3$  homolog, respectively, to predict [29,30,31,32] their probable latent transition temperature (LTT) and to magnify the odd-even effects.


The changing of mesogenic behavior from homolog to homolog in the same novel series is observed by varying number of carbon atom or atoms in *n*-alkyl chain 'R' of -OR group, keeping the rest of the molecular part unchanged throughout a series. Textures of nematic phase are threaded or schlieren and that of the smectic phase are of the type smectic A or C. Analytical, thermal and the spectral data supported molecular structures of homologs. Thermal stabilities for smectic and nematic are  $155^{\circ}C$  and  $180.7^{\circ}C$ , respectively, whose total mesophase length (Sm + N) are from  $30^{\circ}C$  to  $58^{\circ}C$ . The POM image and phase sequence at cooled condition shown in Fig. 3(i) and Fig. 3(ii), respectively.

The disappearance of dimerization of trans-4-*n*-alkoxy cinnamic acids and the lowering of transition temperatures of corresponding novel homologs of present investigation is attributed to the breaking of hydrogen bonding of trans vinyl carboxylic acids by esterification process. The inexistence of mesogenic behaviors by  $C_1$ ,  $C_2$  and  $C_3$  homolog is due to the low magnitudes of dispersion forces and low magnitudes of dipole-dipole interactions which induces unsuitable magnitudes of intermolecular anisotropic forces of cohesion and closeness. Instead, it induces high crystallizing tendency and abruptly breaks the crystal lattices under

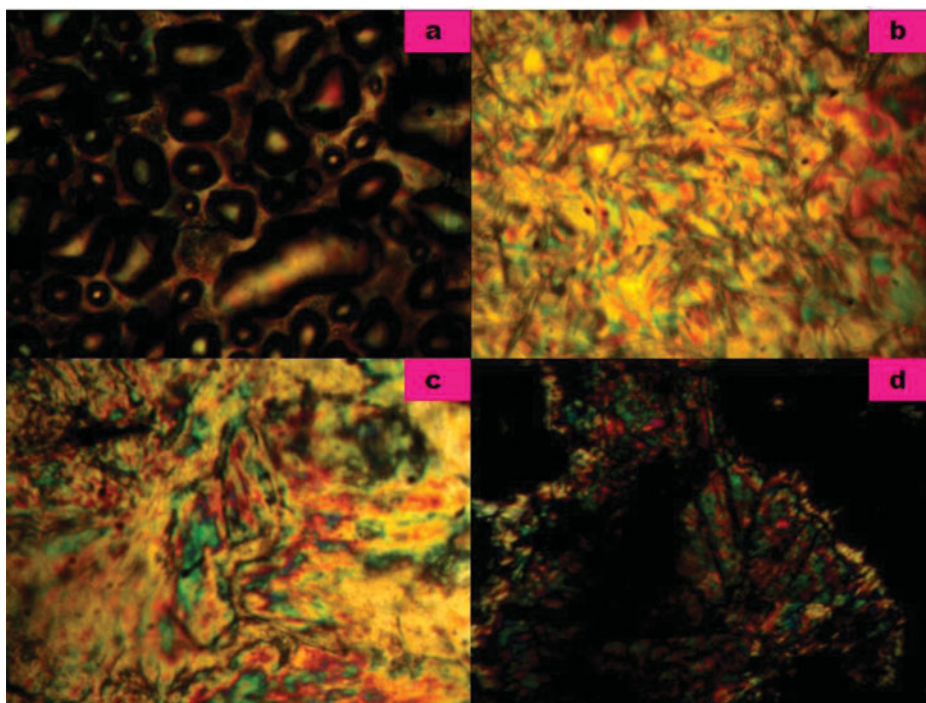


**Figure 3. (i).** (a). Schlieren type texture of nematic phase of comp.  $C_{12}$  at  $178^{\circ}\text{C}$ . (b). Sm C phase of comp.  $C_{14}$  at  $128^{\circ}\text{C}$ . (c). nematic phase of comp.  $C_{16}$  at  $122^{\circ}\text{C}$ . (d). smectic phase of comp.  $C_{18}$  at  $96^{\circ}\text{C}$ .

thermometric condition and sharply transform into isotropic liquid from crystalline state (or vice versa) without passing through an intermediate state of existence LC. The exhibition of smectic nematic mesophase formation is attributed to the suitable magnitudes of anisotropic forces of intermolecular lateral and then end-to-end cohesion and closeness as a consequence

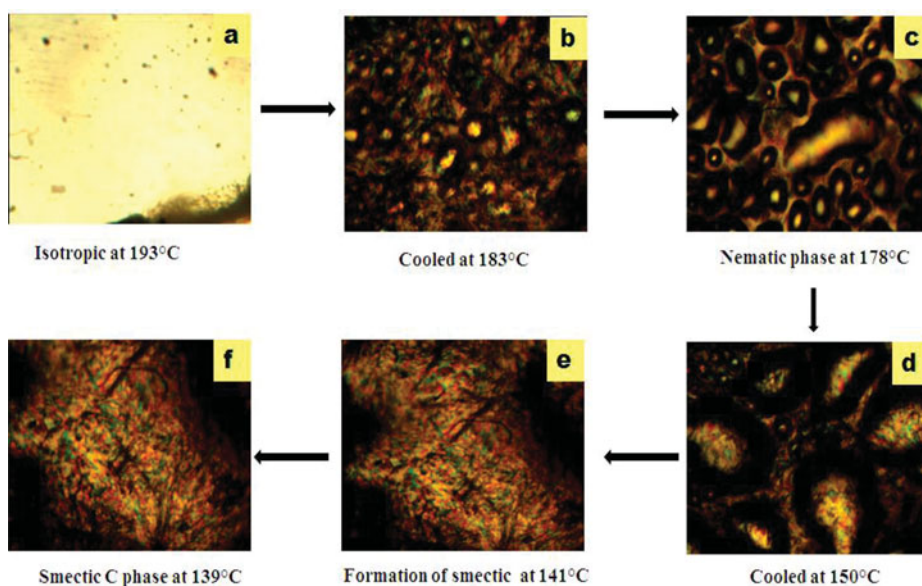

**Figure 3. (ii).** Phase sequence of  $C_{12}$  homolog on cooling condition.

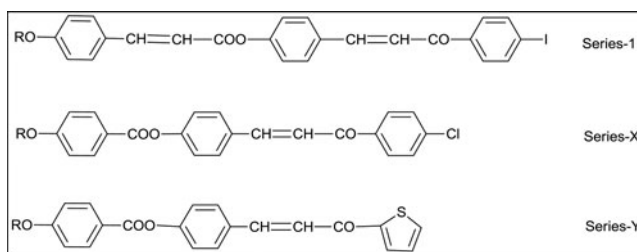

**Figure 4.** Structurally similar analog series.

of favorable molecular rigidity and flexibility, which maintain the floating of a sample substance with sliding layered molecular arrangement due to preoccupied lamellar packing of molecules for definite range of temperatures and then continue floating with residual end to end attractions which is suitable to facilitate floating of the same smectogenic molecular state with statistically parallel orientational order for another higher ranged temperature to show nematic mesophase formation under the influence of externally exposed thermal vibrations. The exhibition of odd-even effect is due to added methylene unit to *n*-alkyl chain 'R' of -OR group up to C<sub>10</sub> or nearby C<sub>10</sub> homolog. However, alternation of transition temperatures diminishes or disappears for higher homologs of longer *n*-alkyl chain 'R' from and beyond C<sub>10</sub> homolog, because longer *n*-alkyl chain may coil or bend or flex or couple with major axis of core structure of molecules. Thus, unexpected status of *n*-alkyl chain eliminates odd-even effect.

The variations in mesomorphic properties and their magnitudes from homolog to homolog in the same novel series of present investigation is attributed to the sequentially and progressively added methylene unit or units at the *n*-alkyl chain 'R' which alters the magnitudes of length to breadth ratio, permanent dipole moment across the long molecules axis, dispersive forces, molecular polarity, polarizability, rigidity, flexibility, etc. affecting intermolecular cohesion and closeness. The extrapolation of Sm-N and the N-I transition curves to C<sub>4</sub> and C<sub>3</sub> homologs for smectic and nematic, respectively, which suggests the possibility of missing the corresponding mesophase formation because extrapolated curves matches with Cr-N and Cr-I points of respective homolog. The changing trends in mesogenic behaviors of present novel series 1 are compared with structurally similar analogs series X [33] and Y [34] as mentioned in below Fig. 4.

Homologous series 1, X, and Y are identical with respect to two phenyl rings and one of the central bridge (-CH = CH-CO-) commonly present linking middle and last phenyl rings either homocyclic or heterocyclic which contributes partly to the total molecular rigidity, as well as left *n*-alkoxy terminal end group -OR for the same analog or homolog from series to series which partly contributes to total molecular flexibility. However, homologous series 1, X, and Y differ with respect to central bridge -CH = CH-COO- linking first and middle phenyl ring of series 1 and -COO- of series X and Y which contributes partly to the total molecular rigidity. Moreover last phenyl ring bonded through -CH = CH-CO- common central bridge with para substituted iodo or chloro group, i.e., (-C<sub>6</sub>H<sub>4</sub>.I and -C<sub>6</sub>H<sub>4</sub>.Cl) in series 1 and X, as well as a heterocyclic ring (-C<sub>4</sub>H<sub>3</sub>S), which partly contribute to the total molecular rigidity and partly to the total molecular flexibility whose magnitudes differ from series to series for the same homolog and from homolog to homolog in the same series. Thus, variations in mesogenic properties and the degree of mesomorphism for the same homolog from series to series or from homolog to homolog in the same series will depend upon the differing magnitudes of differing features like molecular rigidity and/or flexibility as well as differing

**Table 5.** Thermal stability in °C.

Series→	-C <sub>6</sub> H <sub>4</sub> I (series 1)	-C <sub>6</sub> H <sub>4</sub> Cl(series-X)	-C <sub>4</sub> H <sub>3</sub> S (series-Y)
Sm-N or Sm-I Commencement of Smectic phase	155.0	142.6	115.66
	(C <sub>5</sub> -C <sub>18</sub> )	(C <sub>4</sub> -C <sub>16</sub> )	(C <sub>12</sub> -C <sub>16</sub> )
N-I Commencement of Nematic phase	180.7	154.3	126.83
	(C <sub>4</sub> -C <sub>18</sub> )	(C <sub>4</sub> -C <sub>14</sub> )	(C <sub>7</sub> -C <sub>16</sub> )
Total mesophase lengths from minimum to maximum from t1°C to t2°C	30°C-58°C	19.7°C-72.2°C	6.9°C-36.8°C
	C <sub>4</sub> C <sub>8</sub>	C <sub>4</sub> C <sub>14</sub>	C <sub>7</sub> C <sub>14</sub>

molecular polarity and polarizability etc. Following Table 5 represents some thermal data for the series under comparative study.

All the three series under comparative study are

- Smectogenic plus nematogenic in character.
- Smectogenic thermal stabilities of series 1, X, and Y are in decreasing order.
- Nematogenic thermal stabilities of series 1, X, and Y are in decreasing order.
- Smectogenic and nematogenic mesophase commences the earliest from (C<sub>4</sub> and C<sub>3</sub>) in series X and then a little bit later from (C<sub>5</sub> and C<sub>4</sub>) in case of present series 1 and the latest from (C<sub>8</sub> and C<sub>7</sub>) in case of series Y involving heterocyclic ring.
- Lower mesophase length are in decreasing order from series 1 to X to Y; but it is in decreasing order from series X to 1 to Y.

The exhibition of smectogenic property from C<sub>4</sub>, C<sub>5</sub>, or C<sub>8</sub> homolog by the series 1, X, and Y, respectively, is attributed to the presence of lamellar packing of molecules in their preoccupied crystal lattices in solid crystalline state due to the difference occurred in intermolecular attractions by different central bridges linking first and middle phenyl rings viz. -CH = CH-COO- and -COO- in which -CH = CH-COO- is longer and stronger than -COO- containing -CH = CH- vinyl group, involving conjugated double bond, which increases molecular rigidity more than -COO- central bridge. Therefore, the extent of molecular noncoplanarity maintained favorably to facilitated smectic and nematic phase formation earlier than the series X and Y. Simultaneously homologous series X and Y contain identically -COO- central bridge linking first and middle phenyl rings differs in magnitudes of flexibility by -Cl and -H of -C<sub>6</sub>H<sub>4</sub>.Cl and -C<sub>4</sub>H<sub>3</sub>S, respectively, in which -C<sub>4</sub>H<sub>3</sub>S does not contain any flexible group (except -H) like -Cl. Thus, late commencement of smectic and nematic phase as compared to series 1 and X is facilitated; by flexibility difference. Thus, suitable magnitudes of anisotropic forces of intermolecular end-to-end and lateral cohesion and closeness which maintain and facilitate either sliding layered molecular arrangement or/and then statistically parallel orientational order of molecules in floating condition to cause smectic and/or nematic mesophase formation for definite range of temperature, depending upon individual thermal resistivity generated from constitutionally energy stored in each molecule of same homolog from series to series and from homolog to homolog in the same series. Decreasing order of smectic and nematic thermal stabilities is attributed to the decreasing order of mainly molecular flexibility by tails ends and partly due to differences of vinyl carboxy and carboxy central bridges which contributes to molecular rigidity. -I is more polarizable than -Cl and -H due to size difference, the effectiveness of size difference reflects in the order of the thermal stabilities and the lower and upper degree of mesomorphism of series 1 and Y. The exceptionally

highest value of upper degree of mesomorphism (72.2°C) of series X is attributed to the high valued thermal resistivity towards exposed thermal vibrations induced by Vander waals forces of higher magnitude causing intermolecular attractions for its (series-X) C<sub>14</sub> homolog.

## Conclusions

- Novel chalconyl ester derivatives of thermotropic LC behavior is predominantly nematogenic and partly smectogenic whose smectogenic and nematogenic mesophaselengths vary from 17°C to 39°C and 15°C to 30°C, respectively, and it is of middle ordered melting type.
- Group efficiency order derived on the basis of (i) thermal stability (ii) early commencement of smectic phase and (iii) total mesophaselengths for smectic and nematic are as under.
  - (i). Smectic: -C<sub>6</sub>H<sub>4</sub>.I > -C<sub>6</sub>H<sub>4</sub>.Cl > -C<sub>4</sub>H<sub>3</sub>S
  - (ii). Nematic: -C<sub>6</sub>H<sub>4</sub>.I > -C<sub>6</sub>H<sub>4</sub>.Cl > -C<sub>4</sub>H<sub>3</sub>S
  - (iii). Smectic: -C<sub>6</sub>H<sub>4</sub>.Cl > -C<sub>6</sub>H<sub>4</sub>.I > -C<sub>4</sub>H<sub>3</sub>S
  - (iv). Nematic: -C<sub>6</sub>H<sub>4</sub>.Cl > -C<sub>6</sub>H<sub>4</sub>.I > -C<sub>4</sub>H<sub>3</sub>S
  - (v) (Smectic ± Nematic)
  - (vi) Lower: -C<sub>6</sub>H<sub>4</sub>.I > -C<sub>6</sub>H<sub>4</sub>.Cl > -C<sub>4</sub>H<sub>3</sub>S
  - (vii) Upper: -C<sub>6</sub>H<sub>4</sub>.Cl > -C<sub>6</sub>H<sub>4</sub>.I > -C<sub>4</sub>H<sub>3</sub>S
- A phenomena of mesomorphism is very sensitive and susceptible to molecular structure as a consequence of changing magnitudes of molecular rigidity and/or flexibility.
- Present investigation is useful for the study of binary systems and can be useful for pharmaceutical preparations due to their bioactivity.
- Present study supports and raises the credibility to the conclusions drawn earlier.

## Acknowledgments

Authors acknowledge thanks to Dr. R.R.Shah, principal and management of K. K. Shah Jarodwala Maninagar Science College, Ahmedabad. Authors are also thankful to Dr. A.V.Doshi, Ex-principal of M.V.M. Science and Home Sci. College – Rajkot for his constant support, inspirations, and help, as well as valuable suggestions as and when we needed during the course of present investigation. Authors thank to NFDD Centre for the analytical and spectral services.

## References

- [1] Reintitzer, F. (1888). *Monatsh.*, 9, 421.
- [2] Gray, G. W., & Winsor P. A. (Eds) *Liquid crystals and plastic crystals*, Chapter 6.2, The role of liquid crystal in life processes by Stewart, G. T., 1, 308–326.
- [3] Naruma, S. (2001). *Display*, 22(1), 1.
- [4] Kim, W. S., Elston, S. J., & Raynes, F. P. (2008). *Displays*, 29, 458–463.
- [5] Tadwee, I., Sahana, S., & Ramteke, V., Syed, I. (2012). *IJPRAS*, 1, 2, 06–11.
- [6] Calliste, C. A., Bail le, J. C., Trouillas, P., Poug, C., Chulia, A. J. et al (2001). *Anticancer, Res.*, 21, 3949–3956.
- [7] Hertz, E., Lavorel, B., & Faucher, O. (2011). *Nature photon*, 5, 783.
- [8] Jain Upendra, K., Bhatia Richa, K., Rao, Akkipendly R., Singh, Ranjit, Saxena, Ajit K., & Seha, Irun (2014). *Trop. J. Pharma. Res.*, 13(1), 73–80.
- [9] Gaikwad Prajakta, P., & Desai, Maya, T. (2013). *Int. J. Pharma. Res. Rev.*, 2(12), 40–52.
- [10] Imrie, C. T. (1999). *Struct. Bond.*, 95, 149–192.

- [11] Gray, G. W. (1974). In: Gray, G. W., & Winsor, P. A. (eds.) *Liquid Crystals and Plastic Crystals*, Chapter 4, Volume 1, 103–153.
- [12] Gray, G. W. (1962). *Molecular Structures and Properties of Liquid Crystals*; Academic Press: London.
- [13] Collings, P. J., & Hird, M. (1997). *Introduction of Liquid Crystals Chemistry and Physics*; Taylor and Francis Ltd.: U. K.
- [14] Henderson, P. A., Niemeyer, O., & Imrie, C. T. (2001). *Liq. Cryst.*, 28, 463–472.
- [15] Marcos, M., Omenat, A., Serrano, J. L., & Ezcurra, A. (1992). *Adv. Matter*, 4, 285.
- [16] Hird, M., Toyne, K. J., Gray, G. W., & Day, S. E. (1993). *Liq. Cryst.*, 14, 741.
- [17] Hird, M., Toyne, K. J., & Gray, G. W., Day, S. E., & Mc Donell, D. G. (1993). *Liq. Cryst.*, 15, 123.
- [18] Demus, D. (1998). *Liq. Cryst.*, 5, 75–110.
- [19] (i) Suthar, D. M., & Doshi, A. V. (2013). *Mol. Cryst. Liq. Cryst.*, 575, 76–83. (ii) Chauhan, H. N., & Doshi, A. V. (2013). *Mol. Cryst. Liq. Cryst.*, 570, 92–100. (iii) Chaudhary, R. P., Chauhan, M. L., & Doshi, A. V. 575, 88–95. (iv) Bhoya, U. C., Vyas, N. N., & Doshi, A. V. (2012). *Mol. Cryst. Liq. Cryst.*, 552, 104–110.
- [20] Imrie, C. T., & Luckhurst, G. R. (1998). Liquid Dimers and Oligomers in *Handbook of Liquid Crystal, Low Molecular Liquid Crystals*, 28, Demus, D., Goodby, J. W., Gray, G. W., Spiess, H., & Vill, V., eds., Wiley-VCH: Weinheim, 801–833.
- [21] Patel, B. H., & Doshi, A. V. (2015). *Mol. Cryst. Liq. Cryst.*, 607, 78–86.
- [22] Patel, B. H., & Doshi, A. V. (2015). *Mol. Cryst. Liq. Cryst.*, 608, 38–46.
- [23] Suthar, D. M., Doshi, A. A., & Doshi, A. V. (2013). *Mol. Cryst. Liq. Cryst.*, 582, 79–87.
- [24] Suthar, D. M., Doshi, A. A., & Doshi, A. V. (2013). *Mol. Cryst. Liq. Cryst.*, 527, 51–58.
- [25] Demus, D. (1998). *Mol. Cryst. Liq. Cryst.*, 165, 45–84.
- [26] Dave, J. S., & Vora, R. A. (1970). In: Johnson, J. F., & Porter R. S. (Eds.), *Liquid Crystals and Ordered Fluids*, 477, Plenum Press: New York.
- [27] Furniss, B. S., Hannford, A. J., Smith, P. W. G., & Tatchell, A. R. (Revisors). (1989). *Vogel's Textbook of Practical Organic Chemistry* (4th Edn.), 563–649, Longmann Singapore Publishers Pvt. Ltd.: Singapore.
- [28] Uhood, J. A. *International Journal of Molecular Science*, 12, 3182–3190.
- [29] Lohar, J. M., & Doshi, A. V. (1993). *Indian Acad. of Science Bangalore*, 105, 3, 209–214.
- [30] Ganatara, K. J., & Doshi, A. V. (2000). *Journal of Indian Chem. Soc.*, 77, 322–325.
- [31] Bhoya, U. C., Vyas, N. N., & Doshi, A. V. (2012). *Mol. Cryst. Liq. Cryst.*, 552, 104–110.
- [32] Doshi, A. V., Bhoya, U. C., & Travadi, J. J. (2012). *Mol. Cryst. Liq. Cryst.*, 552, 10–15.
- [33] Rabhasia, P. K., & Bhoya, U. C. (2016). *Mol. Cryst. Liq. Cryst.*, 626, 55–62.
- [34] Rabhasia, P. K., Bhola, G. N., & Bhoya, U. C. (2016). *Mol. Cryst. Liq. Cryst.*, 626, 81–89.