


## C–H Activation

## Platinum and Palladium Complexes Containing Cationic Ligands as Catalysts for Arene H/D Exchange and Oxidation\*\*

Marion H. Emmert, J. Brannon Gary, Janette M. Villalobos, and Melanie S. Sanford\*

The direct functionalization of C–H bonds has frequently been deemed a “Holy Grail” of organometallic chemistry.<sup>[1]</sup> A seminal example of this transformation was the demonstration by Shilov and co-workers that platinum(II) salts catalyze the direct oxidation of alkanes into their corresponding alcohols and alkyl halides.<sup>[2]</sup> Subsequent work in this area has focused on surveying diverse ligands for these reactions in an effort to enhance reactivity and selectivity, slow catalyst decomposition, and replace platinum(IV)-based oxidants with more cost-effective alternatives.<sup>[3–5]</sup> In a key development, chemists at Catalytica identified [bpymPtCl<sub>2</sub>] (bpym = bipyrimidine) as a pre-catalyst for the oxidation of CH<sub>4</sub> into CH<sub>3</sub>OSO<sub>3</sub>H in fuming H<sub>2</sub>SO<sub>4</sub> (Scheme 1).<sup>[5]</sup> The reaction

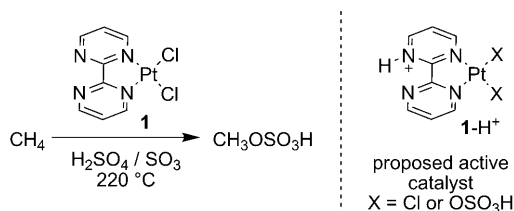


**Scheme 1.** Oxidative functionalization of methane with pre-catalyst **1**.

medium is believed to play several key roles in this system, including acting as a solvent, oxidant, and catalyst activator. Computational studies suggest that the active catalyst (**1-H**<sup>+</sup>) is formed by in-situ protonation of the ligand backbone, which limits oxidative catalyst degradation and renders the platinum center highly electrophilic and reactive for C–H bond cleavage.<sup>[6]</sup>

Despite this initial success, it remains challenging to develop new generations of Group 10 metal catalysts that display higher turnover frequencies and operate in different, less corrosive media.<sup>[3,4]</sup> A key goal of our efforts has been to identify ligands that mimic the desirable properties of protonated bipyrimidine but are stable in the absence of

strong acids.<sup>[7]</sup> Herein, we describe the application of dicationic-bipyridine-based ligands in platinum- and palladium-catalyzed arene H/D exchange and oxidation reactions.

We considered dicationic ligands of general structure **2** (Scheme 2) for several key reasons. First, they contain

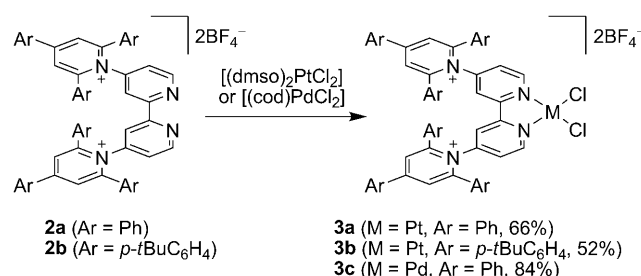

**Scheme 2.** Synthesis of platinum and palladium complexes **3 a–c**. cod = cycloocta-1,5-diene, dmsO = dimethyl sulfoxide.

electron-withdrawing quaternized nitrogen substituents, which should render coordinated metal centers highly electrophilic.<sup>[8]</sup> Second, they are bidentate, sp<sup>2</sup> N-donors, which should allow a direct comparison with other bipyrimidine and bipyridine ligand systems. Third, the quaternized nitrogen atoms are not susceptible to decomposition by dealkylation or deprotonation, which has been problematic in related systems.<sup>[5,7]</sup> Fourth, substituents can easily be added to the pyridinium ring to tune the solubility of these dications. Finally, ligands **2 a** and **2 b** are readily available in four steps from commercially available 2,2'-bipyridine (bpy) in 33 % and 24 % overall yield, respectively (for details, see the Supporting Information).<sup>[9]</sup>

Platinum(II) complexes of **2 a** and **2 b** were synthesized by reaction of these ligands with [(dmsO)<sub>2</sub>PtCl<sub>2</sub>] in methanol at 60 °C to afford **3 a** and **3 b** in 66 % and 52 % yield, respectively, after recrystallization (Scheme 2). The analogous palladium(II) complex **3 c** was prepared in a similar fashion by the reaction of **2 a** with [(cod)PdCl<sub>2</sub>] in dichloromethane at room temperature (84 % yield; Scheme 2). All of these complexes were fully characterized by <sup>1</sup>H, <sup>13</sup>C, and <sup>19</sup>F NMR spectroscopy and elemental analysis.


We first evaluated **3 a–c** as catalysts for H/D exchange<sup>[10]</sup> between [D<sub>4</sub>]acetic acid and benzene using an assay developed in our laboratory.<sup>[10d]</sup> Under our standard conditions, (2 mol % [M], 4 mol % AgBF<sub>4</sub>, 1 equiv C<sub>6</sub>H<sub>6</sub> in 25 equiv of [D<sub>4</sub>]AcOH, 150 °C), these complexes showed very high catalytic activity, with turnover frequencies (TOFs) of 0.1 s<sup>-1</sup> (**3 a,b**) and 0.05 s<sup>-1</sup> (**3 c**) after 15 minutes at 150 °C. For comparison, [dtbpyPtCl<sub>2</sub>] (dtbpy = 4,4'-di-*tert*-butylbipyridine)

[\*] Dr. M. H. Emmert, J. B. Gary, Dr. J. M. Villalobos, Prof. M. S. Sanford  
Department of Chemistry, University of Michigan  
930 N. University Ave, Ann Arbor, MI 48109 (USA)  
Fax: (+1) 734-647-4865  
E-mail: mssanford@umich.edu

[\*\*] We thank the NSF for support of this work through the Center for Enabling New Technologies through Catalysis. M.H.E. thanks the DFG (German Research Council) for a postdoctoral fellowship (EM 219/1-1). J.B.G. thanks the NSF for a predoctoral fellowship.

Supporting information for this article is available on the WWW under <http://dx.doi.org/10.1002/anie.201002351>.

idine), [dtbpyPdCl<sub>2</sub>], and bipyrimidine catalyst **1** provided TOFs of 0.0002, 0.002, and 0.003 s<sup>-1</sup>, respectively, under identical conditions.<sup>[10d]</sup> The catalysts were also compared on the basis of turnover numbers (TONs). Complexes **3a–c** achieved the statistical maximum TON of 242 after 24 hours,<sup>[11,12]</sup> which is also superior to the results with [dtbpyPtCl<sub>2</sub>], [dtbpyPdCl<sub>2</sub>], and **1** (TON = 144 ± 12, 90 ± 18, and 94 ± 13 under analogous conditions).<sup>[10d]</sup> Lowering the catalyst loading of **3a** to 0.1 mol% resulted in turnovers of 3273 ± 110 after 48 hours at 150 °C, which demonstrates the high activity and stability of this species, even upon prolonged heating at elevated temperatures. Finally, we decreased the reaction temperature to 100 °C. As shown in Figure 1, [dtbpyPtCl<sub>2</sub>], [dtbpyPdCl<sub>2</sub>], and **1** promoted very little H/D exchange under these conditions, whilst **3a–c** maintained high activity.

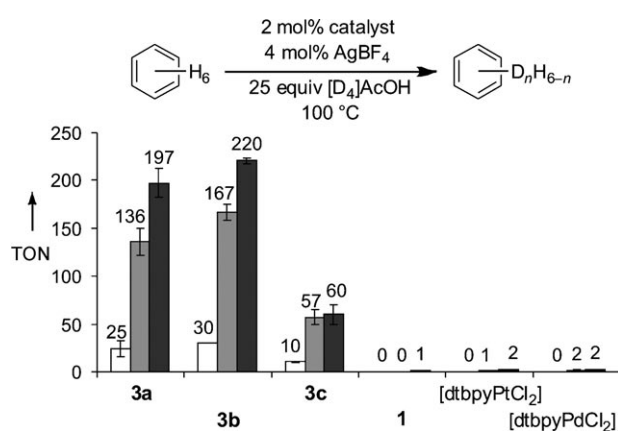

**Figure 1.** Turnover numbers for H/D exchange between benzene and [D<sub>4</sub>]AcOH at 100 °C, catalyzed by **1**, **3a–c**, [dtbpyPtCl<sub>2</sub>], and [dtbpyPdCl<sub>2</sub>] after 2 h (white), 24 h (light gray), and 48 h (dark gray). Conditions: catalyst (2 mol%, 5 μmol), benzene (22.3 μL, 0.250 mmol), AgBF<sub>4</sub> (1.9 mg, 10 μmol), [D<sub>4</sub>]AcOH (0.37 mL, 6.5 mmol, 25 equiv relative to benzene).


There are two possible explanations for the high H/D exchange activity of **3a–c**. The first is that the cationic ligands enhance the reactivity of the coordinated metal center towards arene C–H cleavage to generate metal σ-aryl intermediates (through an organometallic mechanism). An alternative possibility is that the Lewis acidic metal centers promote proton catalysis through an electrophilic aromatic substitution (Ar–S<sub>E</sub>) pathway. To gain insight into the mechanism for H/D exchange, we examined the site-selectivity of D incorporation with catalyst **3a** for a variety of substituted arenes at partial (ca. 25%) conversion. Table 1 compares the observed selectivity (as determined by <sup>1</sup>H NMR spectroscopy) to the product ratio for electrophilic bromination<sup>[13,14]</sup> (Table 1, entries 1–3); furthermore, the selectivity of DCl/CF<sub>3</sub>CO<sub>2</sub>D-catalyzed H/D exchange with bromobenzene is shown in entry 4. In all cases, the site selectivity with **3a** differed dramatically from that observed in Ar–S<sub>E</sub>. This is strongly suggestive of an organometallic pathway for the platinum/palladium-catalyzed H/D exchange reactions.

**Table 1:** Comparison of site-selectivity for arene H/D exchange<sup>[a,b]</sup> at 25% conversion with site-selectivity obtained in electrophilic aromatic bromination.

Entry	R	H/D exchange <i>ortho/meta/para</i> (catalyst)	Ar–S <sub>E</sub> <i>ortho/meta/para</i>
1	Et	1.70:1.33:1 ( <b>3a</b> ) <sup>[a]</sup>	1.72:0.06:1 <sup>[c]</sup>
2	CO <sub>2</sub> Et	1.26:2:1.33 ( <b>3a</b> ) <sup>[a]</sup>	0:2:0 <sup>[d]</sup>
3	Br	2.92:1.19:1 ( <b>3a</b> ) <sup>[a]</sup>	0.48:0.01:1 <sup>[c]</sup>
4	Br	1.15:0.28:1 (DCl/THF) <sup>[b]</sup>	0.48:0.01:1 <sup>[c]</sup>

[a] Conditions: **3a** (3.0 mg, 2.5 μmol, 0.5 mol%), AgBF<sub>4</sub> (1.9 mg, 5.0 μmol, 1.0 mol%), RPh (0.50 mmol, 1.0 equiv), [D<sub>4</sub>]AcOH (0.71 mL, 25 equiv), 150 °C. [b] Conditions: BrPh (26.3 μL, 39.3 mg, 0.250 mmol, 1.00 equiv), [D<sub>1</sub>]TFA (0.51 mL, 0.719 g, 6.25 mmol, 25.0 equiv), DCl in D<sub>2</sub>O (35%, 0.05 mL), 38 h, 150 °C. [c] See Ref. [13]. [d] See Ref. [14]. TFA = trifluoroacetic acid, THF = tetrahydrofuran.

The substrate scope of H/D exchange reactions catalyzed by **3a** was also investigated. As summarized in Figure 2, naphthalene, veratrole, 1,2-dichlorobenzene, bromobenzene, ethylbenzoate, (H<sub>3</sub>C)<sub>3</sub>CCH<sub>2</sub>Ph, *sec*-butylbenzene, cumene,

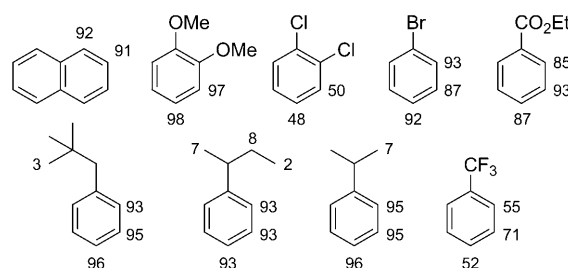


**Figure 2.** Substrate scope of H/D exchange catalyzed by **3a**; numbers in small font are %D incorporation. Conditions: **3a** (3.0 mg, 2.5 μmol, 2.0 mol%), substrate (0.125 mmol, 1.00 equiv), AgOTf (5.0 μmol, 4.0 mol%), [D<sub>4</sub>]AcOH (0.36 mL, 0.40 g, 6.25 mmol, 50 equiv), 48 h (naphthalene, veratrole, PhBr) or 168 h (other substrates). Tf = trifluoromethanesulfonyl.

and trifluorotoluene all underwent extensive (48–98%) aromatic H/D exchange with CD<sub>3</sub>CO<sub>2</sub>D. Significant (2–8%) deuteration was also observed at unactivated sp<sup>3</sup> C–H sites along the alkyl chains. In an interesting contrast, substrates that do not bear a tethered aromatic group (e.g. cyclooctane, 2,2,3,3-tetramethylbutane, and methane) did not show H/D exchange reactivity with catalyst **3a** under analogous conditions. This observation suggests that the arene moiety plays a role in directing the catalyst to the unactivated sp<sup>3</sup> sites, likely via cyclometalation<sup>[15]</sup> or π-coordination.<sup>[16]</sup> The observation of aliphatic H/D exchange provides further evidence to support an organometallic mechanism, as this side reaction is expected to be negligible under proton catalysis.

The H/D-exchange experiments probed the reactivity of **3a–c** in C–H bond cleavage, which is only the first step of a

potential C–H functionalization process. Thus, it was important to determine whether the high reactivity and stability of these new complexes for arene H/D exchange correlated to catalytic activity in arene oxidation. To test this, we conducted preliminary studies of the effect of ligand **2a** on the Pd(OAc)<sub>2</sub>-catalyzed acetoxylation of arenes with PhI(OAc)<sub>2</sub>.<sup>[17,18]</sup> As illustrated in Figure 3, the use of Pd(OAc)<sub>2</sub>/

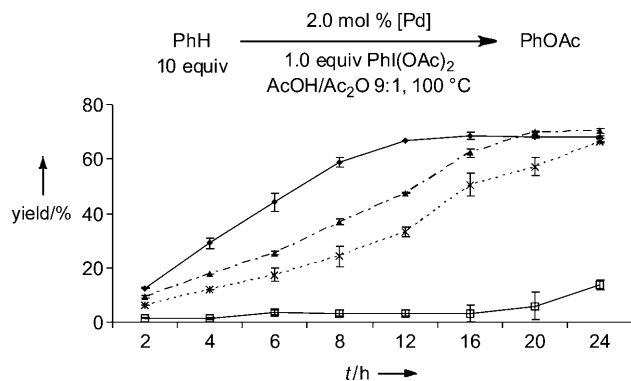

**Figure 3.** Pd<sup>II</sup> catalyzed acetoxylation of benzene. Catalysts [Pd]: (◆) Pd(OAc)<sub>2</sub>/**2a** 2:1; (☆) Pd(OAc)<sub>2</sub>/bpy (2:1); (×) Pd(OAc)<sub>2</sub>; (□) Pd(OAc)<sub>2</sub>/bpym (2:1).

**2a** for the oxidation of benzene resulted in a significantly enhanced reaction rate compared to the best catalysts reported to date for this transformation (Pd(OAc)<sub>2</sub><sup>[17]</sup> or Pd(OAc)<sub>2</sub>/bpy 2:1<sup>[18]</sup>). Similarly enhanced turnover frequencies were obtained in the C–H acetoxylation of naphthalene, 1,2-dichlorobenzene, chlorobenzene, bromobenzene, ethylbenzoate, and  $\alpha,\alpha,\alpha$ -trifluorotoluene using Pd(OAc)<sub>2</sub>/**2a** (for full details, see the Supporting Information). These initial results show that ligand **2a** can be used to generate robust, highly active palladium C–H oxidation catalysts.

In conclusion, the application of cationic pyridinium substituted ligands of general structure **2** for Group 10 C–H functionalization catalysis has been described. Both platinum and palladium complexes of these ligands display high catalytic activity for arene H/D exchange; furthermore, the combination of Pd(OAc)<sub>2</sub>/**2a** shows enhanced activity for arene acetoxylation, compared with the best previously reported catalysts.<sup>[17,18]</sup> Further applications of late transition metal complexes of **2a** and **2b** in C–H functionalization reactions are currently underway in our laboratory.

Received: April 20, 2010  
 Revised: June 1, 2010  
 Published online: July 15, 2010

**Keywords:** C–H activation · H/D exchange · ligand design · oxidation · platinum

- [1] B. A. Arndtsen, R. G. Bergman, T. A. Mobley, T. H. Peterson, *Acc. Chem. Res.* **1995**, *28*, 154–162.
- [2] a) N. F. Goldshleger, V. V. Eskova, A. E. Shilov, A. A. Shteinmann, *Zh. Fiz. Khim.* **1972**, *46*, 1353–1364; b) A. E. Shilov, G. B. Shulpin, *Chem. Rev.* **1997**, *97*, 2879–2932.
- [3] A. F. Heyduk, H. A. Zhong, J. A. Labinger, J. E. Bercaw, *Activation and Functionalization of C–H Bonds*, ACS Symp. Ser. **2004**, *885*, pp. 250–264.
- [4] For examples, see: a) M. Muehlhofer, T. Strassner, W. A. Herrmann, *Angew. Chem.* **2002**, *114*, 1817–1819; *Angew. Chem. Int. Ed.* **2002**, *41*, 1745–1747; b) I. Bar-Nahum, A. M. Khenkin, R. Neumann, *J. Am. Chem. Soc.* **2004**, *126*, 10236–10237; c) D. Meyer, M. A. Taige, A. Zeller, K. Hohlfeld, S. Ahrens, T. Strassner, *Organometallics* **2009**, *28*, 2142–2149; d) G. S. Chen, J. A. Labinger, J. E. Bercaw, *Organometallics* **2009**, *28*, 4899–4901; e) R. Palkovits, M. Antonietti, P. Kuhn, A. Thomas, F. Schüth, *Angew. Chem.* **2009**, *121*, 7042–7045; *Angew. Chem. Int. Ed.* **2009**, *48*, 6909–6912; f) J. E. Kreutz, A. Shukhaev, W. Du, S. Druskin, O. Daugulis, R. F. Ismagilov, *J. Am. Chem. Soc.* **2010**, *132*, 3128–3132.
- [5] R. A. Periana, D. J. Taube, S. Gamble, H. Taube, T. Satoh, H. Fujii, *Science* **1998**, *280*, 560–564.
- [6] a) J. Kua, X. Xu, R. A. Periana, W. A. Goddard, *Organometallics* **2002**, *21*, 511–525; b) X. Xu, J. Kua, R. A. Periana, W. A. Goddard, *Organometallics* **2003**, *22*, 2057–2068; c) A. Paul, C. B. Musgrave, *Organometallics* **2007**, *26*, 793–809; d) M. Ahlquist, R. A. Periana, W. A. Goddard, *Chem. Commun.* **2009**, 2373–2373.
- [7] J. M. Villalobos, A. J. Hickman, M. S. Sanford, *Organometallics* **2010**, *29*, 257–262.
- [8] For example, the Hammett  $\sigma_{para}$  value for NMe<sub>3</sub><sup>+</sup> is 0.96.
- [9] P. P. Lainé, I. Ciofini, P. Ochsenbein, E. Amouyal, C. Adamo, F. Bedioui, *Chem. Eur. J.* **2005**, *11*, 3711–3727; and the references therein.
- [10] For examples, see: a) K. J. H. Young, S. K. Meier, J. M. Gonzales, J. Oxgaard, W. A. Goddard, R. A. Periana, *Organometallics* **2006**, *25*, 4734–4737; b) V. R. Ziatdinov, J. Oxgaard, O. A. Mironov, K. J. H. Young, W. A. Goddard, R. A. Periana, *J. Am. Chem. Soc.* **2006**, *128*, 7404–7405; c) G. Gerdes, P. Chen, *Organometallics* **2004**, *23*, 3031–3036; d) A. J. Hickman, J. M. Villalobos, M. S. Sanford, *Organometallics* **2009**, *28*, 5316–5322.
- [11] All reported TONs and TOFs are corrected for the background H/D exchange reaction of AgCl, which is formed as a by-product under the reaction conditions.
- [12] For TONs obtained after 2 h and 24 h at 2, 1, 0.5, 0.25, and 0.1 mol % catalyst loading (**3a**), see the Supporting Information.
- [13] H. Gilow, *J. Chem. Educ.* **1977**, *54*, 450–452.
- [14] S. Rozen, M. Brand, *J. Chem. Soc. Chem. Commun.* **1987**, 752–753.
- [15] T. G. Driver, M. W. Day, J. A. Labinger, J. E. Bercaw, *Organometallics* **2005**, *24*, 3644–3654.
- [16] N. Ito, H. Esaki, T. Maesawa, E. Imamiya, T. Maegawa, H. Sajiki, *Bull. Chem. Soc. Jpn.* **2008**, *81*, 278–286.
- [17] T. Yoneyama, R. H. Crabtree, *J. Mol. Catal. A* **1996**, *108*, 35–40.
- [18] a) L. Ebersson, L. Jönsson, *J. Chem. Soc. Chem. Commun.* **1974**, 885–886; b) L. Ebersson, L. Jönsson, *Acta Chem. Scand. Ser. B* **1976**, *30*, 361–364.