

Multi-Emissive Difluoroboron Dibenzoylmethane Polylactide Exhibiting Intense Fluorescence and Oxygen-Sensitive Room-Temperature Phosphorescence

Guoqing Zhang,[†] Jianbin Chen,[†] Sarah J. Payne,[†] Steven E. Kooi,[‡] J. N. Demas,[†] and Cassandra L. Fraser^{*,†}

Department of Chemistry, University of Virginia, Charlottesville, Virginia 22904, and Institute for Soldier Nanotechnologies, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139

Received March 22, 2007; E-mail: fraser@virginia.edu

When boron difluoride dibenzoylmethane (BF₂dbm) is coupled with poly(lactic acid) (PLA), a biocompatible, biodegradable polymer,^{1,2} the fluorescence quantum yield is enhanced and unexpected optical properties emerge, namely, temperature-sensitive delayed fluorescence and oxygen-sensitive room-temperature phosphorescence (RTP). Single-component, multi-emissive materials are rare, and synthesis and fabrication of BF₂dbmPLA are straightforward, offering many advantages over existing materials for imaging and ratiometric sensing.³

Fluorescent boron difluoride dyes such as “bodipy”⁴ and boron diketonates⁵ exhibit large molar extinction coefficients and two-photon absorption cross sections, high emission quantum yields, and sensitivity to the surrounding medium.⁶ These features have been exploited in molecular probes,⁴ photosensitizers,⁷ and lasers.⁸ Phosphorescence also offers advantages for optical sensing,³ including larger Stokes shifts and minimal interference from short-lived fluorescence and scattering. But for these boron systems,^{5,9} it is only observed at low temperatures in solid matrices, thus limiting its utility. Though RTP is common for heavy-metal-based luminophores with singlet–triplet state mixing and microsecond–millisecond lifetimes, rigid or organized media and toxic heavy atom assistance (e.g., Pb, Tl, halides) are often required for main group triplet emission,^{3,9,10,11} which is longer lived (millisecond–second) and more sensitive to oxygen quenching. Though a liability for certain light emitting materials applications, this sensitivity can be exploited for oxygen sensors^{3,12} and photodynamic therapy.⁷ Given the limitations of known sensor materials, systems with strong singlet and triplet emission, easy synthesis and fabrication, and good stability and biocompatibility are highly desired.

Hydroxyl-functionalized difluoroboron dibenzoylmethane, BF₂dbmOH (**1**), was prepared for use as an initiator in the ring opening polymerization of lactide to produce BF₂dbm end-functionalized polylactide, BF₂dbmPLA (**2**). The boron complex, **1**, was made from dbmOH¹³ and BF₃•Et₂O in CH₂Cl₂ (60 °C, 1 h). After recrystallization from acetone/hexanes, air-stable, bright yellow needles were obtained in good yield (75%). The boron polymer, **2**, was generated from BF₂dbmOH and DL-lactide using a tin octoate catalyst (1/lactide/Sn(oct)₂ = 1:200:1/50; 130 °C). The solvent-free reaction was stopped at ~50% monomer conversion to avoid higher polydispersity indices (PDIs) noted for longer reaction times, due to transesterification and thermal depolymerization. After precipitation, a pale greenish yellow polymer was obtained. Molecular weight data determined by gel permeation chromatography and ¹H NMR spectroscopy are in good agreement: *M_n*(GPC) = 8800, PDI = 1.09; *M_n*(NMR) = 8600. Furthermore, key proton resonances associated with the boron dbm polymer end group are

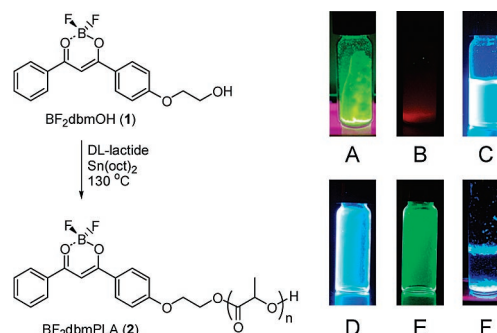


Figure 1. Polymer synthesis and boron initiator and polymer luminescence (λ_{ex} = 365 nm; room temperature in air unless indicated). BF₂dbmOH: (A) solid-state green-yellow fluorescence; (B) red phosphorescence (77 K); (C) blue fluorescent CH₂Cl₂ solution. BF₂dbmPLA: (D) short-lived blue fluorescence and (E) long-lived green phosphorescence for a thin film (N₂); (F) blue fluorescent particle suspension in H₂O after 45 days.

shifted compared to the initiator (e.g., BF₂dbmOCH₂CH₂OR: R = H, 4.04 ppm; R = PLA, 4.54 ppm).

The optical properties of the boron initiator and polymer were investigated in CH₂Cl₂ solution and in the solid state (Figure 1). UV/vis spectroscopic data are similar for BF₂dbmOH (λ_{max} = 397 nm, ϵ = 53 000 M⁻¹ cm⁻¹) and BF₂dbmPLA (λ_{max} = 396 nm, ϵ = 50 100 M⁻¹ cm⁻¹), showing high molar absorptivities characteristic of this family of compounds. Under black light illumination (λ_{ex} = 365 nm) in air, intense blue fluorescence is observed for BF₂dbmOH (Figure 1C) and BF₂dbmPLA (λ_{em} ~ 436 nm), and in both cases, fluorescence quantum yields, ϕ_{F} , are very high (**1**: 0.95; **2**: 0.89; compare to BF₂dbm, 0.20, and 1,3-di(4-methoxyphenyl)-propane-1,3-dione, 0.85).⁶ Due to the near UV excited fluorescence, solutions appear blue even in ambient light or upon flashlight illumination.

In the solid state, in contrast, BF₂dbmOH displays greenish yellow emission that is sensitive to the solid form (λ_{em} , crystals: 540 nm, Figure 1A; powder: 512 nm).¹⁴ Association in the ground state or excited state (e.g., as dimers or excimers) is likely involved. Fluorescence lifetimes, τ , in air for the initiator **1** (in CH₂Cl₂: 2.0 ns; crystals: 8.9 ns) and polymer **2** (in CH₂Cl₂: 1.9 ns) fit to a single-exponential decay, further verifying sample homogeneity. In the solid state, emission spectra for BF₂dbmPLA also exhibit blue fluorescence (foam: 451 nm; film: 440 nm, Figure 1D; air), but fluorescence lifetimes fit to double-exponential decay (foam: 90% 4.8 ns, 10% 20 ns; film: 90% 1.2 ns, 10% 4.4 ns) perhaps due to heterogeneous polymer microenvironments or fluorophore aggregation. Two-photon absorption with blue emission was also confirmed for BF₂dbmPLA using ~800 nm excitation, demonstrating compatibility with bioimaging technologies that afford greater tissue penetration, reduced cell damage, and minimal interference from biological absorbers.¹⁵ Samples continue to emit strongly even

[†] University of Virginia.[‡] Massachusetts Institute of Technology.

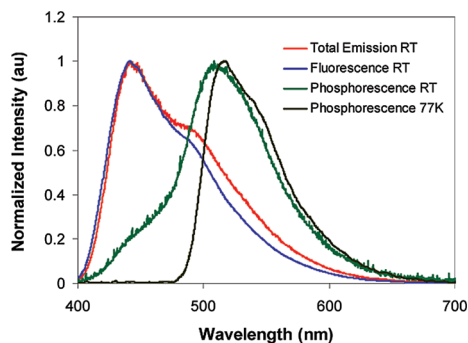


Figure 2. Normalized emission spectra for a BF₂dbmPLA thin film. Room temperature total emission under vacuum (442 nm), fluorescence under air (442 nm), and phosphorescence (509 nm) with delayed fluorescence (~450 nm) under vacuum after the excitation is turned off. The phosphorescence spectrum at 77 K (517 nm) is also shown. (Note the absence of the ~450 nm feature in the low-temperature spectrum.) Reported wavelengths represent emission maxima and $\lambda_{\text{ex}} = 365$ nm.

after months in aqueous suspension (Figure 1F), conditions under which PLA degradation is known to occur.

Upon deoxygenation, solid BF₂dbmPLA also exhibits long-lived, green room-temperature phosphorescence (RTP) (Figure 1E). (No RTP is observed for solutions.) This is surprising because, normally, phosphorescence is only seen at low temperatures for boron compounds of this type.^{5,9} For example, BF₂dbmOH crystals display seconds long red phosphorescence at 77 K (Figure 1B). Triplet thermal decay pathways may be restricted by the rigid polymer medium as in the solid state and solvent glasses. Above the glass transition temperature for BF₂dbmPLA, $T_g = 52$ °C, no phosphorescence is observed. Green RTP is seen for solid BF₂dbmPLA (Figure 1E), including in aqueous suspension, once the excitation source is removed, and can last for as long as 5–10 s.

Room-temperature emission spectra for a BF₂dbmPLA thin film are provided in Figure 2, namely, total emission (fluorescence plus phosphorescence) under vacuum, fluorescence in air where phosphorescence is quenched, and phosphorescence for an evacuated sample following termination of excitation. The green phosphorescence spectrum at 77 K is also shown. Without gating, the primary phosphorescence peak at 509 nm is buried under the much more intense fluorescence peak. In addition to fluorescence and phosphorescence, there is also a shoulder in the phosphorescence spectrum around 450 nm, which closely matches the fluorescence. Given that fluorescence lifetimes are very short and phosphorescence spectra are not collected until after fluorescence has ceased, this feature may be ascribed to delayed fluorescence caused by thermal repopulation from the excited triplet state to the excited singlet state.¹⁶ The shoulder disappears at low temperature, where repopulation may be blocked due to insufficient activation energy, lending support to this proposal. Thus, BF₂dbmPLA serves as a temperature-sensitive material, too.

The long phosphorescence lifetime of BF₂dbmPLA provides a highly sensitive oxygen sensor based on quenching. In the absence of O₂, the RTP decay is complicated, perhaps due to various species or polymer microenvironments in the film. Data can be fit with a triple-exponential giving a preexponential weighted lifetime,¹⁷ τ_{pw0} , of 0.17 s. The lifetime Stern–Volmer plot ($\tau_{\text{pw0}}/\tau_{\text{pw}}$ versus air pressure; air = 21% O₂) (Figure 3) is reasonably linear to ~1 Torr but has complex dynamics beyond that point. With the <1 ms flash lamp, there is a measurable ~30 ms lifetime at 15 Torr, but above 30 Torr, the RTP is rapidly and entirely quenched. Failure to obtain the typical downward curved Stern–Volmer plot may arise from the complexity of the decay and difficulty in measuring contribu-

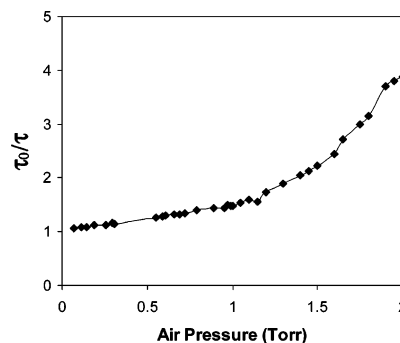


Figure 3. Lifetime Stern–Volmer plot for a BF₂dbmPLA film showing oxygen quenching of room temperature phosphorescence.

tions from shorter lived (<10 ms) and very low amplitude long-lived (>0.1 s) components with the present instrumentation. Further investigation is merited.

By incorporating a classic boron dye into a common biopolymer, a readily processable, single-component, multi-emissive material exhibiting intense fluorescence, delayed fluorescence, and unusual room-temperature phosphorescence is achieved. The optical properties of BF₂dbmPLA are responsive to temperature, oxygen, and the polarity and rigidity of the local medium. Further development of these multifunctional biomaterials for imaging and sensing, including emission color tuning, properties optimization, polymer fabrication, and biological testing, serve as the subjects of future reports.

Acknowledgment. We thank R. C. Somers and Profs. D. G. Nocera, and E. L. Thomas at MIT, and the NSF (CHE 0410061 to J.N.D. and CHE 0350121 to C.L.F.) and Radcliffe Institute for Advanced Study at Harvard University (C.L.F.) for support.

Supporting Information Available: Experimental details for the synthesis and luminescence measurements for **1** and **2**. This material is available free of charge via the Internet at <http://pubs.acs.org>.

References

- (1) Dechy-Cabaret, O.; Martin-Vaca, B.; Bourissou, D. *Chem. Rev.* **2004**, *104*, 6147.
- (2) Albertsson, A.-C. Varma, I. K. *Biomacromolecules* **2003**, *4*, 1466.
- (3) Sanchez-Barragan, I.; Costa-Fernandez, J. M.; Sanz-Medel, A.; Valledor, M.; Campo, J. C. *Trends Anal. Chem.* **2006**, *25*, 958.
- (4) Bodipy = 4,4-difluoro-4-bora-3a,4a-diaza-s-indacene. Haugland, R. P. *The Handbook—A Guide to Fluorescent Probes and Labeling Technologies*, 10th ed.; Spence, M. T. Z., Ed.; Molecular Probes: Eugene, OR, 2005; Chapter 1, Section 1.4.
- (5) Chow, Y. L.; Johansson, C. I.; Zhang, Y.-H.; Gautron, R.; Yang, L.; Rassat, A.; Yang, S.-Z. *J. Phys. Org. Chem.* **1996**, *9*, 7.
- (6) Cogné-Laage E.; Allemand, J.-F.; Ruel, O.; Baudin, J.-B.; Croquette, V.; Blanchard-Desce, M.; Jullien, L. *Chem.—Eur. J.* **2004**, *10*, 1445.
- (7) Gorman, A.; Killoran, J.; O'Shea, C.; Kenna, T.; Gallagher, W. M.; O'Shea, D. F. *J. Am. Chem. Soc.* **2004**, *126*, 10619.
- (8) Pavlopoulos, T. G.; Boyer, J. H.; Sathyamoorthi, G. *Appl. Opt.* **1998**, *37*, 7797.
- (9) Galletta, M.; Puntoriero, F.; Campagna, S.; Chiorboli, C.; Quesada, M.; Goeb, S.; Ziessel, R. *J. Phys. Chem. A* **2006**, *110*, 4348.
- (10) Hurtubise, R. J.; Thompson, A. L.; Hubbard, S. E. *Anal. Lett.* **2005**, *38*, 1823.
- (11) Kuijt, J.; Ariese, F.; Brinkman, U. A. T.; Gooijer, C. *Anal. Chim. Acta* **2003**, *488*, 135.
- (12) DeGraff, B. A.; Demas, J. N. In *Reviews in Fluorescence*; Geddes, C., Lakowicz, J. R., Eds.; Springer Science: New York, 2005; Vol. 2, pp 125–151.
- (13) Bender, J. L.; Corbin, P. S.; Fraser, C. L.; Metcalf, D. H.; Richardson, F. S.; Thomas, E. L.; Urbas, A. M. *J. Am. Chem. Soc.* **2002**, *124*, 8526.
- (14) Mirochnik, A. G.; Fedorenko, E. V.; Kuryavii, V. G.; Bukvetskii, B. V.; Karasev, V. E. *J. Fluoresc.* **2006**, *16*, 279.
- (15) Strehmel, B.; Strehmel, V. In *Advances in Photochemistry*; Neckers, D. C., Jenks, W. S., Wolff, T., Eds.; John Wiley & Sons, Inc.: Hoboken, NJ, 2006; Vol. 29, pp 111–354.
- (16) Fister, J. C., III; Rank, D.; Harris, J. M. *Anal. Chem.* **1995**, *67*, 4269.
- (17) Carraway, E. R.; Demas, J. N.; DeGraff, B. A. *Anal. Chem.* **1991**, *63*, 332.

JA0720255