



## Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl19>

### Exhibition of Induced Mesophases in the Binary Systems Where Both the Components are Non-Mesogenic

A. K. Prajapati<sup>a</sup> & Himanshu M. Pandya<sup>a</sup>

<sup>a</sup> Applied Chemistry Department, Faculty of Technology and Engineering, M.S. University of Baroda, P.B. No. 51, Kalabhavan, Vadodara, 390 001, INDIA

Published online: 27 Oct 2006.

To cite this article: A. K. Prajapati & Himanshu M. Pandya (2001) Exhibition of Induced Mesophases in the Binary Systems Where Both the Components are Non-Mesogenic, *Molecular Crystals and Liquid Crystals Science and Technology. Section A. Molecular Crystals and Liquid Crystals*, 365:1, 43-54, DOI: [10.1080/10587250108025280](http://dx.doi.org/10.1080/10587250108025280)

To link to this article: <http://dx.doi.org/10.1080/10587250108025280>

PLEASE SCROLL DOWN FOR ARTICLE

Taylor & Francis makes every effort to ensure the accuracy of all the information (the "Content") contained in the publications on our platform.

However, Taylor & Francis, our agents, and our licensors make no representations or warranties whatsoever as to the accuracy, completeness, or suitability for any purpose of the Content. Any opinions and views expressed in this publication are the opinions and views of the authors, and are not the views of or endorsed by Taylor & Francis. The accuracy of the Content should not be relied upon and should be independently verified with primary sources of information. Taylor and Francis shall not be liable for any losses, actions, claims, proceedings, demands, costs, expenses, damages, and other liabilities whatsoever or howsoever caused arising directly or indirectly in connection with, in relation to or arising out of the use of the Content.

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden. Terms & Conditions of access and use can be found at <http://www.tandfonline.com/page/terms-and-conditions>

## **Exhibition of Induced Mesophases in the Binary Systems Where Both the Components are Non-Mesogenic**

A. K. PRAJAPATI\* and HIMANSHU M. PANDYA

*Applied Chemistry Department, Faculty of Technology and Engineering,  
M.S. University of Baroda, P.B. No. 51, Kalabhavan, Vadodara-390 001, INDIA*

Binary systems of two non-mesogens exhibiting mesomorphism are rare. In the present study few binary systems of non-mesogens exhibiting smectic and/or nematic mesophases are reported. One of the components is Schiff base having terminal isopropyl group and the other component contains an ester linkage. The binary systems of non-mesogens with terminal isopropyl group having identical structures (homologues) also exhibit induced mesomorphism. Some of the binary compositions exhibit smectic phase at ambient temperature. The phase diagrams of the present study are discussed in detail and the common features emerging from the overall study are outlined.

**Keywords:** Induced Mesophases; Binary Systems; Non-mesogenic Components

### **INTRODUCTION**

Early studies on binary mixtures have suggested the formation of mixed mesomorphism from the pairs of compounds which are non-mesogenic by themselves.<sup>[1-3]</sup> Bennet and Jones<sup>[4]</sup> reported that p-methoxybenzoic acid and p-ethoxybenzoic acid which are non-mesogenic, do exhibit nematic mesophase in their binary mixtures. Lohar<sup>[5]</sup> has confirmed this result and showed that mixtures of the two acids exhibit mixed mesomorphism over a small range of temperature and concentration. Gupta and Vora<sup>[6]</sup> have reported number of binary mixtures where both the components are non-mesogenic exhibit mesomorphism with non-linear tendency of the transition temperature curve. Vora et al<sup>[7]</sup> observed the induced mesomorphism in the binary mixtures where both the components belong to different homologous series. One of the components possesses a nitro group while other component is an ester with -CH<sub>3</sub> or -COOC<sub>2</sub>H<sub>4</sub> terminal group. Prajapati<sup>[8]</sup> reported the induction of smectic mesophase in the binary mixtures of esters having terminal broken

---


\* Author for correspondence.

Downloaded by [Eindhoven Technical University] at 16:16 19 October 2014

## Downloaded by [Eindhoven Technical University] at 16:16 19 October 2014

## Downloaded by [Eindhoven Technical University] at 16:16 19 October 2014

Downloaded by [Eindhoven Technical University] at 16:16 19 October 2014



Downloaded by [Eindhoven Technical University] at 16:16 19 October 2014

- (i). 4-n-Pentyloxybenzylidene 4'-iso-propylaniline(5BiPA)
- (ii). 4-n-Hexyloxybenzylidene 4'-iso-propylaniline(6BiPA)
- (iii). 4-n-Heptyloxybenzylidene 4'-iso-propylaniline (7BiPA) and
- (iv). 4-n-Hexadecyloxybenzylidene 4'-iso-propylaniline (16BiPA) were synthesized by condensation of an appropriate 4-n-alkoxybenzaldehyde with 4-iso-propylaniline as described by Prajapati<sup>[8]</sup>
- (v). 4 (4'-n-Butyloxybenzoyloxy) toluene (4BT) and
- (vi). 4(4'-n-Butyloxybenzoyloxy) nitrobenzene (4BNB) were synthesized by the condensation of 4-n-butyloxybenzoylchloride with p-cresol and p-nitrophenol, respectively by following the procedure described by Dave and Vora.<sup>[10]</sup>

#### Preparation of mixtures

Both the components were weighed accurately in known proportion and melted together in fusion tubes. The mixtures were thoroughly mixed to obtain a homogeneous mixture. The melt was quenched and the solid obtained was ground finely and was used for determining transition temperatures.

The transition temperatures were determined by using a Leitz Laborlux 12 POL microscope provided with a heating stage. The transition temperatures were determined on heating as well as cooling.

## RESULTS AND DISCUSSION



The following six binary mixtures having both the components non-mesogenic are studied.

- System I : 7 BiPA + 4BT  
 System II : 7 BiPA + 4BNB  
 System III : 16 BiPA + 4BNB  
 System IV : 5 BiPA + 4BNB  
 System V : 7 BiPA + 6BiPA  
 System VI : 7 BiPA + 16BiPA

The transition temperatures of the systems I-VI are given in Table I-VI, respectively. The plots of transition temperatures versus mole percent are given in figure I-VI.



#### System I: 7BiPA + 4BT

Reference to binary phase diagram (Figure 1) shows that system is non-mesogenic when the concentration of 7BiPA is low but the monotropic smectic A phase is induced from 35.98 to 88.35 mole % concentration of 7BiPA. The smectic-isotropic transition temperatures curve is extrapolated on the side where monotropic nature is observed. The extrapolation method of finding a transition temperature is more reliable if monotropic mesophases are observed upto certain concentration range<sup>[6,7,11-14]</sup>. The latent transition temperature obtained by this method is 37.5°C for 7BiPA.

**Table-I: Transition temperatures of system-I**

Mole % of A	$S_A$	I
00.00	-	79.0
07.77	-	74.0
17.39	-	58.5
26.53	-	56.0
35.98	(34.0) <sup>a</sup>	54.0
45.73	(34.5)	52.5
55.83	(39.5)	47.0
66.29	(39.0)	50.0
77.12	(37.5)	50.5
88.35	(37.5)	62.5
100.00	-	58.0



<sup>a</sup>values in the parenthesis indicate monotropy

**Table-II: Transition temperatures of system-II**

Mole % of A	Transition Temperatures		
	$S_A$	N	I
00.00	-	-	60.0
09.42	-	(44.5) <sup>a</sup>	60.0
18.92	-	(50.5)	65.0
28.60	41.5	-	71.5
38.39	49.5	-	76.0
48.32	51.0	-	77.0
58.36	42.5	-	75.5
68.57	*	-	74.0
78.90	36.5	-	73.5
89.39	37.0	-	70.5
100.00	-	-	58.0



<sup>a</sup>values in the parenthesis indicate monotropy,

\*mixtures remain smectic on quenching even at 0°C.

**Table-III: Transition temperatures of system-III**

Mole % of A	Transition Temperatures		
	$S_A$	N	I
00.00	-	-	60.0
07.03	-	(48.0) <sup>a</sup>	65.5
14.53	-	(52.0)	74.0
22.57	-	(54.5)	78.0
31.18	(56.0)	(60.5)	74.5
40.49	(60.0)	-	75.0
50.50	(59.0)	-	76.5
61.36	(58.5)	-	77.0
73.12	(57.5)	-	78.5
85.98	(57.0)	-	80.0
100.00	-	-	80.0



<sup>a</sup>values in the parenthesis indicate monotropy.

**Table-IV: Transition temperatures of system-IV**

Mole % of A	Transition Temperatures		
	$S_A$	N	I
00.00	-	-	60.0
10.19	-	(42.0) <sup>a</sup>	61.0
20.30	-	(47.0)	57.0
30.40	(40.0)	(49.0)	56.0
40.45	36.0	-	62.5
50.48	28.5	-	65.0
60.46	*	-	65.0
70.40	*	-	66.0
80.30	39.0	-	67.5
90.19	58.0	-	64.0
100.00	-	-	60.0



<sup>a</sup>values in the parenthesis indicate monotropy.

\*Mixtures remain smectic on quenching even at 0°C.

**Table-V: Transition temperatures of system-V**

Mole % of A	Transition Temperatures	
	$S_A$	I
00.00	-	64.0
09.63	-	67.5
19.32	-	69.0
29.11	-	72.0
38.99	(50.5) <sup>a</sup>	71.5
48.96	(50.0)	70.0
58.97	(48.5)	65.0
69.10	(49.0)	60.5
79.31	(50.0)	56.5
89.60	(46.5)	57.0
100.00	-	58.0

<sup>a</sup>values in the parenthesis indicate monotropy.

**Table-VI: Transition temperatures of system-VI**

Mole % of A	Transition Temperatures	
	$S_A$	I
00.00	-	80.0
13.25	-	81.0
25.55	-	78.5
37.05	(58.0) <sup>a</sup>	74.0
47.80	(54.5)	69.0
57.88	(52.0)	60.0
67.34	(51.0)	58.5
76.22	(49.5)	57.0
84.60	(47.0)	58.0
92.52	-	59.5
100.00	-	58.0

<sup>a</sup>values in the parenthesis indicate monotropy.



**System II: 7BiPA + 4BNB**

The binary phase diagram (Figure 2) exhibits interesting behaviour. The two non-mesogens induced monotropic nematic phase when the concentration of 7BiPA is low (<20 mole %) whereas induced enantiotropic smectic A phase is appear with further increase in the concentration of 7BiPA. The enantiotropic smectic A mesophase persist even upto 89.39 mole % concentration of 7BiPA. This may be due to the marked depression in the melting point of the binary mixture from 18.9 to 89.39 mole % concentration of 7BiPA. In the region of 68.57 to 89.39 mole % concentration of 7BiPA the smA phase obtained at ambient temperature. The latent transition temperature obtained for 4BNB by extrapolation method is 40°C.

**System III: 16BiPA + 4BNB**

Figure 3 shows that an induced monotropic nematic phase appears upto 31.18 mole % concentration of 16BiPA whereas SmecticA mesophase commences at this concentration as a monotropic phase and persist upto 85.98 mole % concentration of 16BiPA. The latent transition temperature obtained for 4BNB by extrapolation method is 40°C and that of 16BiPA is 56.5°C.

**System IV: 5BiPA + 4BNB**

Reference to phase diagram (Figure-IV) shows that the monotropic nematic phase is induced from 10.19 to 30.40 mole % concentration of 5BiPA and monotropic Smectic A appears at this concentration which becomes enantiotropic with further increase in the concentration of 5BiPA. The enantiotropic Smectic A phase persist upto 90.19 mole % concentration of 5BiPA. The system exhibits enantiotropic Smectic A phase at room temperature between 50.48 to 70.40 mole % concentration of 5BiPA.

The latent transition temperature obtained for 4BNB by extrapolation method is 40°C. The value of latent transition temperature obtained in systems II-IV for 4BNB agree well with the value reported by Vora et al<sup>[7]</sup>

**System V: 7BiPA + 6BiPA**

Binary phase diagram (Figure V) exhibits an induced monotropic smectic A phase between 38.99 to 89.60 mole % concentration of 7BiPA. The latent transition temperature obtained by extrapolation for 7BiPA is 38°C.

**System VI: 7BiPA + 16 BiPA**

The system exhibits induced monotropic smectic A phase between 37.05 to 84.60 mole % concentration of 7BiPA (Figure VI). Extrapolated latent transition temperature for 7BiPA is 39°C.

In system I-IV one of the components is a Schiff base with terminal isopropyl group while the other is an ester with -CH<sub>3</sub> or -NO<sub>2</sub> terminal group. System I is purely monotropic smectogenic in nature whereas both smectic and nematic mesophases are induced in the systems II-IV

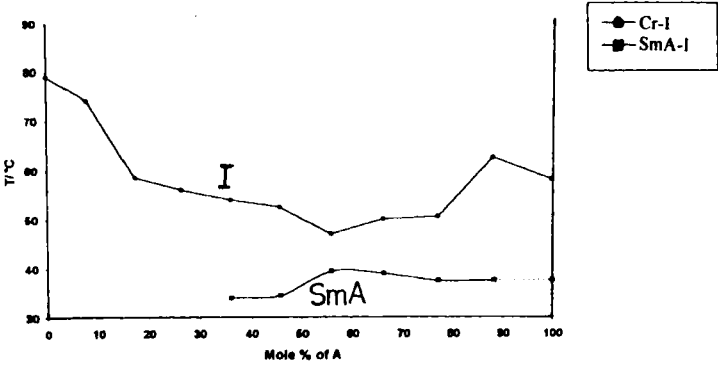


Figure 1: 7BiPA : 4BT(System-I)

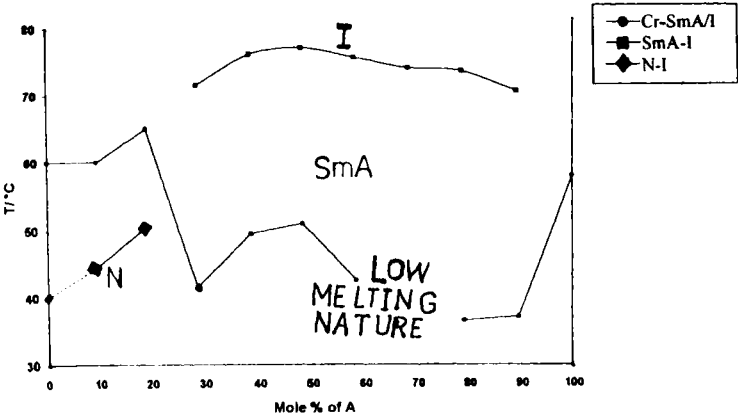


Figure 2: 7BiPA : 4BNB(System-II)

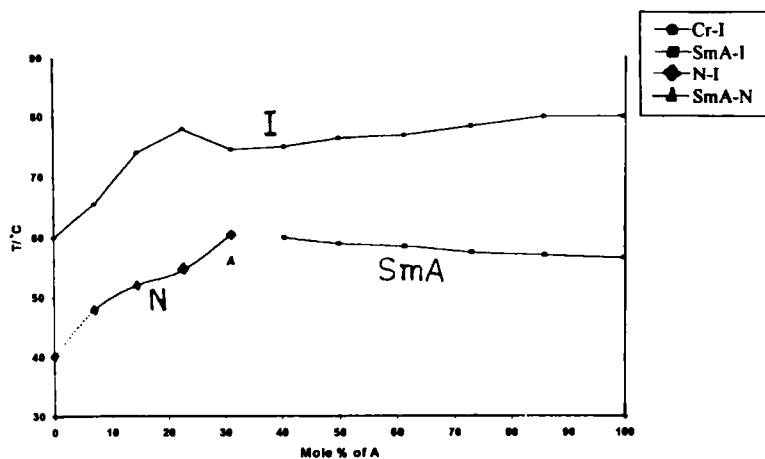


Figure 3: 16 BiPA : 4BNB(System-III)

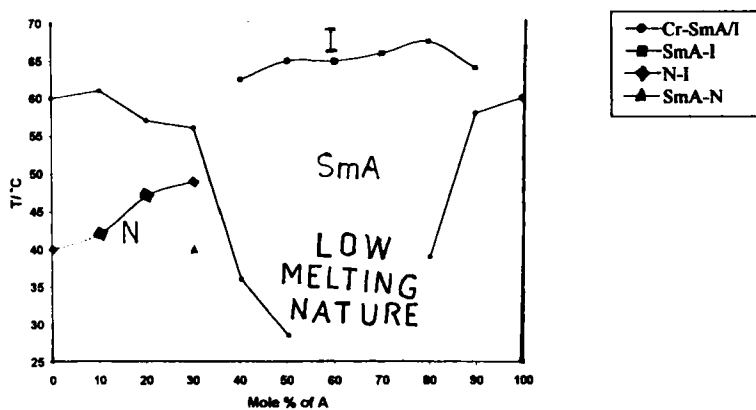


Figure 4: 5 BiPA : 4BNB(System-IV)

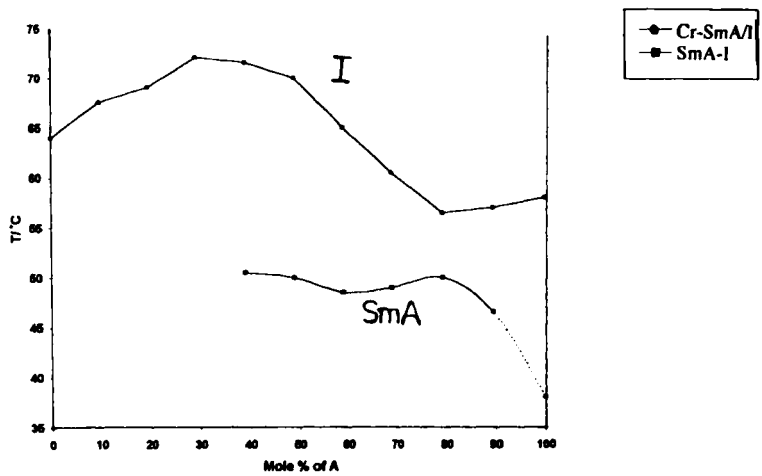


Figure 5: 7 BiPA : 6BiPA(System-V)

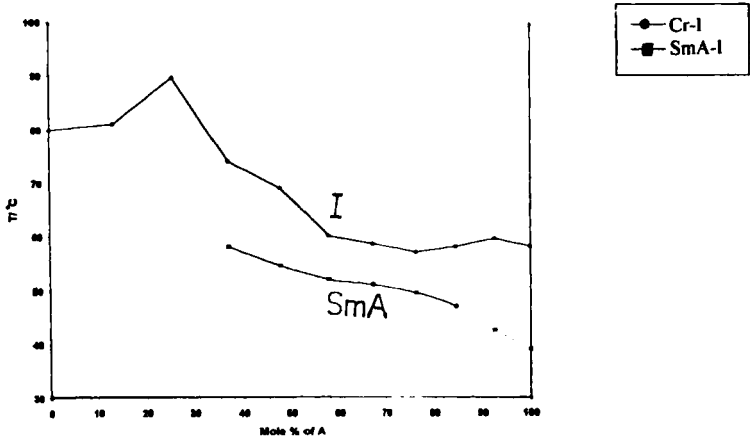


Figure 6: 7 BiPA : 16BiPA(System-VI)

This indicates that the terminal nitro group must be playing some role for the induction of both the phases in the binary systems II-IV. Some binary systems consisting non-mesogenic compounds are also reported in the literature<sup>[6,13]</sup> to give an induced smectic phase along with a nematic phase.

One of the components in binary systems II-IV is 4BNB while the other is a Schiff base with identical structure (homologous) to each other. In systems II and IV, monotropic nematic and enantiotropic SmA phase is observed whereas in system III both nematic and SmA mesophase observed are monotropic in nature. This suggests that terminal alkoxy group contributes towards the induction of an enantiotropic nature of smectic mesophase and to much longer alkoxy chain affects adversely for the induction of an enantiotropic smectic mesophase in the present investigation.

In systems V and VI both the components having identical chemical structures (homologous). Gupta and Vora<sup>[6]</sup> reported in their study that binary systems of non-mesogens having identical structures do not exhibit mesomorphism whereas a monotropic smectic A mesophase is observed in both the present systems V and VI.

The latent transition temperatures obtained for 7BiPA is 37.5, 38.0 and 39.0°C respectively in three systems I, V and VI. The latent transition temperatures obtained for 4BNB is 40°C in all the three systems II to IV. These values of latent transition temperatures obtained by extrapolation is almost the same in different systems indicates homogeneity of the mixtures and reliability of the extrapolation method.

The study provides number of binary systems of non-mesogens which exhibit mesophases at ambient temperatures.

## CONCLUSION

The terminal nitro group is found to be responsible for the induction of both the nematogenic and smectogenic tendency in the present investigation of binary systems with two 'incompatible' components i.e. one with an azomethine central linkage and the other with an ester linkage. In the present work, even though the two components are 'compatible', i.e., both have central azomethine linkage, induced mesophases are exhibited by the binary systems.

Since number of composition of binary systems II and IV exhibit enantiotropic smectic A phase below room temperature they may have potential applications in display devices.

## Acknowledgments

The authors are thankful to Head of the Applied Chemistry Department and Dean, Faculty of Technology and engineering for providing research facilities.

## References

- [1] Vorlander D. and Gahren A., Ber. Dt. Chem. Ges., **40**, 1966 (1907).

- [2] Bogojawlensky A. and Winogradow N., Z. Phys. Chem., **60**, 433 (1907); **64**, 229 (1908).
- [3] Walter R., Ber. Dt. Chem. Ges., **58B**, 2303 (1925).
- [4] Bennett G.M. and Jones B., J. Chem. Soc., 420, (1939).
- [5] Lohar J.M., J. De. Phys., Colleq. C1, **36**, C1-399 (1975).
- [6] Gupta R. and Vora R.A., Mol. Cryst. Liq. Cryst., **106**, 147 (1984).
- [7] Vora R.A., Gupta R. and Patel K., Mol. Cryst. Liq. Cryst., **209**, 251 (1991).
- [8] Prajapati A.K., Ph. D. Thesis, The M.S. University of Baroda, Vadodara, India (1998).
- [9] Mahajan R., Nandedkar H. and Suthar V., Mol. Cryst. Liq. Cryst.
- [10] Dave J.S. and Vora R.A., Pramana, Suppl. No. 1, p. 447 (1975).
- [11] Dave J.S., Patel P.R. and Vasanth K.L., Ind. J. Chem., **4**, 505 (1966); Mol. Cryst. Liq. Cryst., **8**, 93 (1966).
- [12] Dave J.S. and Dewar M.J.S., J. Chem. Soc., 4617(1954); 4305(1955).
- [13] Lohar J.M. and Shah D.S., Mol. Cryst. Liq. Cryst., **28**, 293 (1974).
- [14] Dave J.S. and Vasant K.L., Ind. J. Chem., **7**, 498 (1986).
- [15] Araya K. and Matsunaga Y., Mol. Cryst. Liq. Cryst., **67**, 153 (1981).