

Single-Site Palladium(II) Catalyst for Oxidative Heck Reaction: Catalytic Performance and Kinetic Investigations

Hui Duan, Menghuan Li, Guanghui Zhang, James R Gallagher, Zhiliang Huang, Yu Sun, Zhong Luo, Hongzhong Chen, Jeffrey T Miller, Ruqiang Zou, Aiwen Lei, and Yanli Zhao

ACS Catal., **Just Accepted Manuscript** • DOI: 10.1021/acscatal.5b00569 • Publication Date (Web): 12 May 2015

Downloaded from <http://pubs.acs.org> on May 16, 2015

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

Single-Site Palladium(II) Catalyst for Oxidative Heck Reaction: Catalytic Performance and Kinetic Investigations

Hui Duan,[†] Menghuan Li,[†] Guang-Hui Zhang,^{‡,§} James R. Gallagher,[§] Zhiliang Huang,^{‡,§} Yu Sun,[‡] Zhong Luo,[†] Hongzhong Chen,[†] Jeffrey T. Miller,[§] Ruqiang Zou,[±] Aiwen Lei,^{‡,*} Yanli Zhao^{†,¶*}

[†]Division of Chemistry and Biological Chemistry, School of Physical & Mathematical Sciences, Nanyang Technological University, 21 Nanyang Link, 637371 Singapore

[‡]College of Chemistry and Molecular Sciences, Wuhan University, Wuhan, Hubei 430072, China

[§]Chemical Sciences and Engineering Division, Argonne National Laboratory, Argonne, IL 60439, USA

[±] Department of Materials Science and Engineering, College of Engineering, Peking University, Beijing 100871, China

[¶]School of Materials Science and Engineering, Nanyang Technological University, 639798, Singapore


ABSTRACT: The development of organometallic single-site catalysts (SSCs) has inspired the designs of new heterogeneous catalysts with high efficiency. Nevertheless, the application of SSCs in certain modern organic reactions, such as the C-C bond formation reactions, is still less investigated. In this study, a single-site Pd(II) catalyst was developed, where 2,2'-bipyridine grafted periodic mesoporous organosilica (PMO) was employed as the support of a Pd(II) complex. The overall performance of the single-site Pd(II) catalyst in oxidative Heck reaction was then investigated. The investigation results show that the catalyst displays over 99 % selectivity for the product formation with high reaction yield. Kinetic profiles further confirm its high catalytic efficiency, showing that the rate constant is nearly 40 times higher than free Pd(II) salt. X-ray absorption spectroscopy reveals that the catalyst has remarkable lifetime and recyclability.

KEYWORDS: C-H olefination, cross-coupling reactions, oxidative Heck reaction, periodic mesoporous organosilica, single site Pd(II) catalyst


1. INTRODUCTION

Due to high atom economy and low cost of reactants, palladium catalyzed C-C bond formation based on C-H functionalization has become an important topic in modern organic chemistry.¹⁻⁵ Studies in this field have been focused on developing highly regioselective reactions, or enhancing the catalytic activity by using particular ligands in homogeneous catalytic systems.⁶⁻⁹ However, there is still a general lack of palladium-catalyzed processes that can retain high reactivity and high recovery rate of the catalyst at the same time, both of which are of great importance in catalysis. Since primary valence-state change of palladium during the C-C bond formation reactions is between Pd(0) and Pd(II),^{10,11} the formation of palladium aggregates is common in most palladium-based homogeneous catalytic process, which significantly reduces the catalytic activity. For many catalysts, it is already known that desirable catalytic properties are associated with well-defined active sites containing just a few or even a single metal atom.¹²⁻²⁰ Thus, it is important to develop efficient single-site palladium catalysts and investigate their catalytic performance.

Previous work:

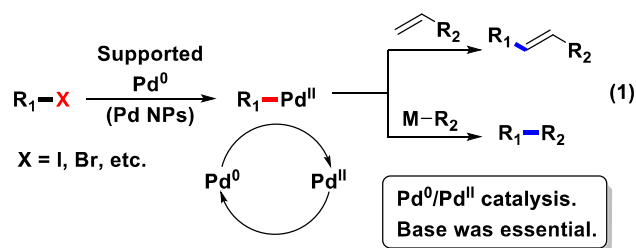


This work:

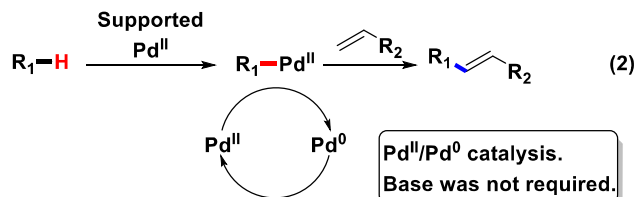

Scheme 1. Palladium catalyzed C-H olefination reactions in previous work and in this work.

Since the earliest application of catalytic cracking process in the petrochemical industry, the utilization of porous materials in catalysis has been extensively studied and widely applied.²¹⁻²⁵ Numerous mesoporous materials have been synthesized. Owing to unique nanostructures, those mesoporous materials provide ideal supports for single-site metal catalysts.²⁶⁻³² Palladium-containing mesoporous materials have been investigated as heterogeneous catalysts for coupling reactions.^{25,33-42} However, the applications of those catalysts were limited in traditional coupling reactions (between C-M and C-X) with palladium nanoparticles or leached homogeneous Pd(0) as the main active species.^{25,43-46} Since mechanistic studies revealed that many C-H functionalization reactions start from Pd(II),⁴⁷⁻⁴⁹ the application of palladium nanoparticle-containing mesoporous materials in these reactions was undesirable. In order to avoid the drawbacks of palladium nanoparticles and expand the application scope of palladium containing mesoporous catalysts, we sought to determine if a single-site Pd(II) C-H/olefin coupling catalyst could be developed (Scheme 1), which should possess higher atom economy and lower production cost for substrates. Furthermore, without the presence of base, the integrity of mesoporous framework would likely be maintained. It is highly possible that this design will prolong the lifetime of catalyst.

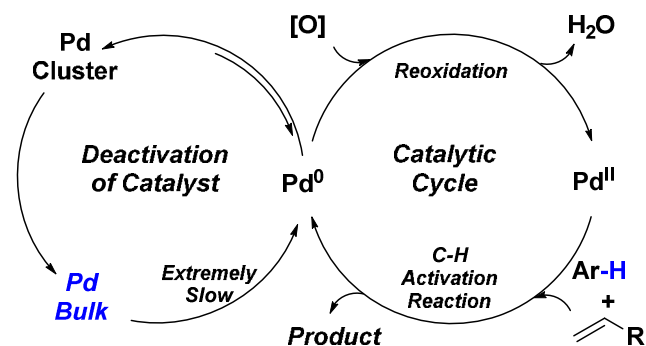


Scheme 2. Palladium catalyzed C-H olefination reactions and the deactivation of catalyst.

Recently, oxidative coupling reactions have attracted much attention.⁴⁹⁻⁵³ These reactions provide new approaches for carbon-carbon and carbon-heteroatom bond formations. Oxidative Heck reaction is one of them, which has been widely investigated.^{3,47,54-56} Up to now, most of the explorations on Fujiwara-Moritani reaction was focused on regioselectivity of arenes. Yu and coworkers made a breakthrough by avoiding the use of excess simple arenes in the substrates.⁵⁷ Previous work demonstrated a plausible mechanism where the activation of C-H bond can only be initiated by Pd(II) in the reaction, whilst the agglomeration of Pd(0) was the main reason for the deactivation of the catalyst (Scheme 2).^{47,58} Thus, the pursuit of prolonging the catalyst lifetime in oxidative Heck reaction is of great importance. The introduction of single site catalyst may provide an ideal approach to improve the lifetime and catalytic efficiency. Herein, we would like to communicate our recent results on the catalytic performance of single-site Pd containing periodic mesoporous organosilica (PMO) in the oxidative Heck reaction.

2. RESULTS AND DISCUSSION

Initially, we started the research by investigating the oxidative Heck reactions that were catalyzed by Pd(II) metal complex grafted PMO. As pyridine based ligands have shown the po-

tency in the C-H olefination reactions,^{8,47,49,56,59-61} a bipyridine containing organosilica precursor (ligand **1**) was designed and synthesized (see Scheme S1 in Supporting Information (SI) for more details). The 2,2'-bipyridine functionalized MCM type PMO was prepared using a procedure adopted from literature.⁶²⁻⁶⁷ Palladium acetate was subsequently loaded into 2,2'-bipyridine grafted PMO to form the Pd(II) complex in the PMO (Scheme 3).

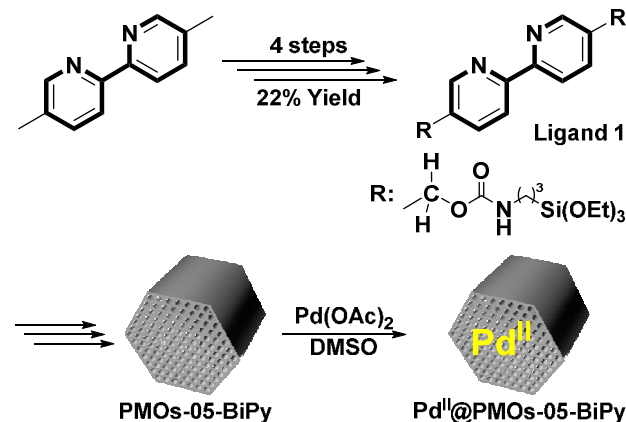

Scheme 3. Preparation of Pd^{II} complex functionalized MCM-41 type PMO.

A series of PMOs were prepared containing ligand **1** and tetraethyl orthosilicate (TEOS) in mole fractions of 0.10:0.90 (PMOs-10-BiPy), 0.05:0.95 (PMOs-05-BiPy) and 0.00:1.00 (PMOs) calculated based on the Si contributions. Surface passivation was achieved by conjugating Et₃SiOEt onto PMOs-05-BiPy to prepare the surface-passivated PMOs (Si-PMOs-05-BiPy). As no orderly mesoporous structure was found in the case of PMOs-10-BiPy, we primarily focused on investigating the properties and performance of PMOs-05-BiPy. To verify the structures of PMOs-05-BiPy and corresponding palladium-loaded Pd^{II}@PMOs-05-BiPy catalyst, the samples were characterized using transmission electron microscopy (TEM), powder X-ray diffraction (XRD), N₂ adsorption/desorption measurement, FT-IR, and thermogravimetric analysis (TGA) techniques. The TEM images (Figure S2 in the SI) and powder XRD results (Figure S3 in the SI) confirmed that the sample PMOs-05-BiPy was of MCM-41 type. The BET surface area, pore size and pore volume were derived from the N₂ adsorption/desorption isotherm (Figures S4 and S5a in the SI). The FT-IR (Figure S5b in the SI) and contact angle measurements (Figure S6 and Table S1 in the SI) were employed to verify the passivation efficiency of Si-PMOs-05-BiPy. FT-IR (Figure S7 and Table S2 in the SI) and TGA (Figure S8 in the SI) data confirmed that the ligand was immobilized into PMOs-05-BiPy.

Previous reports^{33,35,41} on Pd-containing PMO catalysts indicated that the Pd nanoparticles were unavoidable. Thus, it is necessary to study and improve the Pd(II) loading process, since the Pd nanoparticles cannot catalyze the C-H olefination reactions. According to the literature reports, dimethyl sulfoxide (DMSO) is capable of stabilizing the Pd(II) salt.⁶⁸⁻⁷⁰ Based on this rationale, several methods of loading palladium into PMO were evaluated. As shown in Figure 1, no Pd nanoparticles were found when loading the Pd^{II} salt in DMSO at room temperature (Figure 1b, Pd^{II}@PMOs-05-BiPy prepared from Method A in the SI). In order to further increase the Pd^{II} concentration in PMO, we kept DMSO as the loading solvent

while changing other conditions, such as raising the loading temperature to 80 °C and prolonging the loading time to overnight (Figure 1c from Method B). But small Pd nanoparticles appeared in the resulted PMO in these cases. Thus, Pd^{II}@PMOs-05-BiPy prepared from method A was eventually chosen for the subsequent experiments. Pd nanoparticles could evidently be observed in TEM image (Figure 1d) when EtOH was employed as the loading solvent (Method C), which is consistent to the previous reports.

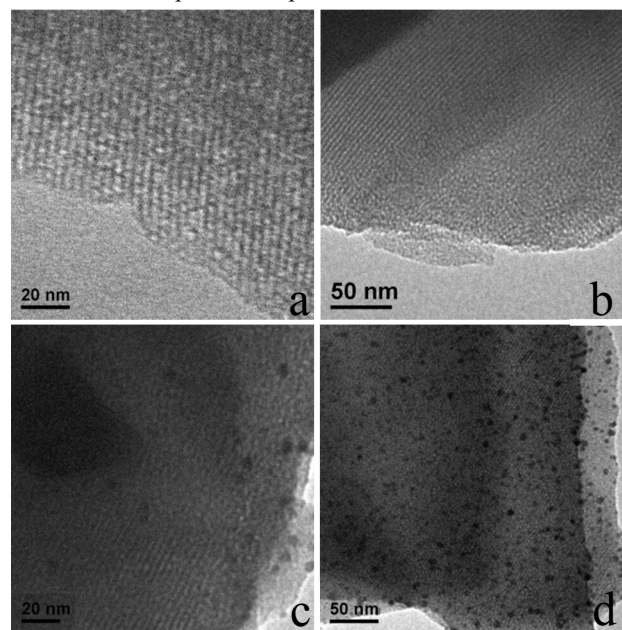


Figure 1. (a) TEM image of PMOs-05-BiPy. (b) TEM image of Pd^{II}@PMOs-05-BiPy prepared from method A. (c) TEM image of the catalyst prepared from method B. (d) TEM image of the catalyst prepared from method C.

After Pd^{II}@PMOs-05-BiPy was obtained using method A, its palladium content (1.1×10^{-4} mmol/mg, 1.2 wt %) was measured by inductively coupled plasma mass spectrometry (ICPMS). The molar ratio (4.1:1.0) between 2,2'-bipyridine and Pd(OAc)₂ was obtained after analyzing the palladium content with the TGA data (Figure S8 in the SI). Due to the mesoporous feature of the materials and low palladium content, no palladium signal could be observed both by X-ray photoelectron spectroscopy (XPS) and energy-dispersive X-ray spectroscopy (EDS). As shown in Figure 2, when compared to palladium foil Pd(0), PdO and Pd(OAc)₂, the Pd K-edge XANES spectrum of fresh Pd^{II}@PMOs-05-BiPy catalyst was very similar to that of PdO and Pd(OAc)₂, giving an edge energy of 24353.8 eV. The observation confirms the existence of Pd(II) species in PMOs.⁷¹⁻⁷³

In order to maintain the Pd^{II} species after catalytic process for reuse, the reaction conditions of oxidative Heck reaction with the Pd^{II}@PMOs-05-BiPy catalyst were optimized using a model reaction between benzene and ethyl acrylate. As shown in Table S3 of the SI, an acceptable yield was obtained when ^tBuOOH was employed as the re-oxidation reagent. We have also tried some other oxidants, such as oxone, potassium persulfate, and (diacetoxyiodo)benzene. When considering the product selectivity and catalyst recovery, ^tBuOOH was the best one for this C-H olefination reaction. More importantly, no Pd nanoparticles were observed from the recycled catalyst,

which proved that the present design concept is reasonable and workable. Furthermore, from the control experiments shown in Table S3 of the SI, it could be concluded that the presence of 2,2'-bipyridine unit in the framework is capable of constraining the palladium atom through coordination, and the mesoporous framework could prevent the agglomeration of Pd(0) during the catalytic cycles. Both of 2,2'-bipyridine unit and mesoporous framework were essentially required in the C-H/olefin coupling reaction catalyzed by this PMO supported Pd(II).

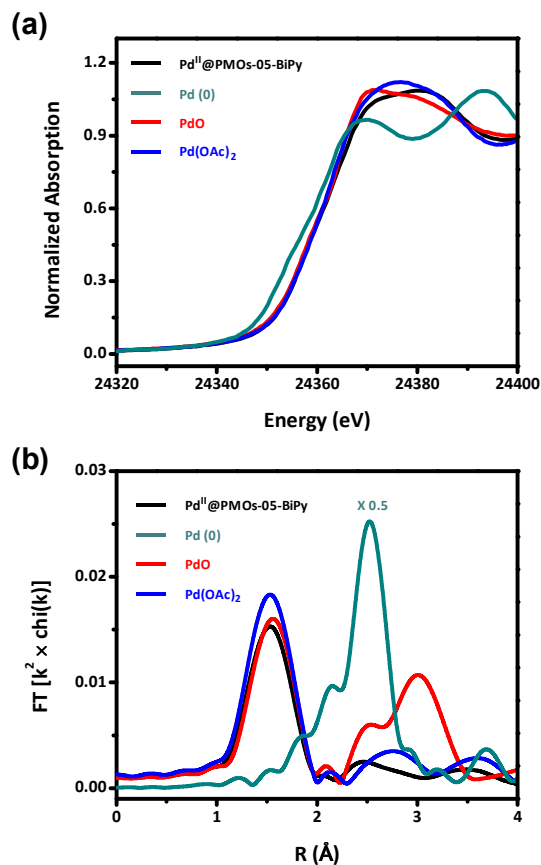


Figure 2. (a) XANES spectra of fresh Pd^{II}@PMOs-05-BiPy catalyst and reference materials. (b) k^2 -weighted Fourier transform magnitudes of fresh Pd^{II}@PMOs-05-BiPy catalyst and reference materials. Fourier transform ranges are listed below: fresh catalyst: $3.08 \text{ \AA}^{-1} - 12.72 \text{ \AA}^{-1}$; Pd(0): $2.25 \text{ \AA}^{-1} - 14.59 \text{ \AA}^{-1}$; PdO: $3.10 \text{ \AA}^{-1} - 11.57 \text{ \AA}^{-1}$; Pd(OAc)₂: $3.05 \text{ \AA}^{-1} - 12.02 \text{ \AA}^{-1}$.

It is well known that the external and internal surfaces of PMOs are covered by silanol groups. Together with the specific nanostructure, silanols inside the channels may influence the diffusion of the reaction substrates significantly. The experimental results in Figure S9 of the SI show that an appropriate concentration ratio of benzene to ethyl acrylate in the model reaction was essential to facilitate the C-H activation and catalytic cycle for the best yield.

Table 1 shows the results of the model reaction catalyzed by different catalysts under the optimal condition from Table S3 and Figure S9 in the SI. In the model reaction, Pd^{II}@PMOs-05-BiPy prepared from method A (Table 1, entry 1) afforded a yield of 58%. When the catalyst prepared through method B ([Pd] = 2.9×10^{-4} mmol/mg, 3.2 wt %) was

employed, the resulted yield dropped to 42 % (Table 1, entry 2). This difference may be caused by lower Pd(II) content from method B. When palladium on PMOs-05-BiPy was mostly in the form of Pd nanoparticles (prepared from method C, $[Pd] = 4.1 \times 10^{-4}$ mmol/mg, 4.5 wt %), the model reaction showed 11 % yield (Table 1, entry 3). Without the 2,2'-bipyridine unit, silanol groups in PMOs alone did not have the ability to hold the palladium as Pd(II). Pd nanoparticles appeared when we tried to load Pd(II) into PMOs, and no activity was found in this model reaction (Table 1, entry 4). From the entry 1 to entry 4, it could be concluded that the Pd nanoparticle formation is deleterious to the catalytic performance under the standard conditions. When the porous material was capped by a G4 dendrimer (Dendrimer-Pd-PMO), only a small amount of product was observed by gas chromatography (Table 1, entry 5). The introduction of bulky dendrimer unit to the PMO catalyst induces an obvious yield decrease, which may be on account of the restricted diffusion process of the reactants (more likely), or reduced palladium leaching to solution if activity from leached metal plays a role (less likely, but future work will explore this possibility). The selectivity was lower when using $Pd(OAc)_2$ as the catalyst (3,3-diphenylacrylic acid ethyl ester as the main byproduct, Table 1, entries 6 and 7).

The turnover numbers (TON) of different catalysts are also shown in Table 1. The TON of $Pd^{II}@PMOs-05-BiPy$ was significantly higher than $Pd(OAc)_2$ (Table 1, entries 1, 6 and 7). Lower TON value (Table 2, entry 6) was obtained when 1.9 mmol % of $Pd(OAc)_2$ was employed as the catalyst. When the loading of $Pd(OAc)_2$ was decreased to 0.5 mmol % (Table 2, entry 7), the TON increased to 56. As expected, the TON increased to 128 when $Pd^{II}@PMOs-05-BiPy$ was employed at a comparable palladium loading concentration (0.4 mmol %). Thus, much higher reaction yield from $Pd^{II}@PMOs-05-BiPy$ indicates that the reaction happens inside the porous framework. Even though the presence of Pd nanoparticles enhances the Pd concentration in the catalyst (Table 2, entry 2), the TON obtained (36) was unsatisfactory, as most of the palladium loaded in this method was Pd(0). In addition, an extremely low TON was observed from entry 3, which is similar to the situation in entry 2. These observations indicate that Pd nanoparticles have no catalytic activity in the C-H olefination reaction. Thus, the catalytic phenomenon could be attributed to the stabilization of active Pd(II) catalyst by the grafted 2,2'-bipyridine ligand on PMOs, retaining its catalytic activity.

Table 1. Effect of different catalysts for the model reaction^a










Entry	Cat.	TON	Selectivity	Yield
1	$Pd^{II}@PMOs-05-BiPy^b$	128	98 %	58 %
2	$Pd^{II}@PMOs-05-BiPy^c$	36	98 %	42 %
3	$Pd^{II}@PMOs-05-BiPy^d$	13	99 %	11 %
4	$Pd^{II}@PMOs^e$	----	----	Trace
5	Dendrimer-Pd-PMOs ^f	----	----	< 5 %
6	$Pd(OAc)_2$ (2.0 mg)	37	88 %	66 %
7	$Pd(OAc)_2$ (0.5 mg)	56	92 %	24 %

(a) Reaction conditions: **S1** (20 mmol), **S2** (0.5 mmol), AcOH as the solvent (3.0 mL), 80 °C, 14 h. The conversion and selectivity


were determined by GC with dodecane as the internal standard. (b) Catalyst was prepared through method A in SI. 20 mg catalyst was used. (c) Catalyst was prepared through method B in SI. 20 mg catalyst was used. (d) Catalyst was prepared through method C in SI. 20 mg catalyst was used. (e) Catalyst without the 2,2'-bipyridine unit was prepared through method A in SI. 20 mg catalyst was used. (f) The palladium content of this catalyst was 0.5 wt %.

After identifying the catalytic activity and optimized reaction conditions, we began our investigation into the scope of the reaction. As shown in Table 2, various arenes and olefins underwent the oxidative olefination using the single-site $Pd^{II}/BuOOH$ system. Although the catalyst loading was as low as 0.4 mmol %, acceptable yields were still obtained. The reactions of active olefins such as ethyl cinnamate and *tert*-butyl acrylate with benzene gave good yields of products **P2** and **P3**. When using styrene and octene as the olefins to couple with benzene, the catalyst $Pd^{II}@Si-PNOs-05-BiPy$ was needed to afford the products **P5** and **P6**, since the silanol groups on catalyst had a noticeable effect on the diffusion process. The reaction between furan and compound **S2** also gave an isolated yield of 64 % for the product **P7**. No regioselectivity was found when using toluene as the arene substrate in the coupling reaction.

Table 2. Substrate scope of single site Pd(II) catalyzed oxidative coupling of arenes with olefins^a

(a) Reaction conditions: 20 mg $Pd^{II}@PMOs-05-BiPy$ (0.4 mmol %) was used without indication, arene (20 mmol without indication), olefin (0.5 mmol), AcOH as the solvent (3.0 mL), 80 °C. (b) The molar ratio of arene and olefin was 60 to 1. (c) The molar ratio of arene and olefin was 60 to 1, and $Pd^{II}@Si-PMOs-05-BiPy$ was used as the catalyst. (d) The molar ratio of furan and olefin was 20 to 1. (e) The molar ratio of arene and olefin was 60 to 1, and a mixture of *o*, *m* and *p*-substituted products was obtained after workup (see Figure S10 in the SI for more details).

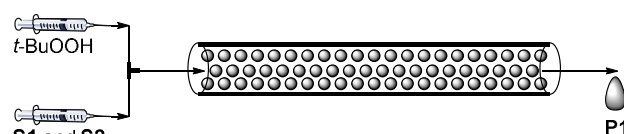

Scheme 4. Set up of the plug flow reactor (PFR).

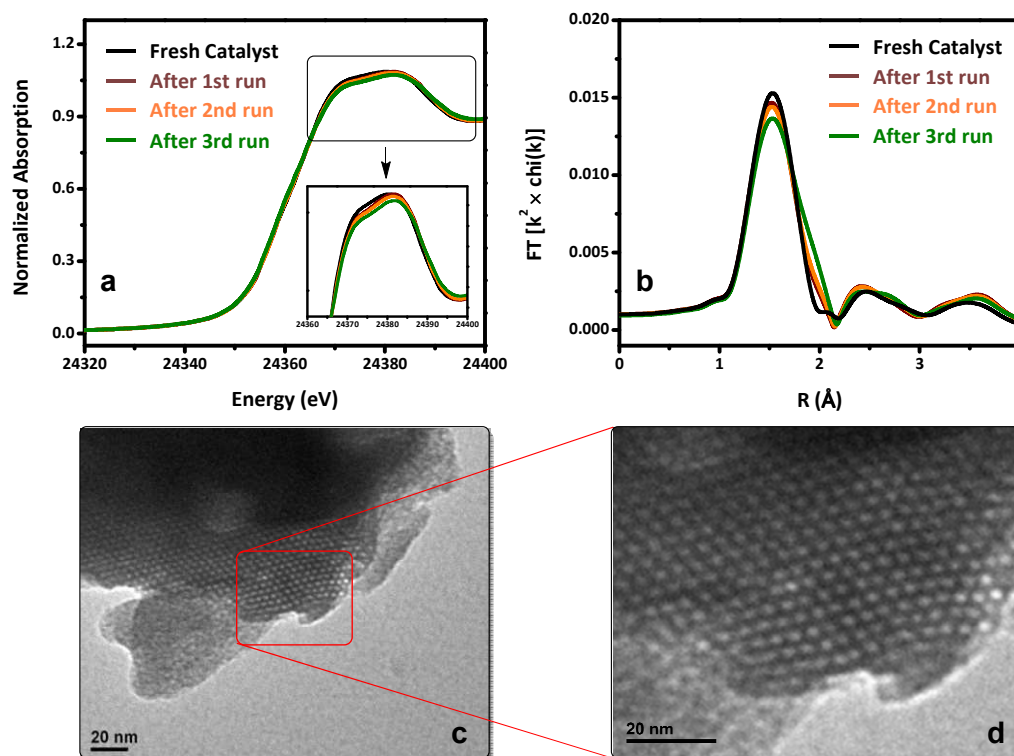


Figure 3. (a) XANES spectra of the fresh and recycled Pd^{II}@PMOs-05-Bipy catalysts; (b) k^2 -weighted Fourier transform magnitudes of the fresh and used Pd(II) catalysts. Fourier transform ranges were listed below. Fresh catalyst: 3.08 Å⁻¹ – 12.72 Å⁻¹; Recycled catalyst after 1st run: 3.09 Å⁻¹ – 12.81 Å⁻¹; Recycled catalyst after 2nd run: 3.08 Å⁻¹ – 12.96 Å⁻¹; Recycled catalyst after 3rd run: 3.10 Å⁻¹ – 13.061 Å⁻¹. (c,d) TEM images of the recycled catalyst after the 3rd run.

To expand the application scope of the catalyst, the model reaction was further optimized in a plug flow reactor (PFR, Scheme 4). The catalyst was packed into an empty HPLC column (inside diameter = 1 mm, length = 100 mm). The two substrates and oxidant were separately filled into two syringes, and then injected through the PFR by a syringe pump at a flow rate of 2 μL/min. The liquid hourly space velocity (LHSV) was 1.69 h⁻¹. The reaction yield was 12 % with the selectivity higher than 99 %. The results indicate that the catalyst has an application potential in continuous-flow processes.

Table 3. Catalytic performance of recovered Pd^{II}@PMOs-05-BiPy in the model reaction^a

Entry	Pd@PMOs-05-BiPy ^b	Pd:BiPy ^c	Selectivity	Yield	TON
1	First Cycle	1.0 : 4.1	98 %	56 %	115
2	Second Cycle	1.0 : 4.5	99 %	48 %	110
3	Third Cycle	1.0 : 4.7	99 %	42 %	98
4	Fourth Cycle	1.0 : 5.1	99 %	39 %	97

(a) Reaction conditions: S1 (20 mmol), S2 (0.5 mmol), AcOH as the solvent (3.0 mL), 80 °C, 14 h, Pd^{II}@PMOs-05-BiPy (20 mg). The conversions were determined by GC with dodecane as the internal standard. (b) Fresh Pd^{II}@PMOs-05-BiPy was used in the first cycle, and then the catalyst was directly used in the following

cycles after being recovered. (c) Molar ratios of palladium and ligand in PMOs.

The recoverability of the catalysts is shown in Table 3. It can be observed that the catalytic effectiveness of Pd immobilized in the mesoporous materials (Pd^{II}@PMOs-05-Bipy) was still maintained in the fourth cycle. The excellent selectivity was obtained from all the first four cycles with slightly decreasing yields in each successive test. The TON of catalyst Pd^{II}@PMOs-05-BiPy was also calculated from these data. Compared to previous TON records in Pd catalyzed oxidative Heck reaction,⁷⁴ this work reached higher TON (420, from the first four runs) without the 1,4-benzoquinone participation. This result shows that the modified PMOs could be an excellent support for the single-site Pd(II) catalyst.

To investigate the oxidative states of the fresh catalyst and recycled Pd^{II}@PMOs-05-Bipy catalysts, X-ray absorption spectroscopy was carried out. As shown in Figure 3, the Pd K-edge XANES spectrum of the fresh catalyst shows the edge energy of 24353.8 eV, confirming the existence of Pd(II) species in Pd^{II}@PMOs-05-BiPy. In order to further explore the stability and recoverability of the developed catalyst, the XANES data for the recycled catalysts were collected as well. As shown in Figure 3a, the edge energy of the first recycled catalyst, the second recycled catalyst, and the third recycled catalyst was almost the same as the fresh catalyst. The EXAFS spectra were also recorded for the fresh and recovered catalysts (Figures S11-S14 and Tables S4 and S5 in the SI). The k^2 -weighted R-space spectra are shown in Figure 3b. For the

fresh catalyst, only Pd(II) species was observed, which showed four coordination at a distance of 2.03 Å. After the catalyst was reused for three times, only Pd(II) species was observed again, and the coordination number was the same as the fresh catalyst. The observations from both XANES and EXAFS spectra were further supported by TEM, where no Pd nanoparticles were found (Figure 3c and 3d). To the best of our knowledge, no catalytic activity of palladium black was found in the oxidative Heck reaction. Moreover, the controlled trials in Table 1 clearly show that the Pd nanoparticles cannot catalyze the oxidative Heck reaction.

Based on these comparison studies, it could be concluded that the mesoporous structure prevented Pd species from the agglomeration and maintained it as Pd(II). It is expected that the metal sites in PMOs are isolated by the long channel structure and can retain their high activity during the catalytic process. Thus, the kinetic behavior of free Pd(OAc)₂ and the Pd^{II}@PMOs-05-BiPy catalyst was determined in the model reaction. As shown in Figures S15 and S16 of the SI, the kinetic plot of Pd^{II}@PMOs-05-BiPy shows a linear increase of conversion with time, which is similar to free Pd(OAc)₂. This observation suggests that the reaction rate is independent of concentrations [S2] and [^tBuOOH], showing zero-order kinetic behavior in [S2] and [^tBuOOH].


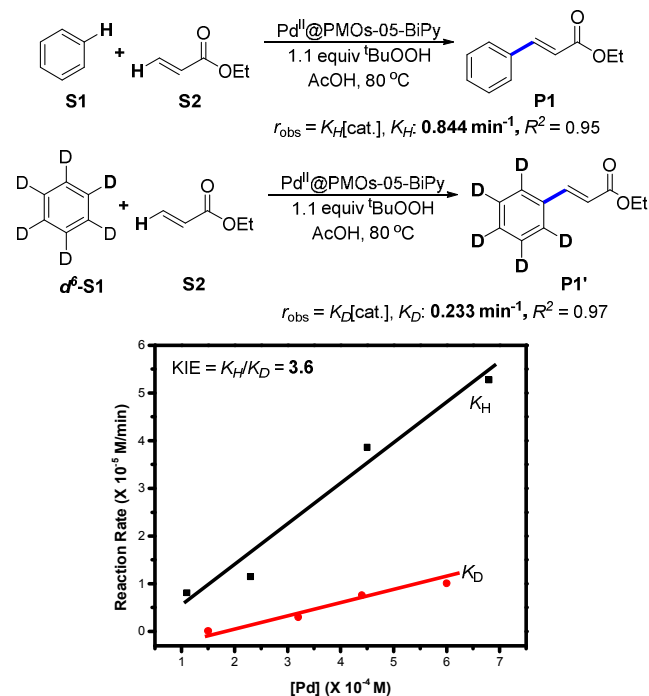


Figure 4. Kinetic profile of single site Pd(II) catalyzed oxidative Heck reaction. K_H is the rate constant from the reaction of benzene (S1), and K_D is the rate constant from the reaction of d^6 -benzene (d^6 -S1).

After more kinetic data were collected, a positive linear dependence on the [Pd] concentration was discovered, which revealed the first-order kinetic behavior in [Pd]. The linear relationship between the rate constants and [Pd] is shown in Figure 4. Although the mesoporous structure might theoretically impede the mass transfer process, the rate constant of Pd^{II}@PMOs-05-BiPy was as high as 0.844 min⁻¹. As compared to the rate constant (0.022 min⁻¹) of free Pd(OAc)₂

shown in Figure S15 of the SI, this result indicates that the catalytic efficiency of the Pd species in Pd^{II}@PMOs-05-BiPy was much higher than that of free Pd(OAc)₂ in the model reaction. Thus, the ligand-grafted mesoporous materials are a promising scaffold for single-site Pd(II) catalyst.

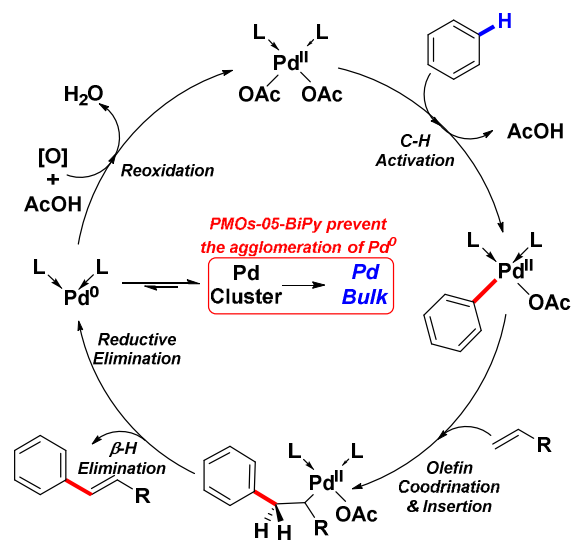

Scheme 5. Proposed catalytic cycle.

The kinetic profiles indicate that reoxidation and olefin insertion were not involved in rate-determining steps under the conditions. To gather more information about the effect of porous materials in this reaction, the kinetic isotope experiments (KIE) were performed to further investigate the catalytic mechanism (Figure 4 and Table S6 in the SI). By using Pd^{II}@PMOs-05-BiPy, the measured K_H/K_D was 3.6, indicating that the C-H bond cleavage is still involved in the rate-limiting step. A proposal for the catalytic cycle is described in Scheme 5. After the C-H cleavage on Pd(II), the olefin would be coordinated to the Pd(II) intermediate generated in said process. Followed by olefin insertion and β -H elimination, the new C-C bond was formed, thus obtaining the desired product together with Pd(0) species after reductive elimination, of which the latter can be reoxidized to Pd(II) and readily join the next catalytic cycle. PMOs-05-BiPy could prevent the agglomeration of Pd(0) and prolong the catalyst lifetime.

3. CONCLUSIONS

In summary, for the first time we have investigated the feasibility of using 2,2'-bipyridine grafted periodic mesoporous organosilica (PMO) as a support of single-site Pd(II) catalyst for catalyzing C-H olefination reactions. The immobilized Pd(II) in PMO has shown higher catalytic activity than that of corresponding homogeneous Pd(OAc)₂, which has been verified by kinetic profiles and kinetic isotope experiments. Its catalytic activity is also effective in the plug flow reactor. Furthermore, several different arenes and olefins have been tested as substrates and acceptable yields have been obtained under low Pd(II) loading. The XANES/EXAFS spectra have demonstrated that the Pd(II) species was the active catalyst in the reaction. In addition, the developed catalyst could be readily recycled with little loss in activity. Thus, this work presents a strategy of integrating active single-site catalysts with the PMO platform for specific organic reactions, offering a new generation of catalysts for pharmaceutical industry.

ASSOCIATED CONTENT

Supporting Information

This material is available free of charge via the Internet at <http://pubs.acs.org>.

Experimental procedures and characterization data for all materials and compounds, TEM and HRTEM images, Powder XRD, TGA, N₂ adsorption/desorption isotherm, FT-IR spectra, X-Ray absorption spectroscopy, kinetic data, ¹H and ¹³C NMR spectra of the products.

AUTHOR INFORMATION

Corresponding Author

*E-mail: zhaoyanli@ntu.edu.sg (Y.Z)

*E-mail: aiwenlei@whu.edu.cn (A.L.)

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This research was supported by the National Research Foundation (NRF), Prime Minister's Office, Singapore under its NRF Fellowship (NRF2009NRF-RF001-015), and Campus for Research Excellence and Technological Enterprise (CREATE) Programme-Singapore Peking University Research Centre for a Sustainable Low-Carbon Future, as well as the NTU-A*Star Silicon Technologies Centre of Excellence under grant No. 112 351 0003. The use of the Advanced Photon Source was supported by the U.S. Department of Energy, Office of Science, and Office of Basic Energy Sciences under contract No. DE-AC02-06CH11357. MRCAT operations were supported by the U.S. Department of Energy and the MRCAT member institutions.

REFERENCES

- Daugulis, O.; Do, H.-Q.; Shabashov, D. *Acc. Chem. Res.* **2009**, *42*, 1074-1086.
- Hashiguchi, B. G.; Bischof, S. M.; Konnick, M. M.; Periana, R. A. *Acc. Chem. Res.* **2012**, *45*, 885-898.
- Sigman, M. S.; Werner, E. W. *Acc. Chem. Res.* **2012**, *45*, 874-884.
- Li, B.; Dixneuf, P. H. *Chem. Soc. Rev.* **2013**, *42*, 5744-5767.
- Mousseau, J. J.; Charette, A. B. *Acc. Chem. Res.* **2013**, *46*, 412-424.
- Fairlamb, I. J. S. *Chem. Soc. Rev.* **2007**, *36*, 1036-1045.
- Seregin, I. V.; Gevorgyan, V. *Chem. Soc. Rev.* **2007**, *36*, 1173-1193.
- Lyons, T. W.; Sanford, M. S. *Chem. Rev.* **2010**, *110*, 1147-1169.
- Neufeldt, S. R.; Sanford, M. S. *Acc. Chem. Res.* **2012**, *45*, 936-946.
- Johansson, S. C. C.; Kitching, M. O.; Colacot, T. J.; Snieckus, V. *Angew. Chem., Int. Ed.* **2012**, *51*, 5062-5085.
- Amatore, C.; Jutand, A. In *Handbook of Organopalladium Chemistry for Organic Synthesis*; John Wiley & Sons, Inc.: New York, 2002; Vol. 1, p 943-972.
- Grasselli, R. K. *Top. Catal.* **2001**, *15*, 93-101.
- Millet, J.-M. M.; Vedin, J. C. *Top. Catal.* **2001**, *15*, 139-144.
- Thomas, J. M. *Top. Catal.* **2001**, *15*, 85-91.
- Volta, J.-C. *Top. Catal.* **2001**, *15*, 121-129.
- Yang, X.-F.; Wang, A.; Qiao, B.; Li, J.; Liu, J.; Zhang, T. *Acc. Chem. Res.* **2013**, *46*, 1740-1748.
- Qiao, B.; Wang, A.; Yang, X.; Allard, L. F.; Jiang, Z.; Cui, Y.; Liu, J.; Li, J.; Zhang, T. *Nat. Chem.* **2011**, *3*, 634-641.
- Lin, J.; Wang, A.; Qiao, B.; Liu, X.; Yang, X.; Wang, X.; Liang, J.; Li, J.; Liu, J.; Zhang, T. *J. Am. Chem. Soc.* **2013**, *135*, 15314-15317.
- Thomas, J. M.; Raja, R. *Acc. Chem. Res.* **2008**, *41*, 708-720.
- Thomas, J. M.; Raja, R.; Lewis, D. W. *Angew. Chem., Int. Ed.* **2005**, *44*, 6456-6482.
- Wang, F.; Li, C.; Sun, L.-D.; Xu, C.-H.; Wang, J.; Yu, J. C.; Yan, C.-H. *Angew. Chem., Int. Ed.* **2012**, *51*, 4872-4876.
- Wang, L.; Yamauchi, Y. *J. Am. Chem. Soc.* **2010**, *132*, 13636-13638.
- Ding, S.-Y.; Gao, J.; Wang, Q.; Zhang, Y.; Song, W.-G.; Su, C.-Y.; Wang, W. *J. Am. Chem. Soc.* **2011**, *133*, 19816-19822.
- Perego, C.; Millini, R. *Chem. Soc. Rev.* **2013**, *42*, 3956-3976.
- Wang, C.; Wang, J.-L.; Lin, W. *J. Am. Chem. Soc.* **2012**, *134*, 19895-19908.
- McKittrick, M. W.; Jones, C. W. *J. Am. Chem. Soc.* **2004**, *126*, 3052-3053.
- Tanabe, K. K.; Siladke, N. A.; Broderick, E. M.; Kobayashi, T.; Goldston, J. F.; Weston, M. H.; Farha, O. K.; Hupp, J. T.; Pruski, M.; Mader, E. A.; Johnson, M. J. A.; Nguyen, S. B. T. *Chem. Sci.* **2013**, *4*, 2483-2489.
- Hackett, S. F. J.; Brydson, R. M.; Gass, M. H.; Harvey, I.; Newman, A. D.; Wilson, K.; Lee, A. F. *Angew. Chem., Int. Ed.* **2007**, *46*, 8593-8596.
- Canivet, J.; Aguado, S.; Schuurman, Y.; Farrusseng, D. *J. Am. Chem. Soc.* **2013**, *135*, 4195-4198.
- Genna, D. T.; Wong-Foy, A. G.; Matzger, A. J.; Sanford, M. S. *J. Am. Chem. Soc.* **2013**, *135*, 10586-10589.
- Park, T.-H.; Hickman, A. J.; Koh, K.; Martin, S.; Wong-Foy, A. G.; Sanford, M. S.; Matzger, A. J. *J. Am. Chem. Soc.* **2011**, *133*, 20138-20141.
- He, J.; Zha, M.; Cui, J.; Zeller, M.; Hunter, A. D.; Yiu, S.-M.; Lee, S.-T.; Xu, Z. *J. Am. Chem. Soc.* **2013**, *135*, 7807-7810.
- Li, H.; Zhu, Z.-H.; Zhang, F.; Xie, S.-H.; Li, H.-X.; Li, P.; Zhou, X.-G. *ACS Catal.* **2011**, *1*, 1604-1612.
- Mehendale, N. C.; Sietsma, J. R. A.; de, J. K. P.; van, W. C. A.; Gebbink, R. J. M. K.; van, K. G. *Adv. Synth. Catal.* **2007**, *349*, 2619-2630.
- Trilla, M.; Borja, G.; Pleixats, R.; Man, M. W. C.; Bied, C.; Moreau, J. J. E. *Adv. Synth. Catal.* **2008**, *350*, 2566-2574.
- Trilla, M.; Pleixats, R.; Man, M. W. C.; Bied, C.; Moreau, J. J. E. *Adv. Synth. Catal.* **2008**, *350*, 577-590.
- Li, L.; Shi, J.-L.; Yan, J.-N. *Chem. Commun.* **2004**, 1990-1991.
- Mehnert, C. P. *Chem. Commun.* **1997**, 2215-2216.
- Elhamifar, D.; Karimi, B.; Rastegar, J.; Banakar, M. H. *ChemCatChem* **2013**, *5*, 2418-2424.
- Mehnert, C. P.; Weaver, D. W.; Ying, J. Y. *J. Am. Chem. Soc.* **1998**, *120*, 12289-12296.
- Karimi, B.; Elhamifar, D.; Clark, J. H.; Hunt, A. J. *Org. Biomol. Chem.* **2011**, *9*, 7420-7426.
- Ping, E.; Venkatasubbaiah, K.; Fuller, T.; Jones, C. *Top. Catal.* **2010**, *53*, 1048-1054.
- Dutta, P.; Sarkar, A. *Adv. Synth. Catal.* **2011**, *353*, 2814-2822.
- Huang, Y.; Lin, Z.; Cao, R. *Chem. - Eur. J.* **2011**, *17*, 12706-12712.
- Budarin, V. L.; Clark, J. H.; Luque, R.; Macquarrie, D. J.; White, R. J. *Green Chem.* **2008**, *10*, 382-387.
- Xu, X.; Li, Y.; Gong, Y.; Zhang, P.; Li, H.; Wang, Y. *J. Am. Chem. Soc.* **2012**, *134*, 16987-16990.
- Chen, X.; Engle, K. M.; Wang, D.-H.; Yu, J.-Q. *Angew. Chem., Int. Ed.* **2009**, *48*, 5094-5115.
- Zhang, H.; Shi, R.; Gan, P.; Liu, C.; Ding, A.; Wang, Q.; Lei, A. *Angew. Chem., Int. Ed.* **2012**, *51*, 5204-5207.
- Zhang, H.; Liu, D.; Chen, C.; Liu, C.; Lei, A. *Chem. - Eur. J.* **2011**, *17*, 9581-9585.
- Liu, C.; Zhang, H.; Shi, W.; Lei, A. *Chem. Rev.* **2011**, *111*, 1780-1824.
- Wang, H.; Wang, L.; Shang, J.; Li, X.; Wang, H.; Gui, J.; Lei, A. *Chem. Commun.* **2012**, 48, 76-78.
- Zhao, Y.; Jin, L.; Li, P.; Lei, A. *J. Am. Chem. Soc.* **2008**, *130*, 9429-9433.
- Zhao, Y.; Wang, H.; Hou, X.; Hu, Y.; Lei, A.; Zhang, H.; Zhu, L. *J. Am. Chem. Soc.* **2006**, *128*, 15048-15049.
- Meng, L.; Liu, C.; Zhang, W.; Zhou, C.; Lei, A. *Chem. Commun.* **2014**, *50*, 1110-1112.
- Meng, L.; Wu, K.; Liu, C.; Lei, A. *Chem. Commun.* **2013**, *49*, 5853-5855.
- Kubota, A.; Emmert, M. H.; Sanford, M. S. *Org. Lett.* **2012**, *14*, 1760-1763.
- Vora, H. U.; Silvestri, A. P.; Engelin, C. J.; Yu, J.-Q. *Angew. Chem., Int. Ed.* **2014**, *53*, 2683-2686.
- Engle, K. M.; Wang, D.-H.; Yu, J.-Q. *J. Am. Chem. Soc.* **2010**, *132*, 14137-14151.
- Emmert, M. H.; Cook, A. K.; Xie, Y. J.; Sanford, M. S. *Angew. Chem., Int. Ed.* **2011**, *50*, 9409-9412.
- Zhang, Y.-H.; Shi, B.-F.; Yu, J.-Q. *J. Am. Chem. Soc.* **2009**, *131*, 5072-5074.
- Ye, M.; Gao, G.-L.; Yu, J.-Q. *J. Am. Chem. Soc.* **2011**, *133*, 6964-6967.
- Asefa, T.; MacLachlan, M. J.; Coombs, N.; Ozin, G. A. *Nature* **1999**, *402*, 867-871.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- (63) Grüning, W. R.; Siddiqi, G.; Safonova, O. V.; Copéret, C. *Adv. Synth. Catal.* **2014**, *356*, 673-679.
- (64) Sun, L.; Mai, W.; Dang, S.; Qiu, Y.; Deng, W.; Shi, L.; Yan, W.; Zhang, H. *J. Mater. Chem.* **2012**, *22*, 5121-5127.
- (65) Takeda, H.; Ohashi, M.; Tani, T.; Ishitani, O.; Inagaki, S. *Inorg. Chem.* **2010**, *49*, 4554-4559.
- (66) Waki, M.; Maegawa, Y.; Hara, K.; Goto, Y.; Shirai, S.; Yamada, Y.; Mizoshita, N.; Tani, T.; Chun, W.-J.; Muratsugu, S.; Tada, M.; Fukuoka, A.; Inagaki, S. *J. Am. Chem. Soc.* **2014**, *136*, 4003-4011.
- (67) Wu, F.; Feng, Y.; Jones, C. W. *ACS Catal.* **2014**, *4*, 1365-1375.
- (68) Diao, T.; Pun, D.; Stahl, S. S. *J. Am. Chem. Soc.* **2013**, *135*, 8205-8212.
- (69) Pun, D.; Diao, T.; Stahl, S. S. *J. Am. Chem. Soc.* **2013**, *135*, 8213-8221.
- (70) Izawa, Y.; Pun, D.; Stahl, S. S. *Science* **2011**, *333*, 209-213.
- (71) Wei Bing, L.; Yuichiro, M.; Masanao, O.; Suminori, T.; Kunio, K.; Kei-ichiro, M.; Toshihiro, M.; Eiji, K.; Ichiro, N. *Phys. Scr.* **2005**, *2005*, 749.
- (72) Waser, J.; Levy, H. A.; Peterson, S. W. *Acta Crystallogr.* **1953**, *6*, 661-663.
- (73) Kirik, S. D.; Mulagaleev, R. F.; Blokhin, A. I. *Acta Crystallogr. Sect. C* **2004**, *60*, m449-m450.
- (74) Jia, C.; Lu, W.; Kitamura, T.; Fujiwara, Y. *Org. Lett.* **1999**, *1*, 2097-2100.

Table of Contents (TOC)

