

Metal-Organic Frameworks with Hexakis(4-carboxyphenyl)benzene – Extensions to Reticular Chemistry and Introducing Foldable Nets

Francoise M. Amombo Noa, Erik Svensson Grape, Steffen M Brülls, Ocean Cheung, Per Malmberg, A. Ken Inge, Christine J. McKenzie, Jerker Mårtensson, and Lars Ohrstrom

J. Am. Chem. Soc., **Just Accepted Manuscript** • DOI: 10.1021/jacs.0c02984 • Publication Date (Web): 20 Apr 2020

Downloaded from pubs.acs.org on April 21, 2020

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

Metal-Organic Frameworks with Hexakis(4-carboxyphenyl)benzene – Extensions to Reticular Chemistry and Introducing Foldable Nets

Francoise M. Amombo Noa,^{a*} Erik Svensson Grape,^b Steffen M. Brülls,^a Ocean Cheung,^c Per Malmberg^a, A. Ken Inge,^b Christine J. McKenzie,^d Jerker Mårtensson,^a Lars Öhrström^{a*}

^a Chemistry and Biochemistry, Dept. of Chemistry and Chemical Engineering, Chalmers University of Technology, SE-41296 Gothenburg, Sweden; ^b Department of Materials and Environmental Chemistry, Stockholm University, Stockholm SE-10691, Sweden; ^c Nanotechnology and Functional Materials, Department of Materials Science and Engineering, Uppsala University, SE-751 21 Uppsala; ^d Department of Physics, Chemistry and Pharmacy, University of Southern Denmark, Campusvej 55, 5230 Odense M, Denmark.

ABSTRACT: Nine metal-organic frameworks have been prepared with the hexagon-shaped linker 1',2',3',4',5',6'-hexakis(4-carboxyphenyl)benzene (H₆cpb) by solvothermal reactions in dimethylformamide (dmf) or dimethylacetamide (dmac) with acetic acid or formic acid as modulators: [Bi₂(cpb)(acetato)₂(dmf)₂·2dmf] **CTH-6** forms a **rtl**-net; 2(H₂NMe₂)[Cu₂(cpb)] **CTH-7** forms a **kgd**-net; [Fe₄(cpb)(acetato)₂(dmf)₄] **CTH-8** and [Co₄(cpb)(acetato)₂(dmf)₄] **CTH-9** are isostructural and form **yav**-nets; 2(HNEt₃)[Fe₂(cpb)] **CTH-10** and the two polymorphs of 2(H₂NMe₂)[Zn₂(cpb)]·1.5dmac, **Zn-MOF-888** and **CTH-11** show **kgd**-nets; [Cu₂(cpb)(acetato)₂(dmf)₂·2dmf], **CTH-12** forms a mixed coordination and hydrogen bonded **sql**-net, and 2(H₂NMe₂)[Zn₂(cpb)] **CTH-13** a similarly mixed **yav**-net. Surface area values (Brunauer–Emmett–Teller, BET) range from 34 m²g⁻¹ for **CTH-12** to 303 m²g⁻¹ for **CTH-9** for samples activated at 120 °C in dynamic vacuum. All compounds show normal (ten-fold higher) molar CO₂ versus N₂ uptake at 298 K, except the 19-fold CO₂ uptake for **CTH-12** containing Cu(II) dinuclear paddlewheels. We also show how perfect hexagons and triangles can combine to a new 3D topology **laf**, a model of which gave us the idea of *foldable network topologies*, as the **laf**-net can fold into a 2D form while retaining the local geometry around each vertex. Other foldable nets identified are **cds**, **cds-a**, **ths**, **sqc163**, **clh**, **4,6T84**, and **tfc** covering the basic polygons and their combinations. The impact of this concept on “breathing” MOFs is discussed. The materials after I₂ sorption, both from gas phase and from MeOH solution, into **CTH-7** was studied by Time of Flight - Secondary Ion Mass Spectrometry (ToF-SIMS) on dried crystals. I₂ was shown to have penetrated the crystals as layers were consecutively peeled off by the ion beam. We suggest ToF-SIMS to be a

method	for	studying	sorption	depth	profiles	of	MOFs.
--------	-----	----------	----------	-------	----------	----	-------

1. INTRODUCTION

Reticular chemistry is not a subdiscipline dealing with particular types of materials, it is a way of thinking of net-forming building blocks and the networks they form in the solid state.¹⁻² The results of reticular chemistry are thus used to design metal-organic frameworks³ (MOFs), zeolites or covalent-organic frameworks (COFs),⁴ but also to understand, and communicate, any network forming chemical system through network topology analysis⁵. Such materials may in addition be allotropes of the elements, polymorphs of ice, Zintl phases, and supramolecular systems.⁴ Here we report a significant extension in hexagon based reticular chemistry, both theoretically and experimentally, using nine new MOFs (Figure 1).

These analyses are important as reticular chemistry not only provides blueprints for these framework-type materials but also systematize them, meaning we can incorporate results in a broader scientific context. For example, poly-

morphs of ice and allotropes of the group 14 elements are seldom discussed together but share both the basic tetrahedral building unit and the resulting network topologies.⁶ A more formal approach to these systems also allows for the use of AI and Machine Learning in the discovery and analysis of network forming materials.⁷⁻⁸

Network topologies may also be directly related to physical properties, such as mechanical anisotropy, giving, for example, large negative thermal expansion behavior.⁹⁻¹⁰ We here introduce *foldable network topology*, a concept that will increase the usefulness of reticular chemistry in the design of physical properties of materials.

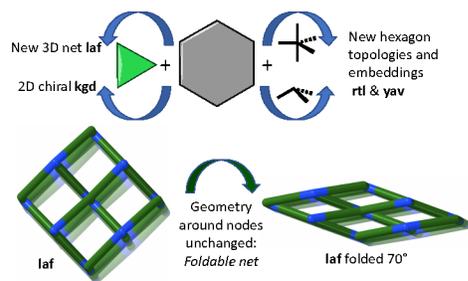


Figure 1. The reticular chemistry of hexagon-based MOF nets is expanded (top). In addition, the concept of foldable network topology is introduced and **laf** is one example (bottom).

An intriguing problem when dealing with periodic networks is how to combine well known geometrical shapes into 3-periodic networks.¹¹ Knowing these construction principles are of paramount importance if we shall ever reach a level of “designing” molecule-based materials in the true sense of crystal engineering.

This is an old research question, with solutions already provided for many shapes in the work of Wells¹² and Robson¹³ on network topologies, Fischer and Koch¹⁴ on sphere packings and the mathematical formulation by O’Keeffe and Delgado-Friedrich.¹⁵⁻¹⁷ However, it transpires that while a large variety of combinations and resulting topologies can be found for most basic shapes, this is not the case for the hexagon. The Cambridge Structural Database (CSD) has been systematically explored for the topology of coordination polymers⁸ (the broader term of which MOFs is a subclass) and compounds with hexatopic hexagonal building blocks are very rare, and only a handful of topologies are known¹¹.

Thus, the hexagon shape has only two reported combinations with three-connected nodes (the nets **cys** and **dnf**, the latter three-nodal¹⁸⁻¹⁹) and one each with the square pyramid (**nts**), the square (**she**), the hexagon itself (**hxg**), and the triangular prism (**htp**). Surprisingly, there are none with either the ubiquitous octahedron or the tetrahedron, nor with a perfect triangle. However, this is not due to a problem with higher-connectivity vertices not being able to combine with the hexagon, as one of the very few known hexagon-based nets forms between the hexagon and the 12-connected truncated tetrahedron giving the **mgc** topology. In addition, the trinodal nets with a minimal number of links (minimal edge-transitive) **kex**, **cez**, and **kez** should be mentioned.²⁰⁻²²

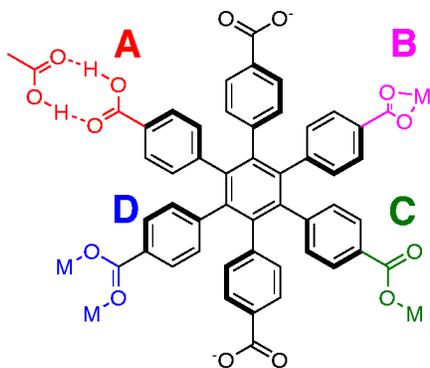


Chart 1. 1,2,3,4,5,6-Hexakis(4-carboxyphenyl)benzene, cpb^{6-} with the different connection modes encountered in this work.

Clockwise from left: the hydrogen bond synthon; chelation; monodentate coordination; the connection to a paddle-wheel

metal Secondary Building Unit (SBU). The conformational chirality of the cpb -unit is emphasized by the bolded bonds.

The experimental basis of our work is based on the distinctly hexagon-shaped hexatopic building block 1,2,3,4,5,6-hexakis(4-carboxyphenyl)benzene, cpb^{6-} (Chart 1) with Bi(III), Cu(II), Fe(II), Co(II) and Zn(II). H_6cpb is one of few such flat and rigid hexagon-shaped building blocks used in MOF chemistry, and only one material with a well-characterized 3D hexagon based network topology has been reported earlier, $[\text{Cu}_3(\text{cpb})(\text{dmf})_{0.5}] \cdot 6\text{H}_2\text{O}$ (**MOF-890**), with the net symbol **htp**, the first compound combining hexagons and triangular prisms (thus a 2-nodal 6-connected net).²³ Apart from the structural studies, we will demonstrate the use of Time of Flight - Secondary Ion Mass Spectrometry (ToF-SIMS) to elucidate the interior contents of MOFs.

The theoretical part is a direct off-spring of our structural analysis and related to our recent work on metal-oxalate topologies.²⁴ We were, among other things, intrigued by the absence in the literature of a 3D net combining hexagons and triangles. Which led us to model-building and the concept of foldable nets.

RESULTS AND DISCUSSION

Reticular chemistry of CTH-6 to CTH-13

CTH-6 forms a 3- and 6-connected net by Bi(III) binding three cpb^{6-} ligands by chelation (mode B, Chart 1). This gives the well-known 3D rutile or **rti** topology, Figure 2, but unlike the common, highest symmetry version of this net, based on triangles and octahedrons, this variety (or embedding) is instead constructed from hexagons and trigonal pyramids.

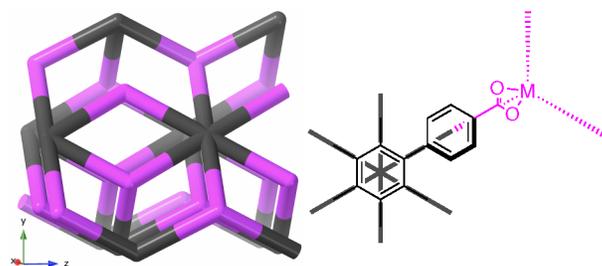


Figure 2. **CTH-6** $[\text{Bi}_2(\text{cpb})(\text{HOAc})_2(\text{dmf})_4]$ with Bi as three-connected purple nodes and cpb^{6-} centroids as six-connected nodes in black. This gives a hexagon and trigonal pyramid version (embedding) of the otherwise octahedron and triangle based **rti**-net.

CTH-8 and **CTH-9** are isostructural and Fe(II) (**CTH-8**) and Co(II) (**CTH-9**) bind to cpb^{6-} using mode D in Chart 1 to form binuclear trigonal paddle-wheels further connected axially by acetate ions to give a 5- and 6-connected net. This forms the **yav**-net, combining hexagons and trigonal bipyramids. The **yav**-net has earlier been reported for $\text{H}_2\text{cpb}^{4-}$ in MOF-889 where the axial links are formed by hydrogen bonding.²³

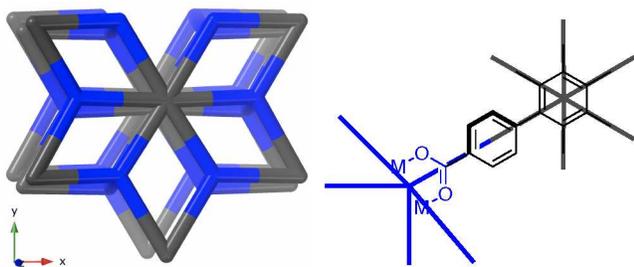


Figure 3. The **yav** net in **CTH-8** and **-9** $[M_4(\text{cpb})(\text{acetato})_2(\text{dmf})_4]$ with Fe(II) or Co(II) as three-connected blue nodes and cpb^{6-} centroids as six-connected nodes in black. Acetate ions from the axial blue connections. A similar, but mixed coordination and hydrogen-bonded, **yav** net, is found in **CTH-13** $2(\text{H}_2\text{NMe}_2)[\text{Zn}_2(\text{cpb})(\text{H}_2\text{O})_2]\cdot 2\text{dmf}$.

Such a **yav**-net by hydrogen bonding is also found in **CTH-13** where a 3- and 6-connected 2D kagome dual, or **kgd**-net, formed by tetrahedral Zn(II) ions binding three cpb^{6-} in Mode C (Chart 1), with additional coordinated water hydrogen bonding to the Zn(II) SBU in the next layer, making Zn into five-connected nodes, see Figure 3.

Another mixed coordination and hydrogen-bonded net is found in **CTH-12** with $\text{H}_2\text{cpb}^{4-}$ where a paddle wheel, Mode D, is combined with Mode A to the square lattice 2D **sql**-net.

Finally, **CTH-7**, **CTH-10**, **Zn-MOF-888** and **CTH-11** all adopt the 3- and 6-connected 2D **kgd**-net frequently seen with hexagonal and triangular nodes having chiral tris-carboxylate coordination entities as three-connected nodes. These compounds differ in the metal ions, Cu(II), Fe(II) and Zn(II), but also in the cations need for charge balance, and the spacing and relative orientation of the **kgd**-nets.

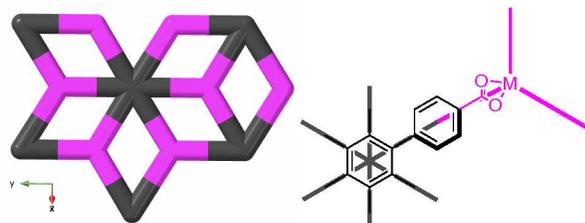


Figure 4. The 2D **kgd** net in **CTH-7**, **CTH-10**, **Zn-MOF-888**, and **CTH-11**, $2(\text{cation})[\text{M}(\text{II})_2(\text{cpb})]\cdot \text{solvent}$.

As octahedral coordination is very common for the metal ions, it is perhaps not surprising that out of the 13 MOFs prepared to date using the cpb ligand, six adopt the **kgd**-net with tris-bis-chelating metal SBUs. Also, for the one benzene ring extended version of H_6cpb , hexakis(4-(4-carboxylphenyl)phenyl)benzene, H_6cpbp this is the most common net, with 2 out of 4 structures (CEFNIN **she**, FEKEK **kgd**, FAKKIO, **kgd**, IXETEM **hxxg**).

With M^{2+} ions these **kgd**-nets need cations to balance the charged ligands. As is clear from Figure 4, each three-connected vertex has three voids and each void is shared by two metal ions, with the ratio of metal to void of 3/2. In the structures reported here, different cations fill these voids and cause a variety of sheet packings of the 2D nets discussed further on in the article.

Derivation of the **laf**-net

The question then occurred to us, what happens if the cations are too big for these voids? For metal-tris-oxalates, a 3D network is assured when the propagation vectors are turned

out of the plane by having the same chirality on all the metal centers, giving the **srs**-net, the most symmetric way of assembling trigonal vertices.²⁴⁻²⁵ Can something similar happen with the **kgd**-nets? In our **kgd** cases, all coordination entities around the hexagon have the same chirality. What if this changes? No net like this, combining perfectly planar equilateral triangles with planar hexagons, has been described in the literature, but physical model building showed this was indeed possible, see Figure 5.

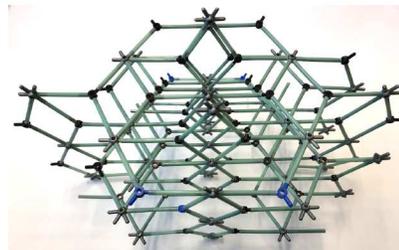


Figure 5. Orbit molecular modeling of the **laf**-net.

The unit cell, space group, and coordinates of the vertices in the model were determined, and Systre¹⁷ used to calculate the most symmetric embedding of the network topology **laf**, see Figure 6. The net has edge transitivity two, that is two symmetry independent links, but with equal lengths, and the point symbols of the new net are 4.8^2 and $4^2.8^{11}.10^2$.

Though not described before, the **laf**-net can be found in the ToposPro²⁶ TTD collection as ‘alb-3,6-P42/mmm’ (related to the 6- and 12-connected **alb**-net) and the search routine yields a few examples. Two compounds stand out as very clear examples (although not discussed as such in the literature): lithium oxalate LIOXAT (Li 3-c, oxalate 6-c), and the hydrogen-bonded bis(guanidinium) 3,6-dinitropyrazolo[4,3-c]pyrazole-1,4-diide, HUCSOP (guanidinium 3-c, pyrazolopyrazole 6-c).

The **laf**-net has large rectangular channels running in two directions and we speculate that larger cations, not fitting into the space in the **kgd**-nets, might template this network just as some larger cations induce the **srs** and other 3D-nets in the tris-oxalate based systems.^{27 24-25}

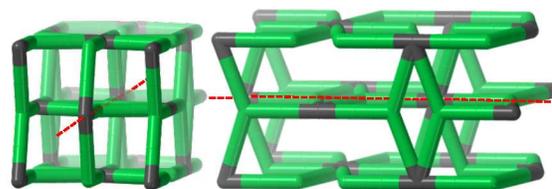


Figure 6. Two views of the new **laf**-net, the only net combining perfect hexagons and perfect equilateral triangles. Folding is possible along the dashed red line coinciding with the direction of the tetragonal z-axis. Note there is no unbroken axis going through the network.

The concept of foldable nets

Inspecting the physical model in Figure 5, we noted that this net can be “folded” along the tetragonal axis while the individual hexagonal and trigonal geometries stay exactly the same, see Figure 7. This property is directly related to the topology of the net and may also translate into real physical properties of a material. It thus merits a bit of discussion and a MOF based on this topology may potentially be a “breathing” MOF, like MIL-53.²⁸

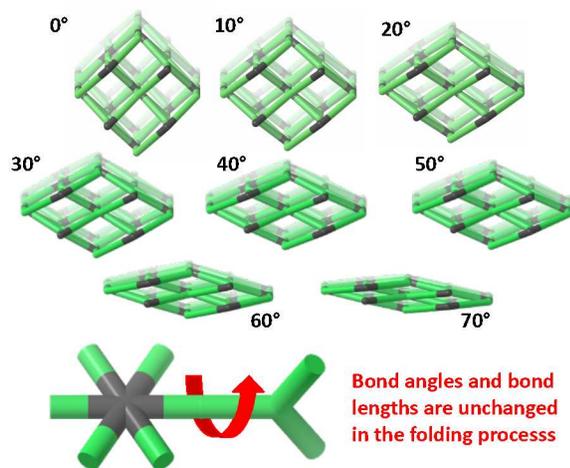


Figure 7. Folding of the **laf**-net is accomplished without changing the geometry of the individual vertices, only by rotation around the trigonal-hexagonal axis. Thus the bond angles and bond lengths of the individual hexagonal and trigonal centers stay the same.

Flexibility in MOFs may have different origins, for exam-

net	vertices*	space gr.	point symbol	links
ths	tri	$I4_1/amd$	10^3	2
clh	tri tri	$P4_2/mmc$	$6^2.12$ 6.12^2	3
cds-a	tri tri	$P4_2/mmc$	4.14^2 4.14^2	3
cds	sq	$P4_2/mmc$	6^6	2
cdl	sq	$P4_2/mmc$	4.8^5	3
cdz	sq sq	$Pmmm$	$6^2.8^4$ $4^2.6^2.8^2$	4
sqc163 [§]	tri tri sq	$Pmmm$	6.8^2 $6^2.8$ $8.10^4.12$	4
tfc	tri sq	$Cmmm$	8^3 8^6	3
tfk	tri sq	$P4_2/mmc$	4.12^2 $4^2.12^4$	2
laf	tri hex	$P4_2/mnm$	4.8^2 $4^2.8^{13}$	2
4,6T84 [¶]	sq hex	$Cmmm$	$4.6^4.8$ $4^8.6^7$	3

ple the rather fluid coordination sphere around Bi being one such factor.²⁹⁻³⁰ Some detailed accounts of different systems have emerged,³¹⁻³⁵ where changes in geometry and ligand conformations are discussed, but little attention seems to have been given to the influence of the topology as such. Férey and Serre invoke “the existence of only even cycles”,³¹ and Wei et al.³⁴ note that the specific 9- and 3-connected **xmz** topology “has a special restriction to the framework breathing mode” but without drawing any general conclusions.

We would like to propose the term *foldable network topologies* (to make the distinction from the more general case of breathing or flexible MOFs) for nets such as **laf**, and offer the following tentative definition: (Assuming vertices and links infinitely small).

Foldable network topologies are topologies that can fold into a flat projection by free rotation between vertices while the angles and edge lengths around each vertex is unchanged.

Two conditions appear to be needed for this: First, the vertices must be flat, rather than polyhedral (hexagons, squares, triangles rather than tetrahedra). Flat vertices are, however, not enough. For example, the two square-based nets **nbo** and **cds** behave quite differently. The **nbo**-net is rigid (easily verifiable on a physical model) while the **cds** is foldable.

Table 1. Examples of foldable topologies

* hex=hexagons, tri=triangles, sq=square. § In the EPINET database ¶ ToposPro TTD collection

So, we need to look at the smallest rings in the nets along potential folding axes. The **laf**-net is folded around an axis passing through 8-rings (with 60° and 120° angles) with two sides parallel to the folding axis, and these 8-rings can be folded flat. The **cds**-net has 6-rings that are already flat while the 6-rings in the **nbo**-net are not flat and cannot be folded flat without compromising the coordination geometry around some vertices. The second condition thus appears to be that the folding axis must pass through smallest rings that are, or can be, folded flat around the folding axis. Two sides of these rings then need to be parallel.

These are not properties that can be directly obtained from the RCSR database, however inspecting a number of candidate nets reveal a few examples. Thus we have identified foldable topologies with all three basic flat polygons, the triangle, the square and the hexagon, and their combinations, except for the hexagon on its own, see Table 1.

In terms of space groups we see that all these foldables are either tetragonal (all angles 90°, foldable along the unique c-axis perpendicular to the a=b axes) or orthorhombic (all angles 90°, foldable along the unique c-axis perpendicular to the a≠b axes). As they fold, these space groups will change to the monoclinic system.

We see a few space groups being predominant in Table 1 but this does not mean that all nets in these space groups are foldable. A requirement, however, is a C_2 -axis coinciding with the folding axis. A few of these nets are illustrated in Figure 8.

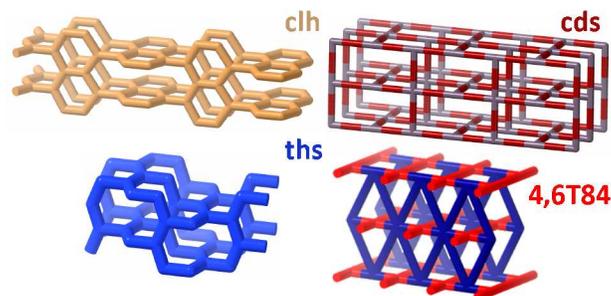


Figure 8. Four of the foldable nets from Table 1, illustrating 3-connected (**clh** and **ths**), 4-connected (**cds**) and 4- and 6-connected (**4,6T84**) nets.

The MIL-53 systems, and the similar 4,4'-(1,4-phenylene)bis(pyrazolato) MOFs from the Long group³⁶ are probably the best known breathing MOFs. They are so-called rod-MOFs, having infinite metal-SBUs running in one direction. Formally we would assign them the **sra** topology,³⁷ built from ladders of tetrahedra, and thus not foldable. However, as the ligand-SBUs all attach to the same points of the rod an alternative simplified description would be the **cds-net**.³⁸ Not surprisingly perhaps the **cds-net** exactly corresponds to the wine-rack analogy often invoked to explain the breathing phenomena in these materials.

An important observation from Table 1 might be that not all these nets are compatible with rod-MOFs (i.e. **ths**, **clh**, **laf**), and thus breathing MOFs may be constructed by other metal-SBUs than infinite rods.

Detailed structure analysis of CTH-6 to CTH-13

Crystal data, experimental and refinement parameters are given in Table S1 and Table S2 in the supporting information.

CTH-6, [Bi₂(cpb)(HOAc)₂(dmf)₄] The structure analysis indicates that in CTH-6, each Bi (III) center is coordinated to nine oxygen atoms; six from a carboxylate group from three cpb linkers, two dmf molecules and an acetic acid molecule. The two last have Bi-O bond lengths of 3.056(7) Å and 2.850(8) Å respectively, significantly longer than the Bi-O carboxylate bonds to the cpb linker that range from 2.208 to 2.218 Å. The dmf with the longer Bi-O bond also hydrogen bonds to the acetic acid. See Figure 9. With all atoms counted the void volume calculated from the crystal structure is 34 % with spherical cavities of diameter 2.4 Å.

CTH-7, 2(Hdma)[Cu₂(cpb)] The asymmetric unit consists of two Cu (II) ions, half a cpb linker and one dimethyl ammonium cation (Hdma⁺). The framework comprises of mononuclear Cu(II) octahedral entities with three points of extension (Figure 10) because of the coordinated cpb linker. The two Cu(II) sites display Jahn-Teller distortions of opposite kinds. The Cu1 entity which does not take part in the hydrogen bonding displays four shorter (1.95-2.03 Å) and two longer (2.51 Å) Cu-O bonds. The Cu2 site (Figure 10) has two shorter (1.99 Å) and four longer (2.21-2.22 Å) Cu-O bonds.

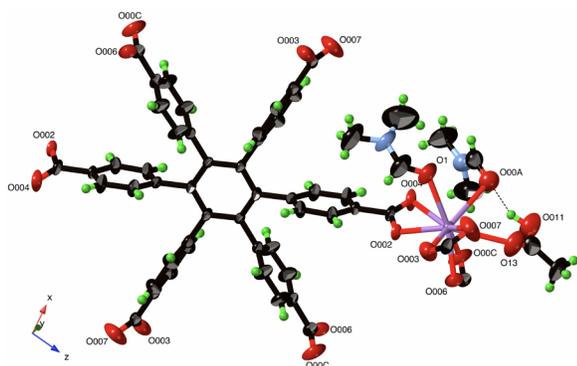


Figure 9. **CTH-6, [Bi₂(cpb)(HOAc)₂(dmf)₄]** Bi-O bonds are in the order of 2.22 Å to 3.06 Å. Ellipsoids are drawn at 50% probability. The **rtf-net** in the structure is illustrated in Figure 2.

Due to high synthesis temperature, the dmf decomposed to dimethylamine, dma which is subsequently protonated and thereby compensates for the common copper oxidation state

of 2+. There is hydrogen bonding between one hydrogen (H1B) of the Hdma⁺ cation and the oxygen atom (O5) of the cpb linker forming a NH...O interaction. This occurs for the Cu2 site and is possibly related to the Jahn-Teller distortion observed. The **CTH-7** structure is further supported by weak CH...O and CH...π interactions. See Figure 10.

Analysis of the void volume in the crystal structure indicates 40 % empty space in the unit cell and connected cavities with radii 2.6 and 1.0 Å respectively, potentially large enough to harbor a dmf molecule. One out of three rhombic shaped pockets in Figure 4. are empty and correspond to these calculated voids.

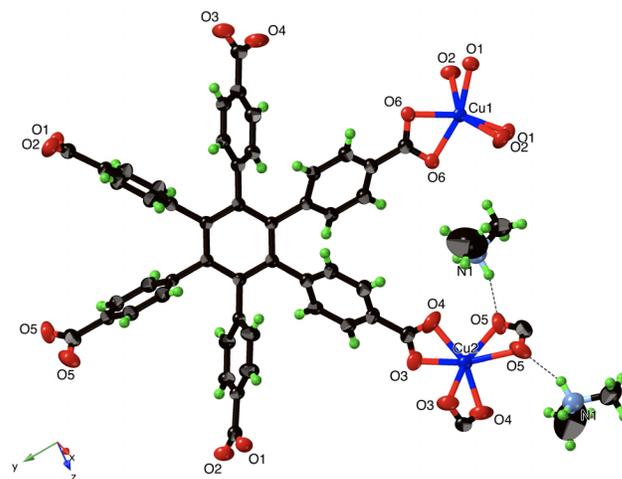


Figure 10. **CTH-7 2(Hdma)[Cu₂(cpb)]**. The two Cu sites display opposite Jahn-Teller distortions, and only Cu2 has hydrogen bonded Hdma⁺ ions. Ellipsoids are drawn at 50% probability. The **kgd-net** in the structure is illustrated in Figure 4.

CTH-8 [Fe₄(cpb)(acetato)₂(dmf)₄] The asymmetric unit contains four Fe(II) centers, two half cpb molecules, four dmf molecules and two acetate anions. There are four crystallographically independent Fe atoms in the structure. Fe1 is connected to three monodentate carboxylates, two dmf and one acetate anion. Fe2 is coordinated to two monodentate carboxylates, one bidentate carboxylate and one acetate anion. The third Fe3 is linked to two monodentate carboxylates, one bidentate carboxylate, one dmf and one acetate anion and finally the fourth, Fe4, connects with three monodentate carboxylates, one dmf and one acetate anion. The acetate anions in **CTH-8** bridge all the Fe atoms found in the framework, see Figure 11. The hexagonal spatial arrangement of the cpb linker and the trigonal bipyramid geometry results in the 3D **yav** topology. (Figure 3).¹⁸ Void volume was calculated as 36% with spherical cavities with diameters 3.4 and 3.2 Å.

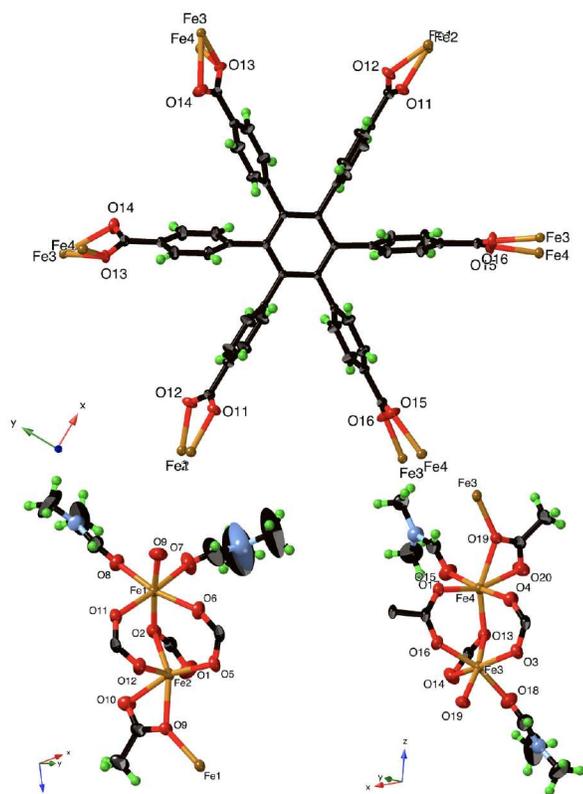


Figure 11. Three different views of **CTH-8**

[Fe₄(cpb)(acetato)₂(dmf)₄] showing the different parts of the structure (**CTH-9** with Co is isostructural). Ellipsoids are drawn at 50% probability. The **yav** net in these structures is illustrated in Figure 3.

CTH-9 [Co₄(cpb)(acetato)₂(dmf)₄] is isostructural with **CTH-8** as the unit cell parameters are similar, the space group identical, and the asymmetric unit content is the same, except Fe replaced by Co. Figure 11 thus illustrates also **CTH-9**.

CTH-10 (HNEt₃)₂[Fe₂(cpb)] crystallizes in the monoclinic chiro-descriptive space group *P*2₁ with *Z* = 2. In the asymmetric unit, there are two cpb⁶⁻ ligands, four Fe atoms and four protonated triethylamine (Htea⁺) molecules. These four protonated Htea⁺ molecules are each hydrogen-bonded to the neighboring carboxylate group of the cpb⁶⁻ forming N-H...O interactions, see Figure 12. **CTH-10** structure is further stabilized by C-H...O and C-H...π interactions.

From a supramolecular point of view, there are three distinct iron coordination entities: Fe01 has two hydrogen-bonded Htea⁺ ions (N...O 3.08-3.23 Å), Fe03 and Fe04 has one hydrogen bonded Htea⁺ (N...O 2.73-2.85 Å), while Fe02 has no hydrogen bonded Htea⁺ attached at all. (Note that in **CTH-7** we saw two different Cu sites.) This also explains the chirality of the structure, because as the chirality changes between each layer, the supramolecular coordination entities also change, meaning that entities with one or zero Htea⁺ ions attached always have one chirality, and the ones with a single Htea⁺ ion hydrogen-bonded always have the opposite chirality. (The Flack parameter is close to 0.5 so the crystal is racemic, the structure however chiral.)

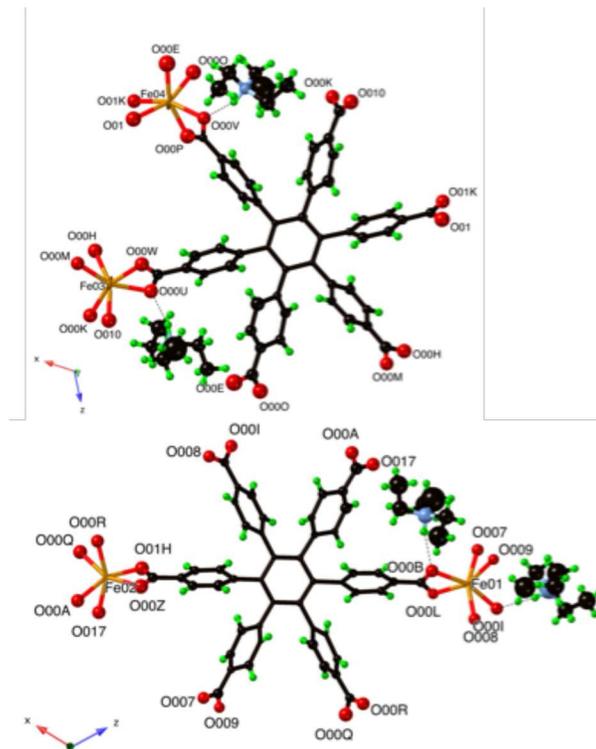


Figure 12. Molecular units form the two symmetry independent **kgd**-nets in **CTH-10 (HNEt₃)₂[Fe₂(cpb)]** showing the different parts of the structure.

The packing is very different from in **CTH-7**, now forming four distinctive layers in the unit cell, as the triethylammonium ions do not fit in a single **kgd**-void but need to share with an empty void in a neighboring sheet. Figure 13 illustrates this. Void volume was calculated as 35%, with a largest cavity with diameter of 3 Å.

Zn-MOF-888 and **CTH-11 2(H₂NMe₂)[Zn₂(cpb)]·1.5dmac** form two polymorphs which grew concomitantly. They were both colorless and had the same morphology. The two polymorphs could not be separated under microscope for thermal analysis (TGA) because their crystals grew on top of each other like twins. Single crystal X-ray diffraction data of either of the two polymorphs was not possible due to the micro-scale particle sizes 2 μm for **Zn-MOF-888** and 1 μm for **CTH-11** acquired from transmission electron microscopy (Figure S2, SI). Instead, 3D electron diffraction (3D ED) was employed by crushing the needle-shaped crystals, permitting structure-determination of the two polymorphs.³⁹

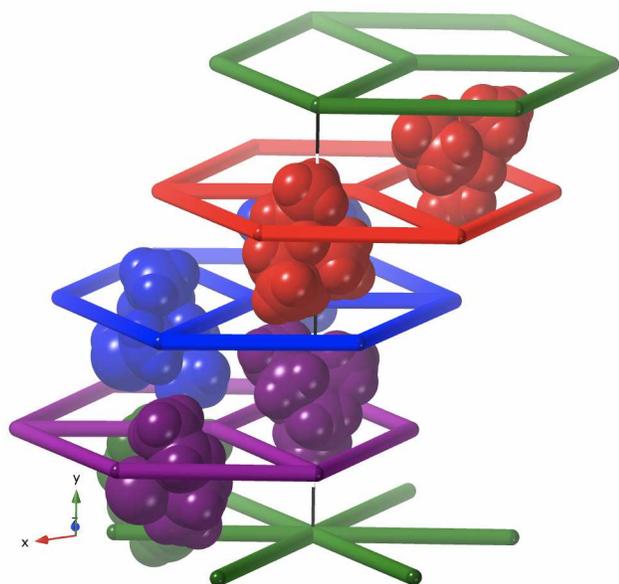


Figure 13. The network packing in the **CTH-10**. The unit cell comprises four different **kgd**-layers depicted in green, violet, blue and red, two of them symmetry independent. The triethylammonium ions attached by hydrogen bonds to each layer are presented in the same color. The axis defining the compartments capped by cpb ligands is indicated with a dashed red-and-black line. Note how the empty compartments in each layer have a counter ion from another layer penetrating.

Both polymorphs crystallize in the monoclinic system space group $C2/c$ with $Z = 2$. Hydrogen atoms were omitted in the polymorphs data refinement. The asymmetric unit of **Zn-MOF-888** contains two Zn atoms, a half cpb linker and the presence of some charge-balancing species in the framework cavities as for **CTH-7**. On the other hand, the asymmetric unit of **CTH-11** consists of one Zn atom, half a cpb molecule and some charge-balancing electron density located in the structure cavities that could not be adequately modeled. Packing diagrams for the two polymorphs viewed along $[001]$ are illustrated in Figure S3-S4. They resemble the **CTH-7** structure from the framework and **kgd** topology point of view but are not isostructural. **Zn-MOF-888**, however, appears to be isostructural with **MOF-888** (CSD code AZAVII), $[\text{Ni}_2(\text{cpb})] \cdot 4.1\text{H}_2\text{O}$,²³ which may cast some doubt about the inferred oxidation state Ni(III) in the latter compound as no extra-framework molecules could be identified or modelled in that case either. The TGA and elemental analysis of **Zn-MOF-888** and **CTH-11** indicate the presence of the counter ion H_2NMe_2 and dmac in the cavities of these structures.

CTH-12 $[\text{Cu}_2(\text{cpb})(\text{acetato})_2(\text{dmf})_2] \cdot 2\text{dmf}$. The single-crystal structure of **CTH-12** comprises one Cu(II) atom, half cpb molecule, 2 dmf and one acetate anion in its asymmetric unit. The Cu(II) center is connected to one cpb, one dmf (which is disordered with site occupancy factors of 0.533 and 0.467, respectively) and one acetate ion forming a paddlewheel with dmf in the axial positions, see Figure 14.

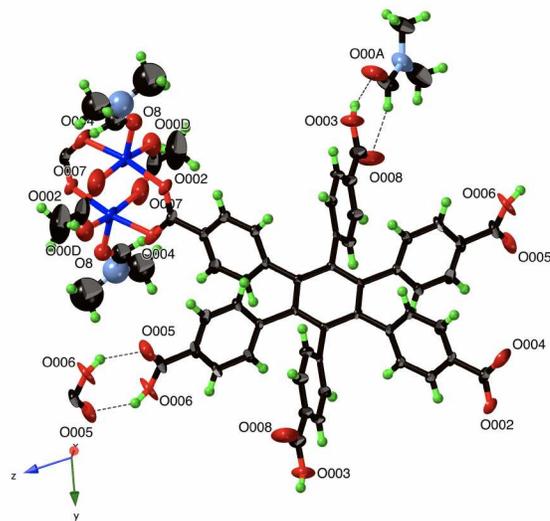


Figure 14. **CTH-12** Ellipsoids are drawn at 50% probability. The resulting **sql**-net in the structure is illustrated in Figure 15.

Only two of the six carboxylic acid moieties of the cpb linker are fully deprotonated, the other carboxylic acid are involved in hydrogen bonding with either themselves forming a dimer resulting in $R^2_2(8)$ rings using graphset notation,⁴⁰ or with the uncoordinated dmf molecule forming the homosynthon $R^2_2(8)$ through a weak $\text{CH} \cdots \text{O}$ interaction. The solvent accessible volume calculated from the crystal structure data is 36% and the largest calculated spherical void has a diameter of 3.6 Å.

We note that among the 373 structures found in the CSD which contain a paddle-wheel motif with at least two acetates bonded to Cu(II), there are only 8 compounds that are not homoleptic in this core structure, the rest, 98 %, all have four acetate ions forming the paddles on the wheel. Moreover, **CTH-12** appears to be the only example of the paddle-wheel forming a linear connecting SBU in a coordination polymer or MOF. On the other hand, there are plenty of examples where the paddle-wheel acts as a linear connector by additional axial ligands.

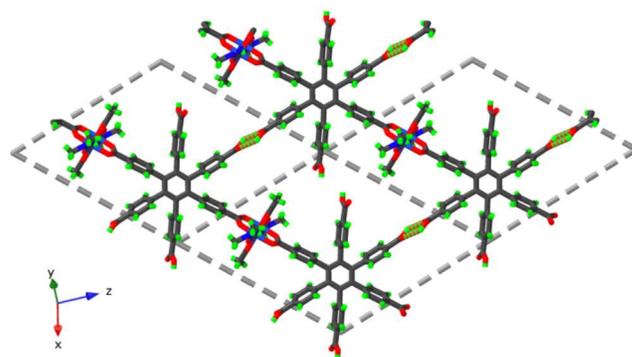


Figure 15. **CTH-12** with the **sql**-net with the dmf and unresolved solvent molecules in the voids hidden. Also shown in grey dashed lines is the position of the **sql**-net in the next layer.

CTH-13 $\text{yav-2}(\text{H}_2\text{NMe}_2)[\text{Zn}_2(\text{cpb})(\text{H}_2\text{O})_2] \cdot 2\text{dmf}$ crystallizes in the monoclinic system space group $C2/c$ and differ from the two other Zn-MOFs in this study in that the Zn(II) ions have a distinct tetrahedral coordination instead of octahedral, and the fourth coordination site is occupied by a

coordinated water molecule. This water ligand holds the **kgd** coordination network sheets together by strong hydrogen bonds, O-H...O=C 2.655 Å, 1.810 Å, 175° forming R₁¹(10) rings using graph-set notation. The third carbonyl oxygen is hydrogen bonding to the Hdma⁺ cation N-H...O=C 2.61 Å, 1.85 Å, 142°. See Figure 16.

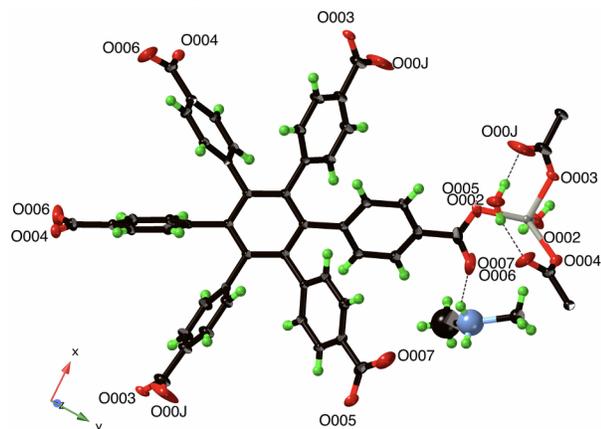


Figure 16. **CTH-13** Ellipsoids are drawn at 50% probability. Water molecules hydrogen bond between the Zn(II) entities forming the **yav**-net (Figure 3).

Chirality aspects

An important feature of network topology that is relevant to discuss here is chirality, as the **cpb** ligand with its distinct propeller shape (see Chart 1) is conformationally chiral. Conformationally chiral molecules are known to adopt chiral network topologies when they form conglomerates, but whether this is the driving force for conglomerate formation is an open question.⁴¹ (Figure S39-S40 reveals the extent of propeller shape of the **cpb** core and of conglomerate formation of **cpb** type compounds.) Of the aforementioned 6- and *n*-connected nets there is only one, **cys**, that is intrinsically chiral. However, none of the hexagon-based nets we have found adopts this topology, and in all cases, we have seen both conformational enantiomers are present in the structures.

One of the previously known **cpb** MOFs, the Cu(II) based **MOF-890** (CSD ref. code AZAVUU), however, crystallizes in a Sohncke Group (*P* 2₁2₁2₁ a “chiral” space group) but with the non-chiral net **htp**. (The **kgd**-net as all 2D nets are non-chiral as they have a mirror plane, however as we have seen, their molecular realization might be chiral.)

MOF	S _{BET} (m ² g ⁻¹)	S _{Lang} (m ² g ⁻¹)	N ₂ uptake (mmol g ⁻¹)	CO ₂ uptake (mmol g ⁻¹)
CTH-7	126	155	0.062	0.533
CTH-8	211	261	0.102	0.983
CTH-9	301	374	0.069	0.733
CTH-10	145	178	0.054	0.494
CTH-12	34	42	0.064	1.209

In terms of chirality, these versions of the **kgd**-net with tris-bischelating octahedral metal centers share some features with the honeycomb (**hcb**) nets constructed from tris-oxalate coordination entities.²⁴⁻²⁵ The latter contain alternating Δ or Λ enantiomers of the metal complexes and in all examples of the **kgd**-net with tris-bischelating octahedral metal centers

(**MOF-888**, **CTH-7**, **CTH-10**, **Zn-MOF-888**, **CTH-11**) we also in each layer see alternating clockwise propellers for the **cpb** ligand and anti-clockwise for the likewise propeller-shaped metal complex (and vice-versa). This is always matched by the opposite chirality in the next layer.

It does, however, mean that for these **kgd**-nets each sheet is chiral, and if one were to deposit a single layer on a surface, an enantiopure surface layer would be generated. This is illustrated in Figure 17.

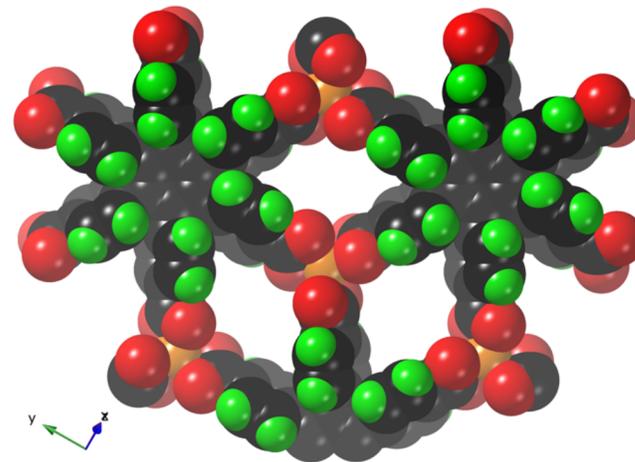


Figure 17. The chiral nature of a single layer **kgd**-net built from **cpb** ligands and octahedral metal entities exemplified by the crystal structure **CTH-7**. Note that each metal entity is homochiral and each **cpb** ligand is present in one of the two conformation enantiomers only. (Counter ions omitted for clarity.)

Physical properties of CTH-6 to CTH-13

Stability. Supporting Information, Figures S5 – S20. Thermal stability assessments of all MOFs in this study were performed using thermogravimetric analysis (TGA) up to 800 °C for all samples and the thermal events are likewise interpreted in the Supporting Information. PXRD patterns of all MOFs, except for **Zn-MOF-888**, **CTH-11**, and **CTH-13** were recorded and compared. Complete data and comments for experimental, calculated and post-gas-sorption PXRD patterns are also available. **CTH-9** and **CTH-12** were additionally characterized by collecting PXRD data at variable temperatures.

Gas sorption studies Sorption experiments were carried out after pretreatment of the samples at 120 °C for 6h dynamic vacuum. Permanent porosity for **CTH-6** to **CTH-12** was demonstrated by N₂ adsorption isotherms at -196 °C (Supporting Information, Figure S21-S38). The S_{BET} and S_{Lang} for **CTH-7**, **CTH-8**, **CTH-9**, **CTH-10**, and **CTH-12** were calculated and are listed in Table 2. **CTH-6** was not deemed pure enough to give unambiguous data and **Zn-MOF-888** was obtained together with **CTH-11** (indicated earlier). As **CTH-8** is isostructural to **CTH-9**, it is reasonable to expect their S_{BET} to be similar, as observed. Apart from the S_{BET} of **CTH-12**, the values are unremarkable.

Table 2 MOF Surface Area, CO₂ and N₂ uptake.

Out of all the tested samples, **CTH-12** has the highest CO₂ uptake under the test conditions. The CO₂-over-N₂ selectivity (simply estimated by the CO₂ uptake /N₂ uptake at 101 kPa) of **CTH-12** was also the highest of all tested samples. The difference is factor 19 rather than a factor 10 as is more

normal and displayed by the other compounds in this study. Recently, dinuclear Cu(II) paddle wheel coordination entities with free metal sites have been suggested to give a higher CO₂ selectivity.⁴² We think a similar effect might explain the behavior of **CTH-12** with some of the axially coordinated dmf molecules generating similar open sites during the pre-gas sorption activation treatment. **CTH-12** is the only compound in this study containing the paddle-wheel motif.

Secondary Ion Mass Spectrometry, SIMS

One of the major ideas of MOF and COF chemistry is to load the structure with compounds not present at synthesis, however, methods to investigate such post-synthetic modifications or diffusion added guests are scarce. We here highlight the possibilities of using ToF-SIMS in MOF research with some preliminary data on the sorption of iodine into **CTH-7**.

The choice to study I₂ sorption is foremost one of convenience. Iodine is easy to detect and not part of the framework, reagents or solvents. There is, however, a potential application of I₂ sorption because of the presence of the isotopes ¹²⁹I and ¹³¹I in radioactive waste and in cases of nuclear accidents. New good sorption methods of iodine are needed, and MOFs are among the most promising materials investigated.⁴³

In the case of gases, it is straight forward to examine this by activating the MOF followed by the measurement of gas sorption isotherms. However, questions may remain about the amount of solvent still in the “activated” material, as very often the same MOF will give different surface area and void volume depending on the precise method of activation.

For MOFs that have been subject to post-synthetic modifications, it may be possible to obtain a crystal-to-crystal transformation and new single-crystal diffraction data, but this is not the normal case. The same is also true when interior solvent molecules are replaced by, for example, a molecular catalyst, in a diffusion process or by diffusion into an activated material. Questions arise whether subsequent catalysis takes place by active species on the surface, or if the catalyst has entered into the material, and then how far and in which state.

The attraction of ToF-SIMS is that the ion beam can slowly dig into the material with a resolution of down to 100 Å giving a depth profile of any species present in crystal with the framework as a convenient internal standard. We note that the only reported SIMS studies on MOFs to date concerns the identification of guest loading in thin films, not depth profiles.⁴⁴⁻⁴⁵

The compound 2(Hdma)[Cu₂(cpb)] **CTH-7** formed large uniformly shaped crystals, and the **kgd**-voids seemed to be good for fitting the I₂ molecules with calculated voids of diameter 5.2 Å. As the experiment requires the crystals to be well visible in the SIMS microscope, they need to have a reasonable size (0.1*0.1 mm), even though the probing area of the ion beam is smaller, typically down to 100*100 nm.

Both MeOH solutions of I₂ and direct I₂ gas sorption by diffusion in a closed desiccator were tested. In both cases, I₂ was shown to have penetrate into the crystals, detected as layers were consecutively peeled away by the ion beam. Figure 18 shows the relative counts of different secondary ions detected, we have taken cyanide ions (from dma or Hdma) as a measure of the framework contents, and we

expect this count to be constant or perhaps to be lower close to the surface for the solution experiment, if dma has been replaced by MeOH.

Penetration is lower for gas-phase and the shorter solution exposure time, while the longer solution exposure indicates saturation. In principle, gas-phase studies are to be preferred as there are then no possibilities of dissolution and recrystallization of parts of the crystal.

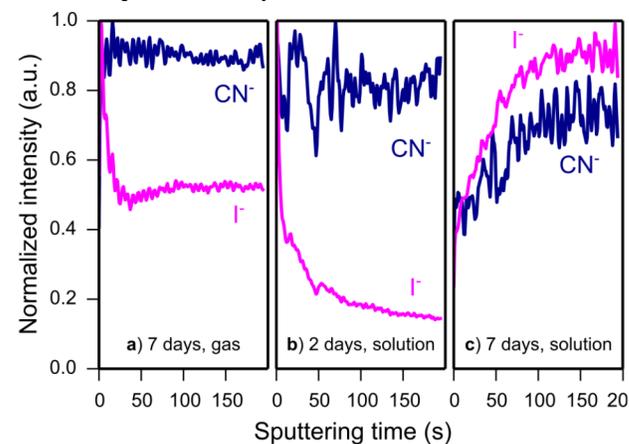


Figure 18. Time of Flight Secondary Ion Mass Spectrometry, (ToF-SIMS) experiments on 2(Hdma)[Cu₂(cpb)]·2dmf **CTH-7** with **A** direct I₂ gas sorption by diffusion in air in a closed desiccator and **B**, **C** MeOH solutions of I₂. Sputter time is proportional to the depth probed in the crystal, and the x-scale corresponds to a depth of approximately 400 Å. The surface probe area is typically 4000*4000 Å, rastered over a large area, typically 60 μm x 60 μm, thus the depth penetration is averaged over a large number of unit cells.

The plot has sputter time instead of the more desirable length scale, however, to accomplish this requires additional measurements with an AFM microscope that could accurately measure the depth of the sputtered hole in order to establish the sputtering time vs depth relation for MOF type materials. From measurements on other materials such as trehalose,⁴⁶ and SiO₂ layer films,⁴⁷ using a similar C60 setup we can, however, estimate that what we see in Figure 18 correspond to a horizontal-scale of around 400 Å.

CONCLUSIONS

We have extended reticular chemistry with two new ways of combining the hexagon with other geometrical figures, the trigonal pyramid in **CTH-6** with the **rtl**-net in a new hexagon embedding, and the new **laf**-net with perfect hexagons and triangles, derived from purely geometrical considerations. This increases the “blueprints” available for hexagon network chemistry with almost 30 %.

Furthermore, we have introduced the concept of foldable network topologies and given examples of the basic polygons and their combinations. Likely, the most important foldable nets (highest symmetry) are: **ths** (triangles), **cds** (squares), **tfk** (triangles and squares), **laf** (triangles and hexagons), and **4,6T84** (squares and hexagons). We suggest the most prominent examples of breathing MOFs can be thought of having the **cds** topology, further explaining this behavior. Moreover, we suggest a new design strategy for breathing MOFs that is not based on rod-MOFs with infinite SBUs.

Finally, we have made the first attempt to obtain depth profiles of guest compounds sorbed into MOFs by Time of Flight Secondary Ion Mass Spectrometry, showing penetration of iodine (I₂) into CTH-7 both from solution and from the gas phase.

EXPERIMENTAL SECTION

Materials and General Procedures

All chemicals utilized for MOF synthesis (details in the Supporting Information) were purchased from Sigma-Aldrich and were used without further purification. All MOF preparations have been performed repeatedly and yields are in general high, close to quantitative with respect to the metal ion except for CTH-6 where the insolubility of H₆cpb in solvents known to give high yield Bi-MOFs prevented optimal conditions. No independent analysis was performed to confirm the presence of protonated dimethylamine as the solvent dimethylformamide (dmf) is easily hydrolyzed to dimethylamine and formic acid. These impurities are always present in dmf unless it is freshly purified and dry. The hydrolysis is particularly efficient under basic conditions but can also occur under acidic conditions, especially if catalyzed by metal ions or other Lewis acids.⁴⁸ To-date protonated dimethyl amine has been detected in over 600 MOF structures in the Cambridge Crystallographic Database⁴⁹. All studied MOF single-crystals were washed and immersed in dmf before conducting single X-ray diffraction analysis to remove any unreacted H₆cpb.

Computational tools. CrystalMaker was used for all structure drawings, and porosity and cavity calculations. For the two latter calculations, van der Waals radii were used. CrystalMaker calculates empty volumes as the residual volume after atomic volumes have been subtracted from the total volume. For the size of cavities, CrystalMaker scans through the structure, aiming to find the largest sphere that can fit into any cavity using multiple iterations.⁵⁰ Systre was used for topology analysis.¹⁷ The new laf-net was discovered by real-life model-building using an Orbit organic and inorganic chemistry model set. A model with several repeating units was constructed and the unit cell, space group, and coordinates of the asymmetric unit were determined. Subsequently, these data were fed into the Systre program and the most symmetric embedding of the net determined. Systre input and output files are found in the supporting material. ToposPro and the TopCryst.com search routine were used to find examples of the laf-net.²⁶

ASSOCIATED CONTENT

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/xxxx>

AUTHOR INFORMATION

Corresponding Authors

* mystere@chalmers.se

* ohrstrom@chalmers.se

ACKNOWLEDGMENT


FMAN. and LÖ are grateful to the Swedish Research Council (#2017-04725). ESG and AKI acknowledge the Swedish Foundation for Strategic Research (SSF) and the Knut and Alice

Wallenberg Foundation (KAW 2016.0072). OC acknowledge the Swedish Research Council for Sustainable Development (FORMAS, #2018-00651) and the ÅForsk Foundation (#19-549). CJM is grateful to the Carlsberg Foundation for funding (grant CF15-0675) for the X-ray diffractometer. We thank Michael O'Keeffe for adding the laf-net to the RCSR and Dr Christian Göb, Rigaku Europe SE, for assistance with the measurement of CTH-13.

REFERENCES

- Ockwig, N. W.; Delgado-Friedrichs, O.; O'Keeffe, M.; Yaghi, O. M., Reticular Chemistry: Occurrence and Taxonomy of Nets and Grammar for the Design of Frameworks. *J. Am. Chem. Soc.* **2005**, *38* (3), 176-182.
- Yaghi, O. M.; O'Keeffe, M.; Ockwig, N. W.; Chae, H. K.; Eddaoudi, M.; Kim, J., Reticular synthesis and the design of new materials. *Nature* **2003**, *423* (6941), 705-714.
- Batten, S. R.; Champness, N. R.; Chen, X. M.; Garcia-Martinez, J.; Kitagawa, S.; Öhrström, L.; O'Keeffe, M.; Suh, M. P.; Reedijk, J., Terminology of Metal-Organic Frameworks and Coordination Polymers (IUPAC recommendations 2013). *Pure and Appl. Chem.* **2013**, *85* (8), 1715-1724.
- Yaghi, O. M.; Kalmutzki, M. J.; Diercks, C. S., *Introduction to Reticular Chemistry - Metal-Organic Frameworks and Covalent Organic Frameworks*. Wiley-VCH: Weinheim, 2019.
- Öhrström, L., Designing, Describing and Disseminating New Materials by using the Network Topology Approach. *Chem. Eur. J.* **2016**, *22* (39), 13758-13763.
- Öhrström, L.; O'Keeffe, M., Network topology approach to new allotropes of the group 14 elements. *Z. Krist. Cryst. Mat.* **2013**, *228* (7), 343-346.
- Chung, Y. G.; Haldoupis, E.; Bucior, B. J.; Haranczyk, M.; Lee, S.; Zhang, H.; Vogiatzis, K. D.; Milisavljevic, M.; Ling, S.; Camp, J. S.; Slater, B.; Siepmann, J. I.; Sholl, D. S.; Snurr, R. Q., Advances, Updates, and Analytics for the Computation-Ready, Experimental Metal-Organic Framework Database: CoRE MOF 2019. *Journal of Chemical & Engineering Data* **2019**, *64* (12), 5985-5998.
- Barthel, S.; Alexandrov, E. V.; Proserpio, D. M.; Smit, B., Distinguishing Metal-Organic Frameworks. *Cryst. Growth Des.* **2018**, *18* (3), 1738-1747.
- Collings, I. E.; Tucker, M. G.; Keen, D. A.; Goodwin, A. L., Geometric switching of linear to area negative thermal expansion in uniaxial metal-organic frameworks. *CrystEngComm* **2014**, *16* (17), 3498-3506.
- Tan, J. C.; Bennett, T. D.; Cheetham, A. K., Chemical structure, network topology, and porosity effects on the mechanical properties of Zeolitic Imidazolate Frameworks. *Proc. Nat. Acad. Sci.* **2010**, *107* (22), 9938-9943.
- Kalmutzki, M. J.; Hanikel, N.; Yaghi, O. M., Secondary building units as the turning point in the development of the reticular chemistry of MOFs. *Science Advances* **2018**, *4* (10).
- Wells, A. F., *Three-dimensional nets and polyhedra*. John Wiley & Sons: New York, 1977.
- Robson, R., A net-based approach to coordination polymers. *Dalton Trans.* **2000**, 3735-3744.
- Koch, E.; Fischer, W., Sphere packings with three contacts per sphere and the problem of the least dense sphere packing. *Z. Kristallogr* **1995**, *210*, 407 - 414.
- Delgado-Friedrichs, O.; O'Keeffe, M.; Yaghi, O. M., Three-periodic nets and tilings: edge-transitive binodal structures. *Acta Cryst. A.* **2006**, *62* (5), 350-355.
- Delgado-Friedrichs, O.; O'Keeffe, M., Three-periodic tilings and nets: face-transitive tilings and edge-transitive nets revisited. *Acta Cryst. A.* **2007**, *63* (4), 344-347.
- Delgado-Friedrichs, O.; O'Keeffe, M., Identification and symmetry computation for crystal nets. *Acta Cryst. Sec. A* **2003**, *59*, 351-360

18. O'Keeffe, M.; Peskov, M. A.; Ramsden, S.; Yaghi, O. M., The Reticular Chemistry Structure Resource (RCSR) Database of, and Symbols for, CrystalNets. *Acc. Chem. Res.* **2008**, *41*, 1782-1789.
19. O'Keeffe, M.; Delgado-Friedrichs, O. *Reticular Chemistry Structure Resource*, 2019. <http://rcsr.anu.edu.au/>.
20. Chen, Z.; Weseliński, L. J.; Adil, K.; Belmabkhout, Y.; Shkurenko, A.; Jiang, H.; Bhatt, P. M.; Guillerm, V.; Dauzon, E.; Xue, D.-X.; O'Keeffe, M.; Eddaoudi, M., Applying the Power of Reticular Chemistry to Finding the Missing alb-MOF Platform Based on the (6,12)-Coordinated Edge-Transitive Net. *J. Am. Chem. Soc.* **2017**, *139* (8), 3265-3274.
21. Chen, Z.; Li, P.; Wang, X.; Otake, K.-i.; Zhang, X.; Robison, L.; Atilgan, A.; Islamoglu, T.; Hall, M. G.; Peterson, G. W.; Stoddart, J. F.; Farha, O. K., Ligand-Directed Reticular Synthesis of Catalytically Active Missing Zirconium-Based Metal–Organic Frameworks. *J. Am. Chem. Soc.* **2019**, *141* (31), 12229-12235.
22. Chen, Z.; Thiam, Z.; Shkurenko, A.; Weselinski, L. J.; Adil, K.; Jiang, H.; Alezi, D.; Assen, A. H.; O'Keeffe, M.; Eddaoudi, M., Enriching the Reticular Chemistry Repertoire with Minimal Edge-Transitive Related Nets: Access to Highly Coordinated Metal–Organic Frameworks Based on Double Six-Membered Rings as Net-Coded Building Units. *J. Am. Chem. Soc.* **2019**, *141* (51), 20480-20489.
23. Nguyen, P. T. K.; Nguyen, H. T. D.; Pham, H. Q.; Kim, J.; Cordova, K. E.; Furukawa, H., Synthesis and Selective CO₂ Capture Properties of a Series of Hexatopic Linker-Based Metal–Organic Frameworks. *Inorg. Chem.* **2015**, *54* (20), 10065-10072.
24. Dazem, C. L. F.; Noa, F. M. A.; Nenwa, J.; Öhrström, L. R., Natural and synthetic metal oxalates – a topology approach. *CrystEngComm* **2019**, *21*, 6156-6164.
25. Öhrström, L.; Larsson, K., What kinds of three-dimensional nets are possible with tris-chelated metal complexes as building blocks? *Dalton Trans.* **2004**, (3), 347-353.
26. Blatov, V. A.; Shevchenko, A. P.; Proserpio, D. M., Applied Topological Analysis of Crystal Structures with the Program Package ToposPro. *Cryst. Growth & Des.* **2014**, *14* (7), 3576-3586.
27. Decurtins, S.; Schmalte, H. W.; Schneuwly, P.; Enslin, J.; Gütllich, P., A concept for the synthesis of 3-dimensional homo- and bimetallic oxalate-bridged networks [M₂(ox)₃]_n. Structural, mössbauer, and magnetic studies in the field of molecular-based magnets. *J. Am. Chem. Soc.* **1994**, *116*, 9521.
28. Parent, L. R.; Pham, C. H.; Patterson, J. P.; Denny, M. S.; Cohen, S. M.; Gianneschi, N. C.; Paesani, F., Pore Breathing of Metal–Organic Frameworks by Environmental Transmission Electron Microscopy. *J. Am. Chem. Soc.* **2017**, *139* (40), 13973-13976.
29. Grape, E. S.; Xu, H.; Cheung, O.; Calmels, M.; Zhao, J.; Dejoie, C.; Proserpio, D. M.; Zou, X.; Inge, A. K., A Breathing Metal–Organic Framework Based on Flexible Inorganic Building Units. *Cryst. Growth Des.* **2020**, *20*, 320-329.
30. Wang, Y.; Takki, S.; Cheung, O.; Xu, H.; Wan, W.; Öhrström, L.; Inge, A. K., Elucidation of the elusive structure and formula of the active pharmaceutical ingredient bismuth subgallate by continuous rotation electron diffraction. *Chemical Communications* **2017**, *53* (52), 7018-7021.
31. Férey, G.; Serre, C., Large breathing effects in three-dimensional porous hybrid matter: facts, analyses, rules and consequences. *Chem. Soc. Rev.* **2009**, *38* (5), 1380-1399.
32. Schneemann, A.; Bon, V.; Schwedler, I.; Senkovska, I.; Kaskel, S.; Fischer, R. A., Flexible metal–organic frameworks. *Chem. Soc. Rev.* **2014**, *43* (16), 6062-6096.
33. Bon, V.; Kavoosi, N.; Senkovska, I.; Kaskel, S., Tolerance of Flexible MOFs toward Repeated Adsorption Stress. *ACS Applied Materials & Interfaces* **2015**, *7* (40), 22292-22300.
34. Wei, Y.-S.; Chen, K.-J.; Liao, P.-Q.; Zhu, B.-Y.; Lin, R.-B.; Zhou, H.-L.; Wang, B.-Y.; Xue, W.; Zhang, J.-P.; Chen, X.-M., Turning on the flexibility of isoreticular porous coordination frameworks for drastically tunable framework breathing and thermal expansion. *Chemical Science* **2013**, *4* (4), 1539-1546.
35. Alexandrov, E. V.; Goltsev, A. V.; Eremin, R. A.; Blatov, V. A., Anisotropy of Elastic Properties of Metal–Organic Frameworks and the Breathing Phenomenon. *Journal of Physical Chemistry C* **2019**, *123* (40), 24651-24658.
36. Mason, J. A.; Oktawiec, J.; Taylor, M. K.; Hudson, M. R.; Rodriguez, J.; Bachman, J. E.; Gonzalez, M. I.; Cervellino, A.; Guagliardi, A.; Brown, C. M.; Llewellyn, P. L.; Masciocchi, N.; Long, J. R., Methane storage in flexible metal–organic frameworks with intrinsic thermal management. *Nature* **2015**, *527* (7578), 357-361.
37. Rosi, N. L.; Kim, J.; Eddaoudi, M.; Chen, B.; O'Keeffe, M.; Yaghi, O. M., Rod Packings and Metal–Organic Frameworks Constructed from Rod-Shaped Secondary Building Units. *J. Am. Chem. Soc.* **2005**, *127* (5), 1504-1518.
38. Tshuma, P.; Makhubela, B. C. E.; Öhrström, L.; Bourne, S. A.; Chatterjee, N.; Beas, I. N.; Darkwa, J.; Mehlan, G., Cyclometalation of lanthanum(III) based MOF for catalytic hydrogenation of carbon dioxide to formate. *RSC Advances* **2020**, *10* (6), 3593-3605.
39. Wang, B.; Rhauderwiek, T.; Inge, A. K.; Xu, H.; Yang, T.; Huang, Z.; Stock, N.; Zou, X., A Porous Cobalt Tetrakisphosphate Metal–Organic Framework: Accurate Structure and Guest Molecule Location Determined by Continuous-Rotation Electron Diffraction. *Chem. Euro. J.* **2018**, *24* (66), 17429-17433.
40. Etter, M. C.; MacDonald, J. C.; Bernstein, J., Graph-set analysis of hydrogen-bond patterns in organic crystals. *Acta Crystallographica Section B* **1990**, *46* (2), 256-262.
41. Johnson, M. T.; Dzolic, Z.; Cetina, M.; Lahtinen, M.; Ahlquist, M. S. G.; Rissanen, K.; Öhrström, L.; Wendt, O. F., Preparation of potentially porous, chiral organometallic materials through spontaneous resolution of pincer palladium conformers. *Dalton Trans.* **2013**, *42*, 8484-8491.
42. Kochetygov, I.; Bulut, S.; Asgari, M.; Queen, W. L., Selective CO₂ adsorption by a new metal–organic framework: synergy between open metal sites and a charged imidazolium backbone. *Dalton Trans.* **2018**, *47* (31), 10527-10535.
43. Xie, W.; Cui, D.; Zhang, S.-R.; Xu, Y.-H.; Jiang, D.-L., Iodine capture in porous organic polymers and metal–organic frameworks materials. *Materials Horizons* **2019**, *6* (8), 1571-1595.
44. Baroni, N.; Turshatov, A.; Oldenburg, M.; Busko, D.; Adams, M.; Haldar, R.; Welle, A.; Redel, E.; Woll, C.; Richards, B. S.; Howard, I. A., Facile loading of thin-film surface-anchored metal–organic frameworks with Lewis-base guest molecules. *Materials Chemistry Frontiers* **2017**, *1* (9), 1888-1894.
45. So, M. C.; Beyzavi, M. H.; Sawhney, R.; Shekiah, O.; Eddaoudi, M.; Al-Juaid, S. S.; Hupp, J. T.; Farha, O. K., Post-assembly transformations of porphyrin-containing metal–organic framework (MOF) films fabricated via automated layer-by-layer coordination. *Chem. Commun.* **2015**, *51* (1), 85-88.
46. Wucher, A.; Cheng, J.; Winograd, N., Molecular Depth Profiling Using a C60 Cluster Beam: The Role of Impact Energy. *The Journal of Physical Chemistry C* **2008**, *112* (42), 16550-16555.
47. Kobayashi, D.; Yamamoto, Y.; Isemura, T., Time-of-flight SIMS depth profiling of Na in SiO₂ glass using C60 sputter ion beam. *Surf. Interface Anal.* **2013**, *45* (1), 113-116.
48. Juillard, J., *Pure Appl. Chem.* **1977**, *49*, 885-892.
49. Groom, C. R.; Bruno, I. J.; Lightfoot, M. P.; Ward, S. C., The Cambridge Structural Database. *Acta Cryst. B* **2016**, *72* (2), 171-179.
50. *Images and video generated using CrystalMaker®: a crystal and molecular structures program for Mac and Windows. CrystalMaker Software Ltd, Oxford, England (www.crystallmaker.com), 2019.*

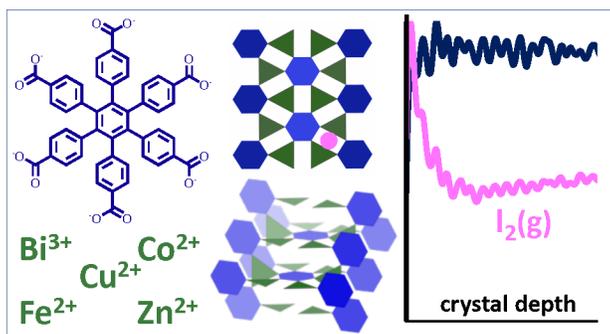

For Table of Contents Only
