



Journal Name

COMMUNICATION

Investigation of easy-plane magnetic anisotropy in P-ligand square-pyramidal Co^{II} single ion magnets

Received 00th January 20xx,
Accepted 00th January 20xxAmit Kumar Mondal,^a Jesús Jover,^b Eliseo Ruiz*^b and Sanjit Konar*^a

DOI: 10.1039/x0xx00000x

www.rsc.org/

In this work we report two pentacoordinated Co^{II}-P₄X₁ Single Ion Magnets (SIMs) based on P-donor ligand. The tetradentate ligand tris[2-(diphenylphosphino)ethyl]phosphine allows the obtention of the isostructural square pyramidal [Co(PP₃)Cl]·ClO₄ (1**) and [Co(PP₃)Br]·ClO₄ (**2**) complexes. Consistent theoretical and experimental studies indicate that these complexes have a high spin (S=3/2) ground state and suggest that the relaxation dynamics is governed by ground state quantum tunneling, whereas its temperature dependence is directed by optical or acoustic Raman processes.**

Single-molecule magnets (SMMs) are molecules that exhibit a slow relaxation of their magnetization from a pure molecular origin. When one of these molecules contains only one metal ion they are referred as single-ion magnets (SIMs). The study of these systems has experienced a huge increase in recent times due to their promising properties in molecular spintronics,¹ high-density information storage,² and qubits for quantum computation.³ In SMMs and SIMs the thermal energy barrier for the reversal of the magnetization (*U*) depends on the total spin (*S*) and the easy axis anisotropy parameter (*D*). *U* can be quantified as $|D|S^2$ and $|D|(S^2 - 1/4)$ for integer and half-integer spins, respectively.⁴ A substantial effort has been devoted to the preparation of new molecules to better understand different phenomena that effect slow relaxation behaviour. The early examples of SMMs were based on polynuclear transition metal complexes⁵ but recently low-nuclearity lanthanide complexes⁶ and even mononuclear lanthanide⁷ and transition-metal complexes⁸ have been reported to show SMM behaviour. Mononuclear transition metal complexes are significant because the relaxation process concerning the ground state, or the

contribution of some excited states, can be tuned via variation of the ligand field around the metal center. The most remarkable feature of SIMs lies in the design and possible estimation of their magnetic anisotropy based on the ligand field theory. Among 3d-SIMs, Co^{II} complexes are mostly important due to the presence of non-integer spin ground state, that decreases the probability of quantum tunnelling of magnetization (QTM).⁹ The first Co^{II} based SIM was reported for a pentacoordinated system with bis(imino)pyridine and thiocyanido ligands.¹⁰ Although many other Co^{II}-based SIMs are reported later with different geometry and coordination environments,⁸ number of pentacoordinated complexes are still scarce and most of them are based on the different combinations of multidentate *N*-donor and monodentate halido/pseudohalido ligands. In contrast, despite the similarity between nitrogen and phosphorus, the usage of P-donor ligands to produce Co^{II} pentacoordinate SIMs has not been reported yet. This work reports the first example of pentacoordinate Co^{II} SIMs based on P-donor ligand having general formula Co^{II}-P₄X₁: [Co(PP₃)Cl]·ClO₄ (**1**) and [Co(PP₃)Br]·ClO₄ (**2**) where PP₃ = tris[2-(diphenylphosphino)ethyl]phosphine. The investigation also reveals the influence of metal coordination geometry on the magnetic anisotropy of the metal complexes. The single-crystal X-ray analysis of **1** and **2** reveals that both complexes are isostructural and crystallize in the triclinic *P*-1 space group (Fig. 1 and Table S1). The tripodal PP₃ ligand coordinates in a tetradentate fashion, with one of the P atom is occupying the axial position, while the fifth position is taken by the halide ion (X = Cl (**1**) and Br (**2**)). The geometry at the Co^{II} centre is best described as a distorted square pyramidal; the calculated τ values for **1** and **2** are 0.331 and 0.354, respectively (Table S2).¹¹ Additional SHAPE¹² analysis confirms that both the complexes can be better described as square pyramidal (1.14 and 1.41 for **1** and **2**) than as trigonal bipyramidal (3.31 and 3.29 for **1** and **2**, Table S3). In both complexes, substantial $\pi \cdots \pi$ interactions and intermolecular hydrogen-bonding are found, favoring the formation of a supramolecular two dimensional arrangement (Fig. S1-S2 and Table S4-S5).

^a Department of Chemistry, Indian Institute of Science Education and Research (IISER), Bhopal By-pass Road, Bhaauri, Bhopal-462066, India.

^b Departament de Química Inorgànica i Orgànica and Institut de Recerca de Química Teòrica i Computacional, Universitat de Barcelona, Diagonal 645, E-08028 Barcelona, Spain.

Electronic Supplementary Information (ESI) available: Synthetic procedure, PXRD pattern, additional figures and plots. CCDC 1455159-1455160. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/x0xx00000x

COMMUNICATION

Journal Name

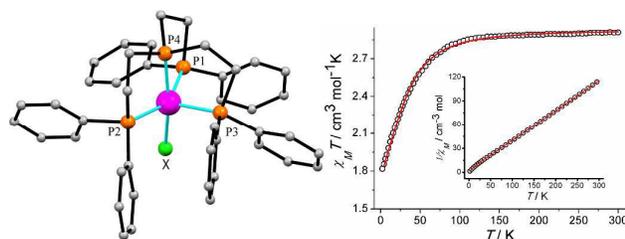


Fig. 1 View of the molecular structures for complexes **1** and **2**, where X = Cl (**1**) and X = Br (**2**); hydrogen atoms are omitted for clarity; $\chi_M T$ vs. T plot measured at 0.1 T for complex **1** (left). The red line is the best fit.

The purity of the as-synthesized products has been confirmed by the good agreement of experimental and simulated bulk phase powder X-ray diffraction patterns based on the single crystal structure data (Fig. S3). DC (direct current) magnetic susceptibility measurements have been performed under an applied field of 0.1 T. At room temperature, $\chi_M T$ values (χ_M = molar magnetic susceptibility) of 2.90 and 2.84 $\text{cm}^3 \text{K mol}^{-1}$ have been obtained for **1** and **2**, respectively. These values are larger than the spin-only value of 1.87 $\text{cm}^3 \text{mol}^{-1} \text{K}$ for a high-spin Co^{II} ion but, nevertheless, they fall within the usual range of 2.1–3.4 $\text{cm}^3 \text{mol}^{-1} \text{K}$ found for highly anisotropic Co^{II} ions with a significant orbital contribution.¹³ Upon cooling from 300 K, the $\chi_M T$ values of **1** and **2** remain constant down to 100 K, below which they decrease, reaching a value of 1.81 and 1.78 $\text{cm}^3 \text{mol}^{-1} \text{K}$ at 2 K, respectively (Fig. 1 and S5). The decrease of the $\chi_M T$ curves at low temperature is mainly due to the intrinsic magnetic anisotropy of the Co^{II} center. Reduced magnetization data ($M/N\mu_B$ vs. H) attain the highest values of 2.42 and 2.35 $N\mu_B$ for **1** and **2** at 2 K and 7 T (Fig. S4–S5). These values are well below the theoretical saturation for an $S = 3/2$ system ($M_{\text{sat}} = 3.3$ for $g = 2.2$). A spin Hamiltonian of eqn (1) is used to describe the magnetic anisotropy qualitatively:

$$H = g\mu_B S \times B + D[S_z^2 - S(S+1)/3] + E(S_x^2 - S_y^2) \quad (1)$$

where the D and E terms represent the single-ion axial and rhombic ZFS parameters. The PHI code¹⁴ has been employed to quantify the anisotropy parameters of the Co^{II} centres by fitting of the $\chi_M T$ vs. T plots. The best fits of the magnetic susceptibility data give $D = 46.4 \text{ cm}^{-1}$, $E = 10.1 \text{ cm}^{-1}$, and $g = 2.31$ for **1**; $D = 40.7 \text{ cm}^{-1}$, $E = 9.3 \text{ cm}^{-1}$, and $g = 2.28$ for **2**. Similar values are found for the anisotropy parameters with electronic structure CASSCF calculations, carried out with either ORCA¹⁵ and MOLCAS¹⁶ (Table 1). In all cases the calculations indicate a quadruplet (3/2) ground state. The quasi-degenerate perturbation theory (QDPT) implemented in ORCA produces very similar results to those obtained by the fit of experimental data although the computed D values seem to be slightly underestimated for both complexes **1** and **2**. The SO-RASSI approach included in the MOLCAS package produces also quite similar E and D values for both complexes, again in good agreement with those obtained from the experimental fit. Other useful computational information, such as the computed low-lying spin-orbit energy states and the orientation of the g - and D -tensors, can be found in the ESI (Table S6–S9 and Fig. S6). The relative energy order of the 3d orbitals has been extracted from the ORCA calculation using the *ab initio* ligand field theory (AILF) method.¹⁷

The final d-orbital splitting for complexes **1** and **2**, which allows the prediction of the lowest energy transitions, is shown in Fig. 2. As may be observed the last doubly occupied orbital is d_{yz} (or d_{xz} ,

Table 1. ORCA and MOLCAS CASSCF+RASSI computed D , $|E/D|$ and g -values for complexes **1** and **2**. ΔE indicates the first excitation energy computed in the spin-free state of the Co^{II} complexes.

Complex	D_{fit} (cm^{-1})	D_{calc} (cm^{-1})	$ E/D _{\text{calc}}$	ΔE (cm^{-1})	g_{xx}, g_{yy}, g_{zz}
1 ^a	46.4	40.1	0.24	1568.7	2.03, 2.27, 2.55
1 ^b	46.4	45.6	0.24	1638.3	2.04, 2.29, 2.56
2 ^a	40.7	38.3	0.24	1559.9	2.03, 2.28, 2.55
2 ^b	40.7	36.9	0.24	1635.2	2.04, 2.30, 2.56

^a ORCA, ^b MOLCAS.

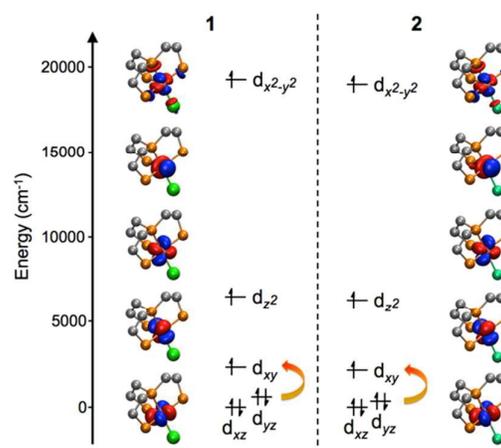


Fig. 2 Co^{II} core and computed d-orbitals for complexes **1** (left) and **2** (right). Orbital relative energies are given in cm^{-1} . Color code: Co = pink, C = gray, P = orange, Cl or Br = green; outer C and H atoms have been omitted for clarity. The curvy orange arrows indicate the lowest energy transitions.

because those cannot be distinguished) and the first semioccupied orbital is d_{xy} for both complexes. Since these orbitals have a different $|m_l|$ value, the contribution to the D value should be positive¹⁸ in complete agreement with the experimental fit. The d-orbital splitting allows the rationalization of the difference in the magnitude of D between both complexes. The presence of a chloride ligand produces a 1746.1 cm^{-1} energy gap while with bromide the gap slightly increases to 1806.1 cm^{-1} ; since the energy gap is smaller for complex **1** it should have a higher D value, as observed both in experiments and calculations.

As mentioned above complexes **1** and **2** constitute a new class of Co^{II} SIMs and therefore the impact of the P-donor atoms on the magnetic properties is difficult to assess. We have carried out an exploration of the Cambridge Structural Database (CSD) looking for other pentacoordinate Co^{II} complexes containing P_4 ligands (either mono or polydentate) and one halide, which could be compared to complexes **1** and **2**. For those complexes, 7 in total, we have carried out a CASSCF calculation equivalent to those of **1** and **2**, and we have also computed their SHAPE analysis regarding the typical 5 vertexes polyhedra (Table 2, entries 1–7). The computed D value for all these $\text{Co}^{\text{II}}\text{-P}_4\text{X}_1$ complexes is positive independent of the ligand arrangement or nature, suggesting that the presence of a P-donor ligand tends to produce easy-plane complexes. CSD refcode DIZQAF (Entry 1 in Table 2) has a negative D value but other parameters derived from the calculations indicate it should be positive (see ESI). Another interesting feature consists of checking whether the magnetic behavior of complexes **1** and **2** can be modulated by

Table 2. SHAPE analysis and computed D values for the studied Co(II)- N_4X_1 complexes.

Entry	Structure	vOC-5	TBPY-5	SPY-5	D (cm ⁻¹)	E/D
1	DIZQAF	6.77	0.74	4.89	-32.8 ^a	0.28
2	JIPCERO1	0.74	5.76	1.10	53.3	0.12
3	NIZDOP	3.76	1.04	2.49	52.4	0.12
4	RUTSUU	4.62	2.01	3.69	86.4	0.28
5	UFUCUV	6.51	1.01	5.11	53.0	0.08
6	VAKFAR	0.77	4.29	1.50	36.6	0.10
7	VAKFEV	0.72	5.91	1.37	46.8	0.15
8	FAWYUX	2.08	5.50	1.39	107.0 ^a	0.29
9	NADTUH	2.01	4.54	0.30	113.6	0.15
10	NUQMAP	2.73	3.46	1.07	104.0	0.10
11	RUJSOE	2.76	2.40	1.18	-71.9 ^a	0.31
12	XOBFZ	2.93	5.76	0.63	-65.9 ^a	0.30

vOC-5: vacant octahedron, TBPY-5: trigonal bipyramid, SPY-5: spherical square pyramid. ^a See full explanation in the ESI.

replacing the P-donor ligand by an equivalent structure containing N-donor atoms *i.e.* Co^{II}- N_4X_1 complexes. This has been already achieved by replacing a (NN₃^{Me}) with an equivalent (NS₃^{IPr}) ligand in mononuclear trigonal bipyramidal Co^{II} complexes.¹⁹ In that case, the decrease of the sigma donor ability in the equatorial plane produces an increase in absolute value in the magnetic anisotropy. Searching the CSD reveals the presence of limited no of Co^{II}- N_4X_1 complexes (5) having a square pyramid shape similar to **1** and **2** (Table 2, entries 8-12). Among those, only one contains a neutral N_4 tetradentate ligand and a chloride where one of the nitrogen atoms takes the axial position (CSD refcode FAWYUX, entry 8 in Table 2, Fig. S7). The computed D value for this complex is positive (107.0 cm⁻¹), indicating that the square pyramid arrangement shown in complexes **1** and **2** seems to produce also easy plane Co^{II}- N_4X_1 complexes, although more examples should be needed to extract a general conclusion. As may be observed, two complexes have negative D values (Table 2, entries 11-12); nevertheless, the E/D value is in the limit (0.3), and thus the sign of D for those complexes is not well defined and may well be positive, as hinted by other computed features (see ESI).

To probe the magnetic relaxation dynamics of both complexes, AC magnetic susceptibility measurements have been performed in the temperature range of 1.8-10 K at a 3.5 Oe ac field. No out-of-phase ac susceptibility (χ_M'') signal was observed under a zero dc field. Nevertheless, upon application of a 2000 Oe dc field, both the complexes show temperature and frequency-dependent ac signals, typically observed for field-induced 3d-SIM species (Fig. 3 and S8-S10). Furthermore, the Cole-Cole plots (Fig. 3 and S10) have been constructed from the frequency-dependent ac susceptibility data. The fit of the χ_M'' vs χ_M' data at each temperature, using the generalized Debye model,²⁰ produces values of α within the ranges 0.03-0.22 (**1**) and 0.05-0.25 (**2**), showing a narrow distribution of the relaxation time. The effective energy barrier (U_{eff}) and relaxation times (τ_0) have been determined using the Arrhenius equation (2):²¹

$$\ln(1/\tau) = \ln(1/\tau_0) - U_{eff}/kT \quad (2)$$

The best fit of equation (2) using the available data produces $U_{eff} = 37.8$ K and $\tau_0 = 8.2 \times 10^{-6}$ s for **1**, and $U_{eff} = 34.5$ K and $\tau_0 = 6.7 \times 10^{-6}$ s for **2** (Fig. S11).

Slightly higher energy barriers are found with the electronic structure calculations, which allow the location of the lowest

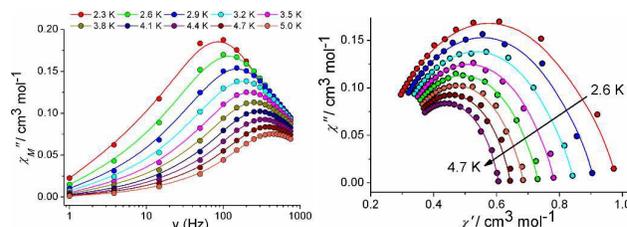


Fig. 3 Frequency dependency of the out-of-phase (χ_M'') (left) AC magnetic susceptibility plots for complex **1** at 2000 Oe; Cole-Cole plots (right) for complex **1**. Solid lines represent the best fit.

Kramer's doublets (KDs) responsible for the relaxation process (Fig. S12). The spin relaxation mechanisms for both complexes show a plausible pathway via a direct quantum tunneling (QTM) in the ground state. The relaxation through a thermally-assisted QTM via the first excited states seems also possible since the second KDs are found at relatively low energies of 83.8 and 79.9 cm⁻¹. On the other hand, the third KD lies much higher in energy (aprox. 1700 cm⁻¹) for both complexes, and thus those states are not expected to participate in the spin relaxation process. The computed spin relaxation mechanisms also indicate that the Orbach processes cannot be completely ruled out and can play a significant role under certain conditions.

In order to acquire a deeper understanding of the magnetic relaxation behaviour, the relaxation times have been reassessed considering the different relaxation processes. The two terms in equation (3) represent the strongly field dependent (related to QTM) and weakly field dependent (Raman, Orbach, etc.) processes (kept as constant, C , in equation (3)).²²

$$\tau^{-1} = B_1 / (1 + B_2 H^2) + C \quad (3)$$

The relaxation time has been studied starting from its field dependence at 2 K (Fig. S13 (left)) and is well defined by this method. Since the τ parameter becomes larger for stronger fields (Fig. S13 (left)), the direct term has not been taken into consideration. τ_{QTM} has been calculated to be 1.36×10^{-4} s and 1.18×10^{-4} s for **1** and **2**, respectively, using equation (3). These values suggest the presence of substantial contribution of ground state quantum tunneling in the relaxation process, as observed in the electronic structure calculations. The temperature dependence of the relaxation time at 0.2 T was studied (Fig. S13 (right)), including the thermally active Orbach and Raman processes.²² The relaxation time is well defined by the method with a single power law (equation (4)).

$$\tau^{-1} = \tau_{QTM}^{-1} + bT^n \quad (4)$$

Values of $n = 5.8$ and 5.3 are obtained for complexes **1** and **2**, respectively (note that the τ_{QTM} values have been kept fixed at 1.36×10^{-4} s and 1.18×10^{-4} s for **1** and **2**, respectively), which are close to the value reported by Colacio *et al.*²³ The Orbach relaxation pathway is not applicable for the studied complexes because the energy barriers obtained from ac susceptibility measurements are lower than the energy gap between the $M_S = \pm 1/2$ and $M_S = \pm 3/2$ doublets. Hence, the combined study of field and temperature dependence of the relaxation time suggests that quantum tunneling is the leading process to relax the magnetization at low temperature. Nevertheless, this relaxation mechanism is directed by the optical or acoustic Raman processes which elucidate the thermal dependence of the relaxation time.

In summary, this work describes the magnetic anisotropy of the first two pentacoordinate Co^{II} SIMs based on P-donor ligand. The experimental fit of the magnetic data indicates that the square pyramid arrangement of the ligand around the metal center produces positive *D* values, as confirmed by the electronic structure calculations. Both experimental and computational approaches indicate that the main relaxation process of the magnetization of these compounds is the quantum tunneling through the ground state.

A.K.M. thanks UGC, India for the SRF fellowship. S.K. thanks DAE-BRNS (Project No. 37(2)/14/09/2015-BRNS), Government of India and IISER Bhopal for generous financial support. The research reported here was supported by the Spanish *Ministerio de Economía y Competitividad* (grant CTQ2015-64579-C3-1-P, MINECO/FEDER, UE). E.R. thanks Generalitat de Catalunya for an ICREA Academia award. J.J. and E.R. thankfully acknowledge the computer resources in the Consorci Serveis Universitaris de Catalunya (CSUC).


Notes and references

†Electronic Supplementary Information (ESI) available: magnetic plots, PXRD, computational details, computed low-lying spin-orbit energy states and magnetic axes are provided.

- L. Bogani and W. Wernsdorfer, *Nat. Mater.*, 2008, **7**, 179.
- R. Sessoli, D. Gatteschi, A. Caneschi and M. A. Novak, *Nature*, 1993, **365**, 141.
- (a) P. Santini, S. Carretta, F. Troiani and G. Amoretti, *Phys. Rev. Lett.*, 2011, **107**, 230502; (b) G. A. Timco, T. B. Faust, F. Tuna and R. E. P. Winpenny, *Chem. Soc. Rev.*, 2011, **40**, 3067; (c) A. Furrer and O. Waldmann, *Rev. Mod. Phys.*, 2013, **85**, 367; (d) G. A. Timco, E. J. L. McInnes and R. E. P. Winpenny, *Chem. Soc. Rev.*, 2013, **42**, 1796.
- (a) O. Waldmann, *Inorg. Chem.*, 2007, **46**, 10035; (b) E. Ruiz, J. Cirera, J. Cano, S. Alvarez, C. Loose and J. Kortus, *Chem. Commun.*, 2008, **2**, 52; (c) F. Neese and D. A. Pantazis, *Faraday Discussions*, 2011, **148**, 229.
- R. Bagai and G. Christou, *Chem. Soc. Rev.*, 2009, **38**, 1011.
- (a) R. J. Blagg, C. A. Murn, E. J. L. McInnes, F. Tuna and R. E. P. Winpenny, *Angew. Chem. Int. Ed.*, 2011, **50**, 6530; (b) J. D. Rinehart, M. Fang, W. J. Evans and J. R. Long, *J. Am. Chem. Soc.*, 2011, **133**, 14236; (c) J. D. Rinehart, M. Fang, W. J. Evans and J. R. Long, *Nat. Chem.*, 2011, **3**, 538; (d) F. Habib and M. Murugesu, *Chem. Soc. Rev.*, 2013, **42**, 3278; (e) D. N. Woodruff, R. E. P. Winpenny and R. A. Layfield, *Chem. Rev.*, 2013, **113**, 5110; (f) J. J. Le Roy, L. Ungur, I. Korobkov, L. F. Chibotaru and M. Murugesu, *J. Am. Chem. Soc.*, 2014, **136**, 8003.
- (a) L. J. Batchelor, I. Cimatti, R. Guillot, F. Tuna, W. Wernsdorfer, L. Ungur, L. F. Chibotaru, V. E. Campbell and T. Mallah, *Dalton Trans.*, 2014, **43**, 12146; (b) V. E. Campbell, H. Bolvin, E. Rivière, R. Guillot, W. Wernsdorfer and T. Mallah, *Inorg. Chem.*, 2014, **53**, 2598; (c) L. Ungur, J. J. Le Roy, I. Korobkov, M. Murugesu and L. F. Chibotaru, *Angew. Chem. Int. Ed.*, 2014, **53**, 4413; (d) A. J. Brown, D. Pinkowicz, M. R. Saber and K. R. Dunbar, *Angew. Chem. Int. Ed.*, 2015, **54**, 5864; (e) A. K. Mondal, S. Goswami and S. Konar, *Dalton*

- Trans.*, 2015, **44**, 5086; (f) S. K. Gupta, T. Rajeshkumar, G. Rajaraman and R. Murugavel, *Chem. Sci.*, 2016, **7**, 5181.
- (a) G. A. Craig and M. Murrie, *Chem. Soc. Rev.*, 2015, **44**, 2135; (b) A. K. Bar, C. Pichon and J.-P. Sutter, *Coord. Chem. Rev.*, 2016, **308**, 346; (c) J. M. Frost, K. L. M. Harriman and M. Murugesu, *Chem. Sci.*, 2016, **7**, 2470; (d) R. Ruamps, L. J. Batchelor, R. Guillot, G. Zakhia, A. -L. Barra, W. Wernsdorfer, N. Guihéry and T. Mallah, *Chem. Sci.*, 2014, **5**, 3418; (e) S. Vaidya, A. Upadhyay, S. K. Singh, T. Gupta, S. Tewary, S. K. Langley, J. P. S. Walsh, K. S. Murray, G. Rajaraman and M. Shanmugam, *Chem. Commun.*, 2015, **51**, 3739.
- M. Murrie, *Chem. Soc. Rev.*, 2010, **39**, 1986.
- T. Jurca, A. Farghal, P. H. Lin, I. Korobkov, M. Murugesu and D. S. Richeson, *J. Am. Chem. Soc.*, 2011, **133**, 15814.
- A. W. Addison, T. N. Rao, J. Reedijk, J. van Rijn and G. C. Verschoor, *J. Chem. Soc., Dalton Trans.*, 1984, **9**, 1349.
- S. Alvarez, P. Alemany, D. Casanova, J. Cirera, M. Llunell and D. Avnir, *Coord. Chem. Rev.*, 2005, **249**, 1693.
- F. E. Mabbs and D. J. Machin, *Magnetism and Transition Metal Complexes*, Dover Publications: Mineola, New York, 2008.
- N. F. Chilton, R. P. Anderson, L. D. Turner, A. Soncini and K. S. Murray, *J. Comp. Chem.*, 2013, **34**, 1164.
- F. Neese, *WIREs Comput. Mol. Sci.*, 2012, **2**, 73.
- (a) G. Karlström, R. Lindh, P.-Å. Malmqvist, B. O. Roos, U. Ryde, V. Veryazov, P.-O. Widmark, M. Cossi, B. Schimmelpfennig, P. Neogrady and L. Seijo, *Comput. Matter Sci.*, 2003, **28**, 222; (b) V. Veryazov, P.-O. Widmark, L. Serrano-Andrés, R. Lindh and B. O. Roos, *Int. J. Quantum Chem.*, 2004, **100**, 626.
- M. Atanasov, D. Ganyushin, K. Sivalingam and F. Neese, *in Molecular Electronic Structures of Transition Metal Complexes II*, Springer Berlin, Heidelberg, 2011.
- (a) S. Gómez-Coca, E. Cremades, N. Aliaga-Alcalde and E. Ruiz, *J. Am. Chem. Soc.*, 2013, **135**, 7010; (b) S. Gómez-Coca, D. Aravena, R. Morales and E. Ruiz, *Coord. Chem. Rev.*, 2015, **289–290**, 379.
- F. Shao, B. Cahier, N. Guihéry, E. Riviere, R. Guillot, A.-L. Barra, Y. Lan, W. Wernsdorfer, V. E. Campbell and T. Mallah, *Chem. Commun.*, 2015, **51**, 16475.
- K. S. Cole and R. H. Cole, *J. Chem. Phys.*, 1941, **9**, 341.
- (a) M. T. Gamer, Y. Lan, P. W. Roesky, A. K. Powell and R. Clérac, *Inorg. Chem.*, 2008, **47**, 6581; (b) P.-H. Lin, T. J. Burchell, R. Clérac and M. Murugesu, *Angew. Chem. Int. Ed.*, 2008, **47**, 8848; (c) G. Xu, Q. Wang, P. Gamez, Y. Ma, R. Clérac, J. Tang, S. Yan, P. Cheng and D. Liao, *Chem. Commun.*, 2010, **46**, 1506; (d) R. J. Blagg, L. Ungur, F. Tuna, J. Speak, P. Comar, D. Collision, W. Wernsdorfer, E. J. L. McInnes, L. F. Chibotaru and R. E. P. Winpenny, *Nat. Chem.*, 2013, **5**, 673.
- (a) A. Abragam and B. Bleaney, *Electron Paramagnetic Resonance of Transition Ions*, Clarendon Press: Oxford, U.K., 1970; (b) M. Atzori, L. Tesi, E. Morra, M. Chiesa, L. Sorace and R. Sessoli, *J. Am. Chem. Soc.*, 2016, **138**, 2154.
- E. Colacio, J. Ruiz, E. Ruiz, E. Cremades, J. Krzystek, S. Carretta, J. Cano, T. Guidi, W. Wernsdorfer and E. K. Brechin, *Angew. Chem. Int. Ed.*, 2013, **52**, 9130.

Table of Contents

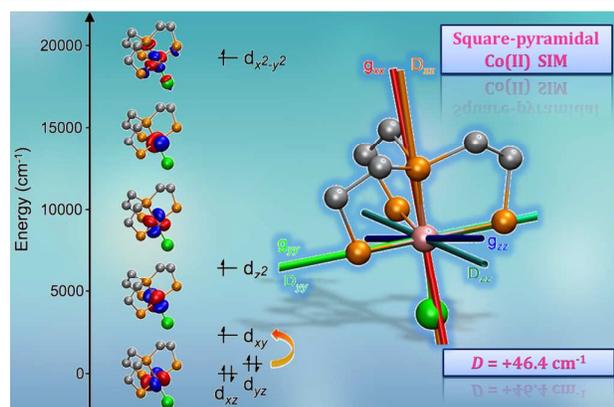

Field induced slow magnetic relaxation behavior has been studied for the first time for two P-donor ligand-based square-pyramidal Co^{II} complexes with an easy-plane magnetic anisotropy.