

# Notes

## Preparation and Characterization of Luminescent SCS and NCN Pincer Platinum Complexes Derived from 3,5-Bis(anilinothiocarbonyl)toluene

Ken Okamoto, Takaki Kanbara,\* Takakazu Yamamoto,\* and Akihide Wada

Chemical Resources Laboratory, Tokyo Institute of Technology, 4259 Nagatsuta, Midori-ku, Yokohama, 226-8503 Japan

Received January 6, 2006

**Summary:** Starting from 5-methyl-1,3-bis(anilinothiocarbonyl)benzene (**1**), two types of luminescent pincer platinum complexes with  $\kappa^3\text{S,C,S}$  and  $\kappa^3\text{N,C,N}$  coordination modes were obtained. Reaction of **1** with  $\text{K}_2\text{PtCl}_4$  afforded a pincer Pt(II) complex (**3**) with the  $\kappa^3\text{S,C,S}$  coordination mode, whereas oxidative cyclization of **1** yielded 5-methyl-1,3-bis(benzothiazol-2-yl)benzene (**2**), which provided a pincer Pt(II) complex (**4**) with the  $\kappa^3\text{N,C,N}$  coordination mode. Molecular structures and photochemical properties of the complexes have been examined. The decay lifetimes of the emission from the complexes were in the range  $10^{-5}$ – $10^{-6}$  s, which were indicative of phosphorescent emission.

### Introduction


Square-planar cycloplatinated complexes are often light emissive,<sup>1</sup> and use of such light emissive metal complexes, especially phosphorescent metal complexes, as emitters in light-emitting diodes (LEDs) has attracted much attention.<sup>2</sup>

\* Corresponding authors. E-mail: tkanbara@res.titech.ac.jp. Fax: +81-45-924-5976.

(1) (a) Brooks, J.; Babayan, Y.; Lamansky, S.; Djurovich, P. I.; Tsyba, I.; Bau, R.; Thompson, M. E. *Inorg. Chem.* **2002**, *41*, 3055. (b) Balashev, K. P.; Puzyk, M. V.; Kotlyar, V. S.; Kulikova, M. V. *Coord. Chem. Rev.* **1997**, *109*, 159. (c) Maestri, M.; Deuschel-Cornioley, C.; von Zelewsky, A. *Coord. Chem. Rev.* **1991**, *111*, 117. (d) Liu, Q.; Thorne, L.; Kozin, I.; Song, D.; Seward, C.; D'Iorio, M.; Tao, Y.; Wang, S. *J. Chem. Soc., Dalton Trans.* **2002**, 3234. (e) Cheung, T.-C.; Cheung, K.-K.; Peng, S.-M.; Che, C.-M. *J. Chem. Soc., Dalton Trans.* **1996**, 1645. (f) Lu, W.; Mi, B.-X.; Chan, M. C.-W.; Hui, Z.; Zhu, N.; Lee, S.-T.; Che, C.-M. *Chem. Commun.* **2002**, 206. (g) Lai, S.-W.; Chan, M. C.-W.; Cheung, T.-C.; Peng, S.-M.; Che, C.-M. *Inorg. Chem.* **1999**, *38*, 4046. (h) Lai, S.-W.; Chan, M. C.-W.; Cheung, K.-K.; Che, C.-M. *Organometallics* **1999**, *18*, 3327. (i) Yam, V. W.-W.; Tang, R. P.-L.; Wong, K. M.-C.; Lu, W. X.-X.; Cheung, K.-K.; Zhu, N. *Chem. Eur. J.* **2002**, *8*, 4066. (j) Williams, J. A. G.; Beeby, A.; Davies, E. S.; Weinstein, J. A.; Wilson, C. *Inorg. Chem.* **2003**, *42*, 8609. (k) Lu, W.; Mi, B.-X.; Chan, M. C. W.; Hui, Z.; Che, C.-M.; Zhu, N.; Lee, S.-T. *J. Am. Chem. Soc.* **2004**, *126*, 4958. (l) Lu, W.; Chan, M. C. W.; Zhu, N.; Che, C.-M.; Li, C.; Hui, Z. *J. Am. Chem. Soc.* **2004**, *126*, 7639. (m) Chiu, B. K.-W.; Lam, M. H.-W.; Lee, D. Y.-K.; Wong, W.-Y. *J. Organomet. Chem.* **2004**, *689*, 2888. (n) Jude, H.; Bauer, J. A. K.; Connick, W. B. *Inorg. Chem.* **2004**, *43*, 725. (o) Jude, H.; Bauer, J. A. K.; Connick, W. B. *Inorg. Chem.* **2002**, *41*, 2275. (p) Kanbara, T.; Yamamoto, T. *J. Organomet. Chem.* **2003**, *688*, 15. (q) Kanbara, T.; Okada, K.; Yamamoto, T.; Ogawa, H.; Inoue, T. *J. Organomet. Chem.* **2004**, *689*, 1860. (r) Jude, H.; Bauer, J. A. K.; Connick, W. B. *Inorg. Chem.* **2005**, *44*, 1211. (s) Farley, S. J.; Rochester, D. L.; Thompson, A. L.; Howard, J. A. K.; Williams, J. A. G. *Inorg. Chem.* **2005**, *44*, 9690. (t) Sotoyama, W.; Satoh, T.; Sato, H.; Matsuura, A.; Sawatari, N. *J. Phys. Chem. A* **2005**, *109*, 9760.

(2) (a) Baldo, M. A.; Thompson, M. E.; Forrest, S. R. *Pure Appl. Chem.* **1999**, *71*, 2095. (b) Richter, M. M. *Chem. Rev.* **2004**, *104*, 3003. (c) Holder, E.; Langeveld, B. M. W.; Schubert, U. S. *Adv. Mater.* **2005**, *17*, 1109, and references therein.

**Scheme 1.** New Pincer Pt(II) Complexes **3** and **4** Derived from **1**

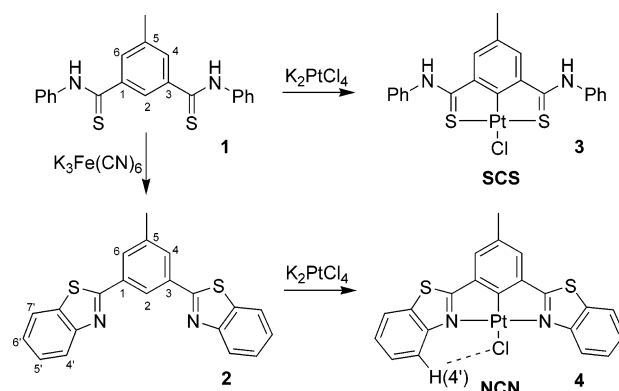


We previously reported that  $\kappa^3\text{S,C,S}$  pincer Pt(II) complexes containing tertiary thioamide-based pincer ligands exhibited strong phosphorescent emission in the glassy frozen state and in the solid state.<sup>1q</sup> We have extended the research and now report that the secondary thioamide compound **1** is a good starting material to afford the two new pincer Pt(II) complexes **3** and **4**.

Secondary thioamides have been used in the field of medical and organic chemistry,<sup>3,4</sup> and it is known that oxidative cyclization of secondary *N*-arylthioamides with  $\text{K}_3[\text{Fe}(\text{CN})_6]$  gives benzothiazole derivatives.<sup>4</sup> Such a cyclization reaction can proceed with bis(secondary thioamide)s, and **1** can be transformed into **2**; thus, from the ligands **1** and **2**, the new complexes **3** and **4** are obtained. Consequently, expansion of the complex synthesis exhibited in Scheme 1 by modifying the aromatic groups in **1** is expected to give various Pt complexes of the types **3** and **4**.

Cyclometalated  $\kappa^2\text{C,N}$  Ir(III) and Pt(II) complexes of 2-arylbenzothiazoles<sup>1a,2c</sup> and related  $\kappa^3\text{N,N,N}$  type metal complexes of neutral tridentate ligands such as 2,6-bis(benzothiazol-

(3) (a) Jagodziński, T. S. *Chem. Rev.* **2003**, *103*, 197. (b) Klingele, M. H.; Brooker, S. *Eur. J. Org. Chem.* **2004**, 3422. (c) Murai, T.; Aso, H.; Tatamatsu, Y.; Itoh, Y.; Niwa, H.; Kato, S. *J. Org. Chem.* **2003**, *68*, 8514. (d) Ach, D.; Reboul, V.; Metzner, P. *Eur. J. Org. Chem.* **2002**, 2573. (e) Ares, J. J. *Synth. Commun.* **1991**, *21*, 625. (f) Tamaru, Y.; Kagotani, M.; Yoshida, Z. *Tetrahedron Lett.* **1981**, *35*, 3409.

(4) (a) Petrova, D.; Jakopčić, K. *Croatica Chem. Acta* **1976**, *48*, 319. (b) Downer, N. K.; Jackson, Y. A. *Org. Biomol. Chem.* **2004**, *2*, 3039. (c) Mathis, C. A.; Wang, Y.; Holt, D. P.; Huang, G.-F.; Debnath, M. L.; Klunk, W. E. *J. Med. Chem.* **2003**, *46*, 2740.

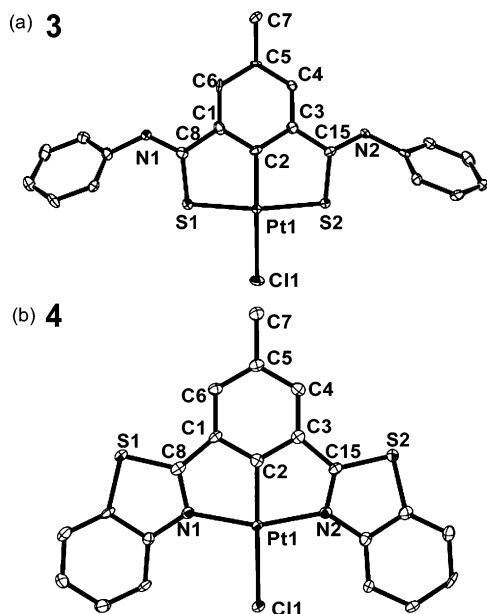

**Figure 1.** X-ray crystal structures of (a) **3** and (b) **4** with thermal ellipsoids drawn at the 50% probability level. Hydrogen atoms and solvated molecules are omitted for simplicity.

2-yl)pyridine have been reported.<sup>5</sup> However, a  $\kappa^3\text{N,C,N}$  pincer complex such as **4** constituted of the benzothiazole unit has not yet been reported to our knowledge. On this basis, we here report that **1** can give two luminescent pincer Pt(II) complexes, **3** and **4**, which are composed of different donor sets with  $\kappa^3\text{S,C,S}$  and  $\kappa^3\text{N,C,N}$  pincer coordination modes, respectively. Molecular structures and photochemical properties of the complexes are also described.

## Results and Discussion

Preparation of **1** is described in the Experimental Section. The oxidative cyclization of **1** using  $\text{K}_3[\text{Fe}(\text{CN})_6]$  afforded **2**. Reactions of **1** and **2** with  $\text{K}_2\text{PtCl}_4$  in acetic acid led to regioselective *ortho,ortho*-cycloplatination at the C-2 position of the centered benzene ring with Pt(II) and afforded the corresponding pincer complexes **3** and **4** in 63 and 51% yields, respectively.

**3** and **4** were fairly stable to air and water and were thermally stable up to 300 °C. **3** showed good solubility in polar organic solvents such as MeOH, EtOH, DMF, and DMSO. **4** was less soluble and showed only low solubility in  $\text{CH}_2\text{Cl}_2$  and  $\text{CHCl}_3$ . The  $^1\text{H}$  NMR spectra of **3** and **4** shown in Figure S1 agree with their structures. In the  $^{13}\text{C}$  NMR spectrum of **3**, the *ortho,ortho*-cycloplatinated carbon ( $\text{C}_{\text{ipso}}$ ) was shifted to a higher magnetic field by 24 ppm according to the  $\sigma$ -bonding to Pt.

The ORTEP drawings of **3** and **4** are presented in Figure 1, and selected bond lengths and bond angles of **1–4** are summarized in Table 1. **3** and **4** have a distorted square-planar geometry similar to each other. As shown in Figure 1a, **3** has a  $\kappa^3\text{S,C,S}$  pincer complex structure, similar to previously reported thioamide-based pincer complexes.<sup>14,6</sup> The Pt–C and Pt–Cl bond lengths are consistent with those of the reported thioamide-based pincer Pt(II) complexes. The C=S bond lengths are longer than those observed with **1**, and the C(S)–N bond

**Table 1.** Selected Bond Lengths and Bond Angles for **1–4**

| Bond Lengths (Å)  |          |            |          |            |
|-------------------|----------|------------|----------|------------|
|                   | 1        | 3          | 2        | 4          |
| Pt–C              |          | 1.957(7)   |          | 1.924(5)   |
| Pt–Cl             |          | 2.389(2)   |          | 2.4254(14) |
| C–S               | 1.671(2) | 1.700(7)   | 1.728(8) | 1.712(5)   |
| C–S               |          | 1.714(7)   | 1.768(6) | 1.724(5)   |
| C(S)–N            | 1.331(2) | 1.31(1)    | 1.311(9) | 1.349(7)   |
| C(S)–N            |          | 1.32(1)    | 1.190(9) | 1.327(7)   |
| Bond Angles (deg) |          |            |          |            |
|                   |          | 3          |          | 4          |
| Cl–Pt–C           |          | 178.76(17) |          | 177.72(16) |
| S–Pt–S            |          | 170.77(6)  |          |            |
| N–Pt–N            |          |            |          | 158.57(18) |

lengths are somewhat shorter than those observed with **1**, indicating that the S-coordination to Pt decreases the double-bond character of the C=S bond. Two DMSO molecules in the crystal are hydrogen bonded to the N–H protons of **3** through the O of DMSO ( $\text{N}\cdots\text{O} = 2.809$  and  $2.852$  Å), in agreement with known hydrogen-bonding donor ability of the N–H hydrogen of the secondary thioamide.<sup>7</sup>

As depicted in Figure 1b, **4** has a  $\kappa^3\text{N,C,N}$  coordination mode. The Pt–C bond length is shorter than those in **3** and related pincer Pt(II) complexes.<sup>1e,8</sup> The cycloplatination brings about a close contact between the H(4') hydrogen of the benzothiazole ring and the Cl ligand in **4**, as depicted in Scheme 1, and distances of 2.66 and 2.70 Å are obtained for the distance between H(4') and Cl by X-ray crystallography. The distance is smaller than the sum (2.95 Å) of the van der Waals radii of H and Cl, indicating the presence of an intramolecular hydrogen bonding interaction between H(4') and Cl.<sup>9</sup> The two benzothiazole rings are nearly parallel to the center benzene ring. The intramolecular hydrogen-bonding interaction agrees with a  $^1\text{H}$  NMR shift of the H(4') hydrogen peak of **2** to a lower magnetic field by 1.77 ppm by the complexation with Pt, as shown in Figure S1.

The crystal-packing diagrams of **3** and **4** exhibit that the complexes are stacked in a head-to-tail fashion with interplanar distances of 3.56 and 3.40 Å for **3** and **4**, respectively, as depicted in Figure S4. The molecular planes are slipped and the Pt $\cdots$ Pt distances between Pt in the upper complex and Pt in the lower complex are 6.00 and 5.51 Å for **3** and **4**, respectively. These data indicate that there is no significant  $d^8-d^8$  interaction.

**Electrochemical Response.** Redox behavior of **3** and **4** has been investigated by cyclic voltammetry, and the data are given in Table 2. Electrochemical reduction of **3** occurs at  $-1.78$  V vs  $\text{Cp}_2\text{Fe}^+/\text{Cp}_2\text{Fe}$ , which is considered to occur mainly at the ligand. The reduction peak is located at a higher potential than that of **1** ( $E_{\text{p}}^{\text{red}} = -2.38$  V), presumably due to bonding to

(5) (a) Boča, M.; Boča, R.; KICKELBICK, G.; LINERT, W.; SVOBODA, I.; FUESS, H. *Inorg. Chem. Acta* **2002**, 338, 36. (b) RÜTTIMANN, S.; MOREAU, C. M.; WILLIAMS, A. F. *Polyhedron* **1992**, 11, 635. (c) ADDISON, A. W.; BURMAN, S.; WAHLGREN, C. G. *J. Chem. Soc., Dalton Trans.* **1987**, 2621. (d) LIVINGSTONE, S. E.; NOLAN, J. D. *J. Chem. Soc., Dalton Trans.* **1972**, 218.

(6) (a) Takahashi, S.; Nonoyama, M.; Kita, M. *Transition Met. Chem.* **1995**, 20, 528. (b) Nojima, Y.; Nonoyama, M.; Nakajima, K. *Polyhedron* **1996**, 15, 3795. (c) Hossain, M. A.; Lucarini, S.; Powell, D.; Bowman-James, K. *Inorg. Chem.* **2004**, 43, 7275. (d) Akaiwa, M.; Kanbara, T.; Fukumoto, H.; Yamamoto, T. *J. Organomet. Chem.* **2005**, 690, 4192. (e) Begum, R. A.; Powell, D.; Bowman-James, K. *Inorg. Chem.* **2006**, 45, 964.

(7) (a) Lee, H.-J.; Choi, Y.-S.; Lee, K.-B.; Park, J.; Yoon, C.-J. *J. Phys. Chem. A* **2002**, 106, 7010. (b) Inoue, Y.; Kanbara, T.; Yamamoto, T. *Tetrahedron Lett.* **2003**, 44, 5167.

(8) (a) Albrecht, M.; van Koten, G. *Angew. Chem., Int. Ed.* **2001**, 40, 3750. (b) Albrecht, M.; Spek, A. L.; van Koten, G. *J. Am. Chem. Soc.* **2001**, 123, 7233. (c) Steenwinkel, P.; Gossage, R. A.; van Koten, G. *Chem. Eur. J.* **1998**, 4, 759, and references therein.


(9) (a) Brammer, L.; Bruton, E. A.; Sherwood, P. *Cryst. Growth Des.* **2001**, 1, 277. (b) Thallapally, P. K.; Nangia, A. *CrystEngComm* **2001**, 27, 1.

**Table 2. Photochemical, Electrochemical, and Thermal Data of 3 and 4**

|                                                  | 3            | 4                    |
|--------------------------------------------------|--------------|----------------------|
| absorption <sup>a</sup> (UV-vis)                 | 294 (25 300) | 321 (23 800)         |
| $\lambda_{\text{max}}/\text{nm}$                 | 383 (5900)   | 388 (5900)           |
| $(\epsilon, \text{M}^{-1} \text{cm}^{-1})$       | 425 (6400)   | 425 (8300)           |
|                                                  | 478 (11 100) | 449 (12 800)         |
|                                                  | 544 (1300)   |                      |
| emission (PL) $\lambda_{\text{max}}/\text{nm}^b$ | 631          | 550, 597, 649, 717sh |
| $\lambda_{\text{max}}/\text{nm}^c$               |              | 550, 597, 649, 718sh |
| $\lambda_{\text{max}}/\text{nm}^d$               | 741          | 702                  |
| $\phi_f^e$                                       | 0.08         | 0.33                 |
| $\tau/\mu\text{s}^f$                             | 3.7          | 9.4 (4.1)            |
| $E_p^{\text{red}}/\text{V}^g$                    | -1.78        | -1.98                |
| $E_p^{\text{ox}}/\text{V}^g$                     | 0.64         |                      |
| $T_{\text{d}10}/^\circ\text{C}^h$                | 331          | 326                  |


<sup>a</sup> In THF. The values in the parentheses are molar absorption coefficients.

<sup>b</sup> In a  $\text{CH}_2\text{Cl}_2$ –THF (3:2) matrix at 77 K. <sup>c</sup> In a  $\text{CH}_2\text{Cl}_2$ –THF (3:2) solution at 298 K. <sup>d</sup> For a microcrystalline sample at 298 K. <sup>e</sup> Quantum yield in a  $\text{CH}_2\text{Cl}_2$ –THF (3:2) matrix at 77 K. *fac*-Tris(2-phenylpyridine)iridium ( $\phi_f = 0.4 \pm 0.1$ ) was used as a reference.<sup>13</sup> <sup>f</sup> Emission decay lifetime at 77 K and that at 298 K in parentheses. <sup>g</sup> Electrochemical oxidation and reduction peak current potentials vs  $\text{Cp}_2\text{Fe}^+/\text{Cp}_2\text{Fe}$ . Measured in a THF solution of  $[(n\text{-Bu})_4\text{N}][\text{BF}_4]$  (0.10 M). <sup>h</sup> Temperature for 10% weight loss under  $\text{N}_2$ .

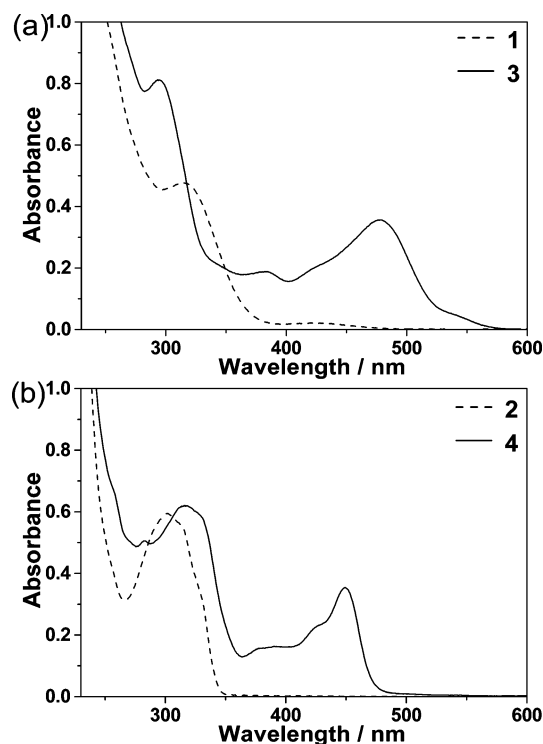**Figure 2.** UV-vis spectra of the ligands and the complexes in THF at room temperature: (a) 1 and 3; (b) 2 and 4.

electron-donating Pt. The oxidation of 3 with  $E_p^{\text{ox}}$  of 0.64 V is considered to take place mainly at Pt, because 1 is oxidized at a considerably higher positive potential ( $E_p^{\text{ox}} = 1.01$  V). 4 exhibits a reduction peak at -1.98 V, and the reduction potential is also at a higher potential than that of 2 ( $E_p^{\text{red}} = -2.49$  V). However, oxidation of 2 and 4 was not observed up to 1.2 V.

**Optical Data.** Figure 2 shows absorption spectra of 1–4. The strong absorption bands around 300 nm are attributed to a  $\pi$ – $\pi^*$  transition in the ligands. 1 exhibits a tail absorption in the range 380–500 nm, which is assigned to an  $n$ – $\pi^*$  transition in the thioamide group.<sup>10,11</sup> Absorption spectra of 3 and 4 show

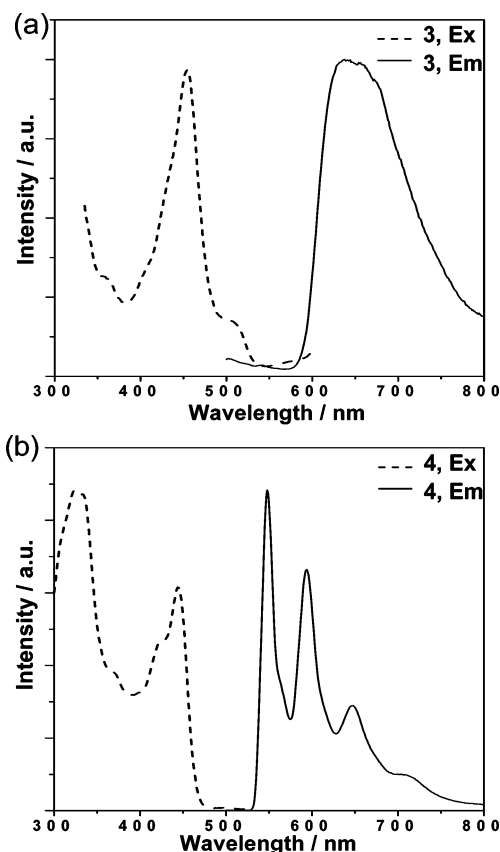**Figure 3.** Excitation and emission spectra of (a) 3 and (b) 4 in a frozen matrix of  $\text{CH}_2\text{Cl}_2$ –THF (3:2) at 77 K.

overlapped absorption bands in the region 400–500 nm, and the shape of the spectra in the region is similar to that of reported cycloplatinated complexes.<sup>1j,s,11</sup> Absorption bands of similar Pt complexes in this region have been assigned to metal-to-ligand charge-transfer (MLCT) transitions.<sup>1q,t</sup> The position of the UV-vis peak of 3 roughly agrees with the difference between the electrochemical oxidation and reduction potentials of 3 ( $0.64 - (-1.98) = 2.62$  V or  $21\,000\text{ cm}^{-1}$ ) and supports the assignment of the UV-vis band to the MLCT band. The UV-vis peak of 3 at about 470 nm exhibits solvatochromism, as shown in Table S1; such solvatochromism is often observed for charge-transfer bands and gives additional support for the assignment to the MLCT band.<sup>12</sup>

3 and 4 were photoluminescent in a glassy frozen state and in the solid; 4 was light emissive even in solutions at room temperature. The photoluminescence data of 3 and 4 are included in Table 2, and Figure 3 shows photoluminescence spectra of 3 and 4. As seen from Figure 3a, 3 shows a broad emission band at about 630 nm when excited with 455 nm light in the glassy frozen state at 77 K. The emission peak is located at a longer wavelength than the onset position of the UV-vis absorption band at about 580 nm, and the emission gives a decay lifetime ( $\tau$ ) of 3.7  $\mu\text{s}$  in the glassy state. These data are indicative of phosphorescent emission. The emission spectrum and lifetime  $\tau$  of 3 are similar to those of reported tertiary thioamide-based pincer Pt(II) complexes,<sup>1q</sup> and the reported emission of the Pt(II) complexes has been assigned to the emission occurring from a <sup>3</sup>MLCT excited state. A microcrystalline sample of 3 exhibited

(10) (a) Petiau, M.; Fabion, J. *THEOCHEM* **2001**, 538, 253. (b) Olszewska, T.; Gdaniec, M.; Poloński, T. *J. Org. Chem.* **2004**, 69, 1248.

(11) Dimitra, K.-D.; Paras, N. Y.; Mavroudis, A. D.; Mauro, C. *J. Inorg. Biochem.* **2000**, 78, 347.

(12) (a) Chen, P.; Meyer, T. J. *Chem. Rev.* **1998**, 98, 1439. (b) Hissler, M.; Connick, W. B.; Geiger, D. K.; McGarrah, J. E.; Lipa, D.; Lachicotte, R. J.; Eisenberg, R. *Inorg. Chem.* **2000**, 39, 447. (c) Pomestchenko, I. E.; Luman, C. R.; Hissler, M.; Ziesler, R.; Castellano, F. N. *Inorg. Chem.* **2003**, 42, 1394.

a weak emission at about 740 nm at room temperature, which was significantly red-shifted from that observed in the glassy frozen state, suggesting stabilization of the excited state by formation of excimer-like adduct(s) in the solid.<sup>14</sup> The layer-to-layer packed structure of **3** seems to be suited for the formation of such an adduct in the solid.

As shown in Figure 3b, **4** in the glassy frozen state exhibits a vibronic-structured emission band in the range 530–750 nm, with a spacing of about  $1400 \pm 60 \text{ cm}^{-1}$ , which corresponds to skeletal vibrational frequencies of the benzothiazole ligand.<sup>1a,i,j</sup> Essentially the same emission spectrum was obtained at room temperature, as depicted in Figure S5. The emission peak of **4** also deviates from the onset position of the UV–vis absorption band. **4** gave long lifetimes of 9.4 and 4.1  $\mu\text{s}$  in the glassy frozen state and in a 3:2 mixture of  $\text{CH}_2\text{Cl}_2$  and THF at room temperature, respectively. The large Stokes shift and the relatively long lifetime suggest that the emission of **4** is also a phosphorescent emission. With reference to previous spectroscopic studies on related pincer Pt(II) complexes such as [5-methyl-1,3-di(2-pyridyl)phenyl- $C^2,N,N'$ ]chloroplatinum(II) (**5**),<sup>1j</sup> the emission from **4** would be assigned to a ligand-centered  $^3(\pi^*\pi)$  transition. The excitation and emission peaks of **4** were observed in a lower energy region by about  $1620 \text{ cm}^{-1}$  than those of **5**, suggesting that the expansion of the aromatic system in the ligand resulted in the reduction of the band gap. In the solid state, the emission peak of **4** was red-shifted to about 700 nm, which was also related to the layer-to-layer stacking of the complex in the solid.

## Conclusion and Scope

S-Coordinating and oxidative cyclization ability of **1** provided two phosphorescent pincer Pt(II) complexes, **3** and **4**, with different  $\kappa^3\text{S,C,S}$  and  $\kappa^3\text{N,C,N}$  coordination systems. The electrochemical, UV–vis, and photoluminescence data support a notion that the emission from **3** originates from the  $^3\text{MLCT}$  excited state. On the other hand, the emission from **4** is considered to originate from  $^3(\pi^*\pi)$  emission. By modifying the structure of the starting material **1**, various new Pt complexes of the types **3** and **4** are considered to be obtained, and the chemistry of the luminescent pincer complexes is expected to be expanded.

## Experimental Section

### Synthesis of 5-Methyl-1,3-bis(anilinothiocarbonyl)benzene (**1**).

To magnesium powder (255 mg, 10.5 mmol) was added dropwise a THF (5 mL) solution of 3,5-dibromotoluene (1.25 g, 5 mmol). The reaction mixture was refluxed under  $\text{N}_2$  for 12 h. The resulting mixture was allowed to cool at  $0^\circ\text{C}$ , and a THF (5 mL) solution of phenylisothiocyanate (1.35 g, 10 mmol) was added. The reaction

mixture was stirred for 24 h at room temperature. After water was added, the resulting yellow precipitate was collected by filtration. The precipitate was washed with chloroform and ether (543 mg, 30% yield).

FAB-mass:  $m/z$  363  $[\text{M} + \text{H}]^+$ .  $^1\text{H}$  NMR (400 MHz in  $\text{DMSO}-d_6$ ):  $\delta$  11.83 (s, 2H), 8.03 (s, 1H), 7.81–7.80 (m, 6H), 7.44 (t,  $J = 7.2 \text{ Hz}$ , 4H), 7.28 (t,  $J = 7.2 \text{ Hz}$ , 2H), 2.46 (s, 3H).  $^{13}\text{C}$  NMR (100 MHz in  $\text{DMSO}-d_6$ ):  $\delta$  196.7, 142.2, 140.0, 137.3, 130.3, 128.5, 126.4, 124.2, 123.5, 21.0. Anal. Calcd for  $\text{C}_{21}\text{H}_{18}\text{N}_2\text{S}_2$ : C, 69.58; H, 5.00; N, 7.73; S, 17.69. Found: C, 69.55; H, 4.85; N, 7.57; S, 17.42.

### Synthesis of 5-Methyl-1,3-bis(2-benzothiazolyl)benzene (**2**).

To a suspension of **1** (181 mg, 0.5 mmol) in ethanol (1 mL) was added a 30% solution of aqueous NaOH (1 mL). The solution was added dropwise to freshly prepared aqueous potassium ferricyanide (1.317 g, 4.0 mmol) at  $80^\circ\text{C}$ , and the reaction mixture was stirred at  $80^\circ\text{C}$  for 30 min. After cooling to room temperature, the precipitate was washed thoroughly with water to give a pale yellow powder of **2** (116 mg, 65% yield).

FAB-mass:  $m/z$  359  $[\text{M} + \text{H}]^+$ .  $^1\text{H}$  NMR (400 MHz in  $\text{CDCl}_3$ ):  $\delta$  8.55 (s, 1H), 8.11 (d,  $J = 7.6 \text{ Hz}$ , 2H), 8.07 (s, 2H), 7.94 (d,  $J = 7.2 \text{ Hz}$ , 2H), 7.52 (s, 2H), 7.42 (t,  $J = 7.6 \text{ Hz}$ , 2H), 2.56 (s, 3H).  $^{13}\text{C}$  NMR (100 MHz in  $\text{CDCl}_3$ ):  $\delta$  167.1, 154.0, 139.8, 135.1, 134.4, 130.3, 126.4, 125.3, 123.3, 121.6, 21.6. Anal. Calcd for  $\text{C}_{21}\text{H}_{14}\text{N}_2\text{S}_2$ : C, 70.36; H, 3.98; N, 7.81; S, 17.89. Found: C, 70.49; H, 3.94; N, 7.46; S, 17.39.

**Synthesis of [5-Methyl-1,3-bis(anilinothiocarbonyl)phenyl- $C^2,S,S'$ ]chloroplatinum(II) (**3**).** A mixture of **1** (36 mg, 0.1 mmol) and  $\text{K}_2\text{PtCl}_4$  (41 mg, 0.1 mmol) in acetic acid (3 mL) was refluxed for 72 h under  $\text{N}_2$ . The resulting orange precipitate was filtered and washed with methanol and water to give a bright reddish powder of **3** (38 mg, 63% yield).

FAB-mass:  $m/z$  556  $[\text{M} - \text{Cl}]^+$ .  $^1\text{H}$  NMR (400 MHz in  $\text{DMSO}-d_6$ ):  $\delta$  12.09 (s, 2H), 8.04 (s, 2H), 7.46–7.63 (m, 10H), 2.34 (s, 3H).  $^{13}\text{C}$  NMR (100 MHz in  $\text{DMSO}-d_6$ ):  $\delta$  202.2, 161.2, 153.9, 143.2, 137.4, 129.2, 129.1, 128.2, 125.6, 20.5. Anal. Calcd for  $\text{C}_{21}\text{H}_{17}\text{ClN}_2\text{PtS}_2$ : C, 42.60; H, 2.89; N, 4.73; Cl, 5.99; S, 10.83. Found: C, 42.03; H, 2.89; N, 4.40; Cl, 5.96; S, 11.17.

**Synthesis of [5-Methyl-1,3-bis(2-benzothiazolyl)phenyl- $C^2,N,N'$ ]chloroplatinum(II) (**4**).** Preparation of **4** was carried out in analogy with that of **3** using **2** to afford a yellow powder of **4** (51% yield).

FAB-mass:  $m/z$  587  $[\text{M} + \text{H}]^+$ , 552  $[\text{M} - \text{Cl}]^+$ .  $^1\text{H}$  NMR (400 MHz in  $\text{CDCl}_3$ ):  $\delta$  9.88 (d,  $J = 8.8 \text{ Hz}$ , 2H), 7.83 (d,  $J = 8.0 \text{ Hz}$ , 2H), 7.66 (t,  $J = 8.0 \text{ Hz}$ , 2H), 7.47 (t,  $J = 8.8 \text{ Hz}$ , 2H), 7.39 (s, 2H), 2.36 (s, 3H). Anal. Calcd for  $\text{C}_{21}\text{H}_{13}\text{ClN}_2\text{PtS}_2$ : C, 42.90; H, 2.23; N, 4.76; Cl, 6.03; S, 10.91. Found: C, 42.91; H, 2.51; N, 4.42; Cl, 6.23; S, 10.23.

**Acknowledgment.** The authors gratefully thank Dr. T. Koizumi of our laboratory for his experimental support. This work has been partly supported by a Grant-in-Aid from the Ministry of Education, Science, Sports, and Culture of Japan.

**Supporting Information Available:** General procedures, X-ray crystallographic data,  $^1\text{H}$  NMR spectra, and UV–vis and photoluminescence data. This material is available free of charge via the Internet at <http://pubs.acs.org>.

OM060016J

(13) King, K. A.; Spellane, P. J.; Watts, R. J. *J. Am. Chem. Soc.* **1985**, *107*, 1431.

(14) Delahaye, S.; Loosli, C.; Liu, S.-X.; Decurtins, S.; Labat, G.; Neels, A.; Loosli, A.; Ward, T. R.; Hauser, A. *Adv. Funct. Mater.* **2006**, *16*, 286, and references therein.