


RSC Advances



This article can be cited before page numbers have been issued, to do this please use: B. Maleki, N. Nasiri, R. Tayebie, A. Khojastehnezhad and H. A. Akhlaghi, *RSC Adv.*, 2016, DOI: 10.1039/C6RA15800E.



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Green Synthesis of Tetrahydrobenzo[*b*]pyrans, Pyrano [2, 3-*c*]pyrazoles and Spiro [indoline-3,4'-pyrano[2,3-*c*]pyrazoles Catalyzed by Nano-structured diphosphate in Water

Behrooz Maleki^{*1}, Negar Nasiri¹, Reza Tayebbe¹ Amir Khojastehnezhad^{*2} and Hossien Ali Akhlaghi¹

¹Department of Chemistry, Hakim Sabzevari University, Sabzevar, 96179-76487, Iran

E-mail: malekibehrooz@gmail.com, Fax: +9844010300; Tel: +985144013324

²Young Researchers and Elite Club, Mashhad Branch, Islamic Azad University, Mashhad, Iran

E-mail: akhojastehnezhad@yahoo.com

Abstract

A green and recoverable nano-structured diphosphate ($\text{Na}_2\text{CaP}_2\text{O}_7$) was synthesized and fully characterized using FT-IR spectra, X-ray diffraction patterns (XRD), scanning electron microscopy (SEM), and energy-dispersive X-ray spectroscopy (EDX) analysis. The nanostructured catalyst has been successfully used as reusable nanostructured catalyst for green, simple and efficient synthesis of tetrahydrobenzo[*b*]pyrans, pyrano[2,3-*c*]pyrazoles and spiro [indoline-3,4'-pyrano[2,3-*c*]pyrazoles in aqueous media. The catalyst shows environmentally benign character, which can be easily prepared, stored, and recovered several times without obvious significant loss of catalytic activity.

Keywords: one-pot multi-component reactions, tetrahydrobenzo[*b*]pyrans and pyrano[2,3-*c*]pyrazoles, nano-structured diphosphate ($\text{Na}_2\text{CaP}_2\text{O}_7$), green chemistry.

Introduction

One important symbol of green chemistry is reducing the use of organic solvents because of the economical and environmental concerns associated with them. Water plays an essential role in life processes and also a medium for the organic synthesis.^{1,2} Water is clean, non-toxic, and hazard-free in handling, non-inflammable, cheap and a readily available solvent. Furthermore, because of its highly polarity, high surface tension, high specific heat capacity and network of hydrogen bonds, water plays a significant role in many reactions.³ In 1980, Breslow discovered that Diels-Alder reactions could be performed in water with a huge acceleration.^{4,5} This discovery led to a considerable interest of synthetic organic chemists in the study of using water

as a reaction solvent.^{6,7} To date, a great number of organic reactions have been carried out in water successfully.⁸

The pyran ring system is present in numerous biologically active natural products as well as many synthetic compounds.⁹ Tetrahydrobenzo[*b*]pyrans and pyrano[2,3-*c*]pyrazoles have a broad spectrum of biological and pharmacological activity, such as anticancer, anti-coagulant, antimicrobial, anti-inflammatory, anti-anaphylactic, and molluscicidal activity.¹⁰⁻¹³

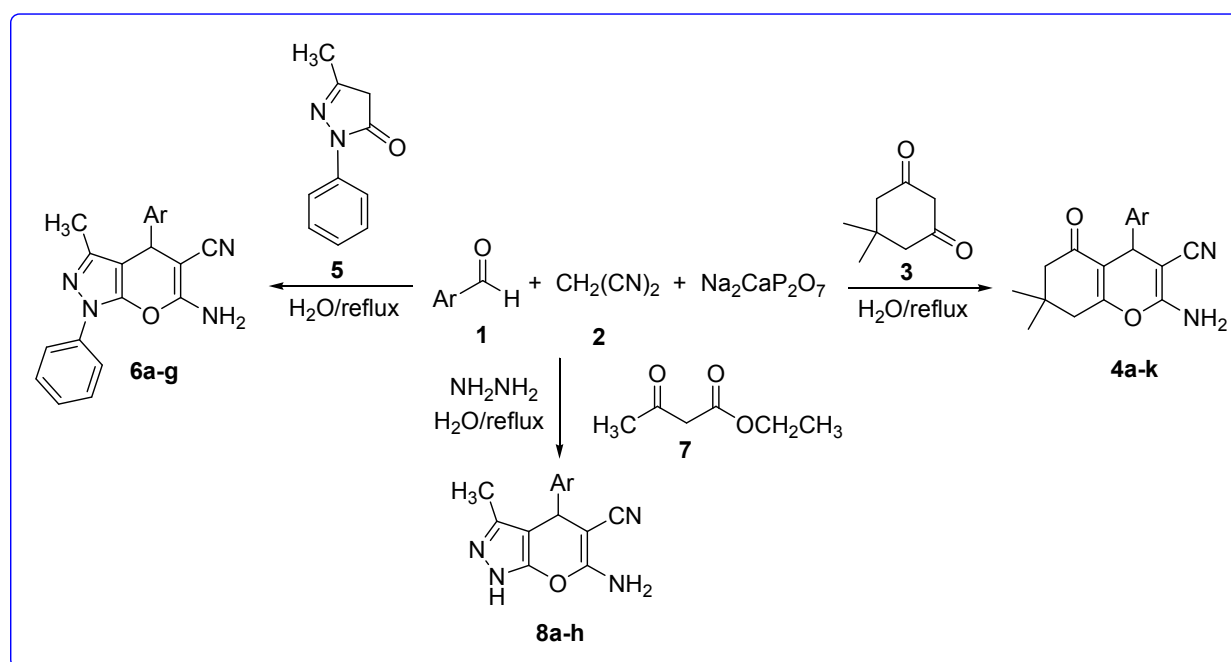
Conventionally, the synthesis of tetrahydrobenzo[*b*]pyrans has been performed through a one-pot reaction of three components in the presence of various catalysts such as the Fe₃O₄@SiO₂-imid-PMA nanoparticle,¹⁴ choline hydroxide based ionic liquid [Ch][OH],¹⁵ red sea sand under microwave or ultrasonic irradiation,¹⁶ hexadecyltrimethyl ammonium bromide (HTMAB),¹⁷ sodium bromide (NaBr),¹⁸ ionic liquids,¹⁹⁻²² tetra-methyl ammonium hydroxide,²³ molecular iodine (I₂),²⁴ *N*-methylimidazole,²⁵ sodium selenite,²⁶ tetrabutylammonium bromide (TBAB),²⁷ amine or amino acid,²⁸ potassium phosphate (K₃PO₄),²⁹ magnetic core-shell titanium dioxide nanoparticles (Fe₃O₄@SiO₂@TiO₂),³⁰ Nano α-Al₂O₃ supported ammonium dihydrogen phosphate (NH₄H₂PO₄/Al₂O₃),³¹ phenylboronic acid [PhB(OH)₂],³² cerium(III) chloride (CeCl₃·7H₂O),^{33,34} nanosized TiO₂,³⁵ silica coated magnetite-polyoxometalate nanoparticles (Fe₃O₄@SiO₂@NH-NH₂-H₃PW₁₂O₄₀),³⁶ meglumine,³⁷ magnetic La_{0.7}Sr_{0.3}MnO₃ nanoparticles,³⁸ RuBr₂(PPh₃)₄,³⁹ lactose,⁴⁰ and silica coated magnetic NiFe₂O₄ nanoparticles supported H₃PW₁₂O₄₀ (NFS-PWA).⁴¹

However, a number of these methods suffer from certain drawbacks such as poor yields, difficult workups, long reaction times, high temperatures, the utilization of alternative energy source (microwave or ultrasonic), and the use of volatile or hazardous organic solvents. Therefore, it seemed desirable to develop a more efficient and a general method for the synthesis of tetrahydrobenzo[*b*]pyrans and pyrano[2,3-*c*]pyrazoles.

On the basis of the information obtained from the nano-structured diphosphate Na₂CaP₂O₇ (DIPH), we predicted that the DIPH can be used as an efficient catalyst for the promotion of the reactions which requires the use of a catalyst to speed-up. So, we were interested to investigate the applicability of this reagent in the promotion of the synthesis tetrahydrobenzo[*b*]pyrans and pyrano [2,3-*c*]pyrazoles.

For the present study, the synthesis of the DIPH has been carried out from Na_2CO_3 , CaCO_3 and $\text{NH}_4\text{H}_2\text{PO}_4$ in 1:1:2 proportion, respectively, by following the literature procedure.⁴² In recent years, the DIPH has been used as catalyst in organic synthesis^{43,44} as it has been shown to be non-toxic, green and stable, inexpensive, safe, non-volatile, non-corrosive and re-usable.

In our progressive program to develop efficient and environmentally benign protocols for the synthesis of various products,⁴⁵⁻⁵⁹ we tried to report a highly efficient method for the synthesis of tetrahydrobenzo[*b*]pyrans and pyrano [2,3-*c*]pyrazoles catalyzed by a DIPH in water (Scheme 1).



Scheme. 1 Synthesis of tetrahydrobenzo[*b*]pyrans and pyrano [2,3-*c*]pyrazoles catalyzed by a DIPH in water.

Nanostructured diphosphate ($\text{Na}_2\text{CaP}_2\text{O}_7$) was characterized by several methods including FT-IR, SEM, XRD and EDX. The existence of P_2O_7 units was confirmed by the symmetrical vibration bands of P–O–P at 720 cm^{-1} as well as the anti-symmetric vibration bands at 890 cm^{-1} . The related vibrations of the PO_4 groups were shared between two fields: a field of symmetrical vibrations at 990 cm^{-1} and 1030 cm^{-1} and another that ranged from 1130 to 1280 cm^{-1} (Figure S1).⁴²⁻⁴⁴ Scanning Electronic Microscopy (SEM) was used to study the morphology of the

surface of $\text{Na}_2\text{CaP}_2\text{O}_7$ (Figure S2). Also, to confirm the formation of $\text{Na}_2\text{CaP}_2\text{O}_7$ nanostructure, the XRD patterns of sample was studied (Figure S3). The XRD pattern of $\text{Na}_2\text{CaP}_2\text{O}_7$ nanostructure indicates that these nanostructures have synthesized well and all of the major peaks matching with the previous literatures.⁴²⁻⁴⁴ Moreover, the elemental analysis obtained from the EDX spectra of catalyst (Figure S4), shows the existence of all of the elements in the $\text{Na}_2\text{CaP}_2\text{O}_7$ nanostructures and these results are in agreement with other results.

At first, we selected the benzaldehyde (1 mmol), dimedone (1 mmol), and malononitrile (2 mmol) as model substrates to establish optimum reaction conditions in the presence of DIPH (Table 1). When the reaction was performed under solvent-free conditions, a low yield of target product was obtained (Entry 1). To find the best solvent for this transformation, the present three-component reaction was screened in methanol, ethanol, and water (Table 2, Entries 2-4). Among these solvents, water was found to be the best one and afforded the highest yield (Entry 5). Then, the amount of the catalyst was evaluated in the model reaction in refluxing water (Entries 6-7). The results showed that 20 mol% of DIPH was the best choice for completing the reaction (Entry 5) and the use of excessive catalyst had no impact either on the rate of the reaction or on the product yield (Entry 7). When the reaction was attempted without a catalyst, it was found that no product was obtained even after 1 h (Entry 8).

Table 1 Optimization of reaction conditions^a

Entry	Catalyst (mol %)	Conditions	Time (min)	Yield (%) ^b
1	20	Solvent-free/100 °C	15	72
2	20	MOH/reflux	10	80
3	20	EtOH/reflux	10	82
4	20	EtOH:Water/reflux	10	88
5	20	Water/reflux	10	94
6	10	Water/reflux	10	84
7	30	Water/reflux	10	94
8	None	Water/reflux	60	None

^a Benzaldehyde (1 mmol), dimedone (1 mmol), malonitrile (1 mmol) in refluxing water.

^b Isolated yields

Under These optimal conditions (Table 1, Entry 4), the scope and specificity of this protocol was further investigated. At first, a broad range of structurally diverse aldehydes were treated

with malononitrile and dimedone (see Table 2) in order to synthesis of tetrahydrobenzo[*b*]pyrans derivatives **4a-k**. As shown in Table 2, all reactions proceeded efficiently and the desired products were obtained from high to excellent yields in relatively short times without any formation of by-products. The reaction of aromatic aldehyde carrying electron donating or electron-withdrawing groups was also successfully carried out with this method (Table 2, Entries 1-11). The reactions showed corresponding compounds in excellent yields.

Encouraged by these results, we extended this study for three component synthesis of pyrano[2,3-*c*]pyrazoles (**6a-g**) in the presence of a catalytic amount of DIPH. Considering the reaction time and the yield, the DIPH (20 mol%) was selected as the optimum catalyst used in the refluxing water. Using the optimized reaction conditions, a range of substituted pyrano[2,3-*c*]pyrazoles were synthesized (Table 2, Entries 12-18). Moreover, the one-pot, four-component synthesis of pyrano[2,3-*c*]pyrazoles could be successfully used for the synthesis of corresponding compounds (**8a-h**). This method was found to be effective for aromatic aldehydes bearing either electron donating or electron-withdrawing substituents (Entries 19-21, 24-26) as well as for the heterocyclic aldehyde (Entries 22, 23).

Table 2 Green synthesis of tetrahydrobenzo[*b*]pyran and pyrano[2,3-*c*]pyrazoles derivatives catalyzed by DIPH in refluxing water


Entry	Ar	Product	Time (min)	Yield (%) ^a	Mp (°C)	Lit. Mp (°C) [ref]
1	Ph	4a	10	94	231-233	231-233 [18]
2	4-ClC ₆ H ₄	4b	10	90	207-209	203-206 [21]
3	4-CH ₃ C ₆ H ₄	4c	10	89	212-214	210-213 [23]
4	3-ClC ₆ H ₄	4d	10	92	230-232	230-232 [23]
5	3-MeOC ₆ H ₄	4e	10	90	192-194	188-190 [20]
6	2-CH ₃ C ₆ H ₄	4f	15	86	212-214	211-212 [41]
7	4-CNC ₆ H ₄	4g	10	95	226-228	225-228 [23]
8	4-NO ₂ C ₆ H ₄	4h	10	95	177-179	177-179 [23]
9	3-NO ₂ C ₆ H ₄	4i	10	94	210-212	211-214 [18]
10	4-BrC ₆ H ₄	4j	10	91	202-204	203-205 [26]
11	2,4-ClC ₆ H ₄	4k	10	90	183-185	180-182 [27]
12	Ph	6a	10	93	164-166	169-171 [17]
13	4-ClC ₆ H ₄	6b	15	86	180-182	175-177 [17]
14	4-BrC ₆ H ₄	6c	15	90	187-188	185-186 [31]

15	4-CH ₃ C ₆ H ₄	6d	20	80	174-177	176-178 [31]
16	4-CH ₃ OC ₆ H ₄	6e	20	82	171-173	170-172 [31]
17	3-NO ₂ C ₆ H ₄	6f	15	90	189-191	190-192 [31]
18	4-NO ₂ C ₆ H ₄	6g	20	87	195-197	197-199 [31]
19	Ph	8a	10	92	244-245	244-245 [19]
20	4-CH ₃ OC ₆ H ₄	8b	15	86	213-215	211-213 [19]
21	4-BrC ₆ H ₄	8c	15	85	246-248	248-250 [19]
22	2-ThienylC ₆ H ₄	8d	10	92	225-226	224-226 [37]
23	4-PyridinC ₆ H ₄	8e	20	90	215-217	216-217 [37]
24	3-BrC ₆ H ₄	8f	15	90	224-226	222-223 [19]
25	4-NO ₂ C ₆ H ₄	8g	10	90	250-252	248-249 [37]
26	3-NO ₂ C ₆ H ₄	8h	15	89	228-230	232-233 [22]

^a Isolated yields

Spiro heterocycles, especially spirocyclic oxindole nucleus, are a substantial category of natural alkaloids that possess various biological and pharmacological activities, such as spirotryptostatin A, B, which are isolated from the fermentation broth of *Aspergillus fumigates*, inhibits of cell cycle at G2/M phase and *Koumine*,⁶⁰ which is one of the alkaloids isolated from the *Gelsemium sempervirens* plant that has antitumor and analgesic activities.⁶¹ Chitosenine as a *Gardneria multiflora* oxindole alkaloid has ganglioblocking action.⁶² These interesting properties promoted us to widen the applicability of this procedure with isatins.⁶³





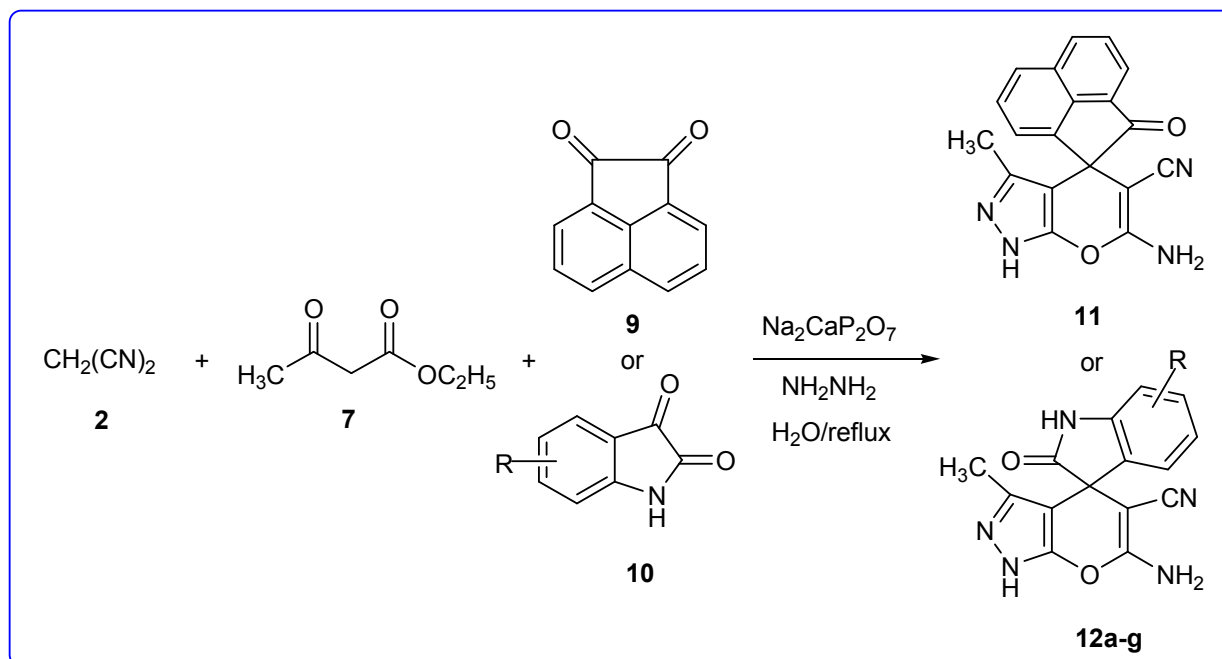
To explore the scope of this reaction to form a spiroheterocyclic compound, we investigated the use of acenaphthylene-1,2-dione (**9**) or isatin (**10**) as a substrate to react with the hydrazine hydrate, malononitrile, ethyl acetoacetate under the optimized conditions. As expected the reaction proceeded well to afford spiro[acenaphthylene-1,4'-pyrano[2,3-*c*]pyrazole (**11**) in 60 min with 64% yield and spiro [indoline-3,4'-pyrano[2,3-*c*]pyrazole] derivatives (**12a-g**) (Scheme 2, Table 3). These successful results clearly indicate that the present catalytic approach is extendable to a wide variety of substrates.



Scheme. 2 Synthesis of spiro-pyrano[2,3-*c*]pyrazole derivative

Table 3. Green synthesis of spiro [indoline-3,4'-pyrano[2,3-*c*]pyrazole] derivatives (**12a-h**) using DIPH in refluxing water

Entry	Products (12a-g)	Time (min)	Yield ^a (%)	Mp (°C)	
				Found	Reported [ref]
12a		50	78	284-286	285-286 [37]
12b		70	74	278-280	279-281 [37]

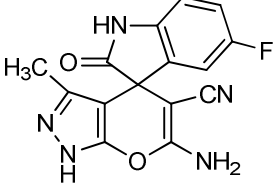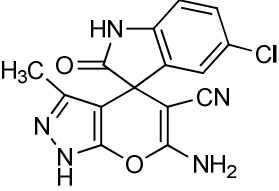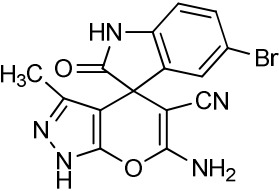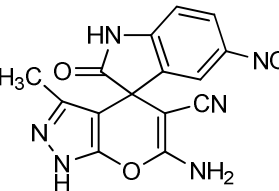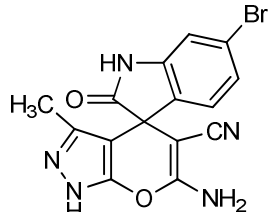12c		40	85	274-276	274-275 [37]
12d		40	87	296-298	297-298 [37]
12e		40	90	280-282	282-283 [37]
12f		35	91	272-274	270-271 [37]
12g		40	82	>300	>300 [63]

^a Isolated yields

The reusability of the catalyst was also investigated. For this purpose, the same model reaction was again studied under optimized conditions. After the completion of the reaction, the acetone was added to the reaction mixture to dissolve the product. Then, the catalyst was removed by filtration. It was re-used directly in the model reaction to give **4a** in yields of 94%, 92%, 91%, 91%, 90% and 89% for six consecutive runs at 10 min.

In order to illustrate the efficiency of our procedure, results for the preparation of tetrahydrobenzo[*b*]pyrans and pyrano[2, 3-*c*]pyrazoles previously reported are compared with

our data (Table 4). The present method using DIPH as catalyst offers several advantages such as excellent yields, a simple procedure, short reaction times, facile work-up and greener conditions. The green aspect of the DIPH catalyst has been discussed in terms of being non-corrosive, presenting fewer disposals problem, facile isolation of the products, and recyclability.

Table 4 Comparison of the efficiencies of various catalysts used in the synthesis of tetrahydrobenzo[*b*]pyrans and pyrano[2, 3-*c*]pyrazoles

Product	Catalyst	Reaction conditions	Time (min)	Yield (%) ^a	[ref]
4a	Fe ₃ O ₄ @SiO ₂ -imid-PMA	H ₂ O/Reflux	20	94	[14]
	Red sea sand	EtOH/Reflux	360	84	[16]
	[Ch][OH]	H ₂ O/80 °C	60	92	[15]
	NaBr/MWI	solvent-free, 70 °C	10	91	[18]
	DIPH	H ₂ O/Reflux	10	94	This study
8a	[bmim]OH	solvent-free/60 °C	10	88	[19]
	L-proline/[Bmim]BF ₄	solvent-free/50 °C	10	90	[22]
	NH ₄ H ₂ PO ₄ /Al ₂ O ₃	EtOH/Reflux	15	80	[31]
	NFS-PWA	EtOH/Reflux	45	90	[41]
	DIPH	H ₂ O/Reflux	10	92	This study

^a Isolated yields.

Conclusion

In conclusion, we have developed a green and simple protocol for the synthesis of tetrahydrobenzo[*b*]pyran and pyrano[2,3-*c*]pyrazole derivatives *via* a three or four component condensation reaction in the presence of DIPH in water. This method was found not only to be applied to aromatic and heteroaromatic aldehydes, but also to be useful for the synthesis of ketone-derived dihydroprano[2,3-*c*]pyrazole, spiro[indoline-3,4'-pyrano[2,3-*c*]pyrazole] and spiro[acenaphthylene-1,4'-pyrano[2,3-*c*]pyrazole]. This procedure provides several advantages such as high yields, wide scope of substrates, short reaction times, non-volatile, non-corrosive, absence of side-reactions, simple work-up procedure, non-toxic, evasion of hazardous catalysts or solvents, and the minimization of cost and waste generation owing to the recycling of the catalyst.

Experimental Section

All reagents were obtained from commercial sources and were used without purification. IR spectra were recorded as KBr pellets on a Shimadzu 435-U-04 spectrophotometer. ^1H and ^{13}C NMR spectra were determined on a Bruker DRX-300 Avance spectrometer in DMSO-d_6 or CDCl_3 , and shifts are given in δ downfield from tetramethylsilane (TMS) as an internal standard. Melting points were determined using an Electrothermal 9200 apparatus and are uncorrected.

General Procedure for the Synthesis of Tetrahydrobenzo[*b*]pyrans (4a-k)

The catalyst, DIPH (20 mol %), was added to a mixture of the aldehydes (1 mmol), malononitrile (1.2 mmol), and dimedone (1 mmol), and 1 ml of water in a 5 ml flask fitted with a reflux condenser. The resulting mixture was heated to reflux (an oil bath) for the appropriate time (see Table 2) with stirring (spin bar). After the completion of the reaction as determined by TLC (hexane-ethyl acetate, 4:1), the acetone (2 ml) was added and the mixture stirred for 2 min. The catalyst was removed by filtration and washed with acetone and calcined at 500 °C for 1 h before re-use. Then the resulting crude reaction mixture was poured onto crushed ice and the precipitated solid was collected and recrystallized from ethanol (96%, 5 ml) to afford the pure tetrahydrobenzo[*b*]pyrans derivatives **4a-k**. The products were identified by their melting points, ^1H -NMR, and IR spectroscopies.

General Procedure for the Synthesis of Pyrano[2,3-*c*]pyrazoles (6a-g)

The catalyst, DIPH (20 mol %), was added to a mixture of the aldehydes (1 mmol), malononitrile (1.2 mmol), and 3-methyl-1-phenyl-2-pyrazoline-5-one (1 mmol), and 1 ml of water in a 5 ml flask fitted with a reflux condenser. The resulting mixture was heated to reflux (an oil bath) for the appropriate time (see Table 2) with stirring (spin bar). After the completion of the reaction as determined by TLC (hexane-ethyl acetate, 4:1), the acetone (2 ml) was added and the mixture stirred for 2 min. The products and catalyst were isolated as described above and recrystallized from 96% ethanol (20 ml) to afford pyrano[2,3-*c*]pyrazoles **6a-g**.

General Procedure for the Synthesis of Pyrano[2,3-*c*]pyrazoles (8a-h)

The catalyst, DIPH (20 mol %), was added to a mixture of the aldehydes (1 mmol), malononitrile (1.2 mmol), hydrazine hydrate (2 mmol), ethylacetoacetate (1 mmol), and 1 ml of water in a 5 ml flask fitted with a reflux condenser. The resulting mixture was heated to reflux (an oil bath) for

the appropriate time (see Table 2) with stirring (spin bar). After the completion of the reaction as determined by TLC (hexane-ethyl acetate, 4:1), the acetone (2 ml) was added and the mixture stirred for 2 min. The products and catalyst were isolated as described above and recrystallized from 96% ethanol (20 ml) to afford pyrano[2,3-*c*]pyrazoles **8a-h**.

General Procedure for the Synthesis of Spiro [indoline-3,4'-pyrano[2,3-*c*]pyrazoles (**12a-g**)

The catalyst, DIPH (20 mol %), was added to a mixture of the isatins (1 mmol), malononitrile (1.2 mmol), hydrazine hydrate (2 mmol), ethylacetoacetate (1 mmol), and 1 ml of water in a 5 ml flask fitted with a reflux condenser. The resulting mixture was heated to reflux (an oil bath) for the appropriate time (see Table 2) with stirring (spin bar). After the completion of the reaction as determined by TLC (hexane-ethyl acetate, 4:1), the acetone (2 ml) was added and the mixture stirred for 2 min. The products and catalyst were isolated as described above and recrystallized from 96% ethanol (20 ml) to afford pyrano[2,3-*c*]pyrazoles **12a-g**.

Spectroscopic Data of Representative Compounds.

2-Amino-3-cyano-4-phenyl-7,7-dimethyl-5-oxo-4*H*-5,6,7,8-tetrahydrobenzo[*b*]pyran (4a), ¹H NMR (300 MHz, CDCl₃, ppm) δ 1.04 (s, 3H), 1.13 (s, 3H), 2.11-2.21 (m, 2H), 2.42 (s, 2H), 4.67 (s, 1H), 6.52 (brs, 2H, D₂O exchangeable), 7.14-7.42 (m, 5H); ¹³C NMR (75 MHz, CDCl₃, ppm) δ 26.32, 27.65, 31.24, 35.09, 39.08, 49.98, 59.74, 113.09, 118.42, 125.86, 126.63, 127.54, 142.68, 158.54, 162.32, 194.24; IR (KBr disc, cm⁻¹): 3314, 3202, 2214, 1688, 1624, 1507, 1482, 1370.

2-Amino-3-cyano-4-(3-methoxyphenyl)-7,7-dimethyl-5-oxo-4*H*-5,6,7,8-tetrahydrobenzo[*b*]pyran (4e). ¹H NMR (300 MHz, DMSO-*d*₆, ppm) δ 0.92 (s, 3H), 1.01 (s, 3H), 2.05 (d, 2H), 2.66 (d, 2H), 3.45 (s, 3H), 4.17 (s, 1H), 7.06 (brs, 2H, D₂O exchangeable), 7.13-7.26 (m, 3H), 7.34 (s, 1H); ¹³C NMR (75 MHz, DMSO-*d*₆, ppm) δ 27.30, 28.78, 32.33, 35.52, 35.58, 38.43, 50.44, 58.41, 112.74, 120.19, 128.91, 129.63, 131.80, 144.16, 158.98, 163.61, 197.00; IR (KBr disc, cm⁻¹): 3370, 3180, 2185, 1660, 1624, 1509, 1492, 1380.

6-Amino-3-methyl-5-cyano-4-(phenyl)-1-phenyl-1,4-dihydropyrano[2,3-*c*]pyrazole (6a), ¹H NMR (300 MHz, DMSO-*d*₆): δ 1.77 (s, 3H), 5.16 (s, 1H), 7.28-7.48 (m, 10H), 7.78 (brs, 2H, D₂O exchangeable); ¹³C NMR (75 MHz, CDCl₃, ppm) δ 25.02, 40.43, 50.45, 59.13, 113.24,

118.67, 126.45, 126.06, 127.67, 128.03, 128.98, 129.14, 130.14, 140.05, 154.05, 162.34; IR (KBr disc, cm^{-1}): 3425, 3332, 2200, 1620, 1590, 1484, 1386.

6-Amino-3-methyl-5-cyano-4-(4-methylphenyl)-1-phenyl-1,4-dihdropyrano[2,3-*c*]pyrazole (6d). ^1H NMR (300 MHz, DMSO-d_6 , ppm): δ 1.01 (s, 3H), 2.46 (s, 3H), 5.12 (s, 1H), 5.98 (brs, 2H, D_2O exchangeable), 7.11-7.79 (m, 9H); ^{13}C NMR (75 MHz, DMSO-d_6 , ppm) δ 25.18, 26.56, 41.04, 50.25, 60.63, 113.24, 118.04, 125.13, 126.45, 127.52, 128.18, 129.89, 130.68, 131.43, 141.67, 153.69, 160.11; IR (KBr disc, cm^{-1}): 3413, 3321, 2196, 1620, 1589, 1448, 1381.

6-Amino-3-methyl-5-cyano-4-(3-nitrophenyl)-1-phenyl-1,4-dihdropyrano[2,3-*c*]pyrazole (6f). ^1H NMR (300 MHz, DMSO-d_6 , ppm): δ 1.79 (s, 3H), 5.16 (s, 1H), 6.05 (brs, 2H, D_2O exchangeable), 7.19-7.68 (m, 8H), 8.01 (s, 1H); ^{13}C NMR (75 MHz, DMSO-d_6 , ppm) δ 25.67, 41.12, 51.61, 61.05, 113.78, 119.14, 125.79, 126.54, 126.98, 127.32, 128.12, 128.67, 129.34, 130.78, 131.05, 140.67, 154.67, 159.89; IR (KBr disc, cm^{-1}): 3420, 3310, 2198, 1618, 1598, 1568, 1490, 1386.

6-Amino-3-methyl-4-(4-methoxyphenyl)-1,4-dihydro-pyrano[2,3-*c*]pyrazole-5-carbonitrile (8b). ^1H NMR (300 MHz, DMSO-d_6 , ppm): δ 1.79 (s, 3H), 3.45 (s, 3H), 4.56 (s, 1H), 6.88 (brs, 2H, D_2O exchangeable), 7.10 (d, 2H), 7.19 (d, 2H), 12.01 (s, 1H, D_2O exchangeable); ^{13}C NMR (75 MHz, DMSO-d_6 , ppm) δ 10.22, 35.17, 36.01, 57.64, 97.82, 121.31, 126.04, 128.64, 136.19, 136.07, 141.64, 155.22, 161.35; IR (KBr disc, cm^{-1}): 3483, 3254, 2191, 1641, 1608, 1492, 1390.

6-Amino-3-methyl-4-(4-bromophenyl)-1,4-dihydro-pyrano[2,3-*c*]pyrazole-5-carbonitrile (8c). ^1H NMR (300 MHz, DMSO-d_6 , ppm): δ 1.75 (s, 3H), 4.81 (s, 1H), 6.48 (brs, 2H, D_2O exchangeable), 7.09 (d, 2H), 7.32 (d, 2H), 12.12 (s, 1H, D_2O exchangeable); ^{13}C NMR (75 MHz, DMSO-d_6 , ppm) δ 10.12, 33.62, 55.69, 96.23, 120.01, 128.45, 129.79, 132.54, 133.30, 135.21, 140.54, 155.89, 161.98; IR (KBr disc, cm^{-1}): 3444, 3238, 2195, 1637, 1600, 1491, 1394.

6'-Amino-3'-methyl-2-oxo-1'H-spiro[indoline-3,4'-pyrano[2,3-*c*]pyrazole]-5'-carbonitrile (12a). ^1H NMR (300 MHz, DMSO-d_6 , ppm): δ 1.54 (s, 3H), 6.91 (s, 1H), 7.02 (s, 2H), 7.17 (s, 2H, D_2O exchangeable), 7.23 (s, 1H), 10.55 (s, 1H, D_2O exchangeable), 12.25 (s, 1H, D_2O exchangeable); IR (KBr disc, cm^{-1}): 3420, 3390, 3330, 3130, 2680, 2180, 1710, 1640, 1580, 1520, 1420, 1320, 1210, 1160, 1050.

Acknowledgements

The authors thank the Research Council of Hakim Sabzevari University for a partial support of this work.

Supporting Information

Electronic Supplementary Information (ESI) available: [including the Figure S1-S4 for characterization of catalyst].

References

1. C. J. Li, *Chem. Rev.*, 2005, **105**, 3095.
2. W. S. Laitonjam, B. Thingom and S. D. Moirangthem, *Org. Prep. Proced. Int.*, 2013, **45**, 246.
3. A. Chanda and V. V. Fokin, *Chem. Rev.*, 2009, **109**, 725.
4. D. C. Rideout and R. Breslow, *J. Am. Chem. Soc.*, 1980, **102**, 7817.
5. R. Breslow, U. Maitra, and D. Rideout, *Tet. Lett.*, 1983, **24**, 1901.
6. A. Lubineau, *J. Org. Chem.*, 1986, **51**, 2142.
7. A. Lubineau, and E. Meyer, *Tetrahedron.*, 1988, **44**, 6065.
8. B. Maleki, M. Baghayeri, S. M. Vahdat, A. Mohammadzadeh and S. Akhoondi, *RSC Adv.*, 2015, **5**, 46545.
9. S. Hatakeyama, N. Ochi, H. Numata and S. Takano, *J. Chem. Soc., Chem. Commun.*, 1988, 1202.
10. L. L. Andreani and E. Lapi, *Bull. Chim. Farm.*, 1960, **99**, 583.
11. M. E. A. Zaki, M. H. A. Soliman, O. A. Hiekal and A. E. Z. Rashad, *Naturforsch C.*, 2006, **61**, 1.
12. E. S. H. El-Tamany, F. A. El-Shahed and B. H. Mohamed, *J. Serb. Chem. Soc.*, 1999, **64**, 9.
13. F. M. Abdelrazek, P. Metz, O. Kataeva, A. Jaeger and S. F. El-Mahrouky, *Arch. Pharm.*, 2007, **340**, 543.

14. M. Esmaeilpour, J. Javidi, F. Dehghani and F. Nowroozi Dodeji, *RSC Adv.*, 2015, **5**, 26625.
15. H. Hu, F. Qiu, A. Ying, J. Yang and H. Meng, *Int. J. Mol. Sci.*, 2014, **15**, 6897.
16. M. Naglaa, A. El-Rahman and R. M. Borik, *World Appl. Sci. J.*, 2014, **31**, 1.
17. T. S. Jin, A. Q. Wang, Z. L. Cheng, J. S. Zhang and T. S. Li, *Synth. Commun.*, 2005, **35**, 137.
18. I. Devi and P. J. Bhuyan, *Tetrahedron Lett.*, 2004, **45**, 8625.
19. J. M. Khurana and A. Chaudhary, *Green Chem. Lett. Rev.*, 2012, **5**, 633.
20. J. Yang, S. Liu, H. Hu, S. Ren and A. Ying, *Chin. J. Chem. Engin.*, 2015, **23**, 1416.
21. H. R. Shaterian, M. Arman and F. Rigi, *J. Mol. Liq.*, 2011, **158**, 145.
22. J. M. Khurana, B. Nand and S. Kumar, *Synth. Commun.*, 2011, **41**, 405.
23. S. Balalaie, M. Sheikh-Ahmadi and M. Bararjanian, *Catal. Commun.*, 2007, **8**, 1724.
24. R. S. Bhosale, C. V. Magar, K. S. Solanke, S. B. Mane, S. S. Choudhary and R. P. Pawar, *Synth. Commun.*, 2007, **37**, 4353.
25. X. Z. Lian, Y. Huang, Y. Q. Li and W. J. Zheng, *Monatsh. Chem.*, 2008, **139**, 129.
26. R. Hekmatshoar, S. Majedi and K. Bakhtiari, *Catal. Commun.*, 2008, **9**, 307.
27. A. Mobinikhaledi and M. A. Bodaghifard, *Acta Chim. Slov.*, 2010, **57**, 931.
28. L. Q. YU, F. Liu and Q. D. You, *Org. Prep. Proced. Int.*, 2009, **41**, 77.
29. D. M. Pore, K. A. Undale, B. B. Dongare and U. V. Desai, *Catal. Lett.*, 2009, **132**, 104.
30. A. Khazaei, F. Gholami, V. Khakyzadeh and A. R. Moosavi-Zare, J. Afsar, *RSC Adv.*, 2015, **5**, 14305.
31. B. Maleki and S. Sedigh Ashrafi, *RSC Adv.*, 2014, **4**, 42873.
32. S. Nemouchi, R. Boulcina, B. Carboni and A. Debaché, *C. R. Chim.*, 2012, **15**, 394.
33. G. Sabitha, K. Arundhati, K. Sudhakar, B. S. Sastry and J. S. Yadav, *Synth. Commun.*, 2009, **39**, 433.
34. K. Ablajan, Li. Ju. Wang, Z. Maimaiti and Y. T. Lu, *Monatsh Chem.*, 2014, **145**, 491.
35. P. L. Anandgaonker, S. Jadhav, S. T. Gaikwad and A. S. Rajbhoj, *J. Clust. Sci.*, 2014, **25**, 483.
36. F. Shahbazi and K. Amani, *Catal. Commun.*, 2014, **55**, 57.

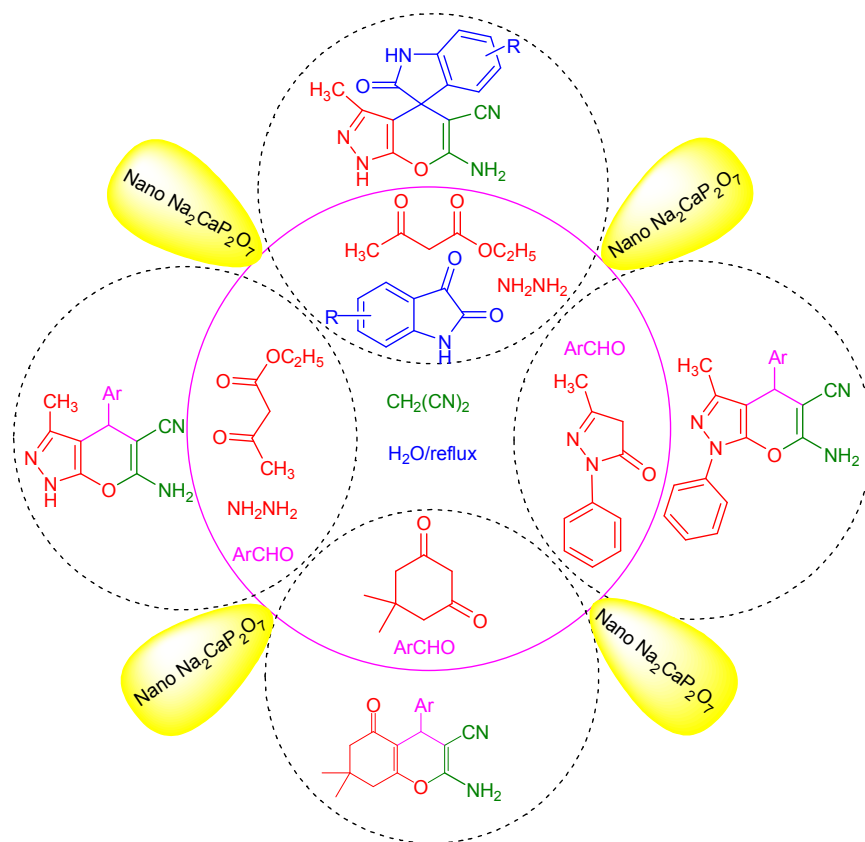
37. R. Y. Guo, Z. M. An, L. P. Mo, S. T. Yang, H. X. Liu, S. X. Wang and Z. H. Zhang, *Tetrahedron.*, 2013, **69**, 9931.
38. A. Azarifar, R. Nejat-Yami, M. Al-Kobaisi and D. Azarifar, *J. Iran. Chem. Soc.*, 2013, **10**, 439.
39. K. Tabatabaeian, H. Heidari, M. Mamaghani and N. O. Mahmoodi, *Appl. Organomet. Chem.*, 2012, **26**, 56.
40. F. Noori Sadeh, M. T. Maghsoodlou, N. Hazeri and M. Kangani, *Res. Chem. Intermed.*, 2015, **41**, 5907.
41. B. Maleki, H. Eshghi, M. Barghamadi, N. Nasiri, A. Khojastehnezhad, S. Sedigh Ashrafi, and O. Pourshiani, *Res. Chem. Intermed.*, 2016, **44**, 3071.
42. A. Elmakssoudi, K. Abdelouahdi, M. Zahouily, J. Clark and A. Solhy, *Catal. Commun.*, 2012, **29**, 53.
43. M. Zahouily, Y. Abrouki and A. Rayadh, *Tetrahedron. Lett.*, 2002, **43**, 7729.
44. A. Solhy, A. Elmakssoudi, R. Tahir, M. Karkouri, M. Larzek, M. Bousmina and M. Zahouily, *Green Chem.*, 2010, **12**, 2261.
45. B. Maleki, S. Hemmati, A. Sedrpoushan, S. Sedigh Ashrafi and H. Veisi, *RSC Adv.*, 2014, **4**, 40505.
46. B. Maleki, S. Babae, and R. Tayeb, *Appl. Organomet. Chem.*, 2015, **29**, 408.
47. B. Maleki, S. Barat Nam Chalaki, S. Sedigh Ashrafi, E. Rezaee Seresht, F. Moeinpour, A. Khojastehnezhad and R. Tayeb, *Appl. Organomet. Chem.*, 2015, **29**, 290.
48. B. Maleki and S. Sheikh, *RSC Adv.*, 2015, **5**, 42997.
49. H. Eshghi, A. Khojastehnezhad, F. Moeinpour, S. Rezaeian, M. Bakavoli, M. Teymouri, A. Rostami and Kamahldin Haghbeen, *Tetrahedron* 2015, **71**, 436.
50. A. Khojastehnezhad, M. Rahimizadeh, H. Eshghi, F. Moeinpour, M. Bakavoli, *Chin. J. Cat.*, 2014, **35**, 376.
51. B. Maleki, E. Akbarzadeh and S. Babae, *Dyes Pigm.*, 2015, **123**, 222.
52. M. Ghiaci, M. Zarghani, F. Moeinpour, A. Khojastehnezhad, *Appl. Organometal. Chem.*, 2014, **28**, 589.

53. A. Khojastehnezhad, M. Rahimizadeh, F. Moeinpour, H. Eshghi, M. Bakavoli, C. R. *Chimie.*, 2014, **17**, 459.
54. B. Maleki, E. Sheikh, E. Rezaei Seresht, H. Eshghi, S. Sedigh Ashrafi, A. Khojastehnezhad and H. Veisi, *Org. Prep. Proced. Int.*, 2016, **48**, 37.
55. B. Maleki and M. Baghayeri, *RSC Adv.*, 2015, **5**, 79746.
56. B. Maleki, *Org. Prep. Proced. Int.*, 2016, **48**, 303.
57. B. Maleki, *Org. Prep. Proced. Int.*, 2016, **48**, 81.
58. R. Tayebbe, K. Savoji, M. K. Razi and B. Maleki, *RSC Adv.*, 2016, **6**, 20687.
59. R. Tayebbe, B. Maleki, F. Mohammadi Zonoz, R. M. Kakhki and T. Kunani, *RSC Adv.*, 2016, **6**, 55319.
60. C. B. Cui, H. Kakeya and H. Osasa, *Tetrahedron* 1996, **52**, 12651.
61. M. Kitajima, T. Nakamura, N. Kogure, M. Ogawa, Y. Mitsuno, K. Ono, S. Yano, N. Aimi and H. Takayama, *J. Nat. Prod.*, 2006, **69**, 715.
62. M. Harada and Y. Ozaki, *Chem. Pharm. Bull.*, 1978, **26**, 48.
63. Y. Zou, Y. Hu, H. Liu and D. Shi, *ACS Comb. Sci.*, 2012, **14**, 38.

Graphical Abstract

Green Synthesis of Tetrahydrobenzo[b]pyrans, Pyrano [2, 3-c] pyrazoles and Spiro [indoline-3,4'-pyrano[2,3-c]pyrazoles Catalyzed by Nano-structured diphosphate in Water

Behrooz Maleki^{*1}, Negar Nasiri¹, Reza Tayebce¹ Amir Khojastehnezhad^{*2} and Hossien Ali Akhlaghi¹



- Preparation of nanostructured diphosphate $\text{Na}_2\text{CaP}_2\text{O}_7$.
- Avoiding of any acid catalysts.
- The prepared catalyst is reusable and eco-friendly.
- The method is easy and contains simple experimental procedure.