


This article was downloaded by: [Fudan University]

On: 12 May 2015, At: 04:42

Publisher: Taylor & Francis

Informa Ltd Registered in England and Wales Registered Number: 1072954
Registered office: Mortimer House, 37-41 Mortimer Street, London W1T 3JH,
UK

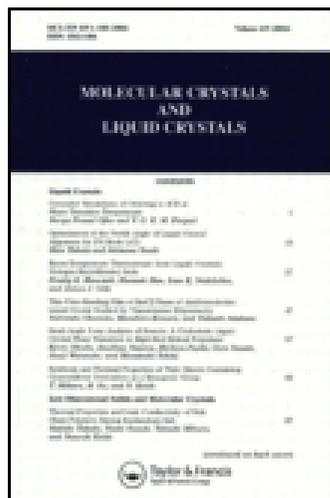

Molecular Crystals and Liquid Crystals

Publication details, including instructions for authors and subscription information:

<http://www.tandfonline.com/loi/gmcl20>

Synthesis and Characterization of Poly(N-arylcarbazole-alt-aniline) Copolymers as Blue-Emitting Host Matrix for Polymer Light-Emitting Diodes

Hui Wang^a, Jeong-Tak Ryu^a, Yoon Soo Han^b, Dae-Hwan Kim^b, Byeong Dae Choi^b, Lee Soon Park^c, Dayong Teng^d & Younghwan Kwon^d

^a College of Information and Communication Engineering, Daegu University, Gyeongsbuk, Korea

^b Department of Display & Nano Materials, Daegu Gyeongsbuk Institute of Science & Technology, Daegu, Korea

^c ADMRC, Department of Polymer Science, Kyungpook National University, Daegu, Korea

^d ADMRC, Department of Chemical Engineering, Daegu University, Gyeongsan, Gyeongsbuk, Korea

Published online: 31 Jan 2007.

To cite this article: Hui Wang, Jeong-Tak Ryu, Yoon Soo Han, Dae-Hwan Kim, Byeong Dae Choi, Lee Soon Park, Dayong Teng & Younghwan Kwon (2006) Synthesis and Characterization of Poly(N-arylcarbazole-alt-aniline) Copolymers as Blue-Emitting Host Matrix for Polymer Light-Emitting Diodes, *Molecular Crystals and Liquid Crystals*, 459:1, 95/[375]-107/[387], DOI: [10.1080/15421400600930417](https://doi.org/10.1080/15421400600930417)

To link to this article: <http://dx.doi.org/10.1080/15421400600930417>

PLEASE SCROLL DOWN FOR ARTICLE

Taylor & Francis makes every effort to ensure the accuracy of all the information (the "Content") contained in the publications on our platform. However, Taylor & Francis, our agents, and our licensors make no representations or warranties whatsoever as to the accuracy, completeness, or suitability for any purpose of the Content. Any opinions and views expressed in this publication are the opinions and views of the authors, and are not the views of or endorsed by Taylor & Francis. The accuracy of the Content should not be relied upon and should be independently verified with primary sources of information. Taylor and Francis shall not be liable for any losses, actions, claims, proceedings, demands, costs, expenses, damages, and other liabilities whatsoever or howsoever caused arising directly or indirectly in connection with, in relation to or arising out of the use of the Content.

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden. Terms & Conditions of access and use can be found at <http://www.tandfonline.com/page/terms-and-conditions>

Synthesis and Characterization of Poly(*N*-arylcarbazole-*alt*-aniline) Copolymers as Blue-Emitting Host Matrix for Polymer Light-Emitting Diodes

Hui Wang

Jeong-Tak Ryu

College of Information and Communication Engineering,
Daegu University, Gyeongbuk, Korea

Yoon Soo Han

Dae-Hwan Kim

Byeong Dae Choi

Department of Display & Nano Materials, Daegu Gyeongbuk Institute
of Science & Technology, Daegu, Korea

Lee Soon Park

ADMRC, Department of Polymer Science, Kyungpook National
University, Daegu, Korea

Dayong Teng

Younghwan Kwon

ADMRC, Department of Chemical Engineering, Daegu University,
Gyeongsan, Gyeongbuk, Korea

*Thermally stable and solution-processable poly(*N*-arylcarbazole-*alt*-aniline) copolymers with high structural integrity were synthesized in good yields via palladium-catalyzed polycondensation of aniline with corresponding *N*-arylcarbazole monomers such as *N*-(2-ethylhexyloxyphenyl)-3,6-dibromocarbazole, bis[6-bromo-*N*-(2-ethylhexyloxyphenyl)carbazole-3-yl] and *N*-(4-(2-ethylhexyl)-3,5-dibromomethylene-phenyl)carbazole, respectively. The optical and electrochemical properties of these copolymers were measured and compared with those of poly(*N*-alkylcarbazole-*alt*-aniline) copolymer. All synthesized poly(*N*-arylcarbazole-*alt*-aniline) copolymers showed maximum UV-Vis absorption peaks at around 300 nm in THF solution, and exhibited maximum photoluminescence peaks in*

Financial support from Daegu Gyeongbuk Institute of Science & Technology (DGIST) was gratefully acknowledged.

Address correspondence to Prof. Y. Kwon, ADMRC, Department of Chemical Engineering, Daegu University, Gyeongsan, Gyeongbuk 712-714, Korea. E-mail: y_kwon@daegu.ac.kr

the blue emission range from 430 to 460 nm. It was also found that poly(*N*-arylcarbazole-*alt*-aniline) copolymers had wider band gap energy than poly(*N*-alkylcarbazole-*alt*-aniline) copolymer.

Keywords: blue emission; host matrix; *N*-arylcarbazole; triarylamine

INTRODUCTION

Since the first report on conjugated polymers as a new class of electroluminescent materials for diodes, the research in this field has been advancing rapidly over the past 15 years [1–3]. So far, a lot of polymers such as poly(phenylene vinylene)s [4], polyphenylenes [5] and poly(fluorene-2,7-diyl) [6] have been paid much attention and have been studied as promising materials for commercial displays. Due to low cost and simplified manufacturing process, polymer light-emitting diodes (PLEDs) have been commercially applied in the fields of display manufacture, digital cameras, portable electronics, consumer goods, automotive systems and communication systems [7].

Carbazole-containing polymers have been widely investigated, since the discovery of good photoconductive properties of poly(*N*-vinylcarbazole) (PVK) [8,9]. It has been generally known that carbazole systems have chemical stability, hole-transporting property and wide band gap energy close to blue light emission. Among them, *N*-arylcarbazoles, resembling the structure of substituted triphenylene derivatives, could be obtained by introducing a phenyl substituent on N atom of carbazole units [10,11]. Martínez *et al.* reported the synthesis of a series of different polysubstituted *N*-arylcarbazole derivatives by a highly efficient carbazole arylation method [12]. Wong *et al.* prepared new 9,9-dihexylfluorene/9-arylcarbazole hybrid copolymers [13]. They pointed out that incorporating the electron-rich *N*-arylcarbazole groups into polyfluorene main chain can increase the HOMO levels as well as retain their blue emission. They also noted that advantage of the robust *N*-arylcarbazole groups increased the thermal stability and glass transition temperature of the resulting polymers compared to the *N*-alkyl-substituted polymers.

In this paper, we synthesized and characterized different types of poly(*N*-arylcarbazole-*alt*-aniline) copolymers as blue-emitting host matrix polymers for PLEDs. The optical and electrochemical properties of these copolymers were discussed with those of *N*-alkyl substituted polymer.

EXPERIMENTAL


Synthesis of Monomers

***N*-(2-ethylhexyl)-3, 6-dibromocarbazole (Monomer 1)**


As shown in Scheme 1, a mixture of 3, 6-dibromocarbazole (18.46 mmol) and K_2CO_3 (37 mmol) in DMF (20 ml) was refluxed in N_2 atmosphere and heated to $80^\circ C$. 2-Ethylhexylbromide (28 mmol) was added dropwise. After complete addition, heating was continued for 16 h. The product was isolated by diethyl ether/water extraction. The organic layer was dried with $MgSO_4$, then filtered and concentrated. The pure white viscous liquid, monomer 1, was obtained by silica column chromatography (eluent: hexane). (Yield: 56%,). 1H NMR (300 MHz in $CDCl_3$): δ 8.11 (2H, Ar-**H**), 7.48 (2H, Ar-**H**), 7.22 (2H, Ar-**H**), 4.18 (2H, -N-**CH**₂-), 1.23 ~ 1.44 (9H, -**CH**-, -**CH**₂-), 0.91 (6H, -**CH**₃).

***N*-(2-Ethylhexyloxyphenyl)-3,6-dibromocarbazole (Monomer 2)**

Synthetic procedure for monomer 2 was presented in Scheme 2. In the first step, 4-bromophenol (1.5 mmol) was dissolved in 100 ml of acetonitrile, then K_2CO_3 (4.5 mmol) was added. The mixture was stirred in N_2 atmosphere at $60^\circ C$. After 30 min, 2-ethylhexylbromide (4.5 mmol) was dissolved in 25 ml of acetonitrile and added to the flask dropwise. After 48 h of reaction, K_2CO_3 was filtered out, and the solvent was evaporated, then the crude product was washed with water and dried with $MgSO_4$. The pure white liquid product, 4-bromo-(2-ethylhexyloxy)-benzene (**I**), was obtained by silica column chromatography (eluent: hexane). (Yield: 66%). 1H NMR (300 MHz in $CDCl_3$): δ 7.33 (2H, Ar-**H**), 6.79 (2H, Ar-**H**), 3.79 (2H, -O-**CH**₂-), 1.71(1H, -**CH**-), 1.29~1.46 (8H, -**CH**₂-), 0.91 (6H, -**CH**₃); ^{13}C NMR (300 MHz in $CDCl_3$): 158.4, 132.0, 116.2, 112.4, 70.6, 39.2, 30.4, 29.0, 23.8, 23.0, 14.1, 11.1.

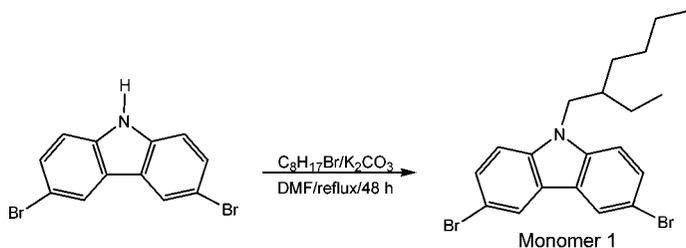

SCHEME 1 Synthetic route to monomer 1.

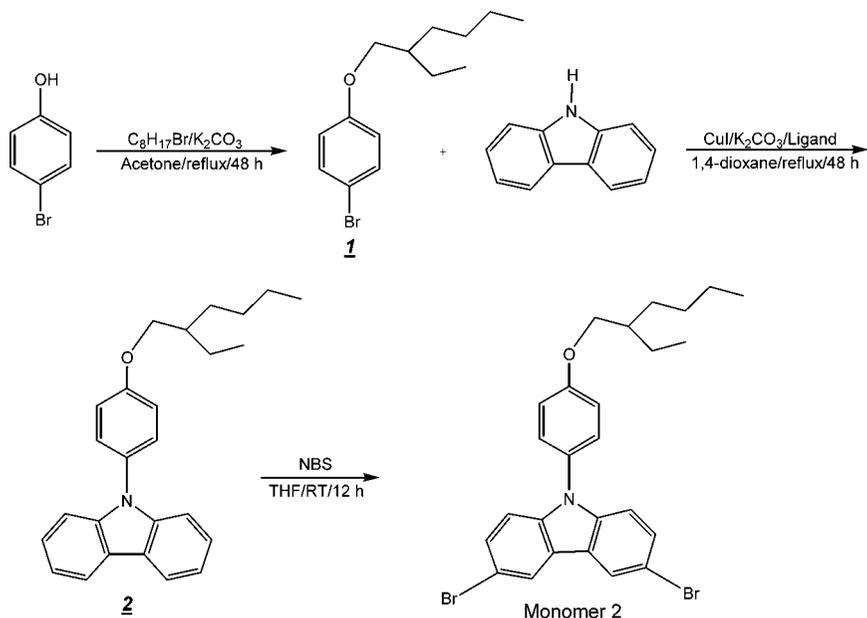

SCHEME 2 Synthetic route to monomer 2.

4-Bromo-(2-ethylhexyloxy)-benzene (**1**) (56.4 mmole), carbazole (7.6 mmol), K_3PO_4 (13.4 mmol), CuI (0.32 mmol) and *trans*-1, 2-cyclohexanediamine (1.27 mmol) were used in the second step. The reaction and workup procedure were carried out as described [14,15]. White solid product, *N*-(2-Ethylhexyloxyphenyl)-carbazole (**2**), was obtained (Yield: 29%). 1H NMR (300 MHz in $CDCl_3$): δ 8.15 (2H, Ar-**H**), 7.44~7.24 (8H, Ar-**H**), 7.08 (2H, Ar-**H**), 3.94 (2H, -O-**CH**₂-), 1.77(1H, -**CH**-), 1.26~1.57 (8H, -**CH**₂-), 0.91 (6H, -**CH**₃); ^{13}C NMR (300 MHz in $CDCl_3$): 158.6, 141.3, 129.9, 128.5, 125.8, 123.0, 120.2, 119.5, 115.5, 109.7, 70.8, 39.2, 30.4, 29.0, 23.8, 23.0, 14.1, 11.1.


In a flask, covered with aluminum oil, a stirred solution of **2** (2.43 mmol) in 60 ml of THF was cooled to 0°C. *N*-bromosuccinimide (NBS, 4.86 mmol) was added in small portion. The mixture was allowed to warm to room temperature overnight. THF was evaporated and the product was purified by extraction with diethyl ether and water. The organic layer was dried $MgSO_4$. The product, monomer 2, was obtained by column chromatography (eluent: hexane/methylene chloride). (Yield: 59%). 1H NMR (300 MHz in $CDCl_3$): δ 8.18 (2H, Ar-**H**), 7.47 (2H, Ar-**H**), 7.36 (2H, Ar-**H**), 7.16 (2H, Ar-**H**), 7.08 (2H, Ar-**H**), 3.94 (2H, -O-**CH**₂-), 1.77(1H, -**CH**-), 1.26~1.57 (8H, -**CH**₂-),

0.91 (6H, $-\text{CH}_3$); ^{13}C NMR (300 MHz in CDCl_3): 159.1, 140.3, 129.2, 128.9, 128.3, 123.6, 123.1, 115.7, 112.7, 111.5, 70.8, 39.3, 30.5, 29.1, 23.8, 23.1, 14.1, 11.1.

Bis[6-bromo-*N*-(2-ethylhexyloxyphenyl)carbazole-3-yl] (Monomer 3)

Synthetic procedure for monomer 3 was presented in Scheme 3. To a stirred solution of **2** (2.9 mmol) in 13 ml of chloroform, FeCl_3 (8.3 mmol) was added. After stirring at room temperature for 24 h, 13 ml of water was added. The organic layer was separated, dried over MgSO_4 , filtered and concentrated. Bis[*N*-(2-ethylhexyloxyphenyl)carbazole-3-yl] (**3**) was obtained by column chromatography (eluent: hexane/dichloromethane) (Yield: 67%) ^1H NMR (300 MHz in CDCl_3): δ 8.44 (2H, Ar-**H**), 8.22 (2H, Ar-**H**), 7.75 (2H, Ar-**H**), 7.49–7.25 (10 H, Ar-**H**), 7.14 (6H, Ar-**H**), 4.21 (4H, $-\text{N}-\text{CH}_2-$), 2.05 (2H, $-\text{CH}-$), 1.50–1.25 (16H, $-\text{CH}_2-$), 0.91 (12H, $-\text{CH}_3$); ^{13}C NMR (300 MHz in CDCl_3): 158.7, 141.8, 140.5, 134.1, 130.1, 128.4, 125.9, 123.6, 123.3, 120.3, 119.6, 118.8, 115.6, 109.9, 70.8, 39.4, 30.5, 29.1, 23.9, 23.1, 14.1, 11.2.

In a flask, covered with aluminum foil, a stirred solution of **3** (2.87 mmol) in 70 ml of THF was cooled to 0°C . NBS (5.74 mmol) was added in small portions. The mixture was allowed to warm to room temperature overnight. The THF was evaporated and the product was purified by extraction with diethylether and water. The organic layer was dried with MgSO_4 and then monomer 3 was obtained by column chromatography (eluent: hexane/dichloromethane). (Yield: 86%)

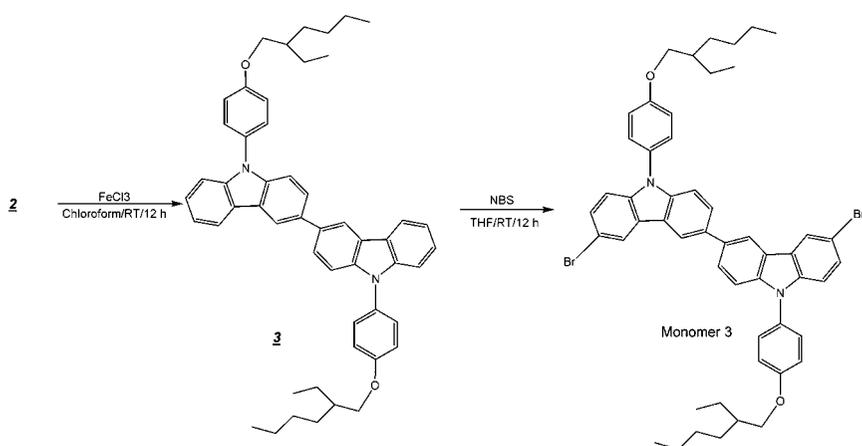


SCHEME 3 Synthetic route to monomer 3.

^1H NMR (300 MHz in CDCl_3): δ 8.25 (2H, Ar-**H**), 7.65 (2H, Ar-**H**), 7.40–7.27 (10H, Ar-**H**), 7.12 (2H, Ar-**H**), 7.02 (4H, Ar-**H**), 4.21 (4H, $-\text{N}-\text{CH}_2-$), 2.05 (2H, $-\text{CH}-$), 1.50–1.25 (16H, $-\text{CH}_2-$), 0.91 (12H, $-\text{CH}_3$); ^{13}C NMR (300 MHz in CDCl_3): δ 158.8, 140.8, 140.4, 134.1, 129.4, 128.6, 128.3, 126.3, 124.9, 123.0, 122.6, 118.8, 115.6, 112.4, 111.3, 110.2, 70.7, 39.4, 30.5, 29.7, 23.8, 23.1, 14.1, 11.2.

***N*-[4-(2-Ethylhexyloxy)-3,5-dibromomethylenephenyl] carbazole (Monomer 4)**

Synthetic procedure for monomer 4 was presented in Scheme 4. 4-Bromo-2,6-dimethylphenol (0.02 mol) in 50 ml of acetonitrile was added to a suspension of potassium hydroxide (0.06 mol) in 200 ml of acetonitrile which was prepared by vigorous stirring for 30 min under N_2 . 2-Ethylhexyl bromide (0.02 mol) was added to the solution, followed by refluxed for 48 h. Potassium hydroxide was filtered out, and the solvent was evaporated, then the crude product was washed with water and dried with MgSO_4 . The pure white liquid product, 5-bromo-2-(2-ethylhexyloxy)-1,3-dimethylbenzene (**4**), was obtained by silica column chromatography (eluent: hexane). (Yield: 63%). ^1H NMR (300 MHz in CDCl_3): δ 7.15 (2H, Ar-**H**), 3.6 (2H, $-\text{O}-\text{CH}_2-$), 2.26 (6H, Ar- CH_3), 2.18 (9H, $-\text{CH}-$, $-\text{CH}_2$), 0.91 (6H, $-\text{CH}_3$).

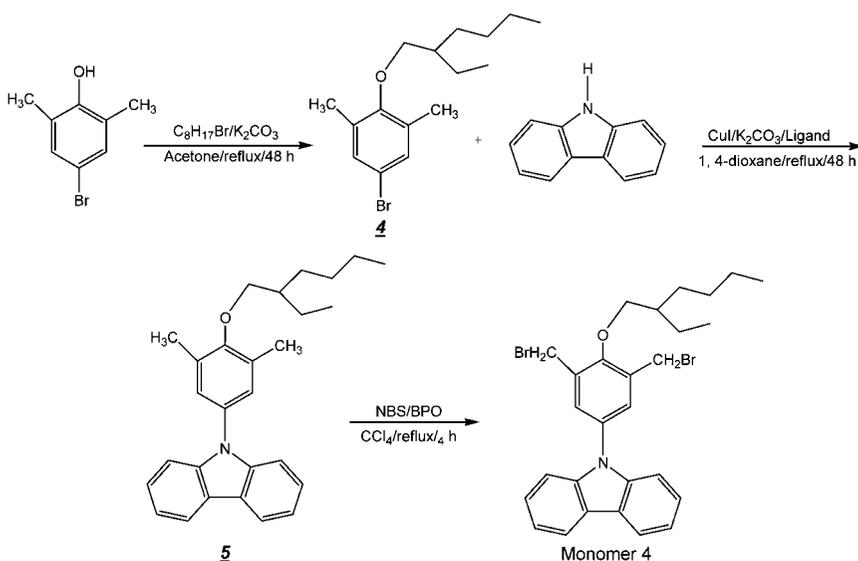

SCHEME 4 Synthetic route to monomer 4.

In the second step, 5-bromo-2-(2-ethylhexyloxy)-1, 3-dimethylbenzene (**4**) (112.79 mmol), carbazole (15.24 mmol), K_3PO_4 (26.72 mmol), CuI (0.64 mmol) and trans-1,2-cyclohexanediamine (2.54 mmol) were used. The reaction and workup procedure were carried out as described [14,15]. White solid product, *N*-[4-(2-ethylhexyloxy)-3, 5-dimethyl-phenyl]carbazole (**5**), was obtained. (Yield: 25%). 1H NMR (300 MHz in $CDCl_3$): δ 7.38 (4H, Ar-**H**), 7.26 (4H, Ar-**H**), 7.16 (2H, Ar-**H**), 3.6 (2H, -O-**CH**₂-), 2.30 (6H, Ar-**CH**₃), 2.18 (9H, -**CH**-, -**CH**₂-), 0.91 (6H, -**CH**₃).

A mixture of *N*-[4-(2-ethylhexyloxy)-3, 5-dimethyl-phenyl]carbazole (**5**) (3.68 mmol), NBS (8.09 mmol) and BPO (0.1618 mmol) were added to CCl_4 at room temperature. The following reaction and workup procedure were carried out as described [14,15]. White solid product, monomer 4, was obtained. (Yield: 45%). 1H NMR (300 MHz in $CDCl_3$): δ 7.48 (4H, Ar-**H**), 7.45 (4H, Ar-**H**), 7.35 (2H, Ar-**H**), 4.6 (4H, **CH**₂Br-), 3.96 (2H, -O-**CH**₂-), 2.25 (9H, -**CH**-, -**CH**₂-), 0.95 (6H, -**CH**₃).

Polymerization

A mixture of monomer 1 (2.60 mmol) (monomer 2, monomer 3 or monomer 4) and aniline (2.60 mmol) was dissolved in toluene (30 ml). NaO-*t*-Bu (7.8 mmol), $Pd_2(dba)_3$ (0.066 mmol) and $P(t-Bu)_3$ (0.4 mmol) were added to the solution at room temperature. The reaction mixture was stirred at 100°C for 48 h. After cooling to room temperature, the mixture was quenched by adding aqueous ammonia (50 ml) and the product was extracted with $CHCl_3$. The organic fraction was concentrated and reprecipitated from $CHCl_3$ /methanol several times. Then, the products were filtered and dried in vacuum.

Characterization


NMR spectra were recorded on a Varian Unity Plus 300 using $CDCl_3$. Molecular weights and molecular weight distributions were measured by Water gel permeation chromatograph (GPC) equipped with Styragel HR 5E column using THF as an eluent against polystyrene standards at room temperature. Thermal analysis was performed on a Seiko EXSTAR 6000 TG/DTA 6300 thermal analyzer at a heating of 20°C/min for thermogravimetric analyzer (TGA) and at a heating of 10°C/min for differential scanning calorimetry (DSC). UV-Visible absorption spectra were taken by Shimadzu UV-2100. The photoluminescence (PL) spectra excited by He-Cd laser at 325 nm were monitored by Optical Multichannel Analyzer (Laser Photonics, OMA

system). The ionization potential (IP) was measured by a photoelectron spectroscopy (Riken Keiki AC-2).

RESULTS AND DISCUSSIONS

Alternating copolymers such as poly[*N*-(2-ethylhexyl)-3,6-carbazole-*alt*-aniline] (**P1**), poly[*N*-(2-ethylhexyloxy)-phenyl]-3,6-carbazole-*alt*-aniline] (**P2**), poly[bis(6-*N*-(4-(2-ethylhexyloxy)-phenyl)-carbazole-3-yl)-*alt*-aniline] (**P3**) and poly[*N*-(4-(2-ethylhexyloxy)-3,5-dimethylene-phenyl)-carbazole-*alt*-aniline] (**P4**) were prepared by using Pd-catalyzed polycondensation as presented in Scheme 5. The common structural characteristics of **P1**, **P2** and **P3** were designed to have a carbazole and a triarylamine unit in the polymer main chain. Compared to *N*-alkyl-substituted **P1**, however, *N*-arylation was employed for **P2** and **P3**. It was reported [16] that the properties of carbazole oligomers were affected by replacing alkyl groups on *N* atom of carbazole with aryl groups. The alkyl groups on *N* atom activated the carbazole ring system through increasing the electron density, compared to the corresponding aryl-substituted compounds. On the other hand, the aryl group on *N* atom was twisted to the carbazole ring and thus could not delocalize π -electrons from carbazole. Therefore, 4, 4'-bis(9-carbazolyl)-biphenyl (CBP) was used as a blue-emitting host matrix for phosphorescent-doped OLED. In addition, **P2** and **P3** were prepared to investigate the effect of *N*-aryl-substituted carbazole content in the polymer backbone. The carbazole group in **P4** was placed in the side chain and the conjugation of the polymer was reduced by incorporating methylene groups in polymer backbone. In all series of polymers, alkyl groups such as 2-ethylhexyl group in **P1** and 2-ethylhexyloxy groups in **P2**, **P3** and **P4** were incorporated to increase the solubility of alternating copolymers in common organic solvents.

All synthesized copolymers were found to be soluble in common organic solvents such as benzene, toluene, chloroform and THF, and showed good quality of film forming. The molecular weights of the copolymers were measured by using GPC, and summarized in Table 1. Relatively low molecular weights of **P2** and **P3** might be explained by increased rigidity of polymer backbone with substituting 2-ethylhexyloxyphenyl group on *N* atom, resulting in premature precipitation of the copolymers during the polymerization. The thermal stability of the copolymers was compared with decomposition temperature (T_d) measured at 5 wt% loss in TGA, as shown in Figure 1 and Table 1. These data revealed that the copolymers had excellent thermal stability under nitrogen atmosphere. **P3** and **P4** showed relatively

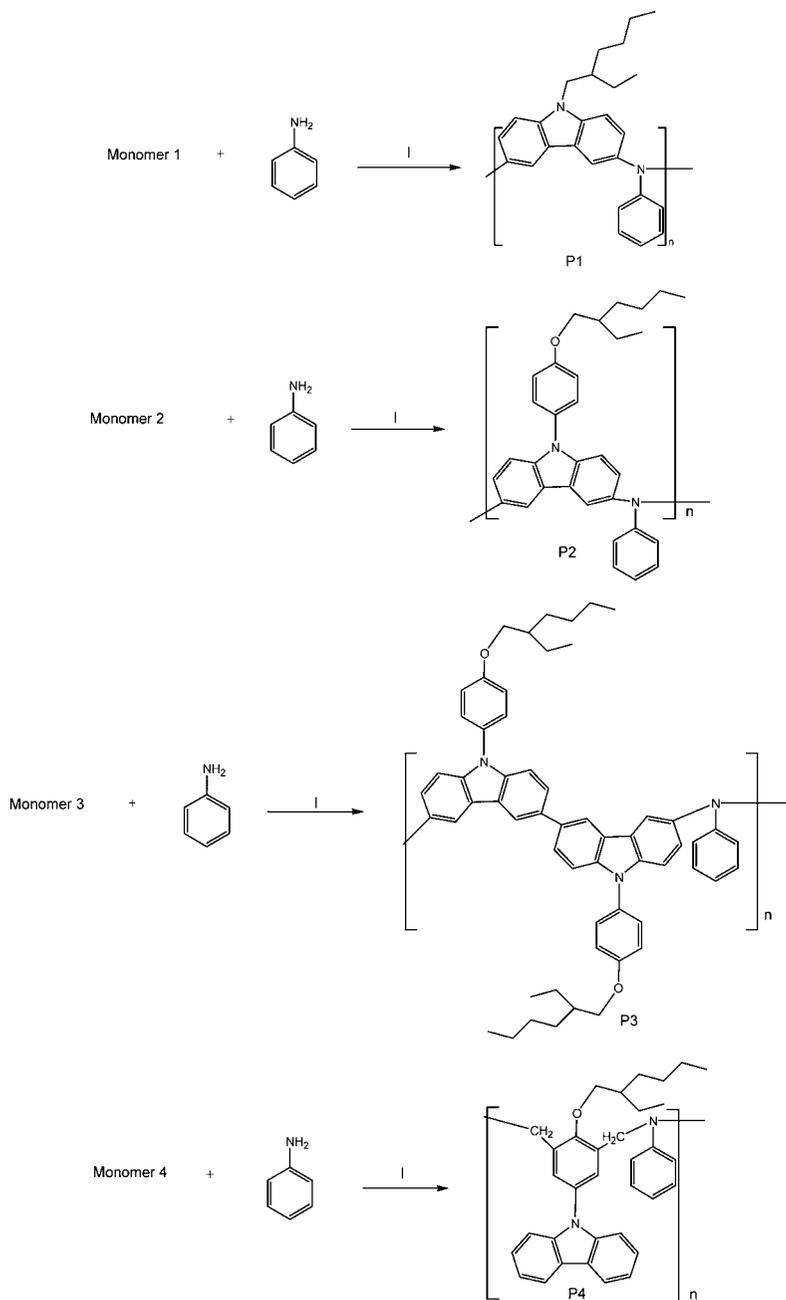

SCHEME 5 Polymerizations via palladium catalyzed polycondensation; Reaction condition (I): Toluene, NaO-*t*-Bu, Pd₂(dba)₃, P(*t*-Bu)₃, 100°C.

TABLE 1 Physical Properties of Polymers


Polymers	M_w (g/mol)	M_w/M_n	T_g ($^{\circ}\text{C}$)	T_d ($^{\circ}\text{C}$) ^a
P1	7,100	1.3	—	442
P2	4,100	1.3	—	415
P3	4,900	1.1	121	409
P4	11,500	1.6	132	327

^aTemperature resulting in 5% weight loss based on initial weight.

high T_g of 121 $^{\circ}\text{C}$ and 132 $^{\circ}\text{C}$, respectively, in Table 1. The T_g 's of **P1** and **P2** could not be measured in this DSC experiment.

UV-Visible absorption and PL emission spectra of the copolymers are presented in Figures 2 and 3, respectively. In Figure 2, the maximum UV-Visible absorption peaks of all copolymers were observed at around 300 nm. When excited at their UV-Visible absorption maxima, the copolymers exhibited PL emission in the blue range from 450 nm to 460 nm. Substitution effect of alkyl and aryl groups on *N* atom was observed. Compared with $\lambda_{\text{max,PL}}$ of **P1**, $\lambda_{\text{max,PL}}$ of **P2** was blue shifted to shorter wavelength, possibly attributed to localized electron density by twisted conformation between carbazole and aryl groups.

Electrochemical properties of the copolymers are summarized in Table 2. Energy levels of the copolymers are also compared as shown in Figure 4. The copolymers showed HOMO energy levels of -5.19 eV for **P1**, -5.35 eV for **P2**, -5.29 eV for **P3** and -5.64 eV for **P4**. Band gap energy levels of the copolymers were also measured from the

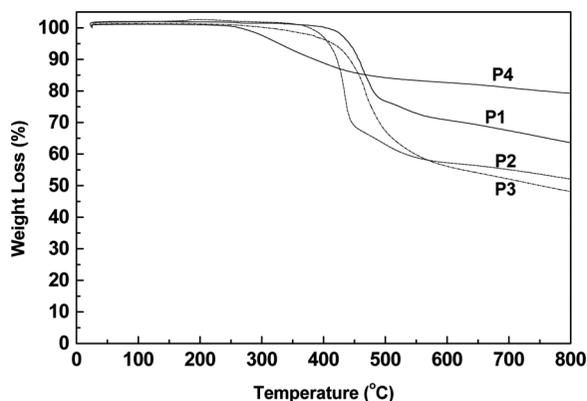**FIGURE 1** TGA curves of alternating copolymers.

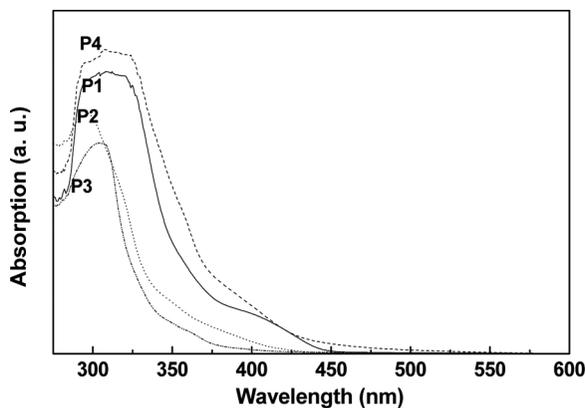


FIGURE 2 UV-Vis absorption spectra of alternating copolymers.

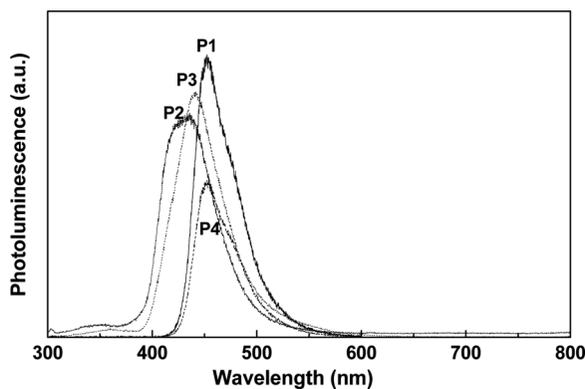


FIGURE 3 Photoluminescence spectra of alternating copolymers.

TABLE 2 Electronic Properties of the Polymers

Polymers	$\lambda_{\max,UV}$ (nm)	$\lambda_{\max,PL}$ (nm)	Band gap (eV) ^a	HOMO (eV) ^b	LUMO (eV) ^c
P1	309	452	2.91	-5.19	-2.28
P2	296	441	3.16	-5.35	-2.19
P3	305	433	3.32	-5.29	-1.97
P4	304	451	3.05	-5.64	-2.59

^aCalculated from the crosspoint of UV-Vis and PL spectrum.

^bMeasured by a RIKEN Keiki AC-2.

^cEstimated from the HOMO and band gap.

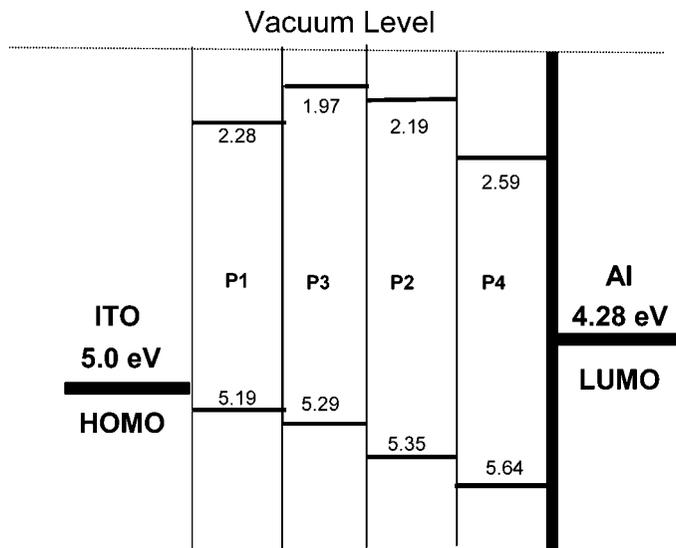


FIGURE 4 Schematic view of energy levels of alternating copolymers.

crosspoint of UV-Visible absorption and PL emission spectra to be 2.91 eV for **P1**, 3.16 eV for **P2**, 3.32 eV for **P3** and 3.05 eV for **P4**. It appeared that changing the substituent group on *N* atom of carbazole unit from 2-ethylhexyl group in **P1** to 2-ethylhexyloxyloxy-phenyl group in **P2-P4** increased band gap energy as well as decreased HOMO energy levels. This might be originated from the twisted conformation between carbazole and aryl groups in **P2-P4** as mentioned previously.

CONCLUSIONS

Synthesis of poly(*N*-arylcarbazole-*alt*-aniline) copolymers such as poly[*N*-(2-ethylhexyloxy)-phenyl]-3,6-carbazole-*alt*-aniline (**P2**), poly[bis(6-*N*-(4-(2-ethylhexyloxy)-phenyl)-carbazole-3-yl)-*alt*-aniline] (**P3**) and poly[*N*-(4-(2-ethylhexyloxy)-3,5-dimethylene-phenyl)-carbazole-*alt*-aniline] (**P4**) was successfully accomplished by using palladium-catalyzed polycondensation. The optical and electrochemical properties of these copolymers were characterized and compared with those of *N*-alkyl substituted counterpart, poly[*N*-(2-ethylhexyl)-3,6-carbazole-*alt*-aniline] (**P1**). It was observed from the optical and electrochemical properties that poly(*N*-arylcarbazole-*alt*-aniline) copolymers could be used as blue emitting host materials for PLEDs, because they

showed blue emission in PL spectra and wider band gap energy compared to the poly(*N*-alkylcarbazole-*alt*-aniline) copolymer.

REFERENCES

- [1] Burroughes, J. H., Bradley, D. D. C., Brown, A. R., Marks, R. N., MacKay, K., Friend, R. H., Burns, P. L., & Holmes, A. B. (1990). *Nature (London)*, *347*, 539.
- [2] Mitschke, U. & Bauerle, P. (2000). *J. Mater. Chem.*, *10*, 1471.
- [3] Neher, D. (2001). *Macromol. Rapid Commun.*, *22*, 1365.
- [4] Berntsen, A., Croonen, Y., Liedenbaum, C., Schoo, H., Visser, R.-J., Vleggaar, J., & Vandeweyer, P. (1998). *Opt. Mater.*, *9*, 125.
- [5] Tanigaki, N., Masuda, H., & Kaeriyama, K. (1997). *Polymer.*, *38*, 1221.
- [6] Bernius, M., Inbasekaran, M., Woo, E., Wu, W., & Wujkowski, L. (2000). *J. Mater. Sci. Mater. Electro.*, *11*, 111.
- [7] Bernius, M. T., Inbasekaran, M., O'Brien, J., & Wu, W. (2000). *Adv. Mater.*, *12*, 1737.
- [8] Scott, J. C., Pautmeier, L. Th., & Moerner, W. E. (1992). *J. Opt. Soc. Am. B.*, *9*, 2059.
- [9] Esen, R., Nakhimowsky, L. A., & Shanks, H. R. (1996). *Mol. Cryst. Liq. Cryst.*, *287*, 255.
- [10] Simmer, J., Güsen, B., Paulus, W., Kettner, A., Schumacher, P., Adam, D., Etzbach, K. H., Siemeseyer, K., Wendorf, J. H., Ringsdorf, H., & Haarer, D. (1996). *Adv. Mater.*, *8*, 815.
- [11] Ochse, A., Kettner, A., Kopitke, J., Wendorf, J. H., & Bäessler, H. (1999). *Phys. Chem. Chem. Phys.*, *1*, 1757.
- [12] Martínez-Palau, M., Perea, E., López-Calahorra, F., & Velasco, D. (2004). *Lett. Org. Chem.*, *1*, 231.
- [13] Wong, W.-Y., Liu, L., Cui, D., Leung, L. M., Kwong, C.-F., Lee, T.-H., & Ng, H.-F. (2005). *Macromolecules.*, *38*, 4970.
- [14] Klapars, A., Antilla, J. C., Huang, X. H., & Buchwald, S. L. (2001). *J. Am. Chem. Soc.*, *123*, 7727.
- [15] Hayat, S., Rahman, A., Choudhary, M. I., Khan, K. M., Schumann, W., & Bayer, E. (2001). *Tetrahedron*, *57*, 9951.
- [16] Brunner, K., Dijken, A. V., Börner, H., Bastiaansen, J. J. A. M., Kiggen, N. M. M., & Langeveld, B. M. W. (2004). *J. Am. Chem. Soc.*, *126*, 6035.