

Host–guest blue light-emitting electrochemical  
cells†

Cite this: DOI: 10.1039/c3tc31983k

Antonio Pertegás,<sup>a</sup> Nail M. Shavaleev,<sup>\*b</sup> Daniel Tordera,<sup>a</sup> Enrique Ortí,<sup>a</sup>  
Mohammad K. Nazeeruddin<sup>b</sup> and Henk J. Bolink<sup>\*a</sup>Received 8th October 2013  
Accepted 25th November 2013

DOI: 10.1039/c3tc31983k

www.rsc.org/MaterialsC

Carbazole, a commonly used hole-transporter for organic electronics, has been modified with an imidazolium cation and a hexafluorophosphate counter-anion to give an ionic hole-transporter. It has been applied as one of the hosts in a host–guest blue light-emitting electrochemical cell (LEC) with the neutral blue emitter FIrPic. We have obtained efficient and bright blue LECs with an electroluminescence maximum at 474 nm and efficacy of 5 cd A<sup>−1</sup> at a luminance of 420 cd m<sup>−2</sup>, thereby demonstrating the potential of the ionic organic charge-transporters and of the host–guest architecture for LECs.

## Introduction

Electroluminescent devices using organic semiconductors are becoming a serious alternative to conventional inorganic technology as their efficiencies and stabilities have improved significantly over the last few years.<sup>1</sup> The most efficient and stable organic light-emitting devices (OLEDs) are based on a multi-stack of low molecular-weight components that use air-sensitive charge-injection layers.<sup>2</sup> The multi-layer architecture is obtained by sequentially evaporating the active species under vacuum. OLEDs require rigorous encapsulation to prevent degradation of the charge-injection layers.<sup>3,4</sup>

Another type of electroluminescent device, referred to as the light-emitting electrochemical cell (LEC), has a simpler architecture and does not rely on air-sensitive charge-injection layers,<sup>5–10</sup> which simplifies its preparation and makes it more cost-efficient. In its simplest form, the LEC consists of a single emitting layer of either an ionic transition-metal complex (iTMC)<sup>9</sup> or a neutral light-emitting material (usually a polymer) mixed with an ionic transporter and a salt.<sup>8,10</sup> The presence of mobile ions facilitates the formation of ionic junctions that lower the barrier for charge injection and make the LEC independent of the work function of the electrode material.<sup>11–17</sup>

Despite these advances, the lack of efficient blue LECs remains a problem. Although several blue LECs have been reported, they exhibit low efficiency, luminance and lifetime.<sup>18–23</sup> Efficacies of up to 18.3 cd A<sup>−1</sup> at a luminance of 14.5 cd m<sup>−2</sup> have been reported for blue-green LECs.<sup>22</sup> For deeper-blue

emission, the performances are worse: 2.6 cd A<sup>−1</sup> at 5.3 cd m<sup>−2</sup> for a sky-blue LEC<sup>23</sup> and 0.65 cd A<sup>−1</sup> at 39 cd m<sup>−2</sup> for the bluest LEC reported so far.<sup>19</sup> With polymers as the active material in a tri-layer structure, an efficient LEC was made (5.3 cd A<sup>−1</sup>).<sup>24</sup> However, in general, the stability of blue LECs is low, from minutes to a few hours; moreover, their colour stability is rarely discussed.


In iTMC–LECs, the iTMC is the only component involved both in charge transport and in emission. With blue LECs, these processes are challenging, because they involve high-energy excitons (blue emitters have a large energy gap between the lowest unoccupied and the highest occupied molecular orbitals). The same problem occurs in OLEDs, which is a reason for the continued search for stable and efficient blue emitters. In OLEDs, charge transport is usually not performed by the emitter but by the specially designed electron- and hole-transporters.<sup>25</sup> In contrast, in LECs, charge transport occurs *via* the emitter and involves its reduction and oxidation. Because charge transport in blue LECs forms high-energy species, efficient blue LECs are hard-to-make. Hence, in LECs, it is of interest to decouple the charge transport and the emission by using different molecules for these processes. LECs rely on ionic movement to reduce the charge injection barriers; therefore, in the LEC, the charge-transporter must be mixed with the emitter and, more importantly, the ionic movement must be maintained; for example, host–guest orange and red LECs have been made with moderate band-gap iTMCs as the host.<sup>26–29</sup>

Here, we report a wide band-gap ionic hole-transporter **NMS25** suitable for blue light-emitting guests. **NMS25** is an aryl-carbazole modified with an imidazolium cation and a hexafluorophosphate counter-anion (Scheme 1). **NMS25** was mixed with a neutral polar electron-transporter **SPPO13** and a neutral blue-phosphorescent iridium(III) emitter **FIrPic** (Scheme 1). We show that the combination of these low molecular weight compounds, when they are sandwiched between two air-stable

<sup>a</sup>Instituto de Ciencia Molecular, Universidad de Valencia, C/Catedrático J. Beltrán 2, ES-46980 Paterna, Valencia, Spain. E-mail: henk.bolink@uv.es

<sup>b</sup>Laboratory of Photonics and Interfaces, Institute of Chemical Sciences and Engineering, École Polytechnique Fédérale de Lausanne, CH-1015 Lausanne, Switzerland. E-mail: shava@mail.ru; Fax: +41 21 693 4111; Tel: +41 21 693 6124

† Electronic supplementary information (ESI) available: Spectroscopy and electrochemistry of **NMS25**. See DOI: 10.1039/c3tc31983k

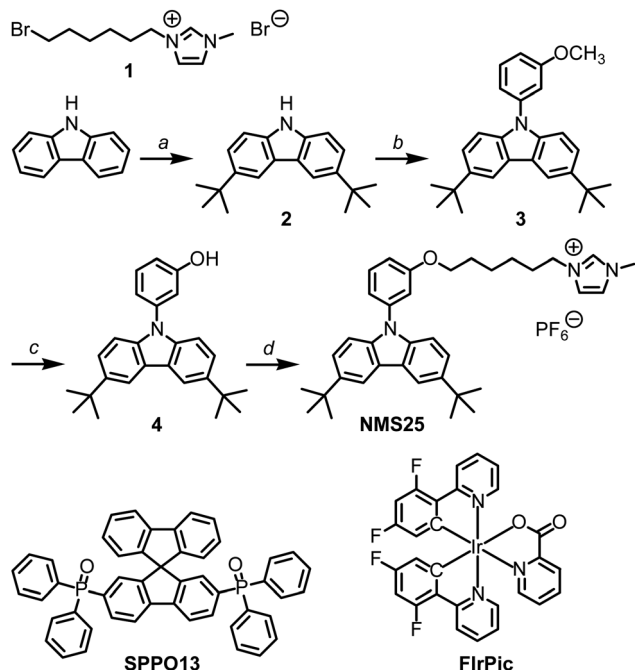

**Scheme 1** Synthesis of NMS25: (a)  $\text{AlCl}_3$ , *tert*-butyl chloride,  $\text{CH}_2\text{Cl}_2$ , under Ar,  $0^\circ\text{C}$  to RT; (b) 3-iodoanisole,  $\text{Cs}_2\text{CO}_3$ ,  $\text{Cu}_2\text{O}$ , DMF, under Ar,  $120^\circ\text{C}$ ; (c) pyridine hydrochloride, under Ar,  $200^\circ\text{C}$ ; (d) **1**,  $\text{K}_2\text{CO}_3$ , DMF, under Ar,  $60^\circ\text{C}$ . Structures of SPP013 and FirPic.

electrodes, gives efficient blue-electroluminescent devices that function as LECs, with a slow turn-on determined by the movement of ions, and that reach an efficacy of  $5 \text{ cd A}^{-1}$  at a luminance of  $420 \text{ cd m}^{-2}$ .

## Results and discussion

### Synthesis and characterization


**NMS25** was prepared in a multi-step procedure, which was up-scaled to give up to 4 g of the product (Scheme 1). In **NMS25**, the *tert*-butyl groups were added to improve the solubility and to block electrochemically-reactive C3 and C6 positions of the carbazole; a long hexyloxy-chain was introduced to prevent interaction of the imidazolium cation with the carbazole. Imidazolium was chosen because it is optically-transparent and electrochemically-inert. **NMS25** is a white solid that is soluble in polar organic solvents; it exhibits electronic absorption with a cut-off at 365 nm in dichloromethane solution (Fig. S1, ESI†). The redox potentials for **NMS25** were measured by cyclic voltammetry. In acetonitrile, **NMS25** undergoes reversible oxidation of the carbazole at 0.77 V (against ferrocene couple), confirming its hole-transport properties, but no reduction down to  $-2.7 \text{ V}$  (Fig. S2, ESI†).

### Electroluminescence devices

Two-layer LECs were prepared by spin-coating from solution. An 80 nm layer of PEDOT:PSS was spin-coated on ITO-glass to increase the reproducibility of the devices. Then, an 80 nm layer of **NMS25**, **SPP013** and **FirPic** was deposited from an anisole solution. Aluminium was used as the top electrode.

To find the optimum ratio of hole- and electron-transporters, we evaluated devices with various mass ratios of **NMS25**:**SPP013** (matrix; Fig. 1). The device configuration was: ITO/PEDOT:PSS (80 nm)/matrix:**FirPic** (80 nm; with 10 wt% **FirPic**) with the ionic liquid (IL) 1-butyl-3-methylimidazolium tetrafluoroborate added in a 4 : 1 molar ratio of matrix:IL/Al. The LECs were run with a block-wave pulsed current at a frequency of 1000 Hz and a duty cycle of 50% at an average density of  $100 \text{ A m}^{-2}$ .

All of the devices exhibit blue electroluminescence from **FirPic** with a maximum at 474 nm and with the typical characteristics of LECs (Fig. 1–4). In pulsed-current mode, the LECs exhibit a rapid decrease of the initially high driving voltage to a lower steady-state value (Fig. 1–4). This is caused by the decrease in injection barriers for electrons and holes as ions migrate to the electrodes. The maximum luminance ( $L_{\text{max}}$ ) and the time when it is reached ( $t_{\text{max}}$ ) vary significantly for the different LECs, thereby complicating the lifetime comparison (as lifetime, for example, defined by the time it takes for the luminance to decrease to half of its maximum value,  $t_{1/2}$ , counted from  $t = 0$ , depends on the luminance). Kalyuzhny *et al.* suggested<sup>30</sup> to characterize the LEC by the total emitted energy ( $E_{\text{tot}}$ ) up to the time when the luminance decreases to the 1/5 of its maximum.

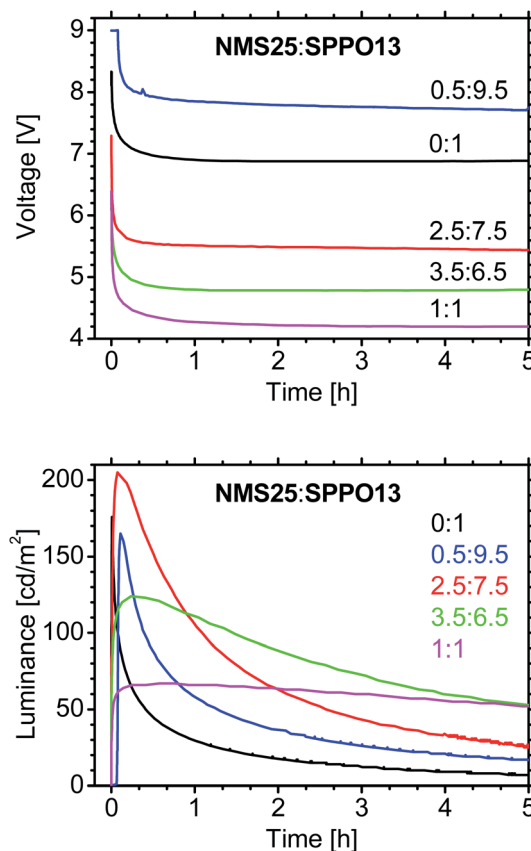

**Fig. 1** Time-dependence of voltage and luminance for LECs with various mass ratios of **NMS25**:**SPP013** (matrix) with 10 wt% **FirPic** and with a 4 : 1 molar ratio matrix:IL 80 nm emitting layer (block-wave pulsed current; 1000 Hz; 50% duty cycle; average density  $100 \text{ A m}^{-2}$ ).

**Table 1** Performance of LECs at a pulsed current of  $100 \text{ A m}^{-2}$  (Fig. 1)

<b>NMS25:SPPO13</b> (mass)	$t_{\text{max}}$ (min)	$L_{\text{max}}$ ( $\text{cd m}^{-2}$ )	$t_{1/2}$ (h)	$E_{\text{tot}}$ (J)	$\text{Eff}_{\text{max}}$ ( $\text{cd A}^{-1}$ )	$\text{EQE}_{\text{max}}$ (%)
0 : 1	0.4	176	0.1	0.01	1.7	0.6
0.5 : 9.5	6.6	165	0.6	0.02	1.6	0.6
2.5 : 7.5	4.2	205	1.1	0.03	1.9	0.8
3.5 : 6.5	14	124	3.9	0.07	1.2	0.5
1 : 1	41	67	14	0.13	0.6	0.3


Table 1 summarizes the performance of LECs. The LEC with the longest lifetime and the highest total emitted energy had an emitting layer with a 1 : 1 mass ratio of **NMS25:SPPO13** (Table 1); its steady-state driving voltage was the lowest, indicating optimized charge-injection/transport (Fig. 1). Hence, this LEC was chosen for optimization.

The thickness of the emitting layer changes the LEC performance;<sup>20</sup> therefore, we varied it from 40 to 80 and to 100 nm (Fig. 2). Although the driving voltage increases for thicker layers, the highest luminance was achieved with an 80 nm layer (Fig. 2). The driving conditions were evaluated by changing the


average current density<sup>31</sup> from 25 to  $100 \text{ A m}^{-2}$ , with the optimum determined to be  $75 \text{ A m}^{-2}$ .

There are two salts in the optimized LEC: the ionic hole-transporter and the IL. A device was also prepared without IL to confirm that it can function as a LEC by using only the ions from **NMS25** (Fig. 3). The LEC without the IL exhibits a higher maximum luminance and efficiency, but a higher driving voltage and a lower stability of the luminance than does the LEC with the IL (Fig. 3).

Here, we demonstrate the potential of the host-guest LECs in terms of efficiency and luminance (in previous reports,<sup>19,23</sup> the stability of blue LECs was low and the focus was on the efficiency). The LEC (without the IL) was optimized by annealing the emitting layer for 1 h at  $100^\circ\text{C}$  prior to the evaporation of the top contact (the annealing changes the morphology and increases the photoluminescence quantum yield of the active layer<sup>32</sup>); the thus manufactured blue LEC exhibits a current efficacy of  $5 \text{ cd A}^{-1}$  at a luminance of  $420 \text{ cd m}^{-2}$  (Fig. 4). These values are significantly higher than are those previously reported for blue LECs.<sup>19,21,23</sup> The lifetime of the optimized LEC (without the IL) is short (Fig. 4); however, it is possible to increase it by adding the IL (Fig. 3 and Table 1).

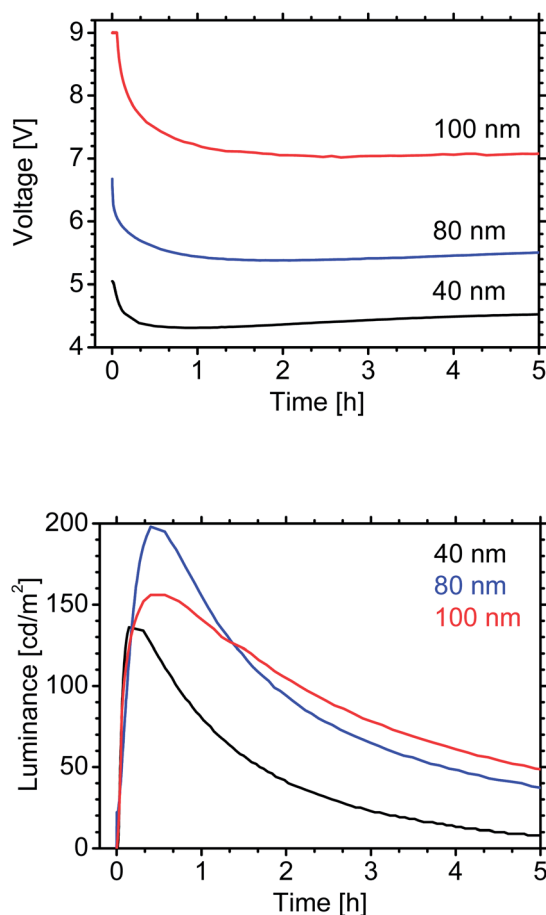

**Fig. 2** Time-dependence of voltage and luminance for LECs with various thicknesses of the emitting layer: **NMS25:SPPO13** (1 : 1 by mass) with 10 wt% **FlrPic** (without IL); pulsed current (1000 Hz; 50% duty cycle; average density  $100 \text{ A m}^{-2}$ ).

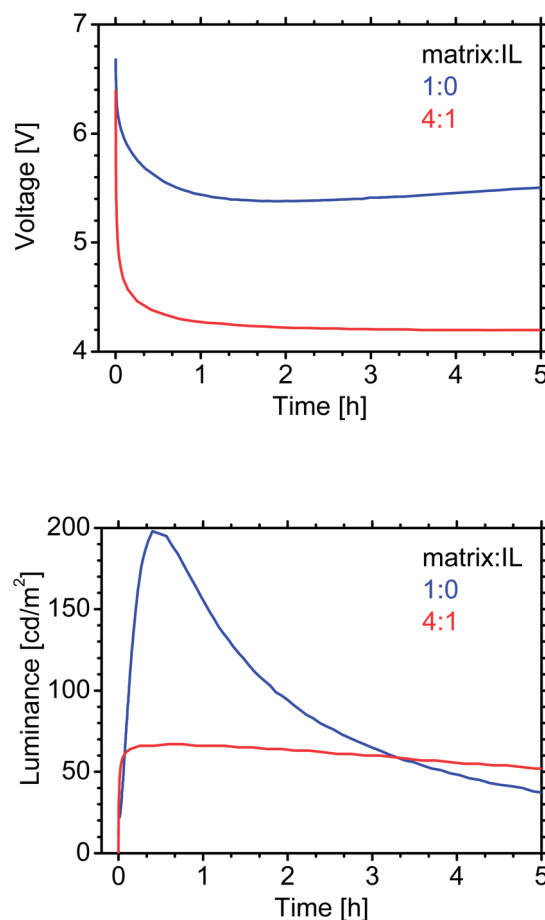

**Fig. 3** Time-dependence of voltage and luminance for LECs with and without an ionic liquid (IL; in molar ratio): 80 nm emitting layer; **NMS25:SPPO13** (matrix; 1 : 1 by mass) with 10 wt% **FlrPic**; pulsed current (1000 Hz; 50% duty cycle; average density  $100 \text{ A m}^{-2}$ ).

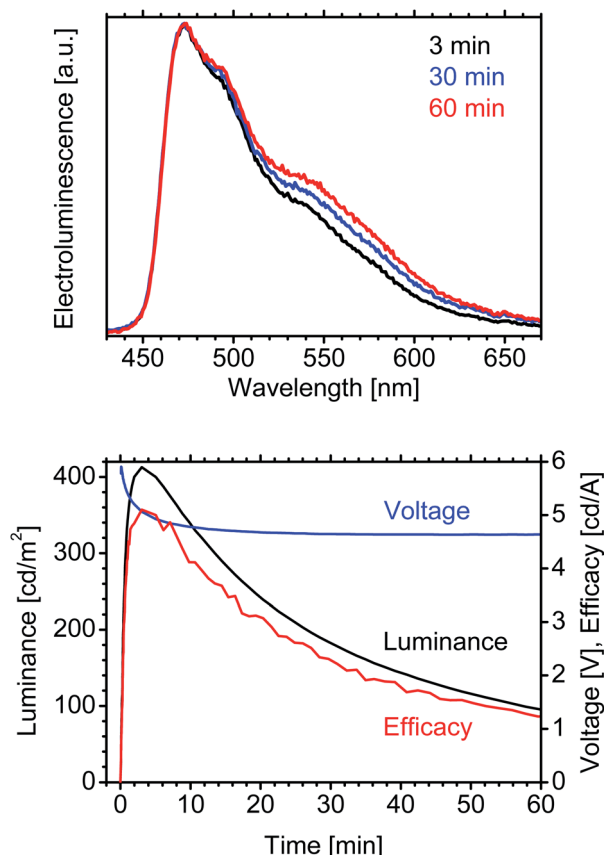


Fig. 4 Time-dependence of electroluminescence spectrum, luminance, voltage and efficacy of optimized LEC (1 : 1 by mass of NMS25:SPPO13 with 10 wt% FlrPic; 80 nm emitting layer; annealed at 100 °C for 1 h; without IL; block-wave pulsed current; 1000 Hz; 50% duty cycle; average density 75 A m<sup>-2</sup>).

Table 2 CIE coordinates for optimized LEC (Fig. 4)

<i>t</i> (min)	CIE ( <i>x</i> )	CIE ( <i>y</i> )	$\lambda_{\text{max}}$ (nm)
3	0.214	0.377	473
5	0.217	0.379	474
10	0.219	0.380	474
30	0.230	0.389	473
60	0.242	0.400	474

In the optimized device, **FlrPic** exhibits only small red-shift of electroluminescence, that is, the host-guest LEC gives stable blue electroluminescence during the 60 min of work (Fig. 4 and Table 2). In contrast, in previous reports, the electroluminescence of blue iTMC-LECs underwent significant red-shift.<sup>33,34</sup>

## Conclusions

Ionic derivatives of charge-transport hosts are successfully applied in host-guest LECs. The performance of these LECs depends on the amount and type of the ions. For a blue LEC, we achieve high colour stability and a maximum efficacy of 5 cd A<sup>-1</sup> at a luminance of 420 cd m<sup>-2</sup>. One can modify neutral charge-

transporters with a suitable ionic group to optimize their performance in organic electronics.

## Experimental

### Materials and methods

Purification and handling of all compounds were carried out under air. All products were stored in the dark. Chemicals from commercial suppliers were used without purification. Chromatography was performed on a column with an i.d. of 30 mm on silica gel 60 (Fluka, Nr 60752). The progress of reactions and the elution of products were followed on TLC plates (silica gel 60 F<sub>254</sub> on aluminum sheets, Merck).

Elemental analyses were performed by Dr E. Solari, Service for Elemental Analysis, Institute of Chemical Sciences and Engineering (ISIC EPFL). <sup>1</sup>H and <sup>13</sup>C NMR spectra were recorded with Bruker AV400 (400 MHz) and AVIII-400 (400 MHz) spectrometers. Mass spectra were recorded with Q-TOF Ultima (Waters) and TSQ7000 (Thermo Fisher) spectrometers (Mass-Spectroscopy Service, ISIC EPFL).

### Synthesis of NMS25

**Imidazolium salt, 1.** The reaction was performed under air while protected from the moisture with a CaCl<sub>2</sub>-filled tube. 1,6-Dibromohexane (5 mL, 7.9 g, 32 mmol, excess, Fluka) was added to a solution of 1-methylimidazole (1 mL, 1.03 g, 12.5 mmol, Fluka) in acetone (10 mL) at RT. The mixture was stirred at 40 °C overnight to give a white suspension. It was filtered to remove white solid, which is the bis-substituted by-product. The solid was washed with acetone and discarded. The combined filtrates were rotor-evaporated to remove the acetone. Chromatography was performed on silica (20 g) with CH<sub>2</sub>Cl<sub>2</sub> to remove the starting material and with 5–10% of CH<sub>3</sub>OH in CH<sub>2</sub>Cl<sub>2</sub> to recover the product (TLC were developed with I<sub>2</sub>; the bis-substituted imidazolium salt follows the product). Viscous pale yellow oil: 2.56 g (7.85 mmol, 63%; C<sub>10</sub>H<sub>18</sub>Br<sub>2</sub>N<sub>2</sub>; *M*<sub>w</sub> 326.07). <sup>1</sup>H NMR (400 MHz, DMSO-*d*<sub>6</sub>):  $\delta$  = 9.12 (s, 1H), 7.79–7.75 (m, 1H), 7.72–7.68 (m, 1H), 4.15 (t, *J* = 7.2 Hz, 2H), 3.84 (s, 3H), 3.52 (t, *J* = 6.8 Hz, 2H), 1.83–1.73 (m, 4H), 1.45–1.35 (m, 2H), 1.30–1.20 (m, 2H) ppm. ESI<sup>+</sup> MS: *m/z* 245.3 ([*M* – Br]<sup>+</sup>, 100%).

**Scaled-up synthesis.** 1-Methylimidazole (2 mL, 2.06 g, 25 mmol) and 1,6-dibromohexane (15 mL, 24 g, 97 mmol, excess) in acetone (25 mL) gave 6 g (18.4 mmol, 74%) of the product. Chromatography was performed on silica (30 g) with 0–1% CH<sub>3</sub>OH in CH<sub>2</sub>Cl<sub>2</sub> to remove the starting material and with 7.5% CH<sub>3</sub>OH in CH<sub>2</sub>Cl<sub>2</sub> to recover 1.

**Di-*tert*-butyl carbazole, 2.** The reaction was performed under argon in dry solvents. Carbazole (5 g, 29.9 mmol) was suspended in CH<sub>2</sub>Cl<sub>2</sub> (100 mL) at RT. AlCl<sub>3</sub> (4 g, 29.9 mmol, Sigma-Aldrich) was added to give a brown suspension. It was cooled to 0 °C and a solution of *tert*-butyl chloride (6.51 mL, 5.53 g, 59.8 mmol, Aldrich) in CH<sub>2</sub>Cl<sub>2</sub> (20 mL) was added drop-wise over 10 min to give a dark yellow suspension. It was allowed to warm to RT, and it was stirred overnight to give brown solution. It was cooled in an ice bath and very cautiously quenched with ice [**Caution:** the quenching is highly exothermic and has an



induction period (!); external cooling (ice bath) is recommended]. Extraction with water and  $\text{CH}_2\text{Cl}_2$  provided at first an orange cloudy organic layer that after multiple washings with water became pale yellow and clear. Hexane (100 mL) was added and  $\text{CH}_2\text{Cl}_2$  was rotor-evaporated to provide a suspension of the product in hexane. It was cooled to RT. The solid was filtered (the filtrate was yellow) and washed with a small volume of hexane. White crystalline solid: 2.90 g (10.4 mmol, 35%). Anal. calcd for  $\text{C}_{20}\text{H}_{25}\text{N}$  ( $M_{\text{W}}$  279.42): C, 85.97; H, 9.02; N, 5.01. Found: C, 86.06; H, 8.94; N, 4.98.  $^1\text{H}$  NMR (400 MHz,  $\text{DMSO}-d_6$ ):  $\delta$  = 10.90 (s, 1H), 8.12 (d,  $J$  = 1.2 Hz, 2H), 7.41 (dd,  $J$  = 8.4, 1.6 Hz, 2H), 7.34 (d,  $J$  = 8.4 Hz, 2H), 1.39 (s, 18H) ppm.  $^{13}\text{C}$  NMR (100 MHz,  $\text{CDCl}_3$ ):  $\delta$  = 142.5, 138.3, 123.8, 123.5, 116.4, 110.3, 35.0, 32.3 ppm. ESI<sup>+</sup> MS:  $m/z$  280.3 ( $\{\text{M} + \text{H}\}^+$ , 100%).

**Aryl carbazole, 3.** The reaction was performed under argon in dry solvents.<sup>35</sup> 3-Iodoanisole (0.45 mL, 0.88 g, 3.77 mmol, small excess, Aldrich), di-*tert*-butyl carbazole **2** (1 g, 3.58 mmol),  $\text{Cs}_2\text{CO}_3$  (3.7 g, 11 mmol, excess, Aldrich),  $\text{Cu}_2\text{O}$  powder (<5  $\mu\text{m}$ , 74 mg, 0.52 mmol, catalyst, Aldrich) in DMF (4.5 mL; 99.8%, extra dry over molecular sieve, AcroSeal, Acros) were stirred at 120 °C for 24 h to give a brownish-green suspension. It was cooled to RT, and it was extracted with water and ether (dark brown solid remains at the phase interface, and the aqueous phase remains a brown suspension). The organic layer was washed with water and evaporated. Chromatography was performed on silica (15 g) with hexane– $\text{CH}_2\text{Cl}_2$  (6/1) to provide the crude product as colourless oil (the starting carbazole is one of the main impurities). It was dissolved in a minimum volume (5 mL) of  $\text{CH}_2\text{Cl}_2$ . Ethanol (15 mL) was added and  $\text{CH}_2\text{Cl}_2$  was rotor-evaporated leaving a suspension of the product in ethanol (the compound easily forms oversaturated ethanol solution; sonication, scratching and seeding may be required to induce the precipitation). The suspension was cooled to 0 °C, filtered, and washed with a small volume of cold (−15 °C) ethanol. White solid: 927 mg (2.40 mmol, 67%;  $\text{C}_{27}\text{H}_{31}\text{NO}$ ;  $M_{\text{W}}$  385.54).  $^1\text{H}$  NMR (400 MHz,  $\text{CDCl}_3$ ):  $\delta$  = 8.16 (d,  $J$  = 2.0 Hz, 2H), 7.56–7.46 (m, 3H), 7.41 (d,  $J$  = 8.8 Hz, 2H), 7.20–7.16 (m, 1H), 7.13 (t,  $J$  = 2.0 Hz, 1H), 7.00 (dd,  $J$  = 8.4, 2.4 Hz, 1H), 3.88 (s, 3H), 1.50 (s, 18H) ppm. **3** is soluble in hexane.

**Scaled-up synthesis.** 3-Iodoanisole (1.8 mL, 3.53 g, 15.1 mmol), di-*tert*-butyl carbazole **2** (4 g, 14.3 mmol),  $\text{Cs}_2\text{CO}_3$  (17 g, 52 mmol),  $\text{Cu}_2\text{O}$  powder (296 mg, 1.55 mmol) in DMF (12 mL; 99.8%, extra dry over molecular sieve, AcroSeal, Acros) were stirred at 120 °C for 24 h. Chromatography on silica (20 g) and re-crystallization from  $\text{CH}_2\text{Cl}_2$  and ethanol (20 mL) gave 4.6 g (11.9 mmol, 83%) of **3**.

**Phenol-carbazole, 4.** The reaction was performed under argon. Aryl carbazole **3** (450 mg, 1.17 mmol) and pyridine hydrochloride ( $\text{Py} \cdot \text{HCl}$ , 15 g, 0.13 mol, excess, used as a reagent and as a solvent, Aldrich) were stirred at 200 °C for 6 h to give pale green solution. It was cooled to RT. The solid reaction mixture was extracted with  $\text{CH}_2\text{Cl}_2$ –water. The organic layer was thoroughly washed with water to remove  $\text{Py} \cdot \text{HCl}$ . Evaporation provided pale-violet foam. Chromatography was performed on silica (12 g) with hexane– $\text{CH}_2\text{Cl}_2$  (3/1) to remove the starting material and with hexane– $\text{CH}_2\text{Cl}_2$  (1/2) to recover the product as a colourless fraction (the fraction may look pale yellow on the

column; a yellow impurity follows the product; intensely coloured by-products remain at the top of the column). Colourless or pale yellow oil which easily foams and slowly solidifies to white or pale green solid: 256 mg (0.69 mmol, 59%;  $\text{C}_{26}\text{H}_{29}\text{NO}$ ;  $M_{\text{W}}$  371.51). The yield can be improved by extending the reaction time.  $^1\text{H}$  NMR (400 MHz,  $\text{DMSO}-d_6$ ):  $\delta$  = 9.9 (s, br, 1H, OH), 8.27 (d,  $J$  = 1.6 Hz, 2H), 7.47 (dd,  $J$  = 8.8, 2.0 Hz, 2H), 7.43 (t,  $J$  = 8.0 Hz, 1H), 7.32 (dd,  $J$  = 8.8, 0.4 Hz, 2H), 6.99 (ddd,  $J$  = 8.0, 2.0, 0.8 Hz, 1H), 6.93 (t,  $J$  = 2.0 Hz, 1H), 6.88 (ddd,  $J$  = 8.0, 2.4, 0.8 Hz, 1H), 1.41 (s, 18H) ppm. Solid **4** turns green upon long exposure to air at RT, but it can be safely stored for indefinite time in a freezer.

**Scaled-up synthesis.** Aryl carbazole **3** (2.12 g, 5.49 mmol) and  $\text{Py} \cdot \text{HCl}$  (40 g, 0.35 mol) were stirred at 200 °C for 7.5 h. Chromatography on silica (30 g) gave 1.25 g (3.36 mmol, 61%) of **4**.

**Scaled-up synthesis.** Aryl carbazole **3** (4.6 g, 11.9 mmol) and  $\text{Py} \cdot \text{HCl}$  (80 g, 0.69 mol) were stirred at 200 °C for 8 h. Chromatography on silica (30 g) gave 3.18 g (8.56 mmol, 72%) of **4**.

#### Carbazole host, NMS25

**Batch 1.** The reaction was performed under argon in dry solvents. Phenol-carbazole **4** (241 mg, 0.65 mmol), imidazolium salt **1** (212 mg, 0.65 mmol), and  $\text{K}_2\text{CO}_3$  (90 mg, 0.65 mmol) were stirred in DMF (4 mL; 99.8%, extra dry over molecular sieve, AcroSeal, Acros) at 60 °C for 24 h to give a white suspension. It was diluted with water (100 mL) containing  $\text{KPF}_6$  (for anion exchange; 0.55 g, 2.99 mmol, excess). The resulting suspension was stirred for 30 min and filtered. The solid was washed with water and hexane. It was extracted with water– $\text{CH}_2\text{Cl}_2$ . The organic layer was washed with water and evaporated. Chromatography was performed on silica (15 g) with 0.5%  $\text{CH}_3\text{OH}$  in  $\text{CH}_2\text{Cl}_2$  to remove impurities and with 2%  $\text{CH}_3\text{OH}$  in  $\text{CH}_2\text{Cl}_2$  to recover the pure product. The product may separate as thick and easily foaming oil; in this case, mixing with ether and sonication followed by evaporation of the solvent converts the oil to a solid. White solid: 300 mg (0.44 mmol, 68%). Anal. calcd for  $\text{C}_{36}\text{H}_{46}\text{F}_6\text{N}_3\text{OP}$  ( $M_{\text{W}}$  681.73): C, 63.42; H, 6.80; N, 6.16. Found: C, 63.66; H, 6.84; N, 6.24.  $^1\text{H}$  NMR (400 MHz,  $\text{CD}_2\text{Cl}_2$ ):  $\delta$  = 8.55 (s, 1H), 8.18 (d,  $J$  = 2.0 Hz, 2H), 7.55–7.47 (m, 3H), 7.40 (d,  $J$  = 8.4 Hz, 2H), 7.25 (s, br, 1H), 7.22 (s, br, 1H), 7.17 (dd,  $J$  = 7.6, 1.2 Hz, 1H), 7.09 (t,  $J$  = 2.4 Hz, 1H), 7.00 (dd,  $J$  = 8.0, 2.0 Hz, 1H), 4.20 (t,  $J$  = 7.2 Hz, 2H), 4.04 (t,  $J$  = 6.0 Hz, 2H), 3.94 (s, 3H), 2.01–1.91 (m, 2H), 1.90–1.80 (m, 2H), 1.65–1.40 (m, 4H, obscured by signal of water protons), 1.48 (s, 18H) ppm.  $^1\text{H}$  NMR (400 MHz,  $\text{DMSO}-d_6$ ):  $\delta$  = 9.08 (s, 1H), 8.28 (d,  $J$  = 2.0 Hz, 2H), 7.76 (t,  $J$  = 1.6 Hz, 1H), 7.67 (t,  $J$  = 1.6 Hz, 1H), 7.54 (t,  $J$  = 8.0 Hz, 1H), 7.47 (dd,  $J$  = 8.4, 1.6 Hz, 2H), 7.32 (d,  $J$  = 8.4 Hz, 2H), 7.15 (d,  $J$  = 7.6 Hz, 1H), 7.10 (t,  $J$  = 2.0 Hz, 1H), 7.04 (dd,  $J$  = 8.4, 2.4 Hz, 1H), 4.15 (t,  $J$  = 6.8 Hz, 2H), 4.04 (t,  $J$  = 6.4 Hz, 2H), 3.82 (s, 3H), 1.86–1.69 (m, 4H), 1.41 (s, 18H), 1.52–1.20 (m, 2H), 1.37–1.26 (m, 2H) ppm.  $^{13}\text{C}$  NMR (100 MHz,  $\text{DMSO}-d_6$ ):  $\delta$  = 160.6, 143.2, 139.2, 139.2, 137.2, 131.5, 124.3, 124.3, 123.6, 122.9, 118.9, 117.3, 114.3, 112.7, 109.8, 68.3, 49.4, 36.4, 35.1, 32.5, 30.0, 29.1, 26.0, 25.6 ppm. ESI<sup>+</sup> TOF MS:  $m/z$  536.36 ( $\{\text{M} - \text{PF}_6\}^+$ , 100%).

**Batch 2, scaled-up synthesis.** Phenol-carbazole **4** (1.25 g, 3.36 mmol), imidazolium salt **1** (1.10 g, 3.37 mmol), and  $\text{K}_2\text{CO}_3$  (0.47 g, 3.40 mmol) in DMF (8 mL; 99.8%, extra dry over molecular sieve, AcroSeal, Acros) at 60 °C for 24 h gave a pale orange

suspension. Work-up with KPF<sub>6</sub> (for anion exchange; 4 g, 22 mmol) and chromatography on silica (35 g) with 0.5–2.0% CH<sub>3</sub>OH in CH<sub>2</sub>Cl<sub>2</sub> (pale green impurity precedes the product) gave 1.45 g of the product that contained a small amount of impurity. The product was dissolved in CH<sub>2</sub>Cl<sub>2</sub> (5 mL) and poured into ether (>200 mL). A solution formed at first, but a fine dense precipitate appeared after 1 min of stirring. It was filtered and washed with ether to provide the pure product: 1.38 g (2.03 mmol, 60%).

**Batch 3, scaled-up synthesis.** Phenol-carbazole **4** (3.18 g, 8.56 mmol), imidazolium salt **1** (2.79 g, 8.56 mmol), and K<sub>2</sub>CO<sub>3</sub> (1.20 g, 8.68 mmol) in DMF (9 mL; 99.8%, Extra Dry over Molecular Sieve, AcroSeal, Acros) at 60 °C for 24 h gave a pale orange suspension. Work-up was performed with KPF<sub>6</sub> (for anion exchange; 13 g, 71 mmol) and by chromatography on silica (30 g) with 0.5–2.0% CH<sub>3</sub>OH in CH<sub>2</sub>Cl<sub>2</sub>. The product was dissolved in CH<sub>2</sub>Cl<sub>2</sub> (15 mL) and poured into ether (>350 mL). A solution formed at first, but a fine dense precipitate appeared after 1 min of stirring. It was filtered and washed with ether to provide the pure product: 4.17 g (6.12 mmol, 71%).

**Electroluminescence devices.** All commercial materials were used as received: aqueous dispersion of poly(3,4-ethylenedioxythiophene):poly(styrenesulfonate) (PEDOT:PSS, CLEVIOS™ P VP Al 4083; Heraeus); ionic liquid (IL) 1-butyl-3-methyl-imidazolium tetrafluoroborate [Bmim][BF<sub>4</sub>] (Aldrich); **SPP013** and **FirPic** (Luminescence Technology Corp.).

The LEC devices were made as follows. Indium tin oxide ITO-coated glass plates were patterned by conventional photolithography (Naranjo Substrates). The substrates were cleaned ultrasonically in water-soap, water and 2-propanol baths. After drying, the substrates were placed in a UV-ozone cleaner (Jelight 42-220) for 20 min. An 80 nm layer of PEDOT:PSS was spin-coated on the ITO-glass substrate. For the emitting layer preparation, the devices were spin-coated at 1000 rpm for 30 s from an anisole solution containing hosts (with 10% wt of **FirPic**). To find the optimum ratio of **NMS25:SPP013** (matrix), we employed solutions with mass ratios of 1 : 0, 0.5 : 9.5, 2.5 : 7.5, 3.5 : 6.5, 1 : 1 (matrix + **FirPic**; 30 mg mL<sup>-1</sup>) for each device and we added [Bmim][BF<sub>4</sub>] to give a 4 : 1 molar ratio of matrix:IL. The effect of the IL was checked by preparing the emitting layer from a solution with a 1 : 1 mass ratio **NMS25:SPP013** (matrix + **FirPic**; 30 mg mL<sup>-1</sup>), without adding any IL. To test the effect of thickness, the solutions of 20, 30 and 40 mg mL<sup>-1</sup> with a 1 : 1 mass ratio **NMS25:SPP013** without IL were spin-coated to give a film thickness of 40, 80 and 100 nm, respectively. After deposition of the emitting layer, the devices were transferred into an inert atmosphere glovebox, where the aluminium electrode was thermally evaporated using a shadow mask. The size of the LEC was 6.5 mm<sup>2</sup>.

The thickness of the films was determined with an Ambios XP-1 profilometer. Thin film photoluminescence spectra and quantum yields were measured with a Hamamatsu C9920-02 Absolute PL Quantum Yield Measurement System. It consists of an excitation light source (a xenon lamp linked to a monochromator), an integration sphere and a multi-channel spectrometer. Time dependence of luminance and voltage was measured by applying pulsed current and by monitoring the

voltage and the luminance simultaneously by a True Colour Sensor MAZeT (MTCSICT Sensor) using a Lifetime Test System designed by BoTEST (Botest OLT OLED Lifetime-Test System). Electroluminescence spectra were recorded with an Avantes fiber-optics photo-spectrometer. The devices were not encapsulated and were characterized inside the glovebox.

## Acknowledgements

This work is supported by the European Union (CELLO, STRP 248043; <http://www.cello-project.eu/>) and the Spanish Ministry of Economy and Competitiveness (MINECO) (MAT2011-24594, CSD2007-00010, and CTQ2009-08790). A.P. and D.T. acknowledge the support of a FPI and FPU grant of the MINECO and MEC, respectively.

## References

- 1 S. Reineke, F. Lindner, G. Schwartz, N. Seidler, K. Walzer, B. Lüssem and K. Leo, *Nature*, 2009, **459**, 234.
- 2 K. Walzer, B. Maennig, M. Pfeiffer and K. Leo, *Chem. Rev.*, 2007, **107**, 1233.
- 3 L. Xiao, S.-J. Su, Y. Agata, H. Lan and J. Kido, *Adv. Mater.*, 2009, **21**, 1271.
- 4 C. Rothe, C.-J. Chiang, V. Jankus, K. Abdullah, X. Zeng, R. Jitchati, A. S. Batsanov, M. R. Bryce and A. P. Monkman, *Adv. Funct. Mater.*, 2009, **19**, 2038.
- 5 Q. B. Pei, G. Yu, C. Zhang, Y. Yang and A. J. Heeger, *Science*, 1995, **269**, 1086.
- 6 K. M. Maness, R. H. Terrill, T. J. Meyer, R. W. Murray and R. M. Wightman, *J. Am. Chem. Soc.*, 1996, **118**, 10609.
- 7 J. D. Slinker, A. A. Gorodetsky, M. S. Lowry, J. J. Wang, S. Parker, R. Rohl, S. Bernhard and G. G. Malliaras, *J. Am. Chem. Soc.*, 2004, **126**, 2763.
- 8 Q. J. Sun, Y. F. Li and Q. B. Pei, *J. Disp. Technol.*, 2007, **3**, 211.
- 9 R. D. Costa, E. Ortí, H. J. Bolink, F. Monti, G. Accorsi and N. Armaroli, *Angew. Chem., Int. Ed.*, 2012, **51**, 8178.
- 10 S. Tang, W.-Y. Tan, X.-H. Zhu and L. Edman, *Chem. Commun.*, 2013, **49**, 4926.
- 11 D. J. Dick, A. J. Heeger, Y. Yang and Q. B. Pei, *Adv. Mater.*, 1996, **8**, 985.
- 12 J. D. Slinker, J. A. DeFranco, M. J. Jaquith, W. R. Silveira, Y. W. Zhong, J. M. Moran-Mirabal, H. G. Craighead, H. D. Abruña, J. A. Marohn and G. G. Malliaras, *Nat. Mater.*, 2007, **6**, 894.
- 13 P. Matyba, K. Maturova, M. Kemerink, N. D. Robinson and L. Edman, *Nat. Mater.*, 2009, **8**, 672.
- 14 S. van Reenen, P. Matyba, A. Dzwilewski, R. A. J. Janssen, L. Edman and M. Kemerink, *J. Am. Chem. Soc.*, 2010, **132**, 13776.
- 15 M. Lenes, G. García-Belmonte, D. Tordera, A. Pertegás, J. Bisquert and H. J. Bolink, *Adv. Funct. Mater.*, 2011, **21**, 1581.
- 16 P. Zalar, Z. B. Henson, G. C. Welch, G. C. Bazan and T. Q. Nguyen, *Angew. Chem., Int. Ed.*, 2012, **51**, 7495.
- 17 E. Zysman-Colman, J. D. Slinker, J. B. Parker, G. G. Malliaras and S. Bernhard, *Chem. Mater.*, 2008, **20**, 388.

- 18 A. B. Tamayo, S. Garon, T. Sajoto, P. I. Djurovich, I. M. Tsyba, R. Bau and M. E. Thompson, *Inorg. Chem.*, 2005, **44**, 8723.
- 19 L. He, L. Duan, J. Qiao, R. J. Wang, P. Wei, L. D. Wang and Y. Qiu, *Adv. Funct. Mater.*, 2008, **18**, 2123.
- 20 M. K. Nazeeruddin, R. T. Wegh, Z. Zhou, C. Klein, Q. Wang, F. De Angelis, S. Fantacci and M. Grätzel, *Inorg. Chem.*, 2006, **45**, 9245.
- 21 M. Mydlak, C. Bizzarri, D. Hartmann, W. Sarfert, G. Schmid and L. De Cola, *Adv. Funct. Mater.*, 2010, **20**, 1812.
- 22 L. He, L. A. Duan, J. A. Qiao, G. F. Dong, L. D. Wang and Y. Qiu, *Chem. Mater.*, 2010, **22**, 3535.
- 23 B. Chen, Y. H. Li, W. Yang, W. Luo and H. B. Wu, *Org. Electron.*, 2011, **12**, 766.
- 24 S. Tang, A. Sandström, J. F. Fang and L. Edman, *J. Am. Chem. Soc.*, 2012, **134**, 14050.
- 25 A. Chaskar, H.-F. Chen and K.-T. Wong, *Adv. Mater.*, 2011, **23**, 3876.
- 26 A. R. Hosseini, C. Y. Koh, J. D. Slinker, S. Flores-Torres, H. D. Abruña and G. G. Malliaras, *Chem. Mater.*, 2005, **17**, 6114.
- 27 H. C. Su, C. C. Wu, F. C. Fang and K. T. Wong, *Appl. Phys. Lett.*, 2006, **89**, 26118.
- 28 H. C. Su, H. F. Chen, Y. C. Shen, C. T. Liao and K. T. Wong, *J. Mater. Chem.*, 2011, **21**, 9653.
- 29 C.-T. Liao, H.-F. Chen, H.-C. Su and K.-T. Wong, *Phys. Chem. Chem. Phys.*, 2012, **14**, 1262.
- 30 G. Kalyuzhny, M. Buda, J. McNeill, P. Barbara and A. J. Bard, *J. Am. Chem. Soc.*, 2003, **125**, 6272.
- 31 D. Tordera, J. Frey, D. Vonlanthen, E. C. Constable, A. Pertegás, E. Orti, H. J. Bolink, E. Baranoff and M. K. Nazeeruddin, *Adv. Energy Mater.*, 2013, **3**, 1338.
- 32 C. Y. Liu and A. J. Bard, *Appl. Phys. Lett.*, 2003, **83**, 5431.
- 33 H. J. Bolink, L. Cappelli, S. Cheylan, E. Coronado, R. D. Costa, N. Lardies, M. K. Nazeeruddin and E. Orti, *J. Mater. Chem.*, 2007, **17**, 5032.
- 34 S. B. Meier, W. Sarfert, J. M. Junquera-Hernandez, M. Delgado, D. Tordera, E. Orti, H. J. Bolink, F. Kessler, R. Scopelliti, M. Gratzel, M. K. Nazeeruddin and E. Baranoff, *J. Mater. Chem. C*, 2013, **1**, 58.
- 35 A. Correa and C. Bolm, *Adv. Synth. Catal.*, 2007, **349**, 2673.