

Three-Dimensional Salphen-Based Covalent Organic Frameworks as Catalytic Antioxidants

Shichen Yan, Xinyu Guan, Hui Li, Daohao Li, Ming Xue,
Yushan Yan, Valentin Valtchev, Shilun Qiu, and Qianrong Fang

J. Am. Chem. Soc., **Just Accepted Manuscript** • DOI: 10.1021/jacs.9b00485 • Publication Date (Web): 04 Feb 2019

Downloaded from <http://pubs.acs.org> on February 5, 2019

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.



Three-Dimensional Salphen-Based Covalent Organic Frameworks as Catalytic Antioxidants

Shichen Yan,[†] Xinyu Guan,[†] Hui Li,[†] Daohao Li,[†] Ming Xue,[†] Yushan Yan,[‡] Valentin Valtchev,^{‡,||} Shilun Qiu,[†] and Qianrong Fang^{*,†}

[†]State Key Laboratory of Inorganic Synthesis and Preparative Chemistry, Jilin University, Changchun 130012, P. R. China

[‡]Department of Chemical and Biomolecular Engineering, Center for Catalytic Science and Technology, University of Delaware, Newark, DE 19716, USA


^{||}Normandie Univ, ENSICAEN, UNICAEN, CNRS, Laboratoire Catalyse et Spectrochimie, 6 Marechal Juin, 14050 Caen, France

Supporting Information Placeholder

ABSTRACT: The development of three-dimensional (3D) functionalized covalent organic frameworks (COFs) is of critical importance for expanding their potential applications. However, the introduction of functional groups in 3D COFs remains largely unexplored. Herein we report the first example of 3D Salphen-based COFs (3D-Salphen-COFs) and their metal-containing counterparts (3D-M-Salphen-COFs). These Salphen-based COFs exhibit high crystallinity and specific surface area in addition to excellent chemical stability. Furthermore, the Cu(II)-Salphen COF displays high activity in the removal of superoxide radicals. This study not only presents a new pathway to construct 3D functionalized COFs, but also promotes their applications in biology and medicine.

Covalent organic frameworks (COFs), an emerging class of crystalline porous materials, are composed of pure organic skeletons connected by strong organic bonds.¹⁻⁶ Since the pioneering work of Yaghi in 2005, various COFs with different backbones and functional groups have been synthesized and employed as platforms for applications such as gas adsorption and separation,⁷⁻⁹ optoelectronics,^{10,11} heterogeneous catalysis,¹²⁻¹⁴ and a number of others.¹⁵⁻²¹ Yet most of the reported COFs are two-dimensional (2D) frameworks with eclipsed stacking structures.^{22,23} Three-dimensional (3D) COFs have recently attracted much attention due to their unique porous structures and outstanding performances.²⁴⁻²⁹ We have reported a series of 3D COFs by the meticulous design of building units, including 3D ionic COFs for selective ion exchange,³⁰ 3D ionic liquid containing COFs with high gas separation ability,³¹ 3D carboxy-functionalized COFs for selective extraction of lanthanide ions,³² and so on.³³⁻³⁵ It must be noted, however, that 3D COFs are still limited so far, and thus the development of 3D COFs, especially 3D functionalized COFs, is important for improving their structural diversity and widening their potential applications.

Scheme 1. Strategy for preparing 3D-Salphen-COFs^a

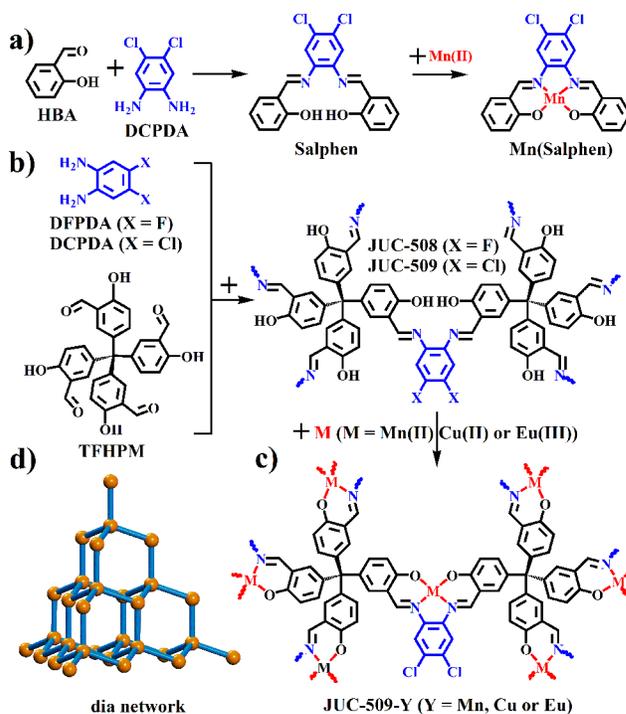

^a(a) The model reaction of Salphen unit and M-Salphen unit based on 2-hydroxybenzaldehyde (HBA) and 4,5-dichlorophenylene-1,2-diamine (DCPDA). (b) Condensation of tetrahedral tetrakis(3-formyl-4-hydroxyphenyl)methane (TFHPM) and two linkers containing diamine, 4,5-difluorophenylene-1,2-diamine (DFPDA) or DCPDA, to give novel 3D-Salphen-COFs, JUC-508 and JUC-509, respectively. (c) The preparation of 3D-M-Salphen-COFs, JUC-509-Y (Y = Mn, Cu or Eu), via the metal incorporation. (d) The non-interpenetrated **dia** network in 3D-Salphen-COFs.

Herein, we addressed the above issues by designing 3D Salphen-based COFs (3D-Salphen-COFs) and their corresponding metal-containing isostructures (3D-M-Salphen-COFs). The obtained COFs showed high crystallinity, open channels, good chemical stability and large specific surface area. Furthermore, various metal ions (Cu(II), Mn(II) and Eu(III)) were successfully incorporated into the Salphen-based COFs, as the Cu(II)-Salphen COF exhibited the best performance in eliminating deleterious oxygen-derived free radicals. To the best of our knowledge, this study is the first case of 3D Salphen-based COFs and the application of COF materials as catalytic antioxidants.

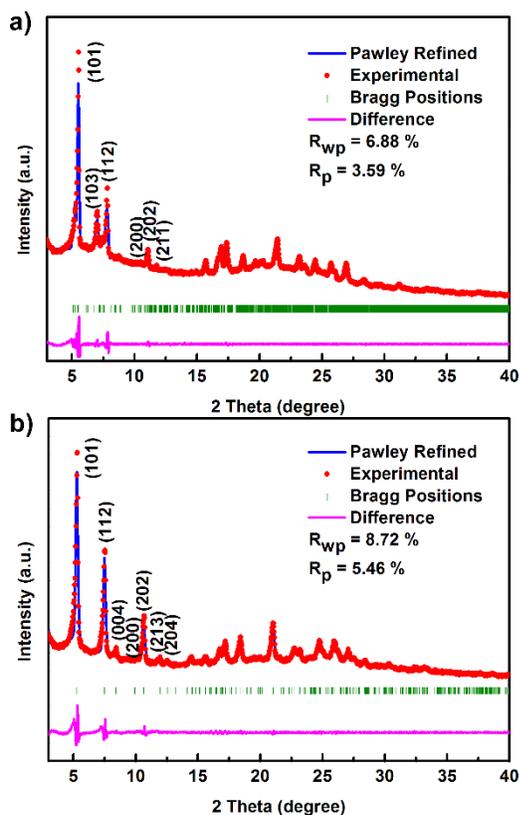


Figure 1. PXRD patterns of JUC-508 (a) and JUC-509 (b).

Our strategy for constructing 3D-Salphen-COFs embraces the form of both COF frameworks and Salphen units synchronously. As shown in Scheme 1a, 2-hydroxybenzaldehyde (HBA) and 4,5-dichlorophenylene-1,2-diamine (DCPDA) afford the model Salphen unit, which can be further assembled into Mn(II)-Salphen unit via the complexation (see the Supporting Information, SI, Section S1). On the basis of this reaction, we synthesized a tetrahedral salicylaldehyde-based monomer, tetrakis(3-formyl-4-hydroxyphenyl)methane (TFHPM). By the condensation of TFHPM and amino-based linkers, 4,5-difluorophenylene-1,2-diamine (DFPDA) or DCPDA, two extended 3D Salphen-based COFs, denoted as JUC-508 and JUC-509 respectively, can be obtained (Scheme 1b). Furthermore, JUC-509 can be gathered into 3D-M-Salphen-COFs by the introduction of Mn(II), Cu(II) or Eu(III) ions, denoted as JUC-509-Y (Y = Mn, Cu or Eu, Scheme 1c). Based on this design, TFHPM can be defined as a 4-connected node, and DFPDA or DCPDA can act as a 2-connected node, which results in the 3D network with the non-interpenetrated **dia** topology due to the steric effect of Salphen unit (Scheme 1d).³⁶

Typically, 3D-Salphen-COFs were synthesized by suspending TFHPM with DFPDA or DCPDA in the mixed solvent of dioxane and mesitylene in the presence of acetic acid followed by heating at 120 °C for 3 days. Complementary characterization have been employed for detailed structural definition of new materials. Scanning electron microscopy (SEM) and transmission electron microscopy (TEM) images of 3D-Salphen-COFs showed flower-like microstructure composed of prismatic several micrometers long crystals (Figures S1-S4). Peaks around 1616 cm^{-1} for JUC-508 and 1618 cm^{-1} for JUC-509 in Fourier transform infrared (FTIR) spectra indicated the formation of imine linkages, which is similar to that from the model Salphen unit (1614 cm^{-1} for imine bands), and the disappearance of peaks at 1659 cm^{-1} for both 3D-Salphen-COFs confirmed the complete transformation of aldehyde groups (Figures S5 and S6). The solid state ^{13}C cross-polarization magic-angle-spinning (CP/MAS) NMR spectra further confirmed the presence of carbon from the C=N bond at 163 ppm for JUC-508 and 161 ppm for JUC-509 (Figures S8 and S9). According to the thermogravimetric analysis (TGA), both 3D-Salphen-COFs are stable up to about 350 °C under nitrogen (Figures S10 and S11). Notably, their crystalline structures can be preserved in a variety of organic solvents and the aqueous solutions at pH = 1~14 (Figures S15-S18).

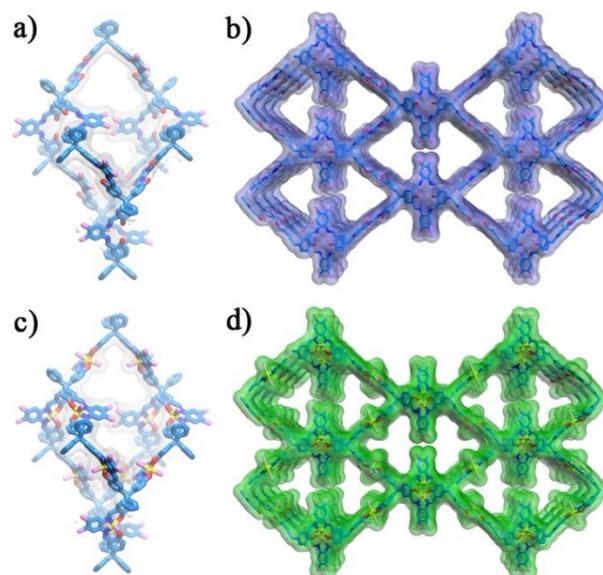


Figure 2. Structural representations of JUC-509 (a and b) and JUC-509-Y (c and d).

The crystal structures of 3D-Salphen-COFs were resolved by the powder X-ray diffraction (PXRD) measurements in conjunction with structural simulations (Figure 1). After a geometrical energy minimization by using the Materials Studio software package³⁷ based on non-interpenetrated **dia** net for 3D-Salphen-COFs, the unit cell parameters were obtained ($a = b = 19.153 \text{ \AA}$, $c = 41.988 \text{ \AA}$ and $\alpha = \beta = \gamma = 90^\circ$ for JUC-508; $a = b = 18.983 \text{ \AA}$, $c = 42.202 \text{ \AA}$ and $\alpha = \beta = \gamma = 90^\circ$ for JUC-509). Furthermore, full profile pattern matching (Pawley) refinements were carried out on the experimental PXRD patterns. Peaks at 5.41, 7.19, 8.02, 10.31, 10.84 and 11.65° for JUC-508 correspond to the (101), (103), (112), (200), (202) and (211) Bragg peaks of space group $I-42d$ (No. 122), respectively; peaks at 5.10, 7.80, 8.37, 9.31, 10.21, 12.17 and 12.53° for JUC-509 correspond to the (101), (112), (004), (200), (202), (213) and (204) Bragg peaks of space group $I-$

42d, respectively. The refinement results matched well with the observed patterns with good agreement factors ($R_{\omega p} = 6.88\%$ and $R_p = 3.59\%$ for JUC-508; $R_{\omega p} = 8.72\%$ and $R_p = 5.46\%$ for JUC-509). We also considered the alternative structures based on the 2-fold interpenetrated **dia** net from the same space group of *I*-42d for both 3D-Salphen-COFs; however, their simulated patterns did not match to the experimental ones (Figures S19-22). On the basis of the above results, these Salphen COFs were proposed to have the expected architectures with non-interpenetrated **dia** topology, which show microporous cavities with a diameter of about 1.2 nm (Figure 2 and Figure S23). Remarkably, almost all of 3D COFs with **dia** topology show multifold interpenetrated structures, and thus the successful preparation of 3D-Salphen-COFs with non-interpenetrated nets will benefit the development of 3D COFs with large pores.

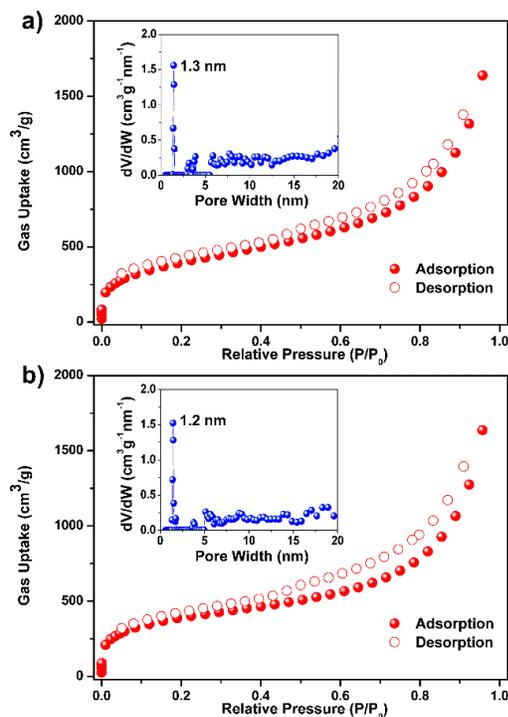


Figure 3. N_2 adsorption-desorption isotherms of JUC-508 (a) and JUC-509 (b). Inset: pore-size distribution calculated by fitting on the NLDFT model to the adsorption data.

The porosity and surface areas were measured by N_2 adsorption and desorption analysis (Figure 3). Both materials show a sharp uptake at a low pressure of $P/P_0 < 0.05$, which is characteristic of the microporous material. The inclination of isotherms in the 0.8-1.0 P/P_0 range and slight desorption hysteresis show the presence of textural mesopores, which is the consequence of the agglomeration of COF crystals.³⁴ The Brunauer-Emmett-Teller (BET) equation was applied over the $0.05 < P/P_0 < 0.30$ range of the isotherms, revealing BET surface areas of $1513 \text{ m}^2 \text{ g}^{-1}$ for JUC-508 and $1443 \text{ m}^2 \text{ g}^{-1}$ for JUC-509 (Figures S27 and S28). Pore size distributions of 3D-Salphen-COFs calculated by nonlocal density functional theory (NLDFT) showed pore with sizes of 1.3 nm for JUC-508 and 1.2 nm for JUC-509, respectively (Figure 3, inset), which is in good agreement with that of the proposed model (1.2 nm).

Encouraged by their high surface area and abundant Salphen units, a series of 3D-M-Salphen-COFs were subsequently acquired by immersing JUC-509 in a methanol solution of

relative metal salts, giving JUC-509-Y (Y = Mn, Cu or Eu). The metal complexation of Salphen COFs could be easily visualized by their color change (Figure S30). Meanwhile, scanning electron microscope-energy dispersive X-ray spectra (SEM-EDS) analysis exhibited the uniform distribution of metal ions in the crystals (Figure S31). The ICP analysis of the resulting M-Salphen COFs showed that most of the Salphen pockets have been occupied by the metal ions (see Section S1 in SI). FTIR spectroscopy indicated the strong interaction between Salphen-COF and metal ions based on the shift of the IR bands for the imine groups from 1618 cm^{-1} (JUC-509) to 1608 cm^{-1} (JUC-509-Cu), 1606 cm^{-1} (JUC-509-Mn) or 1606 cm^{-1} (JUC-509-Eu), which is similar with the results from the model Salphen unit to Mn(II)-Salphen unit (from 1614 cm^{-1} to 1603 cm^{-1} , Figure S7). X-ray photoelectron spectroscopy (XPS) suggested Cu and Mn were in the +2 oxidation state and Eu was in the +3 oxidation state (Figures S32-34). In addition, the retained PXRD patterns of 3D-M-Salphen-COFs pointed out that the crystalline structure was preserved after the metal incorporation (Figure 2 and Figures S24-26). The porosities were evaluated by N_2 adsorption and desorption analysis, which showed values slightly lower than that of the pristine material (Figure S29).

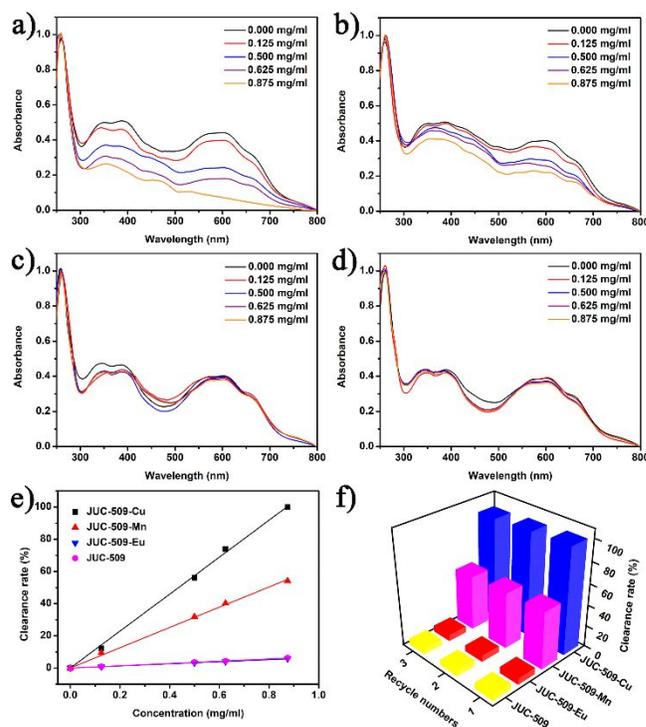


Figure 4. Adsorption spectra of JUC-509-Cu (a), JUC-509-Mn (b), JUC-509-Eu (c) and JUC-509 (d) in antioxidant experiments. (e) The clearance rate based on different concentration. (f) Recyclability study of JUC-509-Cu, JUC-509-Mn, JUC-509-Eu and JUC-509.

We further explored the application of M-Salphen COFs in the removal of superoxide radical anion ($\text{O}_2^{\cdot-}$). It is well known that the overproduction of $\text{O}_2^{\cdot-}$ has been shown to contribute to tissue damage and injury.³⁸ Salens or Salphens with redox-active metal centers are considered as major catalytic antioxidants that catalyze the dismutation reaction of $\text{O}_2^{\cdot-}$ similar to superoxide dismutases (SODs).³⁹ However, the employments of traditional Salphens are strongly limited because of stability and recyclability issues. Herein, 3D-M-Salphen-COFs were chosen as effective oxygen radical removal

agents due to their high surface area, chemical stability and reusability. In addition, similar to those Salphen-based metal complexes for superoxide radicals removal, Salphen-based COFs are also biocompatible.⁴⁰

Typically, $O_2^{\cdot-}$ was generated under sunlight in the presence of methionine and riboflavin, and further reacted with nitrotriazolium blue chloride (NBT) to form a deep blue complex, which exhibited a characteristic absorption at about 560 nm in the UV-Vis spectroscopy.⁴⁰ As shown in Figure 4, 3D-M-Salphen-COFs had different activity in the elimination of superoxide radicals accompanied by the change of catalyst concentration. Among them, JUC-509-Eu had no obvious antioxidant activity, and JUC-509-Cu displayed the best performance (almost 100% clearance rate in only 0.875 mg/ml), which can be attributed to the high catalytic effect of Cu(II) ion.⁴¹ As a comparison, the metal-free pristine material, JUC-509, was tested under the same condition, and showed no evidence for the removal of $O_2^{\cdot-}$ (Figure 4d and 4e), which further demonstrated the critical role of redox-active metal centers in antioxidant activity. ICP analysis of the filtrate after the reaction revealed almost no leaching of metal ions (see Section S1 in SI). PXRDs showed that the recovered solid remained crystalline and structurally intact (Figures S24-26). Most importantly, these M-Salphen COF catalysts can be readily recycled and reused at least three times without obvious loss of activity (Figure 4f). Compared with other common catalytic antioxidants, 3D-M-Salphen-COFs need higher concentrations to remove the oxygen radicals due to their high molecular weight; however, these COFs as heterogeneous catalysts can be easily recycled and reused, which is superior to most of reported catalytic antioxidants.

In conclusion, we have for the first time designed and synthesized 3D-Salphen-COFs and 3D-M-Salphen-COFs. These Salphen-based COFs showed high crystallinity, BET surface area, and chemical stability. Furthermore, the Cu(II)-Salphen COF displayed high performance in the removal of superoxide radicals and could be reused without significant activity loss. 3D Salphen-based COFs successfully prepared in this work may not only open a new pathway to create 3D functionalized COFs, but also expand the applications of COF materials in biology and medicine.

ASSOCIATED CONTENT

Supporting Information

Synthetic procedures, SEM, TEM, FTIR, solid state ^{13}C NMR, TGA, and BET plots. This material is available free of charge via the internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

*qrfang@jlu.edu.cn

Notes

The authors declare no competing financial interests.

ACKNOWLEDGMENT

This work was supported by National Natural Science Foundation of China (21571079, 21621001, 21390394, 21571076, and 21571078), "111" project (B07016 and B17020), Guangdong and Zhuhai Science and Technology Department Project (2012D0501990028), and the program for JLU Science and Technology Innovative Research Team. Q.F

and V.V. acknowledge the support from Thousand Talents program (China).

REFERENCES

- (1) Côté, A. P.; Benin, A. I.; Ockwig, N. W.; O'Keffe, M.; Matzger, A. J.; Yaghi, O. M. Porous, Crystalline, Covalent Organic Frameworks. *Science* **2005**, *310*, 1166.
- (2) Colson, J. W.; Woll, A. R.; Mukherjee, A.; Levendorf, M. P.; Spitler, E. L.; Shields, V. B.; Spencer, M. G.; Park, J.; Dichtel, W. R. Oriented 2D Covalent Organic Framework Thin Films on Single-Layer Graphene. *Science* **2011**, *332*, 228.
- (3) Ding, S. Y.; Wang, W. Covalent organic frameworks (COFs): from design to applications. *Chem. Soc. Rev.* **2013**, *42*, 548.
- (4) Huang, N.; Wang, P.; Jiang, D. L. Covalent organic frameworks: a materials platform for structural and functional designs. *Nat. Rev. Mater.* **2016**, *1*, 16068.
- (5) Fang, Q. R.; Zhuang, Z. B.; Gu, S.; Kaspar, R. B.; Zheng, J.; Wang, J. H.; Qiu, S. L.; Yan, Y. S. Designed synthesis of large-pore crystalline polyimide covalent organic frameworks. *Nat. Commun.* **2014**, *5*, 4503.
- (6) Wang, H.; Zeng, Z.; Xu, P.; Li, L.; Zeng, G.; Xiao, R.; Tang, Z.; Huang, D.; Tang, L.; Lai, C.; Jiang, D.; Liu, Y.; Yi, H.; Qin, L.; Ye, S.; Ren, X.; Tang, W. Recent progress in covalent organic framework thin films: fabrications, applications and perspectives. *Chem. Soc. Rev.* **2019**, *48*, 488.
- (7) Kuhn, P.; Antonietti, M.; Thomas, A. Porous, Covalent Triazine-Based Frameworks Prepared by Ionothermal Synthesis. *Angew. Chem. Int. Ed.* **2008**, *47*, 3450.
- (8) Furukawa, H.; Yaghi, O. M. Storage of Hydrogen, Methane, and Carbon Dioxide in Highly Porous Covalent Organic Frameworks for Clean Energy Applications. *J. Am. Chem. Soc.* **2009**, *131*, 8875.
- (9) Doonan, C. J.; Tranchemontagne, D. J.; Glover, T. G.; Hunt, J. R.; Yaghi, O. M. Exceptional ammonia uptake by a covalent organic framework. *Nat. Chem.* **2010**, *2*, 235.
- (10) Wan, S.; Guo, J.; Kim, J.; Ihee, H.; Jiang, D. A Belt-Shaped, Blue Luminescent, and Semiconducting Covalent Organic Framework. *Angew. Chem. Int. Ed.* **2008**, *47*, 8826.
- (11) Du, Y.; Yang, H.; Whiteley, J. M.; Wan, S.; Jin, Y.; Lee, S. H.; Zhang, W. Ionic Covalent Organic Frameworks with Spiroborate Linkage. *Angew. Chem. Int. Ed.* **2016**, *55*, 1737.
- (12) Ding, S. Y.; Gao, J.; Wang, Q.; Zhang, Y.; Song, W. G.; Su, C. Y.; Wang, W. Construction of Covalent Organic Framework for Catalysis: Pd/COF-LZU1 in Suzuki-Miyaura Coupling Reaction. *J. Am. Chem. Soc.* **2011**, *133*, 19816.
- (13) Li, L. H.; Feng, X. L.; Cui, X. H.; Ma, Y. X.; Ding, S. Y.; Wang, W. Salen-Based Covalent Organic Framework. *J. Am. Chem. Soc.* **2017**, *139*, 6042.
- (14) Han, X.; Xia, Q. C.; Huang, J. J.; Liu, Y.; Tan, C. X.; Cui, Y. Chiral Covalent Organic Frameworks with High Chemical Stability for Heterogeneous Asymmetric Catalysis. *J. Am. Chem. Soc.* **2017**, *139*, 8693.
- (15) Kandambeth, S.; Mallick, A.; Lukose, B.; Mane, M. V.; Heine, T.; Banerjee, R. Construction of Crystalline 2D Covalent Organic Frameworks with Remarkable Chemical (Acid/Base) Stability via a Combined Reversible and Irreversible Route. *J. Am. Chem. Soc.* **2012**, *134*, 19524.
- (16) Calik, M.; Auras, F.; Salonen, L. M.; Bader, K.; Grill, I.; Handloser, M.; Medina, D. D.; Dogru, M.; Löbermann, F.; Trauner, D.; Hartschuh, A.; Bein, T. Extraction of Photogenerated Electrons and Holes from a Covalent Organic Framework Integrated Heterojunction. *J. Am. Chem. Soc.* **2014**, *136*, 17802.
- (17) Zhou, T. Y.; Xu, S. Q.; Wen, Q.; Pang, Z. F.; Zhao, X. One-Step Construction of Two Different Kinds of Pores in a 2D Covalent Organic Framework. *J. Am. Chem. Soc.* **2014**, *136*, 15885.
- (18) Peng, Y. W.; Xu, G. D.; Hu, Z. G.; Cheng, Y. D.; Chi, C. L.; Yuan, D. Q.; Cheng, H. S.; Zhao, D. Mechanoassisted Synthesis of Sulfonated Covalent Organic Frameworks with High Intrinsic Proton Conductivity. *ACS Appl. Mater. Interfaces* **2016**, *8*, 18505.
- (19) Wang, S.; Wang, Q.; Shao, P.; Han, Y.; Gao, X.; Ma, L.; Yuan, S.; Ma, X.; Zhou, J.; Feng, X.; Wang, B. Exfoliation of Covalent Organic Frameworks into Few-layer Redox-Active Nanosheets as Cathode Materials for Lithium-Ion Batteries. *J. Am. Chem. Soc.* **2017**, *139*, 4258.

- (20) Sun, Q.; Aguila, B.; Perman, J.; Earl, L. D.; Abney, C. W.; Cheng, Y.; Wei, H.; Nguyen, N.; Wojtas, L.; Ma, S. Q. Postsynthetically Modified Covalent Organic Frameworks for Efficient and Effective Mercury Removal. *J. Am. Chem. Soc.* **2017**, *139*, 2786.
- (21) Jin, E. Q.; Asada, M.; Xu, Q.; Dalapati, S.; Addicoat, M. A.; Brady, M. A.; Xu, H.; Nakamura, T.; Heine, T.; Chen, Q. H.; Jiang, D. L. Two-dimensional sp^2 carbon-conjugated covalent organic frameworks. *Science* **2017**, *357*, 673.
- (22) Colson, J. W.; Dichtel, W. R. Rationally synthesized two-dimensional polymers. *Nat. Chem.* **2013**, *5*, 453.
- (23) Diercks, C. S.; Yaghi, O. M. The atom, the molecule, and the covalent organic framework. *Science* **2017**, *355*, 923.
- (24) El-Kaderi, H. M.; Hunt, J. R.; Mendoza-Cortés, J. L.; Côté, A. P.; Taylor, R. E.; O'Keeffe, M.; Yaghi, O. M. Designed Synthesis of 3D Covalent Organic Frameworks. *Science* **2007**, *316*, 268.
- (25) Zhang, Y. B.; Su, J.; Furukawa, H.; Yun, Y. F.; Gándara, F.; Duong, A.; Zou, X. D.; Yaghi, O. M. Single-Crystal Structure of a Covalent Organic Framework. *J. Am. Chem. Soc.* **2013**, *135*, 16336.
- (26) Beaudoin, D.; Maris, T.; Wuest, J. D. Constructing monocrystalline covalent organic networks by polymerization. *Nat. Chem.* **2013**, *5*, 830.
- (27) Lin, G. Q.; Ding, H. M.; Yuan, D. Q.; Wang, B. S.; Wang, C. A pyrene-Based, Fluorescent Three-Dimensional Covalent Organic Framework. *J. Am. Chem. Soc.* **2016**, *138*, 3302.
- (28) Yahiaoui, O.; Fitch, A. N.; Hoffmann, F.; Fröba, M.; Thomas, A.; Roeser, J. 3D Anionic Silicate Covalent Organic Framework with srs Topology. *J. Am. Chem. Soc.* **2018**, *140*, 5330.
- (29) Ma, T. Q.; Kapustin, E. A.; Yin, S. X.; Liang, L.; Zhou, Z. Y.; Niu, J.; Li, L. H.; Wang, Y. Y.; Su, J.; Wang, X. G.; Wang, W. D.; Wang, W.; Sun, J. L.; Yaghi, O. M. Single-crystal x-ray diffraction structures of covalent organic frameworks. *Science* **2018**, *361*, 48.
- (30) Li, Z. L.; Li, H.; Guan, X. Y.; Tang, J. J.; Yusran, Y.; Li, Z.; Xue, M.; Fang, Q. R.; Yan, Y. S.; Valtchev, V.; Qiu, S. L. Three-Dimensional Ionic Covalent Organic Frameworks for Rapid, Reversible and Selective Ion Exchange. *J. Am. Chem. Soc.* **2017**, *139*, 17771.
- (31) Guan, X. Y.; Ma, Y. C.; Li, H.; Yusran, Y.; Xue, M.; Fang, Q. R.; Yan, Y. S.; Valtchev, V.; Qiu, S. L. Fast, Ambient Temperature and Pressure Ionothermal Synthesis of Three-Dimensional Covalent Organic Frameworks. *J. Am. Chem. Soc.* **2018**, *140*, 4494.
- (32) Lu, Q. Y.; Ma, Y. C.; Li, H.; Guan, X. Y.; Yusran, Y.; Xue, M.; Fang, Q. R.; Yan, Y. S.; Qiu, S. L.; Valtchev, V. Postsynthetic Functionalization of Three-Dimensional Covalent Organic Framework for Selective Extraction of Lanthanide Ions. *Angew. Chem. Int. Ed.* **2018**, *57*, 6042.
- (33) Li, H.; Pan, Q. Y.; Ma, Y. C.; Guan, X. Y.; Xue, M.; Fang, Q. R.; Yan, Y. S.; Valtchev, V.; Qiu, S. L. 3D Covalent Organic Frameworks with Dual Linkages for Bifunctional Cascade Catalysis. *J. Am. Chem. Soc.* **2016**, *138*, 14783.
- (34) Fang, Q. R.; Wang, J. H.; Gu, S.; Kaspar, R. B.; Zhuang, Z. B.; Zheng, J.; Guo, H. X.; Qiu, S. L.; Yan, Y. S. 3D Porous Crystalline Polyimide Covalent Organic Frameworks for Drug Delivery. *J. Am. Chem. Soc.* **2015**, *137*, 8352.
- (35) Fang, Q. R.; Gu, S.; Zheng, J.; Zhuang, Z. B.; Qiu, S. L.; Yan, Y. S. 3D Microporous Base-Functionalized Covalent Organic Frameworks for Size-Selective Catalysis. *Angew. Chem., Int. Ed.* **2014**, *53*, 2878.
- (36) Delgado-Friedrichs, O.; O'Keeffe, M.; Yaghi, O. M. Three-periodic nets and tilings: edge-transitive binodal structures. *Acta Crystallogr. Sect. A* **2006**, *62*, 350.
- (37) *Materials Studio ver. 7.0*; Accelrys Inc.; San Diego, CA.
- (38) Gilgun-Sherki, Y.; Melamed, E.; Offen, D. Oxidative stress induced-neurodegenerative diseases: the need for antioxidants that penetrate the blood brain barrier. *Neuropharmacology* **2001**, *40*, 959.
- (39) Bian, H. D.; Wang, J.; Wei, Y.; Tang, J.; Huang, F. P.; Yao, D.; Yu, Q.; Liang, H. Superoxide dismutase activity studies of Mn(III)/Cu(II)/Ni(II) complexes with Schiff base ligands. *Polyhedron* **2015**, *90*, 147.
- (40) Riley, D. P. Functional Mimics of Superoxide Dismutase Enzymes as Therapeutic Agents. *Chem. Rev.* **1999**, *99*, 2573.
- (41) Riley, D. P.; Weiss, R. H. Manganese Macrocyclic Ligand Complexes as Mimics of Superoxide Dismutase. *J. Am. Chem. Soc.* **1994**, *116*, 387.

TOC Graphic:

