

Synthesis and optical characterisation of platinum(II) poly-yne polymers incorporating substituted 1,4-diethynylbenzene derivatives and an investigation of the intermolecular interactions in the diethynylbenzene molecular precursors†

Muhammad S. Khan,^{*a} Muna R. A. Al-Mandhary,^a Mohammed K. Al-Suti,^a Timothy C. Corcoran,^a Yaqoub Al-Mahrooqi,^a J. Paul Attfield,^b Neil Feeder,^b William I. F. David,^c Kenneth Shankland,^c Richard H. Friend,^d Anna Köhler,^d Elisabeth A. Marseglia,^{*d} Emilio Tedesco,^d Chiu C. Tang,^e Paul R. Raithby,^{*f} Jonathan C. Collings,^g Karl P. Roscoe,^g Andrei S. Batsanov,^g Lorna M. Stimson^g and Todd B. Marder^{*g}

^a Department of Chemistry, Sultan Qaboos University, P.O. Box 36, Al Khod 123, Sultanate of Oman.

E-mail: msk@squ.edu.om

^b Department of Chemistry, University of Cambridge, Lensfield Road, Cambridge, UK CB2 1EW

^c ISIS Facility, Rutherford Appleton Laboratory, Chilton, Didcot, Oxon, UK OX11 0QX

^d Cavendish Laboratory, University of Cambridge, Madingley Road, Cambridge, UK CB3 0HE

^e CLRC Daresbury Laboratory, Daresbury, Warrington, UK WA4 4AD

^f Department of Chemistry, University of Bath, Claverton Down, Bath, UK BA2 7AY.

E-mail: p.r.raithby@bath.ac.uk

^g Department of Chemistry, University of Durham, South Road, Durham, UK DH1 3LE.

E-mail: Todd.Marder@durham.ac.uk

Received (in Montpellier, France) 15th July 2002, Accepted 27th September 2002

First published as an Advance Article on the web 26th November 2002

A series of 1,4-diethynylbenzene (**1**) derivatives, $\text{H}-\text{C}\equiv\text{C}-\text{R}-\text{C}\equiv\text{C}-\text{H}$ with $\text{R} = \text{C}_6\text{H}_3\text{NH}_2$ (**2**), $\text{C}_6\text{H}_3\text{F}$ (**3**), $\text{C}_6\text{H}_2\text{F}_2$ -2,5 (**4**), C_6F_4 (**5**), $\text{C}_6\text{H}_2(\text{OCH}_3)_2$ -2,5 (**6**) and $\text{C}_6\text{H}_2(\text{O}^n\text{C}_8\text{H}_{17})_2$ -2,5 (**7**) has been synthesised and their crystal structures determined by single crystal (**2**–**5**) or powder (**6**, **7**) X-ray diffraction. The $\text{C}\equiv\text{CH}\cdots\pi_{\text{C}=\text{C}}$ hydrogen bonds dominating structure **1** are gradually replaced by $\text{C}\equiv\text{C}-\text{H}\cdots\text{F}$ ones with the increase of fluorination (**3** \rightarrow **5**), or completely replaced by $\text{C}\equiv\text{CH}\cdots\text{N}$ and $\text{NH}\cdots\pi_{\text{C}=\text{C}}$ bonds in **2**, and $\text{C}\equiv\text{CH}\cdots\text{O}$ in **6** and **7**. The related platinum-based polymers, $\text{trans}[-\text{Pt}(\text{P}^n\text{Bu}_3)_2-\text{C}\equiv\text{C}-\text{R}-\text{C}\equiv\text{C}-]_n$ ($\text{R} =$ as above and C_6H_4), have been prepared and characterised by spectroscopic methods and thermogravimetry, which show that the amino- and methoxy-derivatives have lowest thermal stability while the fluorinated ones exhibit increasing thermal stability with increasing fluorination. Optical spectroscopic measurements reveal that substituents on the aromatic spacer group do not create strong donor–acceptor interactions along the rigid backbone of the organometallic polymers.

Introduction

The last decade has witnessed a growing interest in the use of organic semiconductor materials in light-emitting diodes, lasers, photovoltaic cells and field-effect transistors.¹ Conjugated polymers have shown considerable promise in this context. The need to optimise their processability and so enhance their commercial exploitation has prompted several investigations into the relationship between the chemical and electronic structure. Of particular interest are a series of organic poly-yne polymers that have been employed recently in successful liquid crystal display and photocell technology.² A number of publications have also been dedicated to the chemical and optical characterisation of related tailored organic³ and organometallic^{4,5} oligomers and polymers.


Recently, attention has also been directed toward oligomers, taken not only as model compounds, but also as potential materials for device applications.⁶ They are more crystalline

than the corresponding polymers, allowing for a detailed structural analysis and, thus, an assessment of the structure–electronic property relationship.⁷ There is some evidence that the solid state arrangement of these molecules represents an important factor in determining their optical behaviour.^{5–8} While the π – π stacking interaction between adjacent oligomer molecules or polymer chains has been identified as a key ‘inter-chain’ interaction in solids,⁹ it is possible that hydrogen bonding can also play an important rôle in this context.

Hydrocarbon groups are generally poor donors of hydrogen bonds, but the ethynyl moiety with its acidic H atom is an exception.¹⁰ Furthermore, the concentration of electron density in the triple bond can act as an acceptor, albeit a rather weak one, of an H-bond.¹¹ Thus ethynyl groups can form co-operative H-bonds,¹² similarly to OH groups.¹³ Such a cooperative effect is evident in the crystal structure¹⁴ of 1,4-diethynylbenzene **1**. In order to investigate the effect of various substituents on the crystalline architecture of these organic poly-yne precursors, particularly the stability of the $\text{C}\equiv\text{CH}\cdots\pi_{\text{C}=\text{C}}$ H-bonding in competition¹⁵ with other intermolecular

† Electronic supplementary information (ESI) available: atomic coordinates for **6** and **7**. See <http://www.rsc.org/suppdata/nj/b2/b206946f/>

‡ $\pi_{\text{C}=\text{C}}$ is the midpoint of the $\text{C}=\text{C}$ bond.

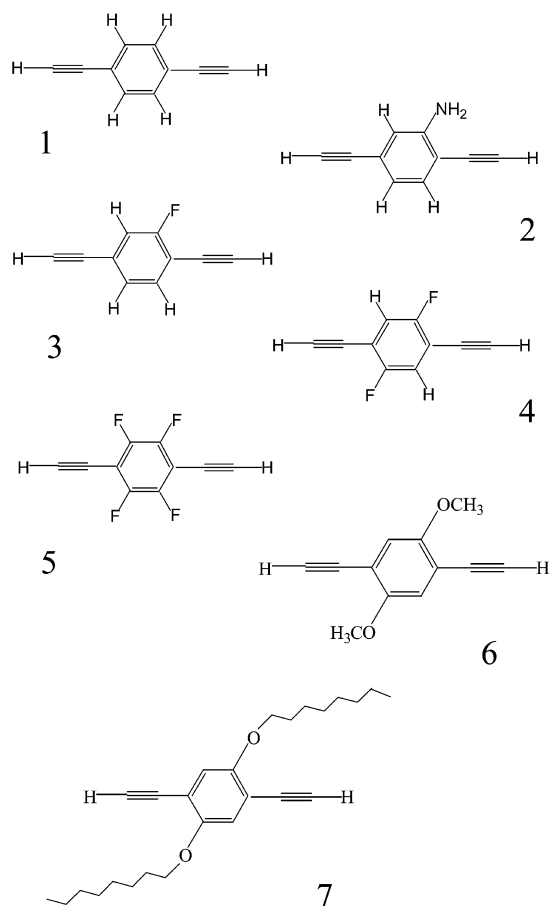


Scheme 1 Compounds $\text{HC}\equiv\text{C}-\text{R}-\text{C}\equiv\text{CH}$.

interactions, *e.g.* $\text{X}-\text{H}\cdots\pi_{\text{C}\equiv\text{C}}$ ($\text{X} = \text{N}, \text{C}$) and $\text{C}-\text{H}\cdots\text{Y}$ ($\text{Y} = \text{N}, \text{O}, \text{F}^{16}$), we synthesised a series of amino-, fluoro- and alkoxy-derivatives of 1,4-diethynylbenzene (**2–7**, see Scheme 1) and structurally characterised them by single crystal and powder X-ray diffraction. The structures of **4** and **5** were determined at variable temperature, to investigate the supposed effects of the latter on weak hydrogen bonds.¹⁷ In addition, these substituted diethynylbenzene ligands have been incorporated into rigid-rod platinum(II)-containing polymers and their thermal and opto-electronic properties investigated systematically.

Results and discussion

Synthesis

The substituted 1,4-diethynylbenzene derivatives were synthesised by a sequence of coupling and protodesilylation reactions. The trimethylsilyl-protected bis(ethynyl) ligand precursors were synthesised by adopting improved procedures for the palladium-catalysed coupling of trimethylsilyl ethyne with dibromo/diiodoaryls¹⁸ (Scheme 2). Conversion of the ligand precursors into their diterminal alkynes **2–7** was accomplished by smooth removal of the trimethylsilyl protecting groups with dilute aqueous KOH in MeOH/THF or with Bu_4NF in THF. The products were purified by silica column chromatography and characterised by elemental analyses and by IR, NMR (^1H and ^{13}C) spectroscopy and mass spectrometry. In order to obtain the diethynylaryls, isolation of the bis(silylethynyl) derivatives is unnecessary. Thus, after the coupling reaction of the dihalide with the terminal alkyne (Scheme 2) was complete, the solvent was evaporated and the resultant residue was treated directly with dilute alkali to give the diethynyl compounds.

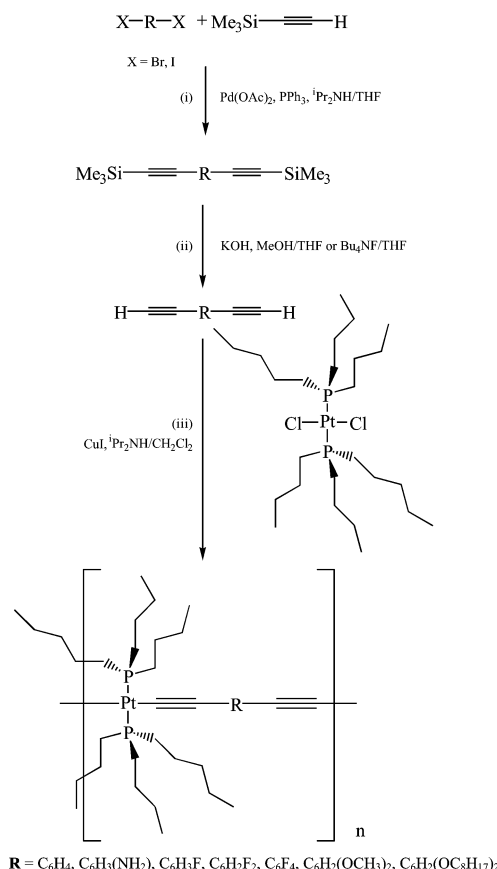

Scheme 2 Reagents: (i) $\text{Pd}(\text{OAc})_2$, PPh_3 , CuI , $i\text{Pr}_2\text{NH}/\text{CH}_2\text{Cl}_2$; (ii) KOH , MeOH/THF , or Bu_4NF , THF ; (iii) $\text{trans}-[\text{PtCl}_2(\text{P}^n\text{Bu}_3)_2]$, CuI , $i\text{Pr}_2\text{NH}/\text{CH}_2\text{Cl}_2$. $\text{R} = \text{C}_6\text{H}_4$ **1**, **8**; $\text{C}_6\text{H}_3\text{NH}_2$ **2**, **9**; $\text{C}_6\text{H}_3\text{F}$ **3**, **10**; $\text{C}_6\text{H}_2\text{F}_2-2,5$ **4**, **11**; C_6F_4 **5**, **12**; $\text{C}_6\text{H}_2(\text{OMe})_2-2,5$ **6**, **13**; $\text{C}_6\text{H}_2(\text{O}^n\text{C}_8\text{H}_{17})_2-2,5$ **7**, **14**.

Compared to the parent **1**, the amino, fluoro and the alkoxy derivatives are relatively stable at low temperature in the absence of light and air; if exposed to either, the initially colourless solids slowly turn off-white, yellow, light brown or light purple. Long storage times at ambient temperature and under aerobic conditions led to the formation of some insoluble material (< 5%), which was presumed to be a polymerisation product.

The platinum-containing poly-yne polymers were obtained by the organometallic polycondensation reaction of the diethynylbenzene derivatives with one equivalent of $\text{trans}-[\text{Pt}(\text{P}^n\text{Bu}_3)_2\text{Cl}_2]$ in $\text{CH}_2\text{Cl}_2/i\text{Pr}_2\text{NH}$ solution in the presence of catalytic quantities of CuI (Scheme 2). The resultant polymers were purified by passing through a short alumina column, and isolated as off-white or yellow solids. The materials were characterised by spectroscopic techniques. The IR spectra showed a single $\nu(\text{C}\equiv\text{C})$ stretching frequency at 2095 cm^{-1} consistent with the *trans*-arrangement of the ethynyl groups. The ^{31}P NMR spectrum of each polymer displayed the expected singlet signal at approximately $\delta -138$ ppm with $J_{\text{Pt-P}}$ coupling confirming the *trans*-configuration of the phosphine ligands. The ^1H NMR spectra of the polymers show the expected resonances corresponding to the substituted 1,4-diethynylbenzene derivatives. The weight average molecular weights (M_w) of the polymers indicate a high degree of polymerisation. The number average molecular weight (M_n) values are in the range of 74 000 to 95 000 g mol^{-1} . These values correspond to between 95 and 128 repeat units in the polymer chain. The molecular weights should be viewed with caution in view of the difficulties associated with utilizing GPC for rigid-rod polymers. GPC is not a direct measure of molecular weight but a measure of the hydrodynamic volume.

Rod-like polymers in solution possess very different hydrodynamic properties from flexible polymers. Thus, by GPC using randomly coiled polystyrene standards, the observed average molecular weights of rigid rod poly-ynes are likely to be inflated to some extent relative to the actual molecular weights. However, the lack of discernable resonances that could be attributed to end groups in the NMR spectra provides support for the view that there is a high degree of polymerisation in these poly-ynes.

Crystal structures of 2–7

Structures of compounds **2–5** were determined by single-crystal X-ray diffraction, and those of the alkoxy derivatives **6** and **7** by powder X-ray diffraction. The molecular structures of **2–7** (see ESI) are unexceptional; the geometry of the 1,4-diethynylbenzene moiety is little affected by the substituents, but the crystal packing and H-bond patterns are significantly different. Comparison with the structure of **1** is instructive. In it the potential donor (ethynyl H) and acceptor ($\text{C}\equiv\text{C}$ bonds) H-bonding sites are not only congruous (moderately polar) but also equal in numbers. This favours the formation of a two-dimensional net of co-operative H-bonds, linking molecules into a puckered layer (Fig. 1, Table 1). In both recent studies this layer was described as parallel to the (1 0 0), *i.e.* *bc*, plane.^{14b,c} In fact, as can be seen from Fig. 2, it is parallel to the (1 0 $\bar{2}$) plane. It is noteworthy that the same mistake was repeated in the description of three crystal structures of *p*-XC₆H₄C \equiv CH (X = Cl, Br or I), pseudo-isomorphous with **1**.¹⁹ There are infinite π - π stacks between molecules of adjacent layers (related by the *a* translation), at normal interplanar separations (*d* in Table 1).

Introduction of a polar (amino) group in **2** contributes two additional “active” H atoms, but only one potential acceptor site (the lone pair of N). The prominent feature of this structure (Fig. 3) is a ring system of co-operative H-bonds, involving four molecules. The ring (having crystallographic *C*₂ symmetry) includes two relatively strong $\text{N-H}\cdots\pi_{\text{C}=\text{C}}$ bonds ($\text{H}\cdots\pi = 2.51$ Å, $\text{N-H}\cdots\pi = 145^\circ$)[§] and two $\text{C}\equiv\text{CH}\cdots\text{N}$ bonds ($\text{H}\cdots\text{N} = 2.44$ Å, $\text{C-H}\cdots\text{N} = 159^\circ$), directed towards the lone pair of the substantially pyramidalised N atom (the valent bond angles at N average 116°). As each molecule participates in two such tetrameric systems, this generates a molecular layer, parallel to the crystallographic (1 0 $\bar{2}$) plane. The other amino-H atom is involved in a bifurcated interaction with two (crystallographically non-equivalent) $\text{C}\equiv\text{C}$ bonds of two different molecules ($\text{H}\cdots\pi = 2.89$ and 2.87 Å, $\text{N-H}\cdots\pi = 128$ and 140° , respectively), belonging to the next layer. The ethynyl group not involved in the co-operative H-bonding points almost perpendicularly towards the benzene ring of one of these molecules (C–H vector/ring plane angle of 81°), with the shortest contacts $\text{H}\cdots\text{C}(4)$ 3.04 and $\text{H}\cdots\text{C}(5)$ 2.98 Å typical for van der Waals interactions.²⁰ The outcome is a peculiar orientation of molecular planes: normal to each other but all normal to the layer plane. Molecules belonging to different layers (as defined by cooperative H-bonds) are nevertheless engaged in π - π stacking with each other (interplanar separations of 3.56 Å), albeit with considerable offset. Unlike all other compounds reported herein, molecule **2** has no crystallographic symmetry and is slightly ‘bent’, the directions of the two bonds forming an angle of $170.8(2)^\circ$.

Crystal structures of **3** and **4** (Fig. 1) are isomorphous with that of **1**. In each case, the molecule lies at a crystallographic inversion centre, which means that in **3** the fluorine atom is disordered, being distributed equally between two positions, related by this centre. Hydrogen bonding in **1**, **3** and **4** is compared in Table 1. The ‘organic’ (*i.e.* bonded to carbon) fluor-

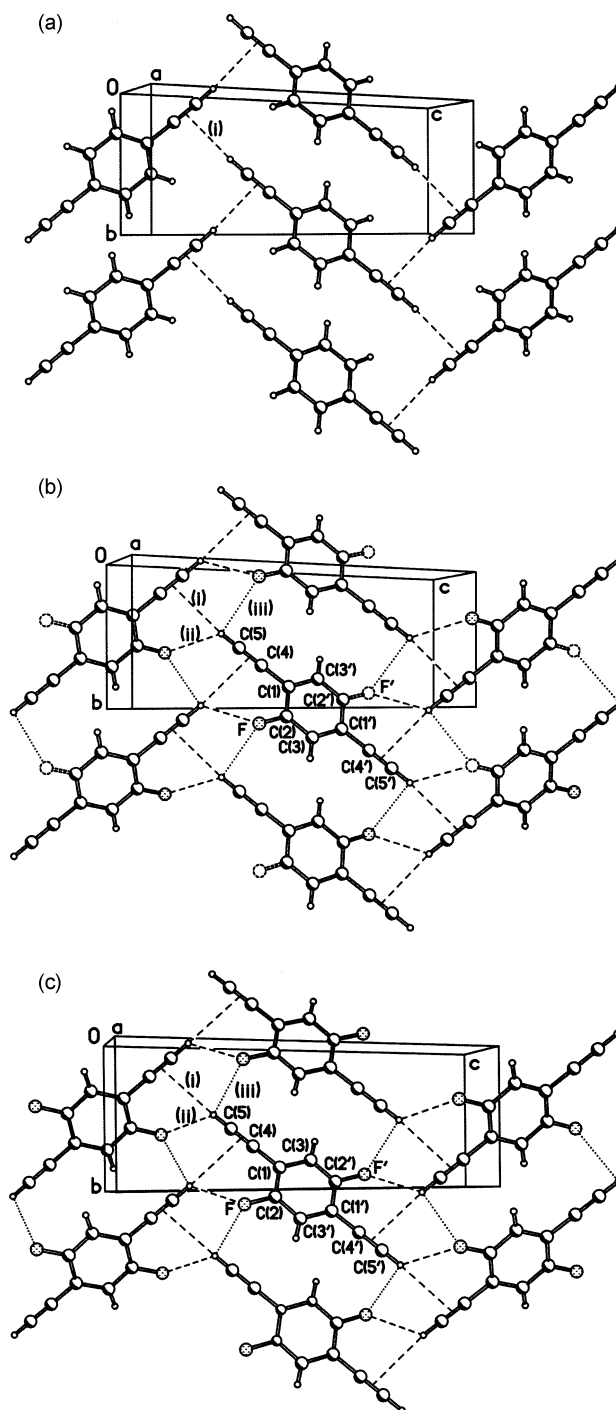


Fig. 1 Crystal structures of **1** (a), **3** (b) and **4** (c); projections on the (1 0 $\bar{2}$) plane.

ine atom, notwithstanding its high formal electronegativity, is known to be very poor H-bond acceptor, and is able to participate in them only in the absence of competition from stronger ones, *e.g.* oxygen.²¹ However, structures **3**, **4** and **5** satisfy the conditions for the formation of $\text{C-H}\cdots\text{F}$ hydrogen bonds, as pointed out by Desiraju *et al.* in a study on fluorobenzenes:²² they contain only C, H and F atoms, and the H atoms are bonded to sp^2 or sp -hybridised C atoms. Indeed, in **3** and **4** the $\text{C}\equiv\text{CH}\cdots\pi_{\text{C}=\text{C}}$ H-bond of **1** is weakened, or rather replaced by a bifurcated H-bond to both the $\text{C}\equiv\text{C}$ group and the fluorine atom of the same molecule, the $\text{C}\equiv\text{CH}\cdots\text{F}$ interaction being the stronger of the two. Thus, the $\text{H}\cdots\pi$ distance increases by *ca.* 0.2 Å from that in **1** to that in **4**. There is also a much longer, but probably electrostatically attractive, contact (iii) with another F atom. Comparison of the structure

[§] All hydrogen bond parameters are calculated for idealized bond lengths C–H 1.08 Å and N–H 1.01 Å.

Table 1 Intermolecular interactions in crystals of **1** and its fluorinated derivatives

| Compound | 1 ^{14b} | 1 ^{14c} | 3 | 4 (A) | 4 (B) | 5 (A) | 5 (B) | 5 (C) |
|--------------------------------|-------------------------|-------------------------|----------|--------------|--------------|--------------|--------------|--------------|
| <i>T</i> /K | 295 | 125 | 180 | 180 | 120 | 273 | 180 | 150 |
| (i) ^a H... π /Å | 2.68 | 2.60 | 2.75 | 2.87 | 2.85 | 2.94 | 2.93 | 2.89 |
| (i) C-H... π /° | 176 | 175 | 168 | 161 | 160 | 129 | 127 | 127 |
| (ii) H...F/Å | | | 2.66 | 2.60 | 2.58 | | | |
| (ii) C-H...F/° | | | 121 | 122 | 122 | | | |
| (iii) H...F/Å | | | 2.86 | 2.94 | 2.88 | 2.49 | 2.41 | 2.41 |
| (iii) C-H...F/° | | | 90 | 116 | 117 | 132 | 136 | 134 |
| <i>d</i> ^b /Å | 3.71 ^c | 3.53 | 3.47 | 3.43 | 3.41 | 3.63 | 3.60 | 3.59 |

^a See notation in Figs. 1 and 4. ^b Mean interplanar separation in the π - π stack. ^c Probably erratum in the original, cannot be verified as atomic coordinates are unavailable.

of **4** at different temperatures (180 and 120 K) shows similar (*ca.* 0.02 Å) thermal expansions of the H-bonds (i) and (ii) and the interplanar separations (*d*) in the π - π stack, but a larger extension of contact (iii). The layers in all three structures are similarly puckered: the dihedral angles between H-bonded molecules are 48° (**1**), 52° (**3**) and 54° (**4**).

The increased degree of fluorination in compound **5** gives rise to completely different crystal packing (Fig. 4). The molecule also possesses crystallographic *C*_i symmetry, but the principal synthon in structure **5** is the pair of inversion-related, parallel and nearly coplanar molecules, linked by two C \equiv CH...F hydrogen bonds (iii), shorter than in **3** and **4** (see Table 1). Thus molecules are linked into an infinite 'ribbon', parallel to the (1 0 $\bar{1}$) direction. There are no continuous π - π stacks of molecules, although each molecule has one neighbour contacting it in a π - π fashion. These molecules, related by an inversion centre, have a longitudinal (parallel to the C \equiv C bond) shift of *ca.* 4.3 Å, so that a C \equiv C bond of one molecule overlaps with the benzene ring of another. The interplanar separation contracts from 3.63 Å at 273 K to 3.59 Å at 150 K.

This double ribbon is surrounded on all sides by four other ribbons, propagating in the same direction but with perpendicular molecular planes. Each ethynyl H atom participates in a rather long inter-ribbon C \equiv CH... π _{C \equiv C} contact (i) (Table 1); the interaction thus can be interpreted as a very asymmetric bifurcated H-bond. Structure determinations at 273, 180 and 150 K did not reveal any substantial change, although thermal expansion in the direction of the strongest H-bond (iii) is somewhat greater than in other directions.

The crystal packing of di-alkoxy derivatives **6** and **7** is shown in Figs. 5 and 6. Both molecules have crystallographic *C*_i symmetry and adopt planar (**6**) or nearly planar (**7**) conformations. Structure **6** comprises puckered layers, parallel to the (1 0 $\bar{2}$) plane and broadly similar to those observed in structures **3** and **4**, in which the molecules are linked by C \equiv CH...O hydrogen bonds (H...O = 2.34 Å, C-H...O = 146°), while the C \equiv CH... π _{C \equiv C} interaction between the same molecules is much weaker than in structures **3** and **4** (H... π = 3.07 Å, C-H... π = 137°). Unlike **1–4**, structure **6** contains no π - π stacks, molecules of adjacent layers contacting in a herring-bone fashion.

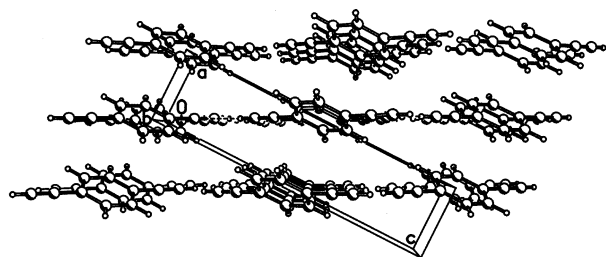
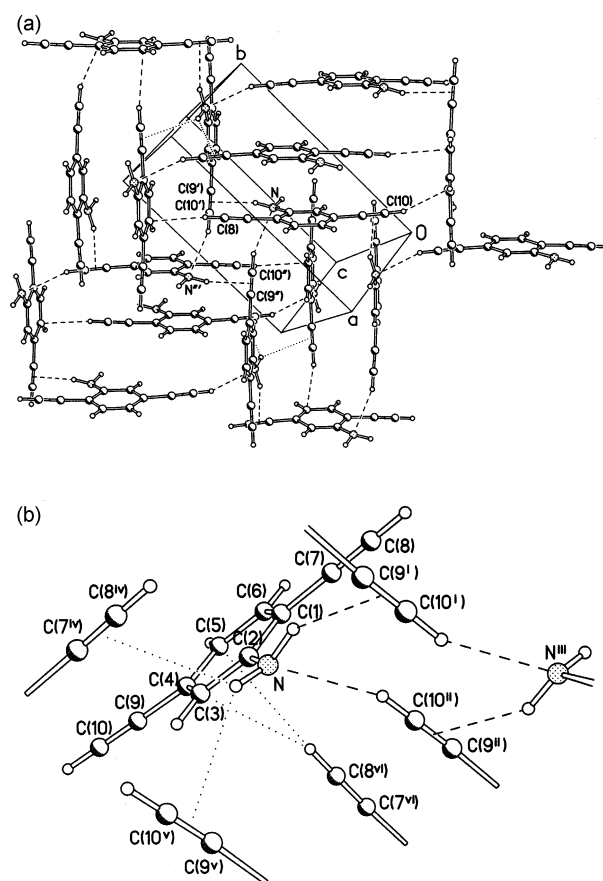
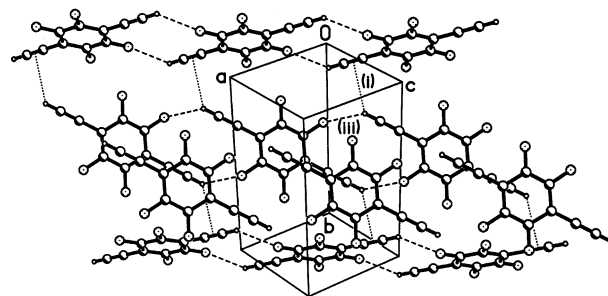
**Fig. 2** Crystal structure of **1**, viewed down the *y* axis.

Fig. 3 (a) Crystal structure of **2**, projected on the (1 0 $\bar{2}$) plane; (b) H-bonds and intermolecular contacts. Symmetry transformations: (i) $1-x, \frac{1}{2}+y, \frac{1}{2}-z$; (ii) $2-x, 1-y, 1-z$; (iii) $x+1, \frac{1}{2}-y, \frac{1}{2}+z$; (iv) $x-1, y, z$; (v) $x, \frac{1}{2}-y, \frac{1}{2}+z$; (vi) $2-x, y-\frac{1}{2}, \frac{1}{2}-z$.

Structure **7** contains nearly-flat layers, in which a synthon, broadly similar to that of structure **5**, can be identified: a centrosymmetric pair of molecules, linked by two C \equiv CH...O hydrogen bonds. These, however, are much weaker than in **6** (H...O = 2.80 Å, C-H...O = 167°). Probably, the crystal structure of **7** is dominated by the close packing of (all-*trans*) *n*-alkyl chains, to which the H-bonding pattern has to adjust. This structure is in good agreement with the structural model proposed recently for the corresponding polymer.^{3b}

Thermal analysis

All the polymer samples exhibited an exotherm coincident with mass loss due to decomposition. Decomposition onset was defined as a mass loss of 2%. The peak decomposition temperature was defined as the first inflection point in the thermogravimetric curve, corresponding to a peak in the derivative of

**Fig. 4** Crystal structure of **5**.

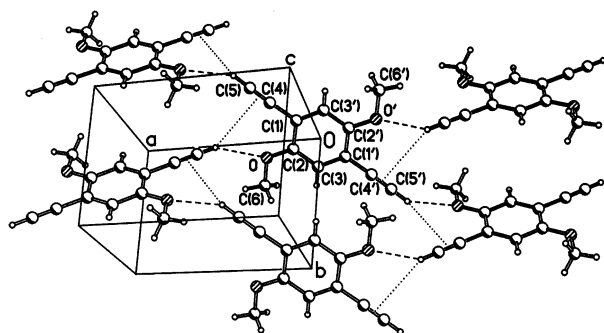


Fig. 5 Crystal structure of 6.

the TG data. This peak usually preceded the peak of the exotherm in the DTA data. The decomposition exotherms were broad with multiple peaks, and the thermogravimetric curve suggests a stepwise process. The results are shown in Table 2 and Fig. 7. Polymers **9** and **13** exhibited the lowest onset decomposition temperatures, while the fluorinated polymers **10–12** exhibited increasing decomposition temperatures with increasing fluorination. Polymer **14** also exhibited one of the highest decomposition temperatures, since the octyloxy groups likely encourage stronger interchain van der Waals bonding.

Optical spectroscopy

The effect of the substitution of the aromatic spacer group on the electronic structure of the platinum(II) poly-yne polymers has been investigated. The absorption and emission spectra taken at room temperature from thin films of polymers **8**, **12** and **13** are shown in Fig. 8. The first absorption band of polymer **8** peaking at 3.26 eV (380 nm) has its origin mostly in the $\pi-\pi^*$ transitions of the conjugated polymer backbone and is associated with the first singlet excited state denoted S_1 .²³ Substitution by fluorine or by methoxy groups leads to a weak red shift of 0.05 eV (6 nm) and 0.15 eV (20 nm), respectively, indicating only slightly more conjugated backbones. Substitution with less than four fluorines, as in **10** and **11**, leads to a correspondingly smaller red shift (not shown here).

The emission spectra consist of two bands. The band just below the onset of absorption at 3 eV is emission from the S_1 state (fluorescence). The band below 2.5 eV has been well characterised for the polymer **8** and other aromatic/hetero-aromatic spacers by time-resolved luminescence measurements and is assigned to emission from the triplet excited state T_1 (phosphorescence).^{8,24} Substitution of the aromatic ring shifts the energy of the T_1 emission by about the same amount as the S_1 emission, so that the S_1-T_1 energy difference remains constant. This can be used to accurately fine-tune the energy of the T_1 state for energy harvesting purposes²⁵ particularly in

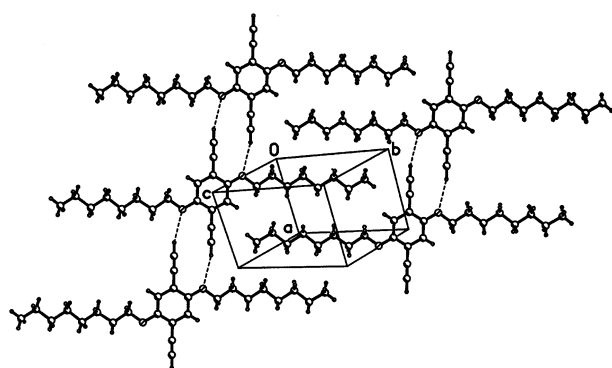


Fig. 6 Crystal structure of 7.

Table 2 Decomposition temperatures (in °C, $\pm 8^\circ\text{C}$) from thermal analysis

| Compound | T_{dec} (onset) | T_{dec} (peak) |
|-----------|--------------------------|-------------------------|
| 9 | 248 | 336 |
| 10 | 300 | 333 |
| 11 | 304 ^a | 337 ^a |
| 12 | 312 | 345 |
| 13 | 254 | 314 |
| 14 | 310 | 353 |

^a Estimated from DTA data only.

analogous organic polymers, where T_1 emission (phosphorescence) is spin-forbidden and cannot be observed. While such a constant S_1-T_1 energy gap has been observed for these organometallic and analogous organic polymers with a variety of spacers its cause is not yet fully understood.^{23,25}

The emission spectra normalised to the fluorescence peak for the polymers with one, two and four fluorine substituents (polymers **10**, **11** and **12**, respectively) are shown in Fig. 9. The relative intensity of phosphorescence increases strongly with the fluorine content.

Conclusions

A number of substituted derivatives of 1,4-diethynylbenzene with electron donating and accepting substituents have been studied, and their structural characterisation performed by both single-crystal and powder X-ray diffraction. An interesting result of this work has been the ability to obtain comparable structural information from conventional techniques (single crystal) and from powder X-ray diffraction.

The packing analysis of the structures of the polymer precursors has also thrown light on the co-presence of weak hydrogen bonding in model compounds of polymers that are of technological interest. In summary the ethynylene moiety provides a good hydrogen bond donor and acceptor, which is able to compete in terms of intermolecular interactions and as structure defining synthons, with more electronegative atoms, such as nitrogen. $\text{C}\equiv\text{CH}\cdots\pi_{\text{C}\equiv\text{C}}$ hydrogen bonds dominate the crystal structure of **1**, and are gradually replaced by $\text{C}\equiv\text{C}-\text{H}\cdots\text{F}$ ones with the increase of fluorination (**3** \rightarrow **5**), as has been noted previously,¹⁹ or completely replaced by $\text{C}\equiv\text{CH}\cdots\text{N}$ and $\text{NH}\cdots\pi_{\text{C}\equiv\text{C}}$ bonds in **2**, and $\text{C}\equiv\text{CH}\cdots\text{O}$ in **6** and **7**. However, it is hard to judge, based solely on geometrical measurements, the relative strength of the $\text{C}-\text{H}\cdots\text{F}$ interactions in these derivatives. A $\text{C}-\text{H}\cdots\pi_{\text{C}\equiv\text{C}}$ bond in **1** has been

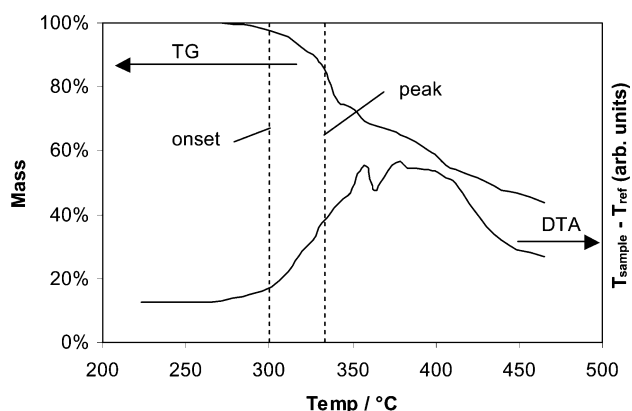


Fig. 7 Simultaneous thermogravimetric (TG) curve (above) and differential thermal analysis (DTA) curve (below) for **10**. The onset and peak decomposition temperatures, as defined in the text, are marked.

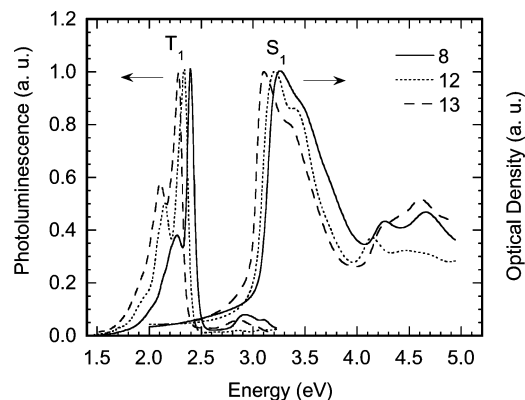


Fig. 8 Absorption and luminescence spectra of the platinum-containing poly-yne polymers **8**, **12** and **13** taken from thin films at room temperature with excitation at 3.4 eV.

estimated being of *ca.* 4 kJ mol⁻¹.²⁶ When alkoxy substituents are present, C–H...O interactions occur, but the presence of long alkyl chains in the structure can impede the formation of these short contacts.

The substituted 1,4-diethynyl benzene ligands have also been incorporated into rigid-rod Pt(II) polymers and their thermal and opto-electronic properties investigated. The substituents on the aromatic spacer have a major effect on the thermal stability of the polymeric complexes but their electronic properties are affected only to a minor extent.

Experimental

General

All reactions were performed under a dry nitrogen atmosphere using standard Schlenk or glove box techniques. Solvents were pre-dried and distilled before use by standard procedures.²⁷ All chemicals, except where stated otherwise, were obtained from Sigma Aldrich and checked for purity by GC/MS prior to use. 1,4-Diiodo-2,5-bis(octyloxy)benzene was prepared by adaptation of the literature method.²⁸

NMR spectra were recorded on Bruker WM-250 or AM-400 spectrometers in CDCl₃ and the ¹H and ¹³C{¹H} were referenced to solvent resonances. Infrared spectra were recorded as CH₂Cl₂ solutions, in a NaCl cell, on a Perkin-Elmer 1710 FT-IR spectrometer, mass spectra on a Kratos MS 890 spectrometer by the electron impact (EI) technique. Microanalyses were performed in the Department of Chemistry, University of Cambridge. Column chromatography was performed in Kieselgel 60 (240–400 mesh) silica gel. GC/MS analyses were

performed on a Hewlett-Packard 5890 Series II/5971A MSD instrument equipped with an HP 7673A autosampler and a fused silica column (30 m × 0.25 mm × 0.25 μm, cross-linked 5% phenylmethyl silicone). The following operating conditions were used: injector, 260 °C; detector, 280 °C; oven temperature was ramped from 70 °C to 260 °C at the rate of 20 °C min⁻¹; helium (UHP grade) was used as the carrier gas; toluene (BDH, 99.7%) was used as an internal integration standard.

Synthesis of 1,4-diethynylbenzene derivatives

1,4-Diethynyl-2-aminobenzene 2. *Coupling.* To an ice-cooled solution of 1,4-dibromo-2-aminobenzene (3.01 g, 12 mmol) in diisopropylamine/THF (75 cm³, 1:4 v/v) under nitrogen were added CuI (29 mg, 0.15 mmol), Pd(OAc)₂ (27 mg, 0.12 mmol) and PPh₃ (157 mg, 0.60 mmol). The solution was stirred for 0.5 h, trimethylsilylethyne (2.95 g, 30 mmol) was then added over 10 min to the vigorously stirred solution; during the addition a white precipitate formed. The suspension was stirred for 30 min in an ice-bath before being warmed to room temperature. After reacting for 30 min at room temperature the mixture was heated to 80 °C for 20 h when TLC, GC analysis and IR spectroscopy indicated that all the starting material had been consumed and the coupling reaction was completed. After being cooled to room temperature, the mixture was filtered to eliminate the ammonium salt and the solvent mixture was removed *in vacuo*.

Protodesilylation. The solid residue was dissolved in THF (50 cm³) with stirring. Methanol (15 cm³) and aqueous KOH (1.50 g, 27 mmol in 5 cm³ water) were added at room temperature to the stirred solution. The reaction mixture was stirred for 2 h. The completion of the desilylation reaction was verified by TLC, GC analysis and IR spectroscopy. The mixture was filtered and the solvent was removed under reduced pressure to leave a yellow residue. This residue was dissolved in the minimum amount of dichloromethane and subjected to column chromatography on silica using hexane–dichloromethane (2:1 v/v) as eluent to afford a pale yellow solid. Recrystallization from hexane with activated charcoal yielded pale yellow micro-crystals (0.62 g, 76% yield). IR (CH₂Cl₂): ν /cm⁻¹ 2108 (–C≡C–), 3300 (C≡CH), 3428 (–NH–). ¹H NMR (250 MHz, CDCl₃): δ 3.12 (s, 1H, C≡C–H), 3.50 (s, 1H, C≡C–H), 4.70 (br s, 2H, NH₂), 7.21 (d, 2H, ar), 7.73 (dd, 1H, ar). ¹³C NMR (100.6 MHz, CDCl₃): δ 78.2, 80.6, 83.1, 84.0 (C≡C), 107.2 (C¹), 117.5 (C³), 121.4 (C⁴), 123.0 (C⁶), 132.2 (C⁵), 148.0 (C²). EI mass spectrum: *m/z* 141 (M⁺). Found: C, 85.03; H, 4.94; N, 9.90; Calc. for C₁₀H₇N: C, 85.08; H, 5.00; N, 9.92%.

1,4-Diethynyl-2-fluorobenzene 3. *Coupling.* To a solution of 1,4-dibromo-2-fluorobenzene (2.5 g, 10 mmol) in diisopropylamine/THF (100 cm³, 1:4 v/v) at reflux under nitrogen was added a catalyst mixture of CuI (24 mg, 0.13 mmol), Pd(OAc)₂ (22 mg, 0.10 mmol) and PPh₃ (131 mg, 0.50 mmol). Trimethylsilylethyne (2.45 g, 25 mmol) was then added over the course of 10 min to the vigorously stirred solution; during the addition a white precipitate formed. The reaction mixture was stirred at reflux for 8 h and the completion of the reaction was verified by TLC, GC analysis and IR spectroscopy. The reaction mixture was allowed to cool to room temperature and the ammonium iodide precipitate was filtered off. The yellow filtrate was evaporated to dryness.

Protodesilylation. Removal of the trimethylsilyl protecting groups was accomplished as for the synthesis of **2** described above. Compound **3** was obtained as an off-white solid in 82% yield. Good quality crystals were obtained by sublimation (15 mmHg, ice-water cooled). IR (CH₂Cl₂): ν /cm⁻¹ 2107 (–C≡C–) and 3300 (C≡C–H). ¹H NMR (250 MHz, CDCl₃): δ 3.21 (s, 1H, C≡C–H), 3.38 (s, 1H, C≡C–H), 7.22 (d, 2H, ar) and 7.46 (d, 1H, ar). ¹³C NMR (100.6 MHz, CDCl₃):

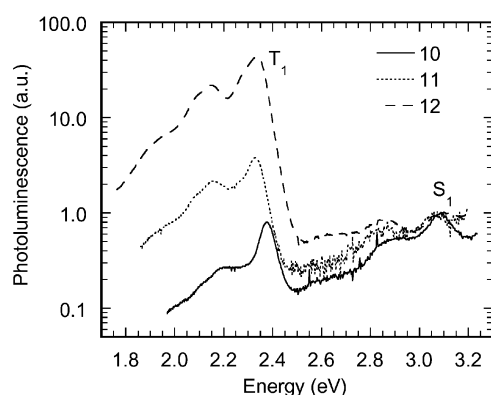


Fig. 9 Room temperature thin-film luminescence spectra of platinum-containing poly-yne polymers **10**, **11** and **12** normalised to the peak of the S₁ emission and shown on a logarithmic scale.

δ 77.1, 80.2, 81.8, 84.1 (C \equiv C), 111.51 (C¹), 119.02 (C³), 124.36 (C⁴), 128.10 (C⁶), 134.20 (C⁵) and 162.65 (C²). EI mass spectrum: m/z 144 (M⁺). Found: C, 83.29; H, 3.58. Calc. for C₁₀H₅F: C, 83.32; H, 3.50%.

1,4-Diethynyl-2,5-difluorobenzene 4. Similar coupling and protodesilylation procedures as in **3** were adopted using 1,4-dibromo-2,5-difluorobenzene (2.72 g, 10 mmol) to give **4** as off-white solid in 95% yield. Good quality crystals were obtained by sublimation (15 mmHg, ice-water cooled). IR (CH₂Cl₂) ν /cm⁻¹: 2107 (C \equiv C-) and 3299 (C \equiv C-H). ¹H NMR (250 MHz, CDCl₃): δ 3.41 (s, 2H, C \equiv CH), 7.24 (d, 2H, ar), ¹³C NMR (100.6 MHz, CDCl₃): δ 75.7, 85.5 (C \equiv C), 112.8 (C^{1,4}), 120.2 (C^{3,6}), 158.9, (C^{2,5}). EI mass spectrum: m/z 162 (M⁺). Found: C, 74.11; H, 2.45; Calc. for C₁₀H₄F₂: C, 74.08; H, 2.49%.

1,4-Diethynyl-2,3,5,6-tetrafluorobenzene 5. *Coupling*^{17e,28}. 1,4-Diiodo-2,3,5,6-tetrafluorobenzene (4.02 g, 10 mmol) and trimethylsilyl ethyne (2.45 g, 25 mmol) were reacted in diisopropylamine/THF (100 cm³, 1:4 v/v) in the presence of catalytic amounts of CuI (24 mg), Pd(OAc)₂ (22 mg) and PPh₃ (131 mg). The coupling reaction was completed after 1 h of reflux. The crude product was worked up, as before, to yield a pale-yellow residue.

Protodesilylation. A similar procedure to that for **4** was adopted to obtain an off-white solid in 82% yield. Good quality crystals were obtained by sublimation (15 mmHg, ice-water cooled). IR (CH₂Cl₂) ν /cm⁻¹: 2106 (C \equiv C-) and 3297 (C \equiv C-H). ¹H NMR (250 MHz, CDCl₃): δ 3.72 (s, 2H, C \equiv CH). ¹³C NMR (100.6 MHz, CDCl₃): δ 68.4, 91.5 (C \equiv C), 104.5 (C^{1,4}), 147.5 (C^{2,3,5,6}). EI mass spectrum: m/z 198 (M⁺). Anal. Found: C, 60.71; H, 1.04; Calc. for C₁₀H₂F₄: C, 60.63; H, 1.02%.

1,4-Diethynyl-2,5-bis(methoxy)benzene 6. *Coupling*²⁹. Similar coupling procedures as in **5** were adopted using 1,4-diiodo-2,5-bis(methoxy)benzene (3.90 g, 10 mmol) to produce the crude trimethylsilyl ethynyl compound.

Protodesilylation. The solid residue was dissolved in THF (50 cm³) and a solution of tetrabutylammonium fluoride (1.1 M, 2 equiv.) was added. The reaction mixture was stirred for 5 min at ambient temperature when TLC, GC analysis and IR spectroscopy indicated that all the starting material had been consumed and the desilylation reaction was completed. The reaction mixture was chromatographed on a small silica gel column using THF as eluent. The solvent was removed *in vacuo* and the crude product was recrystallized in methanol to yield an off-white solid in 86% yield. IR (CH₂Cl₂): ν /cm⁻¹ 2107 (C \equiv C-) and 3299 (C \equiv C-H). ¹H NMR (250 MHz, CDCl₃): δ 3.33 (s, 2H, C \equiv C-H), 3.92 (s, 6H, OCH₃), 7.19 (s, 2H, ar). ¹³C NMR (100.6 MHz, CDCl₃): δ 69.89 (OCH₃), 79.96, 82.57 (C \equiv C), 113.41 (C^{1,4}), 117.89 (C^{3,6}), 154.14 (C^{2,5}). EI mass spectrum: m/z 186 (M⁺). Found: C, 77.46; H, 5.43; Calcd for C₁₂H₁₀O₂: C, 77.40; H, 5.41%.

1,4-Diethynyl-2,5-bis(octyloxy)benzene 7. *Coupling.* Similar coupling procedures as in **5** were adopted using 1,4-diiodo-2,5-bis(octyloxy)benzene (5.87 g, 10 mmol) to produce the crude trimethylsilyl ethynyl compound.

Protodesilylation. Similar desilylation procedures as in **6** were adopted to obtain a pale yellow solid in 79% yield. IR (CH₂Cl₂): ν /cm⁻¹ 2107 (C \equiv C-) and 3299 (C \equiv C-H). ¹H NMR (250 MHz, CDCl₃): δ 0.86 (t, 6H, CH₃), 1.26, 1.40 (both m, 20H, CH₂), 1.78 (m, 4H, CH₂), 3.32 (s, 2H, C \equiv C-H), 3.95 (t, 4H, OCH₂), 6.93 (s, 2H, ar). ¹³C NMR (100.6 MHz, CDCl₃): δ 14.29 (CH₃), 22.85, 26.09, 29.31, 29.42, 29.48, 31.99 (all CH₂), 69.84 (OCH₂), 79.98, 82.60 (C \equiv C), 113.45 (C^{1,4}), 117.92 (C^{3,6}), 154.18 (C^{2,5}). EI mass spectrum: m/z

382 (M⁺). Found: C, 81.52; H, 10.04; Calc. for C₂₆H₃₈O₂: C, 81.63; H, 10.01%.

Polymer preparations. The synthesis of polymer **8** has been reported previously.³⁰ The polymers **9–14** were synthesized by the general procedure outlined below for **9**.

trans-[Pt(PⁿBu₃)₂-(C \equiv C-C₆H₃(NH₂)-C \equiv C)]_n 9. CuI (10 mg) was added to a mixture of *trans*-[Pt(PⁿBu₃)₂Cl₂] (0.670 g, 1.0 mmol) and 1,4-diethynyl-2-amimobenzene (0.141 g, 1.0 mmol) in CH₂Cl₂/^tPr₂NH (50 cm³, 1:1 v/v). The yellow solution was stirred at room temperature over a period of 15 h, after which all volatile components were removed under reduced pressure. The residue was dissolved in dichloromethane and filtered through a short alumina column. After removal of solvent by rotary evaporator, an off-white solid of polymer **9** was obtained in 85% yield (0.750 g). Further purification can be accomplished by precipitating the polymer from dichloromethane solution in methanol. IR (CH₂Cl₂): ν /cm⁻¹ 2094 (C \equiv C-). ¹H NMR (250 MHz, CDCl₃): δ 0.87 (t, 18H, CH₃), 1.40 ((sex, 12H, CH₂), 1.65 (brs, 12H, CH₂), 2.25 (m, 12H, PCH₂), 4.18 (s, 2H, NH₂), 6.58 (d, 2H, ar), 7.12 (d, 1H, ar). ³¹P{¹H} NMR (101.3 MHz, CDCl₃): δ -138.08, *J*_{Pt-P} = 2330 Hz. Found: C, 55.17; H, 8.14; Calc. for (C₃₄H₅₉NP₂Pt)_n: C, 55.26; H, 8.05%. GPC (THF): *M*_n = 94 700 g mol⁻¹ (*n* = 128), *M*_w = 151 500 g mol⁻¹, polydispersity = 1.6.

trans-[Pt(PⁿBu₃)₂-(C \equiv C-C₆H₃F-C \equiv C)]_n 10. Off-white solid (82% yield). IR (CH₂Cl₂): ν /cm⁻¹ 2095 (C \equiv C-). ¹H NMR (250 MHz, CDCl₃): δ 0.82 (t, 18H, CH₃), 1.38 (sex, 12H, CH₂), 1.58 (brs, 12H, CH₂), 2.29 (m, 12H, PCH₂), 7.38 (d, 2H, ar), 7.28 (d, 1H, ar). ³¹P{¹H} NMR (101.3 MHz, CDCl₃): δ -138.50, *J*_{Pt-P} = 2330 Hz. Found: C, 55.15; H, 7.74; Calc. for (C₃₄H₅₇F₂P₂Pt)_n: C, 55.05; H, 7.76%. GPC (THF): *M*_n = 94 650 g mol⁻¹ (*n* = 128), *M*_w = 160 900 g mol⁻¹, polydispersity = 1.7.

trans-[Pt(PⁿBu₃)₂-(C \equiv C-C₆H₂F₂-C \equiv C)]_n 11. Off-white solid (78% yield). IR (CH₂Cl₂): ν /cm⁻¹ 2094 (C \equiv C-). ¹H NMR (250 MHz, CDCl₃): δ 0.77 (t, 18H, CH₃), 1.34 (sex, 12H, CH₂), 1.52 (brs, 12H, CH₂), 2.20 (m, 12H, PCH₂), 7.28 (d, 2H, ar). ³¹P{¹H} NMR (101.3 MHz, CDCl₃): δ -138.50, *J*_{Pt-P} = 2330 Hz. Found: C, 53.65; H, 7.44; Calc. for (C₃₄H₅₆F₂P₂Pt)_n: C, 53.74; H, 7.43%. GPC (THF): *M*_n = 88 230 g mol⁻¹ (*n* = 116), *M*_w = 158 810 g mol⁻¹, polydispersity = 1.8.

trans-[Pt(PⁿBu₃)₂-(C \equiv C-C₆F₄-C \equiv C)]_n 12. Off-white solid (72% yield). IR (CH₂Cl₂): ν /cm⁻¹ 2095 (C \equiv C-). ¹H NMR (250 MHz, CDCl₃): δ 0.75 (t, 18H, CH₃), 1.38 (sex, 12H, CH₂), 1.58 (brs, 12H, CH₂), 2.20 (m, 12H, PCH₂). ³¹P{¹H} NMR (101.3 MHz, CDCl₃): δ -138.50, *J*_{Pt-P} = 2330 Hz. Found: C, 51.36; H, 6.79; Calc. for (C₃₄H₅₄F₄P₂Pt)_n: C, 51.31; H, 6.84%. GPC (THF): *M*_n = 82 500 g mol⁻¹ (*n* = 103), *M*_w = 156 770 g mol⁻¹, polydispersity = 1.9.

trans-[Pt(PⁿBu₃)₂-(C \equiv C-C₆H₄(OCH₃)₂-C \equiv C)]_n 13. Light yellow solid (85% yield). IR (CH₂Cl₂): ν /cm⁻¹ 2095 (C \equiv C-). ¹H NMR (250 MHz, CDCl₃): δ 0.86 (t, 18H, CH₃), 1.38 (sex, 12H, CH₂), 1.58 (brs, 12H, CH₂), 2.20 (m, 12H, PCH₂), 3.70 (s, 6H, OCH₃), 7.10 (s, 2H, ar). ³¹P{¹H} NMR (101.3 MHz, CDCl₃): δ -138.10, *J*_{Pt-P} = 2330 Hz. Found: C, 55.22; H, 8.03; Calc. for (C₃₆H₆₂P₂O₂Pt)_n: C, 55.16; H, 7.97%. GPC (THF): *M*_n = 74 100 g mol⁻¹ (*n* = 95), *M*_w = 111 200 g mol⁻¹, polydispersity = 1.5.

trans-[Pt(PⁿBu₃)₂-(C \equiv C-C₆H₄(OC₈H₁₇)₂-C \equiv C)]_n 14. Light yellow solid (90% yield). IR (CH₂Cl₂): ν /cm⁻¹ 2095 (C \equiv C-). ¹H NMR (250 MHz, CDCl₃): δ 0.84 (t, 24H, CH₃),

Table 3 Crystal data for **2–7**

| | 2 | 3 | 4(A) | 4(B) | 5(A) | 5(B) | 5(C) | 6 | 7 |
|---|------------------------------------|------------------------------------|---|-------------|---|-------------|-------------|--|--|
| Formula | C ₁₀ H ₇ N | C ₁₀ H ₅ F | C ₁₀ H ₄ F ₂ | | C ₁₀ H ₂ F ₄ | | | C ₁₂ H ₁₀ O ₂ | C ₂₆ H ₃₈ O ₂ |
| <i>M_w</i> /g mol ^{−1} | 141.17 | 144.14 | 162.13 | | 198.12 | | | 186.20 | 380.55 |
| <i>T</i> /K | 180 | 180 | 180 | 120 | 273 | 180 | 150 | 290 | 290 |
| <i>λ</i> /Å | 1.54178 | 1.54178 | 1.54178 | 0.71073 | 1.54178 | 1.54178 | 0.71073 | 1.2996 | 1.54178 |
| Crystal system | monoclinic | monoclinic | monoclinic | | monoclinic | | | monoclinic | triclinic |
| Space group | <i>P</i> 2 ₁ / <i>c</i> | <i>P</i> 2 ₁ / <i>c</i> | <i>P</i> 2 ₁ / <i>c</i> | | <i>P</i> 2 ₁ / <i>c</i> | | | <i>P</i> 2 ₁ / <i>c</i> | <i>P</i> $\bar{1}$ |
| <i>a</i> /Å | 5.919(2) | 3.878(1) | 3.8535(7) | 3.828(1) | 6.1510(6) | 6.112(1) | 6.109(2) | 9.1718(1) | 7.6769(8) |
| <i>b</i> /Å | 12.030(4) | 5.947(1) | 5.906(1) | 5.887(1) | 11.524(1) | 11.463(2) | 11.456(4) | 6.04823(7) | 11.682(2) |
| <i>c</i> /Å | 11.026(3) | 15.800(5) | 16.221(5) | 16.204(4) | 5.8204(7) | 5.764(1) | 5.751(2) | 9.54469(1) | 6.926(2) |
| <i>α</i> /° | 90 | 90 | 90 | 90 | 90 | 90 | 90 | 90 | 104.29(1) |
| <i>β</i> /° | 104.17(2) | 93.46(3) | 95.23(3) | 95.21(1) | 98.71(1) | 99.27(2) | 99.35(2) | 107.428(1) | 96.637(8) |
| <i>γ</i> /° | 90 | 90 | 90 | 90 | 90 | 90 | 90 | 90 | 99.671(9) |
| <i>V</i> /Å ³ | 761.2(4) | 363.7(2) | 367.6(2) | 363.7(1) | 397.1(2) | 398.6(1) | 397.1(2) | 505.17(1) | 586.0(2) |
| <i>Z</i> | 4 | 2 | 2 | 2 | 2 | 2 | 2 | 2 | 1 |
| <i>μ</i> /mm ^{−1} | 0.57 | 0.77 | 1.03 | 0.12 | 1.42 | 1.45 | 0.16 | 0.67 | 0.51 |
| Refls. total | 1043 | 920 | 510 | 4764 | 753 | 510 | 4179 | | |
| Refls. unique | 959 | 460 | 466 | 966 | 691 | 506 | 907 | 243 ^a | 70 ^a |
| <i>R</i> _{int} | 0.031 | 0.026 | 0.026 | 0.020 | 0.040 | 0.059 | 0.023 | — | — |
| Refls., <i>I</i> > 2σ(<i>I</i>) | 777 | 369 | 431 | 902 | 601 | 333 | 807 | | |
| <i>wR</i> (<i>F</i> ²) | 0.136 | 0.122 | 0.073 | 0.106 | 0.129 | 0.072 | 0.085 | 0.070 ^b | 0.031 ^b |
| <i>R</i> [<i>I</i> > 2σ(<i>I</i>)] | 0.050 | 0.045 | 0.028 | 0.034 | 0.043 | 0.035 | 0.031 | 0.045 ^c | 0.024 ^c |

^a Total number of inequivalent reflections in the powder pattern; ^b *R*_{wp} for the Rietveld fits; ^c *R*_p for the Rietveld fits.

1.22–1.38 (m, 32H, CH₂), 1.62 (m, 16H, CH₂), 2.20 (m, 12H, PCH₂), 3.75 (t, 4H, OCH₂), 6.82 (s, 2H, ar). ³¹P{¹H} NMR (101.3 MHz, CDCl₃): δ −138.10, *J*_{Pt-P} = 2330 Hz. Found: C, 61.36; H, 9.29; Calc. for (C₅₀H₉₀P₂O₂Pt)_{*n*}: C, 61.26; H, 9.25%. GPC (THF): *M_n* = 94 850 (*n* = 97) g mol^{−1}, *M_w* = 151 750 g mol^{−1}, polydispersity = 1.6.

Molecular weight measurements. Molar masses were determined by gel permeation chromatography (GPC) using two PL Gel 30 cm, 5 micron mixed C columns at 30 °C running in THF at 1 cm³ min^{−1} with a Roth Model 200 high precision pump. A DAWN DSP (Wyatt Technology) Multi-Angle Laser Light Scattering (MALLS) apparatus with 18 detectors and auxiliary Viscotek model 200 differential refractometer/viscometer detectors was used to calculate the molecular weights (referred to GPC LS).

X-Ray crystallography

Single crystal diffraction. X-Ray quality crystals of **2** were obtained by the diffusion of hexane into a concentrated solution of CH₂Cl₂, at room temperature, those of **3**, **4** and **5** by sublimation (see above). Crystal data and experimental details are listed in Table 3. Diffraction experiments for **2**, **3**, **4(A)** and **5(B)** were carried out on a Stoe 4-circle diffractometer, for **5(A)** on a Rigaku AFC6S 4-circle diffractometer, both using graphite-monochromated Cu-Kα radiation ($\bar{\lambda}$ = 1.54178 Å); for **4(B)** and **5(C)** on a SMART 3-circle diffractometer with a 1K CCD area detector, using graphite-monochromated Mo-Kα radiation ($\bar{\lambda}$ = 0.71073 Å). In all cases, crystals were cooled with Cryostream (Oxford Cryosystems) open-flow N₂ gas cryostat. Absorption corrections were performed for **3** and **4** (A and B) by a semi-empirical method, based on ψ -scans. The structures were solved by direct methods using the SHELXS-86 program³¹ (or SIR92³² for **5**) and refined by full-matrix least squares against *F*², using SHELXL-97 software.³³

CCDC reference numbers 196099–196102. See <http://www.rsc.org/suppdata/nj/b2/b206946f/> for crystallographic data in CIF or other electronic format.

Powder diffraction. X-Ray diffraction experiment for a polycrystalline sample of **6** was carried out on Station 2.3 of the

Daresbury Synchrotron Radiation Source (λ = 1.2996 Å) using a flat plate geometry, that for **7** on a Stoe powder X-ray diffractometer equipped with a linear PSD, using Cu-Kα radiation ($\bar{\lambda}$ = 1.5406 Å) from a sealed-tube source. Both diffraction patterns were indexed using the DICVOL91 program³⁴ and each structure solved using the DASH suite of programs.³⁵ The structure solution details are summarised in Table 4.

It was clear from the space groups and lattice parameters that the molecules in both structures lie at crystallographic inversion centres and have no translational degree of freedom. The trial structures were subjected to an optimisation in which torsion angles were the only internal degrees of freedom, and limits on the external degrees of freedom were derived from the Euclidean normalisers of the relevant space groups,³⁶ while the molecule was anchored on a dummy atom lying at the origin of the unit cell. Structure solutions were deemed to have been obtained when the χ^2 figure of merit fell below a predetermined value.

Finally, the fractional coordinates obtained at the end of the simulated annealing runs were verified by Rietveld refinements using the GSAS program.³⁷ In both cases, the scale factor, cell constants, and parameters describing a linear interpolated background function and the diffraction peak shape were varied. The highly-resolved synchrotron powder pattern of **6** contained sufficient data for the atomic coordinates and isotropic

Table 4 Structure solution details for **6** and **7**

| | 6 | 7 |
|---|----------|----------|
| Data range used/degrees | 5–40 | 7–34 |
| Number of intensities extracted | 74 | 66 |
| χ^2 for Pawley profile fit | 7.67 | 2.94 |
| Number of atoms in model, excluding dummy | 12 | 33 |
| Internal degrees of freedom | 1 | 8 |
| Initial simulation temperature (χ^2 units) | 300 | 100 |
| Final simulation temperature (χ^2 units) | 280 | 4.5 |
| Initial χ^2 for intensities | 3740 | 1825.6 |
| Final χ^2 for intensities | 63.1 | 24.4 |
| χ^2 for Rietveld profile fit of SA model (refine scale + ITF only) | 18.17 | 5.61 |

U-factors of all non-hydrogen atoms to be refined independently while the H atom positions were restrained to idealised positions, giving an excellent fit with the final $\chi^2 = 5.32$. The powder diffraction pattern of **7** contained an amorphous component at $2\theta > 34^\circ$, therefore only the data below this limit were used in the solution and subsequent Rietveld refinement. The refinement of atomic coordinates being unstable, these were fixed and an overall isotropic *U*-factor was refined, giving a good fit with the final $\chi^2 = 2.24$.

SHELXTL software³⁸ was used for analysing the geometry and for graphical presentation of all structures (**1–7**).

Optical measurements. Thin films of the Pt(II) poly-ynes **8–13** and were spun from dichloromethane solution on quartz substrates using a conventional photoresist spin-coater. Films were typically 100–150 nm in thickness as measured on a Dektak profilometer. The optical absorption was measured with a Hewlett-Packard ultraviolet-visible (UV-VIS) spectrometer. Photoluminescence (PL) was measured with the sample in a continuous-flow helium cryostat, excitation being provided by the UV lines (334–365 nm) of a continuous wave (cw) argon ion laser. Typical intensities used were a few mW mm⁻². The emission spectra were recorded using a spectrograph with an optical fiber input, coupled to a cooled charge coupled device (CCD) array (Oriol Instaspec IV).

Thermal analysis. Thermal analysis (differential thermal analysis, DTA, and thermogravimetry, TG) of **2–7** was performed simultaneously in a Stanton-Redcroft model STA-780 Simultaneous Thermal Analyser under flowing N₂. Sample masses were ~1 mg packed with ~2 mg Al₂O₃ in open Inconel crucibles. The reference crucible contained Al₂O₃. Samples were heated at 10 °C min⁻¹ to 465 °C. The thermocouple readings were calibrated using a series of DTA standard materials: KNO₃, In, Sn, Ag₂SO₄, and K₂SO₄ as well as Pb and Al as secondary standards, using the same heating rates as the samples.

Acknowledgements

We thank Mr. Jon P. Wright (Department of Chemistry, University of Cambridge) for helpful discussions during indexing and Rietveld refinement of the data on compounds **6** and **7**. M. S. K. gratefully acknowledges Sultan Qaboos University Research Grant No. IG/SCI/CHEM/02/02, EPSRC (U.K.) for a Visiting Fellowship and Sultan Qaboos University for a research leave. A. K. thanks Peterhouse, Cambridge for a Research Fellowship and the Royal Society for a University Research Fellowship. We also acknowledge the EPSRC grant GR/L52581 (J. P. A.) and GR/L92761 (P. R. R.) and for a studentship (to J. C. C.).

References

- J. H. Burroughes, D. D. C. Bradley, A. R. Brown, R. N. Marks, K. Mackay, R. H. Friend, P. L. Burn and A. B. Holmes, *Nature*, 1990, **347**, 539; N. Tessler, G. J. Denton and R. H. Friend, *Nature*, 1996, **382**, 695; J. J. M. Halls, C. A. Walsh, N. C. Greenham, E. A. Marseglia, R. H. Friend, S. C. Moratti and A. B. Holmes, *Nature*, 1995, **376**, 498; G. Yu, J. Gao, J. C. Hummelen, F. Wudl and A. J. Heeger, *Science*, 1995, **270**, 1789; F. Garnier, R. Hajlaoui, A. Yassar and P. Srivastava, *Science*, 1994, **265**, 1684.
- A. Montali, C. Bastiaansen, P. Smith and C. Weder, *Nature*, 1998, **392**, 261; C. Weder, C. Sarwa, A. Montali, C. Bastiaansen and P. Smith, *Science*, 1998, **279**, 835.
- (a) C. Weder and M. S. Wrighton, *Macromolecules*, 1996, **29**, 5157; (b) T. Yamamoto, K. Honda, N. Ooba and S. Tomaru, *Macromolecules*, 1998, **31**, 7; (c) H. Li, D. R. Powell, R. K. Hayashi and R. West, *Macromolecules*, 1998, **31**, 52; (d) A. Beeby, K. Findlay, P. J. Low and T. B. Marder, *J. Am. Chem. Soc.*, in the press; (e) C. Dai, P. Nguyen, T. B. Marder, A. J. Scott, W. Clegg and C. Viney, *Chem. Commun.*, 1999, 2493; (f) M. Biswas, P. Nguyen, T. B. Marder and L. R. Khundkar, *J. Phys. Chem. A*, 1997, **101**, 1689; (g) P. Nguyen, G. Lesley, T. B. Marder, I. Ledoux and J. Zyss, *Chem. Mater.*, 1997, **9**, 406.
- D. Beljonne, H. F. Wittman, A. Köhler, S. Graham, M. Younus, J. Lewis, P. R. Raithby, M. S. Khan, R. H. Friend and J. L. Bredas, *J. Chem. Phys.*, 1996, **105**, 3868; J. Lewis, N. J. Long, P. R. Raithby, G. P. Shields, W.-Y. Wong and M. Younus, *J. Chem. Soc., Dalton Trans.*, 1997, 4283; M. Younus, A. Köhler, S. Cron, N. Chawdhury, M. R. A. Al-Mandhary, J. Lewis, N. J. Long, R. H. Friend and P. R. Raithby, *Angew. Chem., Int. Ed.*, 1998, **37**, 3036; N. Chawdhury, A. Köhler, R. H. Friend, M. Younus, N. J. Long, P. R. Raithby and J. Lewis, *Macromolecules*, 1998, **31**, 722; M. C. B. Colbert, J. Lewis, N. J. Long, P. R. Raithby, M. Younus, A. J. P. White, D. J. Williams, N. N. Payne, L. Yellowlees, D. Beljonne, N. Chawdhury and R. H. Friend, *Organometallics*, 1998, **17**, 3034; J. Lewis, P. R. Raithby and W.-Y. Wong, *J. Organomet. Chem.*, 1998, **556**, 219; M. S. Khan, M. R. A. Al-Mandhary, M. K. Al-Suti, N. Feeder, S. Nahar, A. Köhler, R. H. Friend, P. J. Wilson and P. R. Raithby, *J. Chem. Soc., Dalton Trans.*, 2002, 2441; P. Li, B. Ahrens, K.-H. Choi, M. S. Khan, P. R. Raithby, P. J. Wilson and W.-Y. Wong, *CrysoEngComm*, 2002, **4**, 405.
- N. Chawdhury, A. Köhler, R. H. Friend, W.-Y. Wong, J. Lewis, M. Younus, P. R. Raithby, T. C. Corcoran, M. R. A. Al-Mandhary and M. S. Khan, *J. Chem. Phys.*, 1999, **110**, 4963.
- K. Mullen and G. Wegner, *Electronic Materials: The Oligomer Approach*, Wiley-VCH, New York, 1998.
- U. H. F. Bunz, V. Enkelmann, L. Kloppenburg, D. Jones, K. D. Shimizu, J. B. Claridge, H.-C. zur Loye and G. Lieser, *Chem. Mater.*, 1999, **11**, 1416.
- F. Wittmann, R. H. Friend, M. S. Khan and J. Lewis, *J. Chem. Phys.*, 1994, **101**, 2693.
- J. Cornil, D. A. dos Santos, X. Crispin, R. Silbey and J. L. Bredas, *J. Am. Chem. Soc.*, 1998, **120**, 1289.
- G. R. Desiraju, *J. Chem. Soc., Chem. Commun.*, 1990, 454; P. J. Langley, J. Hulliger, R. Thaimattam and G. R. Desiraju, *New J. Chem.*, 1998, **22**, 1307; J. M. A. Robinson, D. Philp, B. M. Kariuki and K. D. M. Harris, *Chem. Commun.*, 1999, 329.
- T. Steiner, *J. Chem. Soc., Chem. Commun.*, 1995, 95; D. Philp and J. M. A. Robinson, *J. Chem. Soc., Perkin Trans. 2*, 1998, 1643.
- S. Kumar, K. Subramanian, R. Srinivasan, K. Rajagopalan, A. M. M. Schreurs, J. Kroon, G. Koellner and T. Steiner, *J. Mol. Struct.*, 1998, **448**, 51.
- T. Steiner, B. Lutz, J. van der Maas, N. Veldman, A. M. M. Schreurs, J. Kroon and J. A. Kanters, *Chem. Commun.*, 1997, 191.
- (a) N. A. Ahmed, A. I. Kitaigorodsky and M. Sirota, *Acta Crystallogr., Sect. B*, 1972, **28**, 2875; (b) J. M. A. Robinson, B. M. Kariuki, R. J. Gough, K. D. M. Harris and D. Philp, *J. Solid State Chem.*, 1997, **134**, 203; (c) H.-C. Weiss, D. Bläser, R. Boese, B. M. Doughan and M. M. Haley, *Chem. Commun.*, 1997, 1703.
- T. Steiner, E. B. Starikov and M. Tamm, *J. Chem. Soc., Perkin Trans. 2*, 1996, 67.
- V. R. Vangala, A. Nangia and V. M. Lynch, *Chem. Commun.*, 2002, 1304.
- T. Steiner, *J. Chem. Soc., Chem. Commun.*, 1994, 101.
- (a) S. Thorand and N. Krause, *J. Org. Chem.*, 1998, **63**, 8551; (b) M. S. Khan, M. R. A. Al-Mandhary, M. K. Al-Suti, A. K. Hisahm, P. R. Raithby, B. Ahrens, M. F. Mahon, L. Male, E. A. Marseglia, E. Tedesco, R. H. Friend, A. Köhler, N. Feeder and S. J. Teat, *J. Chem. Soc., Dalton Trans.*, 2002, 1358; (c) R. Ziessel, J. Suffert and M.-T. Youinou, *J. Org. Chem.*, 1996, **61**, 6535; (d) P. Nguyen, Z. Yuan, L. Agocs, G. Lesley and T. B. Marder, *Inorg. Chim. Acta*, 1994, **220**, 289; (e) M. S. Khan, A. K. Kakkar, N. J. Long, J. Lewis, P. R. Raithby, P. Nguyen, T. B. Marder, F. Wittman and R. H. Friend, *J. Mater. Chem.*, 1994, **4**, 1227; (f) M. Moroni, J. Le Moigne, T. A. Pham and J.-Y. Bigot, *Macromolecules*, 1997, **30**, 1964.
- H.-C. Weiss, R. Boese, H. L. Smith and M. M. Haley, *Chem. Commun.*, 1997, 2403.
- R. S. Rowland and R. Taylor, *J. Phys. Chem.*, 1996, **100**, 7384.
- J. A. K. Howard, V. J. Hoy, D. O'Hagan and G. T. Smith, *Tetrahedron*, 1996, **52**, 12 613; J. D. Dunitz and R. Taylor, *Chem. Eur. J.*, 1997, **3**, 89.
- V. R. Thalladi, H.-C. Weiss, D. Blaser, R. Boese, A. Nangia and G. R. Desiraju, *J. Am. Chem. Soc.*, 1998, **120**, 8702.
- J. S. Wilson, A. Köhler, R. H. Friend, M. K. Al-Suti, M. R. A. Al-Mandhary, M. S. Khan and P. R. Raithby, *J. Chem. Phys.*, 2000, **113**, 7627.

- 24 (a) V. Cleave, G. Yahioğlu, P. Lebarney, R. H. Friend and N. Tessler, *Adv. Mater.*, 1999, **11**, 285; (b) M. A. Baldo, D. F. O'Brien, Y. You, A. Shoustikov, S. Sibley, M. E. Thompson and S. R. Forrest, *Nature*, 1998, **395**, 151.
- 25 A. Köhler, J. S. Wilson, R. H. Friend, M. K. Al-Suti, M. S. Khan, A. Gerhard and H. Bässler, *J. Chem. Phys.*, submitted.
- 26 D. Philp and J. M. A. Robinson, *J. Chem. Soc., Perkin Trans. 2*, 1998, 1643.
- 27 *Purification of Laboratory Chemicals*, eds. W. L. F. Armarego and D. D. Perrin, Butterworth-Heinemann, London, 1996.
- 28 T. Sargent, A. T. Shuglin and C. A. Mathia, *J. Med. Chem.*, 1984, **27**, 1071.
- 29 T. X. Neenan and G. M. Whitesides, *J. Org. Chem.*, 1988, **53**, 2489.
- 30 S. J. Davies, B. F. G. Johnson, M. S. Khan and J. Lewis, *J. Chem. Soc., Chem. Commun.*, 1991, 187; N. Hagihara, K. Sonogashira and S. Takahashi, *Adv. Polym. Sci.*, 1980, **41**, 149; S. Takahashi, H. Morimoto, E. Murata, S. Kataoka, K. Sonogashira and N. Hagihara, *J. Polym. Sci. Polym. Chem. Edu.*, 1982, **20**, 565.
- 31 G. M. Sheldrick, *Acta Crystallogr., Sect. A*, 1990, **46**, 467.
- 32 A. Altomare, G. Casciarano, C. Giacovazzo, A. Guagliardi, M. C. Burla, G. Polidori and M. C. Camalli, *J. Appl. Crystallogr.*, 1994, **27**, 435.
- 33 G. M. Sheldrick, SHELXL97, Program for crystal structure refinement, Göttingen, 1997.
- 34 A. Boulton and D. Louer, *J. Appl. Crystallogr.*, 1991, **24**, 987.
- 35 K. Shankland, W. I. F. David and T. Csoka, *Z. Kristallogr.*, 1997, **212**, 550; W. I. F. David, K. Shankland and N. Shankland, *Chem. Commun.*, 1998, 931; R. E. Dinnebier, P. Sieger, H. Nar, K. Shankland and W. I. F. David, *J. Pharm. Sci.*, 2000, **89**, 1465.
- 36 G. S. Pawley, *J. Appl. Crystallogr.*, 1981, **14**, 357.
- 37 A. C. Larson and R. B. Von Dreele, General Structure Analysis System (GSAS), Los Alamos National Laboratory, Report LAUR 86-748, 1994.
- 38 SHELXTL, An integrated system for solving, refining and displaying crystal structures from diffraction data, Ver. 5.10. Bruker AXS, Madison, Wisconsin, USA, 1997.