

A Novel Amine-Free Dianchoring Organic Dye for Efficient Dye-Sensitized Solar Cells


Hao-Chun Ting,[†] Chih-Hung Tsai,^{‡,§} Jia-Hong Chen,[†] Li-Yen Lin,[†] Shu-Hua Chou,[†] Ken-Tsung Wong,^{*,†} Tsung-Wei Huang,[‡] and Chung-Chih Wu^{*,‡}

Department of Chemistry, National Taiwan University, Taipei, 10617, Taiwan,
Department of Electrical Engineering, Graduate Institute of Electro-optical Engineering
and Graduate Institute of Electronics Engineering, National Taiwan University, Taipei,
10617, Taiwan, and Department of Opto-Electronic Engineering, National Dong Hwa
University, Hualien 97401, Taiwan

kenwong@ntu.edu.tw; chungwu@cc.ee.ntu.edu.tw

Received November 12, 2012

ABSTRACT

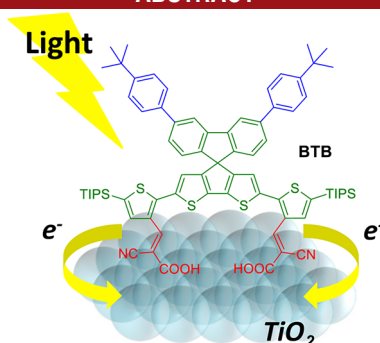

An amine-free oligothiophene-based dye (BTB) featuring a tailor-made dianchoring function, a spiro-configured central unit, and bulky end-capping TIPS groups to diminish intermolecular interactions and to suppress aggregation-induced self-quenching was synthesized to achieve efficient dye-sensitized solar cells with a high power conversion efficiency of 6.52%.

Since Grätzel's pioneering work in 1991, dye-sensitized solar cells (DSSCs) have evolved to be a potential candidate for a next-generation photovoltaic device.¹ Over the past two decades, tremendous research has been focused toward the search for efficient photosensitizers with desired physical properties, such as low band gap, high molar extinction coefficient, well-aligned energy levels, and suppressed aggregation behavior. To date, DSSCs with a remarkable power conversion efficiency (PCE) exceeding 11% have been realized using Ru-based sensitizers.²

Very recently, DSSCs sensitized with complementary porphyrin-based and organic dyes have achieved a PCE as high as 12.3%,³ making contemporary DSSCs highly competitive with other thin-film photovoltaic technologies. As such, metal-free organic dyes have attracted significant attention due to their various advantages such as great flexibility in structural tuning, low cost, resource availability, and generally large molar extinction coefficients.⁴

[†] Department of Chemistry, National Taiwan University.

[‡] Department of Electrical Engineering, National Taiwan University.

[§] National Dong Hwa University.

(1) O'reagen, B.; Grätzel, M. *Nature* **1991**, 353, 737.

(2) (a) Nazeeruddin, M. K.; Kay, A.; Rodicio, I.; Humphry-Baker, R.; Mueller, E.; Liska, P.; Vlachopoulos, N.; Graetzel, M. *J. Am. Chem. Soc.* **1993**, 115, 6382. (b) Nazeeruddin, M. K.; Zakeeruddin, S. M.; Jirousek, M.; Humphry-Baker, R.; Liska, P.; Vlachopoulos, N.; Shklover, V.; H. Fischer, C.; Grätzel, M. *Inorg. Chem.* **1999**, 38, 6298.

(3) Yella, A.; Lee, H.-W.; Tsao, H. N.; Yi, C.; Chandiran, A. K.; Nazeeruddin, M. K.; Diau, E. W.-G.; Yeh, C.-Y.; Zakeeruddin, S. M.; Grätzel, M. *Science* **2011**, 334, 629.


(4) (a) Mishra, A.; Fischer, M. K. R.; Bauerle, P. *Angew. Chem., Int. Ed.* **2009**, 48, 2474. (b) Clifford, J. N.; Ferrero, E. M.; Viterisi, A.; Palomares, E. *Chem. Soc. Rev.* **2011**, 40, 1635. (c) Zeng, W.; Cao, Y.; Bai, Y.; Wang, Y.; Shi, Y.; Zhang, M.; Wang, F.; Pan, C.; Wang, P. *Chem. Mater.* **2010**, 22, 1915. (d) Hagfeldt, A.; Boschloo, G.; Sun, L.; Kloo, L.; Pettersson, H. *Chem. Rev.* **2010**, 110, 6595. (f) Yen, Y.-S.; Chou, H.-H.; Chen, Y.-C.; Hsu, C.-Y.; Lin, J. T. *J. Mater. Chem.* **2012**, 22, 8734. (e) Ooyama, Y.; Harima, Y. *Eur. J. Org. Chem.* **2009**, 2903. (f) Lin, L.-Y.; Tsai, C.-H.; Wong, K.-T.; Huang, T.-W.; Wu, C.-C.; Chou, S.-H.; Lin, F.; Chen, S.-H.; Tsai, A.-I. *J. Mater. Chem.* **2011**, 21, 5950.

In the designs of metal-free organic dye sensitizers, the dipolar donor–(π -conjugated spacer)–acceptor (D– π –A) system is the most widely adopted molecular architecture, in which various arylamines such as triarylamine, carbazole, phenothiazine, and indoline are generally utilized as electron-donating moieties. The incorporation of these strong electron-donating groups in organic dyes facilitates effective photoinduced intramolecular charge transfer (ICT) and is, thus, beneficial in improving their light-harvesting abilities. Despite the wide adoption of such conventional arylamine-based donor structures, there were few reports of amine-free organic sensitizers.⁵ The replacement of arylamines with an electron-rich moiety bearing a relatively compact spatial volume as the donor group enables the sensitizers to have higher dye densities on TiO₂ surfaces, rendering feasible the fabrication of cocktail cells for panchromatic photon harvesting.⁶ In addition to the core skeletons, tailoring the structure and number of anchoring groups is also a research focus for developing efficient organic sensitizers.⁷ For Ru-based sensitizers, the number of anchoring groups (carboxylic acid) can be fine-tuned from one to four to control interfacial charge transfer.⁸ Recently, several organic sensitizers composed of two anchoring groups have also been introduced,⁹ and these dianchoring organic sensitizers were found to possess several advantages such as extended π -conjugation, increased electron extraction channels, multibinding abilities, higher photocurrent, and enhanced stability over their monoanchoring counterparts.¹⁰ As remarkable examples, the DSSCs sensitized with

benzothiadiazole- and phenothiazine-based multianchoring dyes had demonstrated PCEs exceeding 6%.¹¹

Here, we report a new amine-free dianchoring organic sensitizer, **BTB** (Scheme 1). This novel molecule was designed with the following structural characteristics: (i) it adopts oligothiophene as an electron-donating backbone to endow the dye with visible light absorption and a large molar extinction coefficient; (ii) the anchoring groups (cyanoacrylic acid) are introduced at γ -positions of the terminal thiophene rings to match the distance between the neighboring adsorption sites of the anatase TiO₂ surface and to ensure dianchoring adsorption (*vide infra*), which is critical for efficient electron transfer and better stability for dyes; (iii) it incorporates a spiro-configured central unit as a steric bulky group to diminish intermolecular interactions and to suppress aggregation-induced self-quenching that is usually encountered in organic dyes;¹² (iv) introduced bulky end-capping TIPS groups together with the central spiro-configured aryl group can form a hydrophobic shell to block the electrolyte diffusion and to reduce dark currents.

Scheme 1. Synthesis of Amine-Free Dianchoring Dye **BTB**

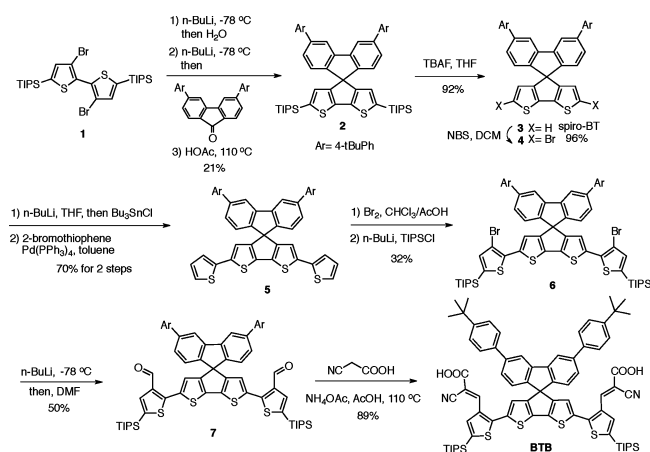

Scheme 1 depicts the synthesis of **BTB**. We established a modified approach for synthesizing spiro-bridged bithiophene, which avoids the use of reported cyclopenta[2,1-*b*:3',4'-*b'*]dithiophene-4-one¹³ as the essential intermediate. Our synthesis started from the selective lithium-bromine exchange reaction of 3,3',5,5'-tetrabromo-2,2'-bithiophene¹⁴ with *n*-BuLi, followed by quenching with chlorotriisopropylsilane (TIPS-Cl) to give TIPS-capped bithiophene **1** (46%).¹⁵ For the subsequent cyclization reaction, the introduction of TIPS groups on the reactive α -position of thiophene is essential for preventing possible intermolecular

(5) (a) Tan, S.; Zhai, J.; Fang, H.; Jiu, T.; Ge, J.; Li, Y.; Jiang, L.; Zhu, D. *Chem.—Eur. J.* **2005**, *11*, 6272. (b) Yang, H.-Y.; Yen, Y.-S.; Hsu, Y.-C.; Chou, H.-H.; Lin, J. T. *Org. Lett.* **2010**, *12*, 16. (c) Guo, K.; Yan, K.; Lu, X.; Qiu, Y.; Liu, Z.; Sun, J.; Yan, F.; Guo, W.; Yang, S. *Org. Lett.* **2012**, *14*, 2214.

(6) (a) Chen, C.-H.; Hsu, Y.-C.; Chou, H.-H.; Thomas, K. R. J.; Lin, J. T.; Hsu, C.-P. *Chem.—Eur. J.* **2010**, *16*, 3184. (b) Cid, J.-J.; Yum, J.-H.; Jang, S.-R.; Nazeeruddin, M. K.; Martinez-Ferrero, E.; Palomares, E.; Ko, J.; Grätzel, M.; Torres, T. *Angew. Chem., Int. Ed.* **2007**, *46*, 8358.

(7) (a) Cao, D.; Peng, J.; Hong, Y.; Fang, X.; Wang, L.; Meier, H. *Org. Lett.* **2011**, *13*, 1610. (b) Hong, Y.; Liao, J.-Y.; Cao, D.; Zang, X.; Kuang, D.-B.; Wang, L.; Meier, H.; Su, C.-Y. *J. Org. Chem.* **2011**, *76*, 8015.

(8) (a) Angelis, F. D.; Fantacci, S.; Selloni, A.; Grätzel, M.; Nazeeruddin, M. K. *Nano Lett.* **2007**, *7*, 3189. (b) Grätzel, M. *Inorg. Chem.* **2005**, *44*, 6841.

(9) (a) Heredia, D.; Natera, J.; Gervaldó, M.; Otero, L.; Fungo, F.; Lin, C.-Y.; Wong, K.-T. *Org. Lett.* **2010**, *12*, 12. (b) Yen, Y.-S.; Chen, W.-T.; Hsu, C.-Y.; Chou, H.-H.; Lin, J. T.; Yeh, M.-C. *P. Org. Lett.* **2011**, *13*, 4930. (c) Jiang, X.; Karlsson, K. M.; Gabrielson, E.; Johansson, E. M. J.; Quintana, M.; Karlsson, M.; Sun, L.; Boschloo, G.; Hagfeldt, A. *Adv. Funct. Mater.* **2011**, *21*, 2944. (d) Wu, T.-Y.; Tsao, M.-H.; Su, S.-G.; Wang, H. P.; Lin, Y.-C.; Chen, F.-L.; Chang, C.-W.; Sun, I.-W. *J. Braz. Chem. Soc.* **2011**, *22*, 780. (e) Li, Q.; Shi, J.; Li, H.; Li, S.; Zhong, C.; Guo, F.; Peng, M.; Hua, J.; Qin, J.; Li, Z. *J. Mater. Chem.* **2012**, *22*, 6689. (f) Sahu, D.; Padhy, H.; Patra, D.; Yin, J.-F.; Hsu, Y.-C.; Lin, J.-T.; Lu, K.-L.; Wei, K.-H.; Lin, H.-C. *Tetrahedron* **2011**, *67*, 303. (g) Sirohi, R.; Kimb, D.-H.; Yu, S.-C.; Lee, S. H. *Dyes Pigments* **2012**, *92*, 1132. (h) Chu, H.-C.; Sahu, D.; Hsu, Y.-C.; Padhy, H.; Patra, D.; Lin, J.-T.; Bhattacharya, D.; Lu, K.-L.; Wei, K.-H.; Lin, H.-C. *Dyes Pigments* **2012**, *93*, 1488. (i) Ramkumar, S.; Manoharan, S.; Anandan, S. *Dyes Pigments* **2012**, *94*, 503.

(10) (a) Abboto, A.; Leandri, V.; Manfredi, N.; Angelis, F. D.; Pastore, M.; Yum, J.-H.; Nazeeruddin, M. K.; Grätzel, M. *Eur. J. Org. Chem.* **2011**, 6195. (b) Abboto, A.; Manfredi, N.; Marini, C.; Angelis, F. D.; Mosconi, E.; Yum, J.-H.; Xianxi, Z.; Nazeeruddin, M. K.; Grätzel, M. *Energy Environ. Sci.* **2009**, *2*, 1094.

(11) (a) Mikroyannidis, J. A.; Sureshb, P.; Roy, M. S.; Sharmab, G. D. *J. Power Sources* **2010**, *195*, 3002. (b) Park, S.-S.; Won, Y. S.; Choi, Y. C.; Kim, J. H. *Energy Fuels* **2009**, *23*, 3732.

(12) Liu, D.; Fessenden, R. W.; Hug, G. L.; Kamat, P. V. *J. Phys. Chem. B* **1997**, *101*, 2583.

(13) (a) Lucas, P.; Mehdi, N. E.; Ho, H. A.; Belanger, D.; Breau, L. *Synthesis* **2000**, 9, 1253. (b) Mitschke, U.; Bauerle, P. *J. Chem. Soc., Perkin Trans. 1* **2001**, 740.

(14) Usta, H.; Lu, G.; Facchetti, A.; Marks, T. J. *J. Am. Chem. Soc.* **2006**, *128*, 9034.

(15) Baumgartner, T. *Appl. Organomet. Chem.* **2005**, *19*, 859.

reactions. The crucial intermediate **2** was obtained via a three-step process: (1) **1** was treated with *n*-BuLi and subsequent protonation with water; (2) the resulting mono-bromo intermediate was further treated with *n*-BuLi, followed by addition of a fluorenone, which was prepared by a Suzuki–Miyaura coupling reaction of 3,6-dibromo-9*H*-fluoren-9-one¹⁶ and 4-*tert*-butylphenylboronic acid;¹⁷ (3) the corresponding alcohol intermediate was subjected to acid-mediated intramolecular Friedel–Crafts cyclization in acetic acid to give **2** (21%, three steps). Protodesilylation of **2** with tetrabutylammonium fluoride yielded *spiro*-BT (**3**), which was then reacted with *N*-bromosuccinimide to give dibromo-BT (**4**) in 96% yield. Compound **4** was *in situ* transformed into a distannyl intermediate with *n*-BuLi, followed by quenching with Bu₃SnCl and then reaction with 2-bromothiophene to give tetrathiophene **5** (70%). The brominations at α - and γ -positions of the terminal thiophenes of **5** were successfully achieved by treating with bromine to give the tetrabromo intermediate, which was reacted with *n*-BuLi followed by the treatment with TIPS-Cl to produce **6** (32%, two steps). The bromo groups of **6** were converted to their corresponding carbaldehydes (**7**) by lithiation with *n*-BuLi and subsequently quenching with *N,N*-dimethylformamide. Finally, the dialdehyde **7** was condensed with cyanoacetic acid in the presence of ammonium acetate to afford the target dye **BTB** in 89% yield via a Knoevenagel reaction.

The electronic absorption spectrum of **BTB** in solution (10^{-5} M in THF) is shown in Figure 1a. The absorption spectrum of **BTB** shows two major absorption bands at $\lambda_{\text{max}} = 317$ (ϵ , 30 800 M⁻¹ cm⁻¹) and 490 nm (ϵ , 30 000 M⁻¹ cm⁻¹), respectively. The shorter wavelength band can be attributed to the π – π^* transition of the local spiro-configured 3,6-disubstituted fluorenyl group,¹⁶ whereas the longer one can be assigned to the π – π^* transition of the tetrathiophene-based chromophore. The absorption spectrum of **BTB** anchoring on a 7 μ m porous TiO₂ nanoparticle film (Figure 1b) shows an absorption maximum of 506 nm, which is red-shifted by 16 nm as compared to that in THF solution. The red shift is possibly due to the interaction between the TiO₂ surface and dyes that increases the delocalization of the π^* -orbital of the entire conjugated configuration and thus lowers the energy level of the π^* -orbital.¹⁸ The observed broad and red-shifted absorption of **BTB** on the TiO₂ nanoparticle film will be beneficial to improve the light-harvesting capability, resulting in the higher photocurrent density and better PCEs.¹⁹

The interactions between carboxylic groups of **BTB** and TiO₂ were probed by FTIR. Figure 2 shows the FTIR spectra of pristine **BTB** and **BTB** adsorbed on the TiO₂ surface. Obviously, the cyano group absorption band

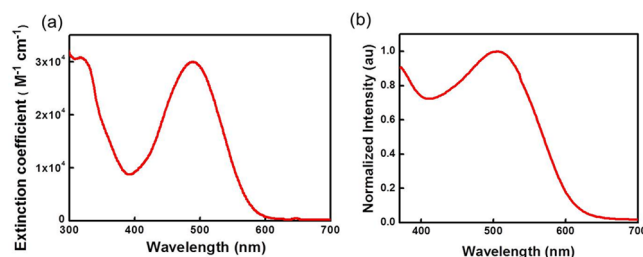


Figure 1. (a) Absorption (measured in THF solution 10^{-5} M) of **BTB**. (b) Absorption spectra of **BTB** anchoring on the 7 μ m porous TiO₂ nanoparticle film.

(2215 cm⁻¹) remained unchanged before and after interacting with TiO₂, indicating cyano groups were not involved in anchoring functions. For **BTB** adsorbed on the TiO₂ film, the IR absorption band at 1700 cm⁻¹ corresponding to the free carboxylic acid groups disappeared, while the absorption band at 1620 cm⁻¹ (overlapped with aromatic C=C stretching) appeared, which was identified as asymmetric stretching of carboxylate adsorbed on TiO₂. The absence of free carboxylic groups as indicated by the FTIR is a good indication of the dianchoring adsorption of **BTB** on the TiO₂ surface, agreeing with the previously reported behavior of dianchoring dyes.²⁰

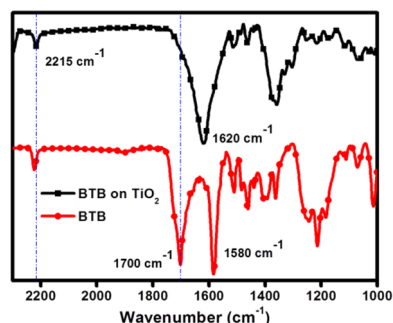


Figure 2. FTIR spectra of **BTB** measured as solid powders (●) and as stained onto the 7 μ m porous TiO₂ nanoparticle film (■).

To gain more insight into the structural and electronic features of **BTB**, DFT (density function theory) calculations were performed. The distance between two anchoring carboxylic acid groups of **BTB** was calculated to be *ca.* 10.72 Å (Figure S1), which nicely matches the distance between two neighboring adsorption sites (10.23 Å) on the anatase TiO₂ surface.²¹ This result confirms **BTB** possesses a suitable molecular configuration for dianchoring adsorption on the TiO₂ surface. This dianchoring feature is believed to benefit efficient surface adherence and

(16) Estrada, L. A.; Neckers, D. C. *J. Org. Chem.* **2009**, *74*, 8484.

(17) (a) Paul, V.; Roberts, B. P. *J. Chem. Soc., Perkin Trans. 2* **1988**, 1895. (b) Ashton, P. R.; Harris, K. D. M.; Kariuki, B. M.; Philp, D.; Robinson, J. M. A.; Spencer, N. *J. Chem. Soc., Perkin Trans. 2* **2001**, 2166.

(18) Tang, J.; Hua, J.; Wu, W.; Li, J.; Jin, Z.; Long, Y.; Tian, H. *Energy Environ. Sci.* **2010**, *3*, 1736.

(19) Tang, Z.-M.; Lei, T.; Jiang, K.-J.; Song, Y.-L.; Pei, J. *Chem.—Asian J.* **2010**, *5*, 1911.

(20) Park, J.; Barolo, C.; Sauvage, F.; Barbero, N.; Benzi, C.; Quagliotto, P.; Coluccia, S.; Censo, D. D.; Grätzel, M.; Nazeeruddin, M. K.; Viscardi, G. *Chem. Commun.* **2012**, *48*, 2782.

(21) Hagfeldt, A.; Grätzel, M. *Acc. Chem. Res.* **2000**, *33*, 269.

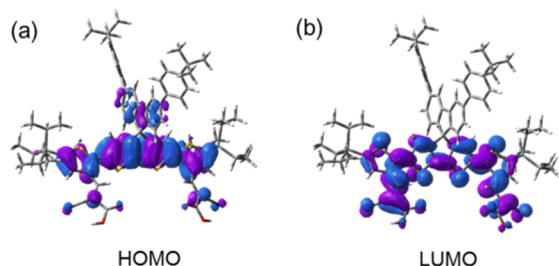


Figure 3. DFT HOMO and LUMO of **BTB** calculated at the B3LYP/6-31G(d) level.

subsequent electron transfer. In addition, DFT calculations suggest that the HOMO of **BTB** is mainly localized on the spirofluorene-bridged oligothiophene, whereas the LUMO is populated through the oligothiophene-conjugated backbone and cyanoacrylic acid fragments (Figure 3). This spatially separated arrangement of HOMO/LUMO ensures not only effective intramolecular charge transfer between donor and acceptor moieties but also efficient photoinduced electron injection from **BTB** to the TiO_2 electrode.

The electrochemical properties of **BTB** were investigated by cyclic voltammetry. As shown in Figure S2, **BTB** exhibits two reversible oxidation waves. The first oxidation potential (E_{ox} , 1.25 V vs normal hydrogen electrode, NHE) is more positive than the iodide/triiodide (I^-/I_3^-) redox couple (0.4 V vs NHE), indicating oxidized **BTB** is able to accept electrons from I^- thermodynamically for effective dye regeneration. The zero-zero excitation energy (E_{0-0} , 2.31 eV) estimated from the intersection of the absorption and emission spectra was combined with the ground-state oxidation potential (E_{ox}) to calculate the excited-state oxidation potential ($E_{\text{ox}}^* = E_{\text{ox}} - E_{0-0}$). The more negative E_{ox}^* (−1.06 V vs NHE) of **BTB** relative to the conduction band edge of TiO_2 (−0.5 V vs NHE)²² reveals the electron injection from excited **BTB** to TiO_2 should be energetically favorable.

The photovoltaic characteristics of **BTB** as a sensitizer for DSSCs were evaluated with a sandwich DSSC cell using 0.6 M 1-butyl-3-methylimidazolium iodide (BMII), 0.05 M LiI, 0.03 M I_2 , 0.5 M 4-*tert*-butylpyridine, and 0.1 M guanidinium thiocyanate in a mixture of acetonitrile–valeronitrile (85: 15, v/v) as the redox electrolyte (details of the device preparation and characterization are described in the Supporting Information (SI)). The incident monochromatic photon-to-current conversion efficiency (IPCE) spectrum of the DSSC is shown in Figure 4a. The DSSC based on **BTB** shows an IPCE of > 70% from 330 to 570 nm and reaches an IPCE maximum of 91% around

(22) Klein, C.; Nazzeeruddin, M. K.; Censo, D. D.; Liska, P.; Grätzel, M. *Inorg. Chem.* **2004**, *43*, 4216.

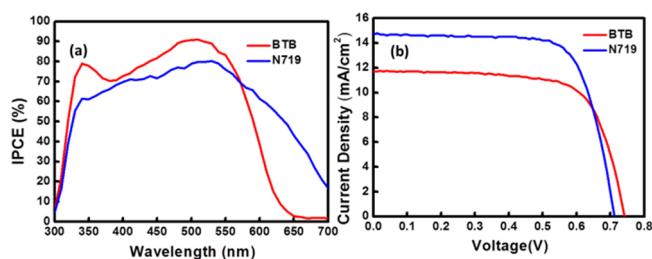


Figure 4. (a) IPCE spectra of DSSCs based on **BTB** (red) and **N719** (blue). (b) Current–voltage curves for DSSCs incorporating **BTB** (red) and **N719** (blue) under AM 1.5 G simulated sunlight.

500 nm, indicating highly efficient DSSC performance. Figure 4b shows the current density–voltage (J – V) curve of the DSSC under standard global AM 1.5G solar irradiation. The short-circuit photocurrent density (J_{SC}), open-circuit voltage (V_{OC}), and fill factor (FF) of the DSSC based on **BTB** are 12.51 mA/cm^2 , 0.74 V, and 0.70, respectively, yielding an overall PCE of 6.52%. For a fair comparison, the **N719**-sensitized DSSC was also fabricated and tested under similar conditions (see SI). The efficiency of the **BTB** cell reaches ~85% of the **N719** cell efficiency.

In summary, a new tailor-made amine-free, dianchoring DSSC sensitizer (**BTB**) featuring a tetrathiophene as the donor skeleton and elaborately equipped with cyanoacrylic acid anchoring groups at the γ -positions of terminal thiophene rings has been synthesized and characterized. The DFT calculation showed the distance (10.72 Å) between two carboxylic acid groups of **BTB** was close to the two neighboring adsorption sites on the anatase TiO_2 surface, rendering proper dianchoring adsorption, confirmed by the absence of free carboxylic acid in the FTIR spectra. A DSSC sensitized with **BTB** exhibited a high PCE of 6.52% with $J_{\text{SC}} = 12.51 \text{ mA}/\text{cm}^2$, $V_{\text{OC}} = 0.74 \text{ V}$, and $\text{FF} = 0.70$. Our study introduces a new approach to developing amine-free, dianchoring sensitizers for efficient and stable DSSCs.

Acknowledgment. The authors gratefully acknowledge financial support from the National Science Council of Taiwan (NSC 99-2221-E-002-118-MY3, 98-2119-M-002-007-MY3).

Supporting Information Available. Synthesis, characterization, copies of ^1H and ^{13}C NMR spectra, device fabrication, and optimization of solar cells. This material is available free of charge via the Internet at <http://pubs.acs.org>.

The authors declare no competing financial interest.