

From a Dissymmetrical Oxamidate Ligand to a 2D Coordination Polymer: Synthesis, Crystal Structure and Magnetic Properties

Bao Lin Liu^a, Juan Dang^a, Shuang Quan Zang^b, Qing Lun Wang^c, and Ruo Jie Tao^a

^a Institute of Molecular and Crystal Engineering, College of Chemistry and Chemical Engineering, Henan University, Kaifeng 475001, P. R. China

^b Department of Chemistry, Zhengzhou University, Henan 450052, P. R. China

^c Department of Chemistry, Nankai University, Tianjin 300071, P. R. China

Reprint requests to Prof. Ruo Jie Tao. Fax: +86-378-3881960. E-mail: rjtao@henu.edu.cn

Z. Naturforsch. **2010**, *65b*, 1240–1244; received May 23, 2010

A new dissymmetrical oxamidate ligand has been used to construct a metal-organic network. Using this ligand, a novel coordination polymer, namely $\{[\text{Cu}(\text{obe})]_2\text{Cu}\cdot\text{CH}_3\text{OH}\cdot\text{H}_2\text{O}\}_n$ (**1**) [$\text{H}_3\text{obe} = \text{N}1$ -(2-carboxyphenyl)- $\text{N}2$ -(2-hydroxyethyl)oxalamide] has been synthesized and characterized by single-crystal X-ray analysis. The structure of complex **1** consists of neutral trinuclear complex units. Through *syn-anti* carboxylate bridges, the complex features a 2D structure with a helical substructure. Its magnetic properties have been investigated.


Key words: Oxamidate Ligand, Crystal Structure, Magnetic Properties

Introduction

The crystal engineering of solid-state metal coordination supramolecules is one of the most active research topics of current chemistry and molecular science due to the theoretical aspects related to the topologies of novel networks with inner cavities and channels [1], as well as their potential applications in catalysis [2], host-guest chemistry [3], and molecular electronics [4]. Self-assembly of suitably designed ligands with transition metal ions allows the creation of inorganic architectures with defined geometry and special properties [5–7].

It is well known that a carboxylate group can bridge two metal ions to give rise to a wide variety of polynuclear complexes ranging from discrete entities to three-dimensional systems [8–10]. In these complexes, a carboxylate group can assume many types of bridging conformations, the most important being triatomic *syn-syn*, *anti-anti*, *syn-anti*, and monoatomic [11]. As expected, the magnetic properties are closely related to the bridging conformation adopted by the carboxylate group in these polynuclear systems. It should be noted that, as far as we know, only a few fully structurally and magnetically characterized singly *syn-anti* carboxylate-bridged complexes have been reported so far [12–15].

Oxamidate derivatives are known to be versatile organic ligands. One of the most outstanding characters

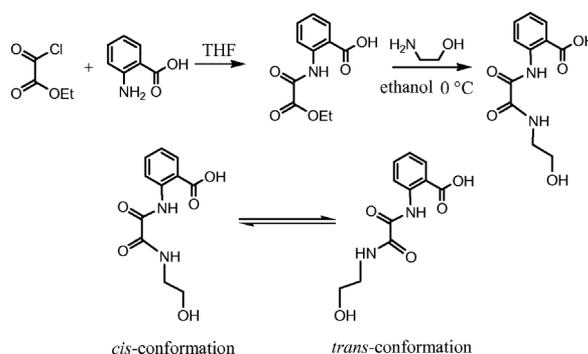

Scheme 1. Synthetic route to ligand H₃obe.

of these ligands is the easy transformation of *cis-trans* conformations, which makes it practical to design tunable molecular materials with extended structures and desired properties. The flexibility can give rise to a rich variety of complexes and extended structures, but it allows much less control over the final type of complex obtained [16].

With these facts in mind, the new dissymmetrical ligand *N*1-(2-carboxyphenyl)-*N*2-(2-hydroxyethyl)oxalamide, abbreviated as H₃obe, has been prepared in this work (Scheme 1). Based on this ligand, we describe the synthesis, crystal structure and magnetic properties of a novel coordination polymer, namely $\{[\text{Cu}(\text{obe})]_2\text{Cu}\cdot\text{CH}_3\text{OH}\cdot\text{H}_2\text{O}\}_n$ (**1**), which is a 2D framework containing both dissymmetri-

cal *trans*-oxamidate bridges and *syn-anti* carboxylate bridges.

Experimental Section

Materials

Cu(ClO₄)₂·6H₂O was prepared as an in-house reagent. Other chemicals were commercial reagent grade and used without further purification.

Caution! Perchlorates are potentially explosive, thus only a small amount of material should be prepared and handled with care.

Synthesis of the ligand H₃obea

A 50 mmol (6.83 g) portion of ethyl oxalyl chloride in 10 mL of THF (THF = tetrahydrofuran) was added dropwise into 40 mL of a THF solution of 50 mmol (6.86 g) of anthranilic acid. After 1 h, the mixture was added dropwise to a solution which contained 20 mL of absolute ethanol and 30 mL of ethanolamine at 0 °C. The resulting solution was stirred for 24 h, and H₃obea was precipitated as a colorless powder, washed with diethyl ether and dried under vacuum. Yield: 10.8 g (86 %). – Anal. for C₁₁H₁₂N₂O₅: calcd. C 52.38, H 4.79, N 11.11; found C 52.36, H 4.80, N 11.14 %. – IR (KBr): ν_{C=O}(oxamidate group) = 1636; ν_{as(COO)} (ν_{COOH} un-ionized) = 1672 cm⁻¹.

Synthesis of the complex {[Cu(obea)]₂Cu·CH₃OH·H₂O}_n (I)

H₃obea (0.1 mmol, 0.0252 g), NaOH (0.3 mmol, 0.012 g) and CuCl₂·2H₂O (0.1 mmol, 0.017 g) were dissolved in water (5 mL) in a test tube. A solution of Cu(ClO₄)₂·6H₂O (0.1 mmol, 0.0371 g) in methanol (5 mL) was then carefully added to the top of this solution without disturbing it. Blue block-shaped single crystals suitable for X-ray analysis were obtained after four weeks. Yield: 46%. – Anal. for C₂₃H₂₁N₄O₁₂Cu₃: calcd. C 37.53, H 2.88, N 7.61; found: C 37.43, H 2.83, N 7.67 %. – IR (KBr): ν_{C=O} = 1628 cm⁻¹.

Physical measurements

Elemental analyses for carbon, hydrogen and nitrogen were performed on a Perkin-Elmer 2400II elemental analyzer. The infrared spectra were recorded on an Avatar-360 spectrometer using KBr pellets in the range of 400–4000 cm⁻¹. Variable temperature magnetic susceptibility data were obtained on microcrystalline samples from 5 to 300 K in a magnetic field of 10 KG, using a Quantum Design MPMS-7 SQUID magnetometer. Diamagnetic corrections were made with Pascal parameters for all constituent atoms.

Table 1. Crystallographic data and refinement parameters for complex I.

Empirical formula	C ₂₃ H ₂₁ N ₄ O ₁₂ Cu ₃
Formula weight	737.07
Crystal system	monoclinic
Space group	P2 ₁ /c
a, Å	10.5442(10)
b, Å	7.1479(7)
c, Å	17.5062(17)
β, deg	105.465(2)
V, Å ³	1271.7(2)
Z	2
D _{calc} , g cm ⁻³	1.93
μ(MoK _α), mm ⁻¹	2.6
T, K	293(2)
λ, Å	0.71073
Index ranges	–11 ≤ h ≤ 12, –8 ≤ k ≤ 7, –20 ≤ l ≤ 20
Ref. total / independ. / R _{int}	6119 / 2238 / 0.0581
Ref. parameters	228
R1 / wR2 ^a [I ≥ 2 σ(I)]	0.0492 / 0.1248
R1 / wR2 ^a (all data)	0.0690 / 0.1317
Goodness-of-fit ^b	1.064
Δρ _{min} (max / min), e Å ⁻³	0.875 / –0.495

^a R1 = Σ||F_o| – |F_c|| / Σ|F_o|, wR2 = [Σw(F_o² – F_c²)² / Σw(F_o²)²]^{1/2}, w = [σ²(F_o²) + (0.0720 P)² + 0.1919 P]⁻¹, where P = (Max(F_o², 0) + 2F_c²) / 3; ^b GoF = [Σw(F_o² – F_c²)² / (n_{obs} – n_{param})]^{1/2}.

Table 2. Selected bond lengths (Å) and angles (deg) for complex I.

Cu(1)–N(2) ^{#1}	1.932(4)	Cu(1)–N(2)	1.932(4)
Cu(1)–O(3) ^{#1}	1.964(3)	Cu(1)–O(3)	1.964(3)
Cu(2)–O(1)	1.894(4)	Cu(2)–O(4)	1.934(3)
Cu(2)–N(1)	1.959(4)	Cu(2)–O(2) ^{#2}	1.958(3)
Cu(2)–O(1W)	2.533(9)	Cu(2)–O(6)	2.549(10)
N(2)–Cu(1)–N(2) ^{#1}	180	N(2) ^{#1} –Cu(1)–O(3) ^{#1}	83.90(15)
N(2)–Cu(1)–O(3) ^{#1}	96.10(15)	N(2) ^{#1} –Cu(1)–O(3)	96.10(15)
N(2)–Cu(1)–O(3)	83.90(15)	O(3) ^{#1} –Cu(1)–O(3)	180
O(1)–Cu(2)–O(2) ^{#2}	86.20(15)	O(4)–Cu(2)–O(2) ^{#2}	93.94(15)
O(1)–Cu(2)–O(4)	172.93(18)	O(1)–Cu(2)–N(1)	93.43(15)
O(4)–Cu(2)–N(1)	86.55(15)	O(2) ^{#2} –Cu(2)–N(1)	178.98(15)
O(1)–Cu(2)–O(1W)	88.0(3)	O(4)–Cu(2)–O(1W)	98.9(3)
O(2) ^{#2} –Cu(2)–O(1W)	100.2(2)	N(1)–Cu(2)–O(1W)	78.9(2)
O(1)–Cu(2)–O(6)	85.5(3)	O(4)–Cu(2)–O(6)	87.6(3)
O(2) ^{#2} –Cu(2)–O(6)	78.6(2)	N(1)–Cu(2)–O(6)	102.4(2)
O(1W)–Cu(2)–O(6)	173.5(3)		

Symmetry codes: ^{#1} –x + 1, –y + 1, –z + 2; ^{#2} –x, y + 1/2, –z + 3/2; ^{#3} –x, y – 1/2, –z + 3/2.

X-Ray analysis

A single crystal with dimensions 0.14 × 0.13 × 0.06 mm³ was used for the structure determination using a Bruker SMART APEX CCD diffractometer with graphite-monochromatized MoK_α radiation (λ = 0.71073 Å) at r.t. (ω scan technique). Lorentz, polarization and absorption corrections were applied. The crystal structure was solved by Direct Methods with the SHELXTL program and refined

by full-matrix least-squares procedures with anisotropic displacement parameters for all non-hydrogen atoms [17]. All H atoms could be detected in the difference electron density maps. Nevertheless, they were positioned at idealized positions and refined using a riding model. Analytical expressions of neutral-atom scattering factors were employed, and anomalous dispersion corrections were incorporated. Crystallographic data are summarized in Table 1. Selected bond lengths and bond angles are shown in Table 2.

CCDC-706284 contains the supplementary crystallographic data for this paper. These data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif.

Results and Discussion

IR spectra

The ligand H₃obeas exhibits one $\nu_{\text{C=O}}$ vibration band of the oxamidate group at *ca.* 1636 cm⁻¹ [18], one $\nu_{\text{as(COO)}}$ vibration band at *ca.* 1672 cm⁻¹ (ν_{COOH} un-ionized) [19], and $\nu_{\text{N-H}}$ bands of the oxamidate group at *ca.* 3082 and 3102 cm⁻¹. These bands are all missing in the spectrum of the complex because of the loss of the protons of both the COOH and N-H (oxamidate group) groups. It must be noted that one new sharp strong band observed in the complex **1** (1628 cm⁻¹) is the result of an overlap between $\nu_{\text{as(COO)}}$ of the ionized carboxylate group and the vibration of the oxamidate group ($\nu_{\text{C=O}}$) acting in a bidentate mode. No peak can be assigned unambiguously to metal-ligand vibrations in the range below 600 cm⁻¹, since the ligand itself has several absorptions in this region.

Description of the crystal structure

X-Ray single crystal structure analysis has revealed that complex **1** crystallizes in the space group *P2₁/c*. As shown in Fig. 1, complex **1** consists of a trinuclear neutral molecule, one water molecule, and one methanol molecule. The trinuclear neutral molecule has a centrosymmetric structure with a Cu1 ion in its center. Two oxamidate anions act as bridges between the central and the outer metal ions. The Cu–Cu distance through the oxamido bridge is 5.189(5) Å. The coordination geometry around the Cu1 ion is approximately square-planar, composed of two oxygen atoms and two nitrogen atoms from two *trans*-oxamidate bridges. The Cu2 ion has a distorted octahedral coordination, the equatorial positions being composed of two oxygen atoms (O1, O4), and one nitrogen atom (N1) of the *trans*-oxamidate bridge, and one carboxylic oxy-

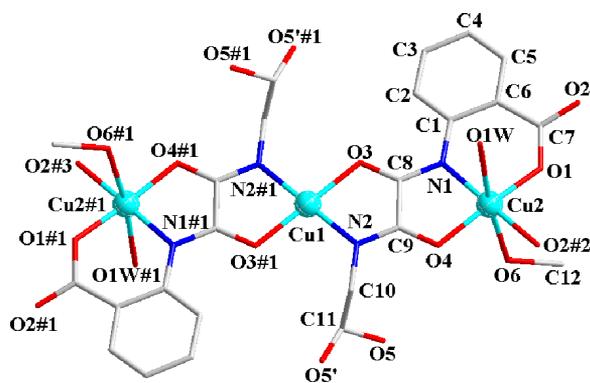


Fig. 1. Trinuclear unit of complex **1** (symmetry codes: #1 $-x + 3, -y + 3, -z$; #2 $-x + 2, -y + 1/2, -z - 1/2$; #3 $-x + 2, y - 1/2, -z - 1/2$; hydrogen atoms, methanol and water molecule are omitted for clarity).

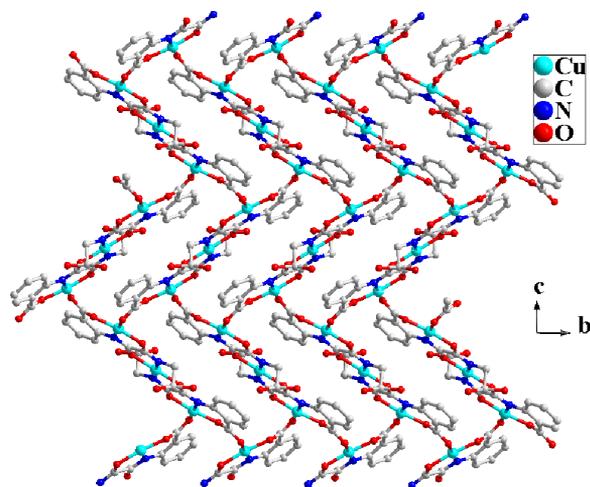


Fig. 2. The 2D structure of complex **1** as seen along the crystallographic *a* axis (hydrogen atoms, methanol and water molecules are omitted for clarity).

gen atom (O2#2) from another *trans*-oxamidate bridge. The axial positions are filled with one oxygen atom (O1W) from water, and one oxygen atom (O6) from methanol. Fig. 1 indicates that O5 is disordered over two sites.

These trinuclear units are linked by coordinative bonds between carboxylic oxygen atoms and Cu ions to form a novel double helical 2D coordination polymer, as illustrated in Fig. 2.

As noted earlier, each carboxylate group in the dissymmetrical ligand is in the *syn-anti* conformation and bridges two copper atoms *via* its two oxygen atoms. The bridging Cu–O–C–O–Cu pathway observed here gives rise to an interesting helical structure. Besides the

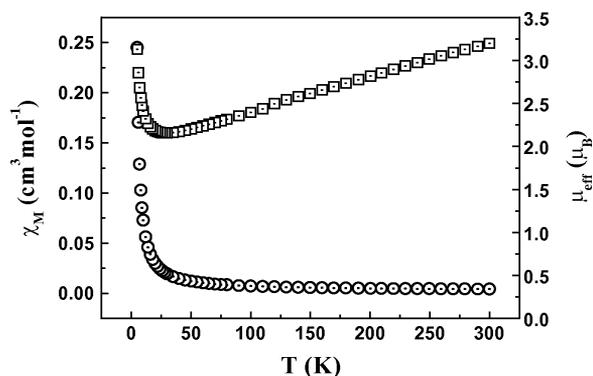


Fig. 3. χ_M versus T and μ_{eff} versus T plots for complex **1**.

syn-anti mode of the carboxylate, the *cis* arrangement of the two carboxylate ligands around the metal ion is important for the occurrence of the helical structure. Because left-handed and right-handed helical chains coexist in the crystal structure, the whole crystal does not exhibit chirality. The occurrence of a helical structure in compound **1** is attributable to the fact that the steric orientation of the carboxyl groups is remarkably flexible.

Magnetic properties

The magnetic susceptibility of the complex has been measured in the range of 5–300 K. The curves of

χ_M and μ_{eff} versus T are shown in Fig. 3. At r. t., the μ_{eff} value of complex **1** is $3.20 \mu_B$, which is slightly larger than that expected for uncoupled trinuclear ions ($3.00 \mu_B$). Upon cooling, the μ_{eff} value of the complex decreases regularly, approaching a minimum around 30 K with $\mu_{\text{eff}} = 2.15 \mu_B$. Finally, the μ_{eff} value of complex **1** increases as the temperature is further lowered to 5 K, which is possibly due to a ferromagnetic interaction between the trinuclear units through the *syn-anti* carboxylate bridges.

Conclusion

In summary, a novel helical 2D coordination polymer has been synthesized and characterized structurally and magnetically. In this complex, trinuclear units are linked by coordination bonds between carboxylic oxygen atoms and Cu ions to form a novel 2D coordination polymer. To our knowledge, complex **1** is the only helical coordination polymer containing both dissymmetrical *trans*-oxamidate bridges and *syn-anti* carboxylate bridges. The magnetic properties were discussed with respect to the crystal structure.

Acknowledgement

We acknowledge the generous financial support of the Natural Science Foundation of Henan Province (No. 092300410031).

- [1] a) B. F. Hoskins, R. Robson, *J. Am. Chem. Soc.* **1990**, *112*, 1546–1554; b) R. Robson, B. F. Abrahams, S. R. Batten, R. W. Gable, B. F. Hoskins, J. Liu, *Supramolecular Architecture*, American Chemical Society, Washington, DC, **1992**, chapter 19; c) O. M. Yaghi, G. Li, *Angew. Chem.* **1995**, *107*, 232–234; *Angew. Chem., Int. Ed. Engl.* **1995**, *34*, 207–209; d) J. R. Black, N. R. Champness, W. Levason, G. Reid, *Inorg. Chem.* **1996**, *35*, 4432–4438; e) L. Carlucci, G. Ciani, D. M. Proserpio, A. Sironi, *Inorg. Chem.* **1995**, *34*, 5698–5700.
- [2] M. Fujita, Y. J. Kwon, S. Washizu, K. Ogura, *J. Am. Chem. Soc.* **1994**, *116*, 1151–1552.
- [3] a) O. M. Yaghi, C. E. Davis, G. Li, H. Li, *J. Am. Chem. Soc.* **1997**, *119*, 2861–2868; b) S. Kawata, S. Kitagawa, H. Kumagai, C. Kudo, H. Kamesaki, T. Ishiyama, R. Suzuki, M. Kondo, M. Katada, *Inorg. Chem.* **1996**, *35*, 4449–4461; c) H. Zhang, X. Wang, B. K. Teo, *J. Am. Chem. Soc.* **1996**, *118*, 11813–11821.
- [4] a) M. S. E. Fallah, E. Rentschler, A. Caneschi, R. Sessoli, D. Gatteschi, *Angew. Chem.* **1996**, *108*, 2081–2083; *Angew. Chem., Int. Ed. Engl.* **1996**, *35*, 1947–1949; b) H. Miyasaka, N. Matsumoto, H. Okawa, N. Re, E. Gallo, C. Floriani, *J. Am. Chem. Soc.* **1996**, *118*, 981–994.
- [5] a) J. M. Lehn, *Supramolecular Chemistry: Concepts and Perspectives*, VCH, Weinheim, **1995**; b) O. M. Yaghi in *Access in Nanoporous Materials*, (Eds.: T. L. Pinnavania, M. F. Thorpe), Plenum, New York **1995**, pp. 111.
- [6] a) O. Sato, T. Iyoda, A. Fujishima, K. Hashimoto, *Science* **1996**, *271*, 49–51; b) H. J. Choi, M. P. Suh, *J. Am. Chem. Soc.* **1998**, *120*, 10622–10628.
- [7] a) S. R. Batten, R. Robson, *Angew. Chem.* **1998**, *110*, 1558–1595; *Angew. Chem. Int. Ed.* **1998**, *37*, 1460–1494; b) P. J. Hagraman, D. Hagraman, J. Zubieta, *Angew. Chem.* **1999**, *111*, 2798–2848; *Angew. Chem. Int. Ed.* **1999**, *38*, 2638–2684; c) A. J. Blake, N. R. Champness, P. Hubberstey, W. S. Li, M. A. Withersby, M. Schröder, *Coord. Chem. Rev.* **1999**, *183*, 117–138.
- [8] R. J. Doedens, *Prog. Inorg. Chem.* **1976**, *21*, 209–231.
- [9] S. J. Rettig, R. C. Thompson, J. Trotter, S. Xia, *Inorg. Chem.* **1999**, *38*, 1360–1363.
- [10] V. Tangoulis, G. Psomas, C. Dendrinou-Samara, C. P.

- Raptopoulou, A. Terzis, D.P. Kessissoglou, *Inorg. Chem.* **1996**, *35*, 7655–7660.
- [11] E. Colacio, J.M. Domínguez-Vera, M. Ghazi, R. Kivekäs, M. Klinga, J.M. Moreno, *Eur. J. Inorg. Chem.* **1999**, 441–445.
- [12] E. Colacio, J.M. Domínguez-Vera, R. Kivekäs, J.M. Moreno, A. Romerosa, J. Ruiz, *Inorg. Chim. Acta* **1993**, *212*, 115–121.
- [13] K. K. Nanda, A. W. Addison, E. Sinn, L. K. Thompson, *Inorg. Chem.* **1996**, *35*, 5966–5967.
- [14] D. Schulz, T. Weyhermüller, K. Wieghardt, C. Butzlaff, A. X. Trautwein, *Inorg. Chim. Acta* **1996**, *247*, 387–394.
- [15] S. Sen, M. K. Saha, T. Gupta, A. K. Karmakar, P. Kundu, S. Mitra, M. B. Hursthouse, K. M. A. Malik, *J. Chem. Crystallogr.* **1998**, *28*, 771–777.
- [16] a) H. Ojima, K. Nonoyama, *Coord. Chem. Rev.* **1988**, *92*, 85; b) R. Ruiz, J. Faus, F. Lloret, M. Julve, Y. Journaux, *Coord. Chem. Rev.* **1999**, *193*, 1069–1117.
- [17] a) R. H. Blessing, *Acta Crystallogr.* **1995**, *A51*, 33–38; b) G. M. Sheldrick, SHELXTL (version 5.1), Bruker Analytical X-ray Systems Inc., Madison, Wisconsin (USA) **1997**. See also: G. M. Sheldrick, *Acta Crystallogr.* **1990**, *A46*, 467–473; *ibid.* **2008**, *A64*, 112–122.
- [18] K. Nakamoto, *Infrared and Raman Spectra of Inorganic and Coordination Compounds*, 5th ed., Part B, John Wiley, New York, **1997**.
- [19] Y. Akhiff, J. Server-Carrió, J. Garcí-Lozano, E. Esquivá, J. V. Folgado, L. Soto, *Inorg. Chem.* **1999**, *38*, 1174–1185.