

A Journal of the Gesellschaft Deutscher Chemiker

Angewandte Chemie

GDCh

International Edition

www.angewandte.org

Accepted Article

Title: Control of surface barriers in mass transfer to modulate methanol-to-olefins reaction over SAPO-34 zeolites

Authors: Shichao Peng, Mingbin Gao, Hua Li, Miao Yang, Mao Ye, and Zhongmin Liu

This manuscript has been accepted after peer review and appears as an Accepted Article online prior to editing, proofing, and formal publication of the final Version of Record (VoR). This work is currently citable by using the Digital Object Identifier (DOI) given below. The VoR will be published online in Early View as soon as possible and may be different to this Accepted Article as a result of editing. Readers should obtain the VoR from the journal website shown below when it is published to ensure accuracy of information. The authors are responsible for the content of this Accepted Article.

To be cited as: *Angew. Chem. Int. Ed.* 10.1002/anie.202009230

Link to VoR: <https://doi.org/10.1002/anie.202009230>

Control of surface barriers in mass transfer to modulate methanol-to-olefins reaction over SAPO-34 zeolites

Shichao Peng,^{[a], [b]} Mingbin Gao,^{[a], [b]} Hua Li,^{* [a]} Miao Yang,^[a] Mao Ye,^{* [a]} and Zhongmin Liu^[a]

- [a] S. Peng, M. Gao, Dr. M. Yang, Dr. H. Li, Prof. Dr. M. Ye, Prof. Dr. Z. Liu
National Engineering Laboratory for Methanol-to-Olefins, Dalian National Laboratory for Clean Energy, Dalian Institute of Chemical Physics, Chinese Academy of Sciences
Dalian 116023 (P. R. China)
E-mail: lihua@dicp.ac.cn; maoye@dicp.ac.cn
- [b] S. Peng, M. Gao
University of Chinese Academy of Sciences
Beijing 100049 (P. R. China)

Supporting information for this article is given via a link at the end of the document.

Abstract: Mass transfer of guest molecules has great impact on the applications of nanoporous crystalline materials and particularly the shape selective catalysis over zeolites. Control of mass transfer to alter reaction over zeolites, however, remains an open challenge. Recent studies show that, in addition to intracrystalline diffusion, surface barriers represent another transport mechanism which may dominate the overall mass transport rate in zeolites. Here, we demonstrate the methanol-to-olefins (MTO) reaction can be modulated by regulating surface permeability in SAPO-34 zeolites with improved chemical liquid deposition and acid etching. Our results explicitly show the reduction of surface barriers can prolong catalyst lifetime and promote light olefins selectivity, which opens a potential avenue for improving reaction performance by controlling the mass transport of guest molecules in zeolite catalysis.

Mass transfer of guest molecules in nanoporous crystalline materials is of fundamental significance in processes spanning heterogeneous catalysis and gas separation.^[1] One of particularly notable applications is zeolite catalysts widely utilized for producing liquid fuel and chemicals, in favor of the unique shape selectivity.^[2] Routinely limitation of mass transfer, especially molecular diffusion, which is related to topological structures of zeolites and steric dimension of molecules, is considered governing shape selective catalysis. The mechanism underlying molecular diffusion in zeolites, however, is quite involved and not yet fully understood.

It is recently found that, despite the well-acknowledged intracrystalline diffusion that is intrinsic to molecular properties and material structures, surface barriers represent another important transport mechanism.^[3] The origins of surface barriers, though not fully understood, are closely related to the non-ideality of zeolite crystals which can be the consequences of, among others, surface modification, defects formation, and pores decoration.^[4] As revealed by interference microscopy (IFM) and infrared microscopy (IRM),^[4b, 5] surface barriers may dominate the overall mass transport rate in zeolite catalysts. Despite the importance of surface resistance in mass transfer over zeolite crystals being qualitatively identified, controlling the performance of catalytic reaction by directed modulation of surface barriers remains an open challenge.

Methanol-to-olefins (MTO), first commercialized in 2010, has gained considerable interests for effectively producing ethylene and propylene from alternative resources such as natural gas, coal, and biomass.^[6] SAPO-34 zeolites have been accepted well suitable for MTO owing to the special CHA-type structure, in

which heavy aromatic species are readily generated and accumulated within cavities during olefins formation. This can result in the pronounced mass transport limitation for the large molecules and thus the enhanced light olefins selectivity.^[7] It is shown by IFM that the dominating transport mechanism of methanol in SAPO-34 zeolites is surface barriers.^[4b] Based on the distribution of coke species (i.e. heavy aromatics) observed by confocal fluorescence microscopy (CFM), the researchers further speculated that surface barriers may have significant impact on MTO reaction.^[8] This provides important and practical implications on the possibility of altering MTO reaction via regulating the mass transport. In this work, for the first time, we demonstrate the modulation of MTO reaction over SAPO-34 zeolites by controlling surface permeability of guest molecules.

The external surface of zeolite crystals can be decorated by post-synthesis treatments,^[9] including chemical liquid/vapor deposition (CLD/CVD) and HF etching. However, modifying zeolite surfaces by these conventional methods would cause the suppression of acid density^[10] and damage of internal structure of crystals^[11], unavoidably changing intracrystalline diffusivities of guest molecules. To achieve the modulation of surface barriers, a prerequisite is that the modification is only made for external surface of crystals while the change of interiors is negligible. In doing so, SAPO-34 zeolite samples were first synthesized hydrothermally^[12] and denoted as SAPO-34-B. Then part of SAPO-34-B samples were decorated by CLD of tetraethoxysilane (TEOS), denoted as SAPO-34-L. In the CLD treatment, although the SiO₂ on the outer surface may increase the surface sticking probability, multiple deposits likely cause pore blockage.^[2b] As a consequence, it is more difficult for molecules to enter the crystals, resulting in the pronounced surface barriers or low surface permeability in SAPO-34-L. As the large molecules of TEOS could hardly pass the nanopores, the decoration was expected to occur on the external surface of SAPO-34-L. Parts of SAPO-34-B samples were treated by etching with acetic acid solution, removing the structural defects and opening the orifices.^[3b] These samples would have reduced surface barriers, denoted as SAPO-34-H. As organic template could effectively prevent acetic acid from entering the interior, a minor change of internal structures of SAPO-34-H is also expected. Furthermore, a decrease of acid strength for etching was achieved to avoid the destruction of crystals and assure the stability of samples. The details of synthesis and modifications are described in Supporting Information.

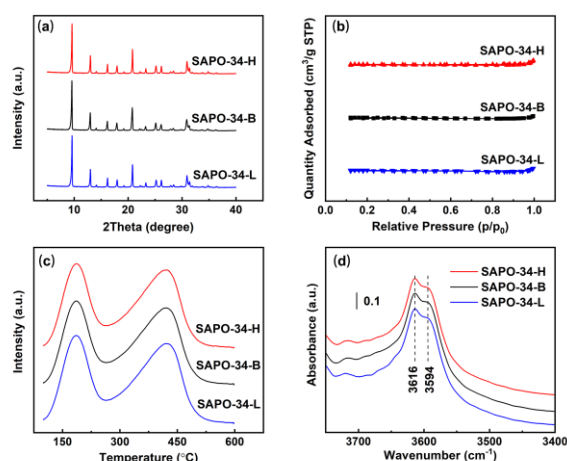


Figure 1. XRD patterns (a), nitrogen adsorption-desorption isotherms (b), NH₃-TPD profiles (c), and DRIFT spectra (d) of three SAPO-34 samples.

The changes of interior structure and acid properties of SAPO-34 zeolites after modifications were carefully examined. The XRD patterns of all three SAPO-34 samples are shown in Figure 1a, which manifest typical characteristic diffraction peaks of the CHA topology, showing the stability of zeolites to the surface modifications. Table S1 shows the relative crystallinity calculated based on the characteristic peaks at $2\theta = 9.4$, 12.8 and 20.5° , and indicates that the relative crystallinity is invariant for three samples. The SEM images of three samples are depicted in Supporting Information (Figure S1), showing a similar morphology of cubic crystals with an average size of $2\ \mu\text{m}$ and no clear morphological changes after surface modifications. The Si/Al molar ratios (Table S1) suggest that the compositions of crystals are essentially the same for three samples. Figure 1b shows the N₂ adsorption-desorption isotherms, and the corresponding properties are also reported in Table S1. The treated zeolites exhibit similar micropore surface area and volume with the SAPO-34-B and little mesopore volume are detected, which suggests that there are no obvious changes in pore structure after treatments. From the NH₃-TPD curves (Figure 1c), two separated desorption peaks exist around 187 and 421°C , corresponding to weak and strong acid sites in the samples, and no significant changes have been observed in the strength of surface acid sites. Besides, the acid densities of three SAPO-34 samples are similar (Table S1). In DRIFTS as shown in Figure 1d, the absorption bands at around 3616 and $3594\ \text{cm}^{-1}$ are assigned to the vibrations associated with bridging hydroxyl (Si-OH-Al) groups,^[13] which refer to Brønsted acid sites, i.e. the active sites for MTO reaction. As can be seen, DRIFTS profiles are nearly uniform, indicating that Brønsted acid sites were almost unaffected by the decoration of surfaces. Thus it can be summarized that, based on the structure, texture and acidic property of the three SAPO-34 samples shown in Figure 1 and Table S1, all three SAPO-34 samples have nearly the same intracrystalline characteristics regardless of the treatments.

The surface barriers and intracrystalline diffusion of guest molecules were quantified through uptake rate measurements. The dual resistance model (DRM) has been proposed to account for the combined effect of surface barriers and intracrystalline diffusion in uptake rate profile:^[14]

$$\frac{m_t}{m_\infty} = 1 - \sum_{n=1}^{\infty} \frac{2L^2 \exp\left(-\frac{\beta_n^2 D t}{l^2}\right)}{(\beta_n^2 + L^2 + L)\beta_n^2}; \quad \beta_n \tan \beta_n = L = \frac{\alpha l}{D} \quad (1)$$

where m_t/m_∞ is the normalized loading, t the uptake time, D the intracrystalline diffusivity, α the surface permeability, and l the equivalent radius. Nevertheless, DRM requires in prior information of D to derive α or vice versa. Recently, Gao et al.^[15] proposed to estimate α from the initial uptake rate

$$\left.\frac{m_t}{m_\infty}\right|_{\sqrt{t} \rightarrow 0} \cong \frac{\alpha}{l} (\sqrt{t})^2 \quad (2)$$

and D from the fitting of uptake curves with DRM. The SAPO-34 zeolite crystals are approximately treated as cubes with the equivalent radius calculated by $l = b/4.06$, where b represents the length of crystal.

It should be stressed α and D varies with guest molecules of interest. However, MTO reaction is very complicated and many intermediates and products would be formed. The surface barriers are dependent upon the guest molecules in terms of size, structure, and polarity. In MTO the ethene and propene are targeted products. It is shown that the kinetic diameter of propene is comparable to the size of nanopores of SAPO-34 zeolites, and the limitation of diffusion of molecules larger than propene leads to the high light olefins selectivity.^[16] To minimize the influence of adsorption and reaction, propane, rather than propene, was used as the model molecule in deriving α and D . The adsorption curve of propane at 40°C was measured by intelligent gravimetric analyzer (IGA), which was further used to derive α and D for three SAPO-34 samples. Figure 2 show α and D of propane fitted with Eq. (1) and (2). For propane, similar D is observed for all three samples, which is in accordance with the uniform structural, textural and acid properties shown in Figure 1. An apparent increase in α is observed for three samples in the order of SAPO-34-L, SAPO-34-B and SAPO-34-H. For comparison, the adsorption curve of methanol was also measured by IGA at 20°C . Similar trends of D and α can also be observed for methanol for three samples.

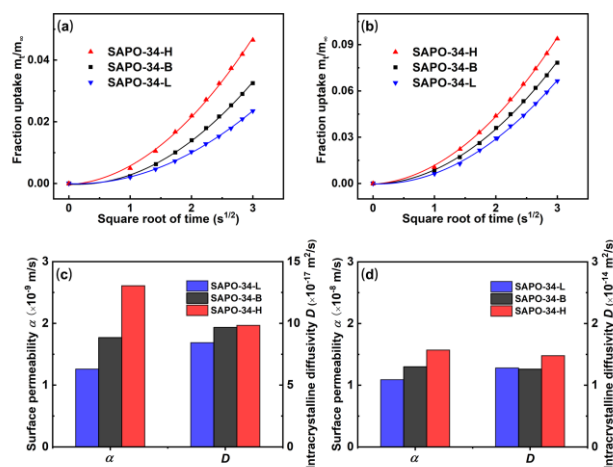


Figure 2. Initial uptake rates of propane (a) at 40°C and methanol (b) at 20°C in three SAPO-34 samples. The scatters represent the experimental data while solid lines are fitting results by Eq. (2). The correlation coefficient R^2 of all fitting is greater than 0.999. Surface permeability and intracrystalline diffusivity of propane (c) and methanol (d) derived by the uptake rates (Supporting Information Figure S2) following Gao et al.^[15]

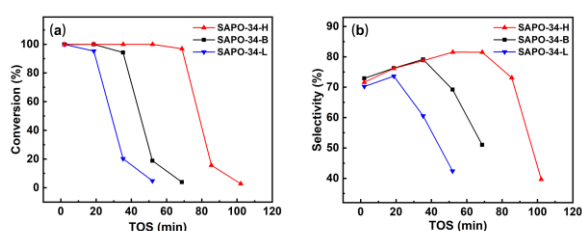


Figure 3. Methanol conversion (a) and light olefins (ethene, propene) selectivity (b) as a function of time on stream (TOS) in MTO reaction over SAPO-34 samples. Reaction condition: 450 °C, methanol WHSV = 5.0 h⁻¹.

As effective diffusivity has been frequently applied to understand molecular transport, we also calculated the effective diffusivity.^[4b] It is found that, although the variation of effective diffusivity is in accordance with our findings for surface permeability, the mechanism of mass transport cannot be directly inferred. A detailed discussion is including in Supporting Information.

The SAPO-34 samples were evaluated by performing MTO reaction at 450°C under atmospheric pressure with a weight hourly space-velocity (WHSV) of 5.0 h⁻¹. Figures 3a and b respectively illustrate the methanol conversion and light olefins selectivity. The catalyst lifetime is defined as the time with methanol conversion above 95%. It is shown that the catalyst lifetime for SAPO-34-B is 35 min, which, after modification, is extended to 69 min for SAPO-34-H and shortened to 19 min for SAPO-34-L. Considering that the interior structures of crystals were almost unchanged as revealed above, the variation of catalyst lifetime could be mainly related to surface barriers of guest molecules, i.e. SAPO-34 zeolites would have an extended lifetime in MTO reaction with the increase of surface permeability. Figure 4 further shows the surface permeabilities of propane and methanol with regard to catalyst lifetime. As can be seen, catalyst lifetime depicts a linearly increase with surface permeability of guest molecules. It is not clear at present whether such a linear relation is intrinsic or not, which nevertheless deserves further study. As for the light olefins selectivity, it is shown in Figure 3b that SAPO-34-H which has reduced surface barriers exhibits higher peak selectivity of 81.6%, while SAPO-34-L which has enhanced surface barriers shows a low peak selectivity of 73.6%. Note that peak light olefins selectivity for SAPO-34-B is 79.2%.

It has been previously shown that surface barriers would symmetrically affect guest molecules in moving in and out of the zeolite crystals.^[17] The increase of surface barriers would limit the corresponding guest molecules diffuse outward the crystals during MTO reaction and enhance further transformation of light olefins to heavy aromatics in the cavities, which lowers the light olefins yield and weakens the resistance to inactivation. In this sense, a shorter catalyst lifetime and lower light olefins selectivity is expected. Therefore, it is possible to modulate catalyst lifetime and light olefins selectivity in MTO reaction by controlling the surface barriers in SAPO-34 zeolites.

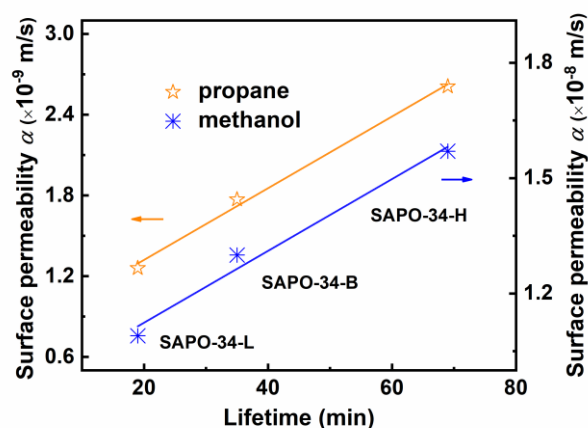


Figure 4. The surface permeability of propane and methanol with regard to the lifetime of SAPO-34 zeolites. The scatters represent the experimental data while solid lines are linearly fitting results.

In conclusion, for the first time we demonstrate the controlling of surface barriers in SAPO-34 zeolites can be applied to modulate catalyst lifetime and light olefins selectivity in MTO reaction. Through CLD and acid etching, we can modify the surface properties while maintaining the morphology, internal structure and acid properties of SAPO-34 zeolites, which make it possible to regulate surface permeability without changing the intracrystalline diffusivity of guest molecules. Essentially decreasing surface barriers would cause a longer catalyst lifetime and higher light olefins selectivity. Despite serving as the explicit evidence on the correlation between surface barriers and catalytic performance, this work opens an avenue to improve reaction performance by controlling mass transport of guest molecules in zeolite catalysis.

Acknowledgements

This work is supported by the National Natural Science Foundation of China (Grant No.91834302).

Conflict of interest


The authors declare no competing financial interests.

Keywords: Zeolite catalysis • Surface Barriers • Modulation • SAPO-34 • Methanol-to-olefins

- [1] aG. T. Whiting, N. Nikolopoulos, I. Nikolopoulos, A. D. Chowdhury, B. M. Weckhuysen, *Nat. Chem.* **2019**, 11, 23-31; bZ. Guo, X. Li, S. Hu, G. Ye, X. Zhou, M. O. Coppens, *Angew. Chem. Int. Ed.* **2020**, 59, 1548-1551; cY. Wu, S. Zeng, D. Yuan, J. Xing, H. Liu, S. Xu, Y. Wei, Y. Xu, Z. Liu, *Angew. Chem. Int. Ed.* **2020**; dK. Li, D. H. Olson, J. Seidel, T. J. Emge, H. Gong, H. Zeng, J. Li, *J. Am. Chem. Soc.* **2009**, 131, 10368-+; eG. Ye, Y. Sun, Z. Guo, K. Zhu, H. Liu, X. Zhou, M.-O. Coppens, *J. Catal.* **2018**, 360, 152-159; fM. Gao, H. Li, W. Liu, Z. Xu, S. Peng, M. Yang, M. Ye, Z. Liu, *Nat. Commun.* **2020**, 11, 3641.

- [2] aU. Olsbye, S. Svelle, M. Bjorgen, P. Beato, T. V. Janssens, F. Joensen, S. Bordiga, K. P. Lillerud, *Angew. Chem. Int. Ed.* **2012**, 51, 5810-5831; bS. Zheng, H. R. Heydenrych, H. P. Roger, A. Jentys, J. A. Lercher, *Topics Cata.* **2003**, 22, 101-106; cS. Zheng, A. Jentys, J. Lercher, *J. Cata.* 2006, 241, 304-311.
- [3] aL. Heinke, J. Karger, *Phys. Rev. Lett.* **2011**, 106, 074501; bF. Hibbe, C. Chmelik, L. Heinke, S. Pramanik, J. Li, D. M. Ruthven, D. Tzoulaki, J. Karger, *J. Am. Chem. Soc.* **2011**, 133, 2804-2807; cS. M. Rao, E. Saraçi, R. Gläser, M.-O. Coppens, *Chem. Eng. J.* **2017**, 329, 45-55.
- [4] aW. L. Duncan, K. P. Moller, *Adsorp.-J. Int. Adsorp. Soc.* **2005**, 11, 259-273; bJ. C. Saint Remi, A. Lauerer, C. Chmelik, I. Vandendael, H. Terryn, G. V. Baron, J. F. Denayer, J. Karger, *Nat. Mater.* **2016**, 15, 401-406.
- [5] aJ. Karger, T. Binder, C. Chmelik, F. Hibbe, H. Krautscheid, R. Krishna, J. Weitkamp, *Nat. Mater.* **2014**, 13, 333-343; bL. Zhang, C. Chmelik, A. N. van Laak, J. Karger, P. E. de Jongh, K. P. de Jong, *Chem. Commun. (Camb)* **2009**, 6424-6426; cC. Chmelik, J. Karger, *Chem. Soc. Rev.* 2010, 39, 4864-4884.
- [6] aM. Stocker, *Micro. Meso. Mater.* **1999**, 29, 3-48; bM. Ye, H. Li, Y. Zhao, T. Zhang, Z. Liu, *Adv. Chem. Eng.* **2016**, 47, 279-335.
- [7] aS. Gao, S. Xu, Y. Wei, Q. Qiao, Z. Xu, X. Wu, M. Zhang, Y. He, S. Xu, Z. Liu, *J. Cata.* **2018**, 367, 306-314; bW. Dai, G. Wu, L. Li, N. Guan, M. Hunger, *ACS Cata.* **2013**, 3, 588-596; cP. Tian, Y. Wei, M. Ye, Z. Liu, *ACS Cata.* **2015**, 5, 1922-1938.
- [8] aL. Karwacki, E. Stavitski, M. H. Kox, J. Kornatowski, B. M. Weckhuysen, *Angew. Chem. Int. Ed.* **2007**, 46, 7228-7231; bD. Mores, E. Stavitski, M. H. Kox, J. Kornatowski, U. Olsbye, B. M. Weckhuysen, *Chem. - Eur. J.* **2008**, 14, 11320-11327; cQ. Qian, J. Ruiz-Martinez, M. Mokhtar, A. M. Asiri, S. A. Al-Thabaiti, S. N. Basahel, H. E. van der Bij, J. Kornatowski, B. M. Weckhuysen, *Chem. - Eur. J.* **2013**, 19, 11204-11215.
- [9] aX. Hou, Y. Qiu, X. Zhang, G. Liu, *Rsc Adv.* 2016, 6, 54580-54588; bJ. Wloch, *Micro. Meso. Mater.* **2003**, 62, 81-86; cS. J. Reitmeyer, O. C. Gobin, A. Jentys, J. A. Lercher, *Angew. Chem. Int. Ed.* **2009**, 48, 533-538; dO. C. Gobin, S. J. Reitmeyer, A. Jentys, J. A. Lercher, *J. Phys. Chem. C* **2011**, 115, 1171-1179.
- [10] S. R. Zheng, H. R. Heydenrych, A. Jentys, J. A. Lercher, *J. Phys. Chem. B* **2002**, 106, 9552-9558.
- [11] G. Ye, Z. Guo, Y. Sun, K. Zhu, H. Liu, X. Zhou, M.-O. Coppens, *Chem. Ing. Technik* **2017**, 89, 1333-1342.
- [12] G. Liu, P. Tian, J. Li, D. Zhang, F. Zhou, Z. Liu, *Micro. Meso. Mater.* **2008**, 111, 143-149.
- [13] S. Bordiga, L. Regli, D. Cocina, C. Lamberti, M. Bjorgen, K. P. Lillerud, *J. Phys. Chem. B* **2005**, 109, 2779-2784.
- [14] J. Kärger, D. M. Ruthven, *New J. Chem.* **2016**, 40, 4027-4048.
- [15] M. Gao, H. Li, M. Yang, S. Gao, P. Wu, P. Tian, S. Xu, M. Ye, Z. Liu, *Commun. Chem.* **2019**, 2.
- [16] aH. Oikawa, Y. Shibata, K. Inazu, Y. Iwase, K. Murai, S. Hyodo, G. Kobayashi, T. Baba, *Appl. Cata. A Gen.* **2006**, 312, 181-185; bP. Cnudde, R. Demuynck, S. Vandenbrande, M. Waroquier, G. Sastre, V. Van Speybroeck, *J. Am. Chem. Soc.* **2020**, 142, 6007-6017.
- [17] aG. Sastre, J. Kärger, D. M. Ruthven, *J. Phys. Chem. C* **2019**, 123, 19596-19601; bD. M. Ruthven, *J. Phys. Chem. C* **2015**, 119, 29201-29202.

Entry for the Table of Contents

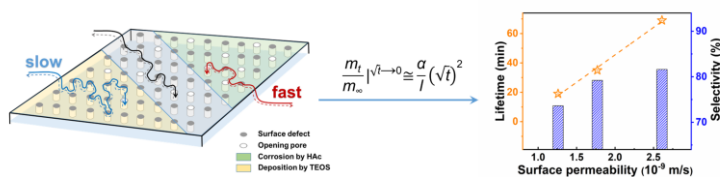

Surface barriers of guest molecules, which dominate the mass transport in SAPO-34 zeolites, have been controlled to modulate the methanol-to-olefins reaction performance. The reduction of surface barriers can prolong catalyst lifetime and prompt product selectivity.