

Journal Pre-proof

Synthesis and characterization of Ag⁺ and Zn²⁺ co-doped CaWO₄ nanoparticles by a fast and facile sonochemical method

N.F. Andrade Neto, B.P. Dias, R.L. Tranquilin, E. Longo, M. Li, M.R.D. Bomio, F.V. Motta



PII: S0925-8388(19)34863-7

DOI: <https://doi.org/10.1016/j.jallcom.2019.153617>

Reference: JALCOM 153617

To appear in: *Journal of Alloys and Compounds*

Received Date: 4 October 2019

Revised Date: 16 December 2019

Accepted Date: 30 December 2019

Please cite this article as: N.F.A. Neto, B.P. Dias, R.L. Tranquilin, E. Longo, M. Li, M.R.D. Bomio, F.V. Motta, Synthesis and characterization of Ag⁺ and Zn²⁺ co-doped CaWO₄ nanoparticles by a fast and facile sonochemical method, *Journal of Alloys and Compounds* (2020), doi: <https://doi.org/10.1016/j.jallcom.2019.153617>.

This is a PDF file of an article that has undergone enhancements after acceptance, such as the addition of a cover page and metadata, and formatting for readability, but it is not yet the definitive version of record. This version will undergo additional copyediting, typesetting and review before it is published in its final form, but we are providing this version to give early visibility of the article. Please note that, during the production process, errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

© 2019 Published by Elsevier B.V.

CRedit author statement

- **N. F. Andrade Neto:** Conceptualization, Methodology, Software, Validation, Investigation, Data Curation, Writing - Original Draft, Visualization, Supervision, Project administration.
- **B. P. Dias:** Methodology, Validation, Investigation, Visualization,
- **R. L. Tranquilin:** Resources, Data Curation,
- **E. Longo:** Resources, Data Curation,
- **M. Li:** Resources, Data Curation,
- **M. R. D. Bomio:** Conceptualization, Methodology, Validation, Investigation, Resources, Writing - Original Draft, Visualization, Supervision, Project administration, Funding acquisition.
- **F. V. Motta:** Conceptualization, Methodology, Validation, Investigation, Resources, Writing - Original Draft, Visualization, Supervision, Project administration, Funding acquisition.

Synthesis and characterization of Ag⁺ and Zn²⁺ co-doped CaWO₄ nanoparticles by a fast and facile sonochemical method

N.F. Andrade Neto^{1*}, B.P. Dias¹, R.L. Tranquilin², E. Longo², M. Li³, M.R.D. Bomio¹,
F.V. Motta¹.

¹LSQM – Laboratory of Chemical Synthesis of Materials – Department of Materials Engineering, Federal University of Rio Grande do Norte – UFRN, P.O. Box 1524, Natal RN, Brazil.

²CDMF-UFSCar, Universidade Federal de São Carlos, P.O. Box 676, São Carlos, SP 13565-905, Brazil.

³IFSC, USP, Av. Trabalhador São Carlense, 400, CEP 13566-590 São Carlos, SP, Brazil

***Corresponding author.** Tel/fax: +55-84-3342-2406

E-mail: netoandrade@ufrn.edu.br (N. F. Andrade Neto)

Abstract

In this work, Ag^+ and Zn^{2+} co-doped CaWO_4 nanoparticles were obtained by fast and facile sonochemical method. The nanoparticles were characterized by X-ray diffraction (XRD), Fourier transformed infrared spectroscopy (FTIR), Raman spectroscopy, scanning electron microscopy (SEM), transmission electron microscopy (TEM), visible ultraviolet spectroscopy (UV-Vis) and photoluminescence property. The photocatalytic activity was studied against methylene blue (MB) dye under sunlight and CaWO_4 powders were tested in 3 reuse cycles. The diffractograms indicate the non-formation of secondary phases and the Rietveld refinement estimated the crystallite sizes, being 27.38, 19.89, 18.70 and 16.39 nm for the pure, Ag, Zn and Ag:Zn samples, respectively. SEM and TEM images showed that the particles are agglomerated and have a mean diameter ranging from 16.76 (Ag:Zn) to 71.76 nm (pure). Defects generated by doping shift the gap band to higher energies and act to prevent electron/hole (e^-/h^+) pair recombination, reducing photoluminescence and favoring CaWO_4 photocatalysis. Scavenger methodology indicated that h^+ is the main mechanism acting in photocatalysis, and the reuse tests indicated that the silver-doped sample, even with the better initial response, loses efficiency over the course of the cycle, while the co-doped sample maintains efficiency, and is therefore indicated for reuse photocatalysis applications in methylene blue dye degradation.

Keywords: Sonochemical method; Ag and Zn co-doped CaWO_4 ; photoluminescence; photocatalysis.

1. Introduction

Environmental policies regarding industrial waste treatment become stricter with industrial advancement. Waste from the textile and food industries receives special attention due to the generation of organic and water-soluble waste, which harms the local fauna and flora [1]. Thus, treating these residues using advanced oxidative processes (AOP) based on heterogeneous photocatalysis is widely reported in the literature, where a semiconductor material acts as a catalyst in the photocatalytic process [2-5]. TiO_2 is the most studied semiconductor material because it has good photocatalytic properties and is non-toxic [6, 7]. However, this material has limited properties, mainly due to its crystalline structure. Thus, materials that have a more complex structure, such as two different cations, are gaining attention.

Semiconductor materials of XWO_4 ($\text{X} = \text{Ca}, \text{Cu}, \text{Zn}, \text{Cd}$) structures are widely reported in the literature due to the excellent properties derived from their microstructure [8-11]. In heterogeneous photocatalysis, e^-/h^+ pairs are generated when the semiconductor is excited by sufficient energy radiation to overcome its gap energy (E_{gap}) [11]. If these charges do not recombine to their initial state, they migrate to the surface of the materials and react with the medium to generate reactive oxygen species (ROS), which have a high capacity for degradation of organic pollutants [12]. Among these materials, CaWO_4 has gained attention for photocatalytic applications due to its chemical and thermal stability, in addition to having a high direct E_{gap} (~ 4.5 eV), making it difficult to recombine the e^-/h^+ pairs [13-15].

Heterojunctions or doping are normally performed in order to improve CaWO_4 properties, thus altering the recombination rate of the photogenerated e^-/h^+ pairs [15-17]. Zhang *et al.* [18] showed that one way to optimize CaWO_4 photocatalytic activity is by synthesizing a biochar composite, which reduces the recombination of the electron/hole pairs photogenerated. Meanwhile, Huang *et al.* [19] showed that CaWO_4

co-doping with Er/Yb and Tm/Yb increases their photocatalytic activity by generating more O_2^- radicals. The mechanisms of $CaWO_4$ photocatalysis are little discussed in the literature, as most of the studies report the photoluminescent and electrochemical properties. In addition, the vast majority of works report rare-earth doping of $CaWO_4$. Thus, in this work transition metal ions (Ag^+ and Zn^{2+}) co-doped $CaWO_4$ nanoparticles were synthesized by the fast and facile sonochemical method, explaining the main photocatalytic mechanisms acting on pure and doped material and reusability against methylene blue cationic dye.

2. Materials and methods

Calcium nitrate ($Ca(NO_3)_2 \cdot 4H_2O$ - Alfa Aesar, 98%), silver nitrate ($AgNO_3$ - Synth, 99%), sodium tungstate ($Na_2WO_4 \cdot 2H_2O$ - Synth, 99.5%), zinc nitrate ($Zn(NO_3)_2 \cdot 6H_2O$ - Sigma-Aldrich, 98%), polyvinylpyrrolidone (PVP - $(C_6H_9NO)_n$ - Vetec P.M. 40.000), ammonium hydroxide (NH_4OH - Synth, 30%) and deionized water were used as precursor materials.

A solution containing 2 mmol calcium nitrate, 10 mmol PVP and 40 mL deionized water (solution I) and a solution containing 2 mmol sodium tungstate, 10 mmol PVP and 40 mL deionized water (solution II) was initially prepared. Both solutions were kept under stirring for 10 min for complete homogenization. After this time, solution (I) was immersed in the solution (II) and stirred for 10 min, forming a transparent solution (solution III). Ammonium hydroxide was added for pH control, setting it to 10, making the solution a whitish color. The solution (III) was then taken to a Branson 102C ultrasonic tip (20 kHz) where it remained for 30 min. After ultrasonic treatment, the precipitate was centrifuged and washed with deionized water until pH neutralization. The powders were then dried for 24 h at 60 °C. Silver and zinc doped samples followed the same methodology, with silver nitrate and zinc nitrate

stoichiometrically added at 4 mol% proportions to calcium nitrate in solution (I). The co-doped sample was performed using 2% silver and 2% zinc. The bare powder was named Pure, while the doped samples were named Ag, Zn and Ag:Zn, according to doping.

The powders were characterized by X-ray diffraction (Shimadzu, XRD-6000) using $\text{CuK}\alpha$ radiation (1.5418 \AA), in which the powders were scanned from 10 to 90° using a speed of $1^\circ/\text{min}$ and step of 0.02° . Rietveld refinement using the General Structure Analysis System (GSAS) program with graphical interface EXPGUI [20] was performed to obtain more crystallographic information. To do so, we used background, scale factor, microstructure, crystal, texture and strain parameters for refinement. The Fourier Transform Infrared (FTIR) technique was performed using the Shimadzu IRTracer-100 equipment, with scanning from 500 to 4000 cm^{-1} . The Raman scattering spectra were recorded at room temperature in the frequency range from 100 to 1200 cm^{-1} with a resolution of 2 cm^{-1} and 64 scans, using a VERTEX 70 RAMII Bruker spectrophotometer (USA) with a Nd:YAG laser (1024 nm) and the maximum output power kept at 100 mW . A scanning electron microscope (SEM) was used to observe the organization and morphology of the powders. Transmission electron microscopy (TEM) and high-resolution transmission electron microscopy (HRTEM) was performed in the FEI TECNAI G2 F20 microscope operating at 200 kV . The UV-Vis spectroscopy was performed on a Shimadzu UV-2550 equipment, with a wavelength range of 200 to 900 nm and programmed for the diffuse reflectance mode. Kubelka-Munk function [21] was applied to convert reflectance data in absorbance, and the Wood and Tauc methodology [22] was used to estimate the bandgap (E_{gap}) energy. The photoluminescence (PL) measurements were obtained using a 325 nm laser at room temperature in a Mosospec

27 monochromator (Thermal Jarrel Ash, USA) coupled to an argon laser photomultiplier (Coherent Innova 90 K, USA).

2.1. Photocatalytic activity

The efficiency of the powders as catalyst was estimated by discoloration of the methylene blue (MB) dye at pH 5 and maximum absorbance at 664 nm. To do so, 5 mg of powder was maintained in contact with 50 mL of MB solution (10^{-5} molL⁻¹ concentration) under UV radiation. The powder was maintained in contact with the MB dye for 20 min to eliminate adsorbent effects. After this, the solutions were illuminated by six UVC lamps (TUV Philips, 15 W) for 120 min. The photocatalytic activity was then determined by the variation of the dye absorption bands in a Shimadzu UV-2600 spectrophotometer.

The mechanism acting on the photocatalytic process was determined by the use of charge, electron (e⁻) and hole (h⁺), and hydroxyl radical (·OH) scavengers. For this, isopropyl alcohol (1 mL alcohol/100 mL dye), EDTA (7.2 mg EDTA/100 mL dye) and AgNO₃ (8.5 mg AgNO₃/100 mL dye) were used to suppress the action of hydroxyl radicals (·OH), positive charges (h⁺) and negative charges (e⁻), respectively.

3. Results and discussion

Fig. 1a presents the diffractograms for the CaWO₄ samples obtained by the sonochemical method. According to the diffractograms, it can be seen that they align with the ICSD 15586 card, referring to the tetragonal crystalline system CaWO₄ and space group I 41/a. It is also observed that there was no formation of secondary phases. Fig. 1b shows an enlargement of the highlighted area in the diffractograms (Fig. 1a), referring to the main plane (112) of CaWO₄. It can be seen that it shifts to greater angles with the occurrence of doping, which is more evident for the silver-doped sample. Displacement of diffraction peaks to larger angles is usually associated with reduced

interplanar crystal spacing [12]. Further crystalline information on doping in the CaWO_4 lattice was obtained through the Rietveld refinement. Fig. 2 presents the refined diffractograms for CaWO_4 samples, highlighting the difference between observed and theoretical values. Table 1 presents the crystallographic data obtained through the Rietveld refinement, as well as the refinement adjustment data.

The R_p , χ^2 , and $R(F)^2$ are a quality parameter for evaluation of the Rietveld refinement quality. values close to 1 for the R_p and χ^2 and values below to 0.1 for $R(F)^2$ indicate a good refinement. In addition, visual analysis between observed and calculated curves allows this analysis. Thus, the data obtained from the Rietveld refinement have coherence. Ca^{2+} has an ionic radius of 0.106 nm, while Ag^+ and Zn^{2+} have an ionic radius of 0.113 and 0.083 nm, respectively. Even with greater ionic radius, the difference between the Ag^+ and Ca^{2+} valences promotes compression distortions in the CaWO_4 lattice, causing crystal size reduction to occur [23]. The changes resulting from doping can be seen in Table 1, where (according to the refinement) the c/a ratio of tetragonal crystals increases with silver doping, being in agreement with the reduction in interplanar spacing and consequent displacement of crystalline peaks. By looking at Figs. 2e and 2f, it is easy to visualize the W coordinates to four oxygen atoms, forming the tetragonal cluster $[\text{WO}_4]$, while Ca is coordinates to eight oxygen atoms, forming the cluster $[\text{CaO}_8]$. Such changes in the crystalline structure associated with the non-formation of secondary phase peaks indicate the correct incorporation of Ag^+ and Zn^{2+} ions into the CaWO_4 lattice.

Insert Fig. 1

Insert Fig. 2

Insert Table 1

Figure 3a shows the Fourier transform infrared spectroscopy (FTIR) spectra for the CaWO_4 powders. The wideband centered around 3400 cm^{-1} , as well as the band around 2300 cm^{-1} , present in all samples corresponds to the elongation vibrations between O-H for water molecules adsorbed on the surface of the powders [24]. The bands centered at 2930 , 1649 and 1434 cm^{-1} correspond to the bonds between C-H₂, C-OH and C-O, indicating the presence of PVP surfactant on the surface of the powders [24]. The intense 760 cm^{-1} centering band is associated with asymmetric elongation vibration (ν_3) between O-W-O present in tetrahedron WO_4^{2-} [25]. As highlighted in Fig. 3a, silver doping generates the appearance of a band at 555 cm^{-1} , while zinc doping promotes the appearance of a band at 622 cm^{-1} , so these bands are associated with elongation vibrations between Ag-O and Zn-O, respectively.

Raman scattering spectroscopy was performed with frequency ranging from 100 to 1200 cm^{-1} . According to Silva *et al.* [26], broad vibrations mode in Raman spectra indicates a short-range structural disorder. Thus, the well-defined vibrations modes indicate a low level of defects in the CaWO_4 lattice. The bands at 910, 836, 794, 398, 330, 208 and 114 cm^{-1} are associated with the CaWO_4 tetragonal phase. The 910 cm^{-1} band is associated with the symmetrical elongation (ν_1) between W-O and the 330 cm^{-1} band is associated with the symmetrical elongation (ν_2) of the O-W-O. The band at 836 cm^{-1} corresponds to the anti-symmetrical elongation (ν_3) and the band at 398 cm^{-1} corresponds to the anti-symmetrical elongation (ν_4) of the W-O [27]. The CaWO_4

scheelite group presents a strong covalent bond W-O forming the WO_4^{2-} ionic group and weak interaction with the Ca^{2+} cations [28]. The noise increase in Raman spectra for silver-doped samples is due to the defects generated in the CaWO_4 lattice, indicating the short-range structural disorder is more present in these samples.

More information about the CaWO_4 lattice defects was obtained through the symmetrical elongation peaks ν_1 , between W-O, and ν_2 , between O-W-O. For this, the peak was adjusted with the Gauss function in Origin software and are shown in Fig. S1 at supplementary material and the data are shown in table 2. According to obtained data, the vibration mode ν_1 shifted to a lower frequency when doping with silver, while zinc doping and the codoped sample shifted to a higher frequency than the pure sample. While vibration mode ν_2 shifted to lower frequencies in all samples. The width at half height (FWHM) of vibration modes ν_1 and ν_2 increased for all doped samples over pure. Thus, the results are consistent with those shown in the XRD results, where an increase in disorder is expected with the replacement of Ca atoms by Ag and Zn.

Insert Fig. 3

Insert Table 2

Fig. 4 shows SEM images for CaWO_4 samples. As shown in Fig. 4a (Pure), there is the presence of micrometer-scale beads, and it is evident from the enlarged image that these beads are formed by misshaped morphology nanoparticles. Figs 4b-4d indicate that doping provides for a loss of tendency to form micrometer spheres where nanoparticles randomly agglomerate. The CaWO_4 nanoparticle size estimation was performed using ImageJ software [29]. The histograms obtained are shown in Fig. S2 in the supplementary material. As shown in the histograms, the pure sample has a mean

diameter of 71.76 (\pm 8.85) nm, while samples doped with Ag, Zn and Ag:Zn have diameters of 40.13 (\pm 6.47), 42.05 (\pm 9.69) and 16.76 (\pm 2.53), respectively.

Insert Fig. 4

Small scale nanoparticle formation is easily accomplished by the sonochemical method. In this methodology, the generation and implosion of microbubbles generate high local temperature and pressure. This results in almost instantaneous nucleation of various crystallites, which are prevented from growing due to the rapid duration of temperature and pressure [1]. In addition, the use of PVP as a surfactant prevents crystal growth, favoring the formation of small-scale particles. According to Ávila-López *et al.* [30], the use of low concentration solutions favors forming irregularly shaped nanoparticles. Thus, the surfactant/precursor ratio (5:1) used in this work was sufficient to guarantee forming particles with small diameters. As highlighted in the Raman and DRX pattern, silver causes a large number of internal defects in the CaWO_4 lattice. These defects act to alter the surface energy of the crystals and consequently their growth, thus generating particles with smaller diameters (Fig. S1) and which clump together in order to reduce the surface energy.

Transmission electron microscopy (TEM) and high resolution (HRTEM) were performed due to the high agglomeration of the nanoparticles, as seen through the SEM images. Fig. 5 shows the images obtained for the pure (Fig. 5a) and Ag:Zn (Fig. 5b) samples, followed by the magnifications obtained by HRTEM. Via the images, the reduction in nanoparticle size is clearly observed by the co-doped sample, and the particles have no spherical character. The interplanar spacing was estimated using HRTEM images, obtaining values of 3.10 and 3.08 Å for the pure and Ag:Zn samples,

respectively. Such spacings are characteristic of the (112) plane, which corresponds to the main plane of CaWO_4 , as highlighted in Fig. 1.

Insert Fig. 5

Further information regarding the structural disorder obtained by Ag and Zn doping in the CaWO_4 lattice was obtained by ultraviolet-visible spectroscopy. Fig. 6a shows the absorption curves obtained by applying the Kubelka-Munk equation to the reflectance data. According to the obtained spectra, an increase in the absorption intensity as silver and zinc doping occurs is noticed, as well as the band shifting to shorter wavelengths, indicating higher absorption in the ultraviolet region. Absorption in the ultraviolet region is characteristic of CaWO_4 and is associated with charge transfer transitions from the 2p electron of oxygen entering the empty 5d tungsten orbitals in the WO_4^{2-} complex [31, 32]. Thus, increased absorption accompanied by shifting to shorter wavelengths is associated with a higher level of defects in the CaWO_4 lattice as doping is performed.

Figs 6b-6e illustrate the curves obtained by extrapolating the linear portion of the curves obtained by the allowed direct transition [33], applying the Wood and Tauc model for estimating the bandgap (E_{gap}) of the powders. Through these curves, the pure samples of Ag, Zn and Ag:Zn show E_{gaps} of 4.39, 4.39, 4.50 and 4.59 eV, respectively. As shown in Fig. 6a, doping provides greater absorption in the ultraviolet region, indicating an increase in the energy required for exciting the valence band electron to the conduction band. The increase in E_{gap} is probably associated with the Burstein-Moss effect, where defects generated by the insertion of silver and zinc occupy locations near the conduction band, shifting it to higher energy values [34].

Insert Fig. 6

Fig. 7a shows the photoluminescence spectra accompanied by their respective emission colors and Fig. 7b illustrates the position in the CIE diagram obtained for the CaWO_4 samples in this study. The pure sample shows the highest intensity and broadband centered at 500 nm, covering much of the visible spectrum. The CaWO_4 broadband is characteristic of ${}^3\text{T}_1$, ${}^3\text{T}_2 \rightarrow {}^1\text{A}_1$ transitions relative to WO_4^{2-} and WO_6^{6-} groups [35]. The photoluminescent capacity of the materials is directly related to the recombination velocity of the e^-/h^+ pairs, where the facilitation of this recombination generates higher photoluminescent intensities [36]. As shown above, doping promotes the appearance of CaWO_4 lattice defects; thus, these defects act as impediment centers for the recombination of e^-/h^+ pairs, reducing the material photoluminescence [37]. Silver-doped and silver-zinc-codoped samples have the lowest luminescent intensities due to the presence of silver, and their use is widely reported due to the creation of high impedance traps in the e^-/h^+ pair recombination [38]. In contrast to the reduction in luminescent intensity with silver doping, an increase in photocatalytic capacity is expected. The displacement of the absorption band with zinc doping occurs due to the emergence of oxygen vacancies, favoring emission in the blue region [38]. The coherence between the theoretical and emission colors can be observed with the assistance of the CIE diagram, as highlighted in Fig. 7a.

Insert Fig. 7

The photocatalytic activity of CaWO_4 powders was estimated by the variation of methylene blue dye concentration when subjected to UV radiation. Fig. 8a shows the

curves of the variation in methylene blue dye concentration over the test time. The powders were initially maintained under agitation without the presence of light to eliminate the adsorptive effects. As seen in Fig. 8a, the silver-doped sample exhibits greater photocatalytic activity, completely reducing MB dye concentration after 120 min, while pure, Zn and Ag:Zn samples reduced the concentration by 25.99, 55.51 and 63.78%, respectively. Increased photocatalytic activity with silver and zinc doping are frequently reported in the literature [23, 39-41]. Silver doping generates oxygen vacancies to balance the loads in the CaWO_4 lattice due to differences in valence with calcium. Even with calcium and zinc ions having the same valence, they have a different ionic radius, where zinc is smaller. This difference between the rays promotes the formation of internal strains, which hinder the movement of photogenerated e^-/h^+ pairs, improving photocatalytic activity. This can be proven by the reduction in photoluminescent activity as previously shown. As shown in the photoluminescent tests, oxygen vacancies act as impediment centers for e^-/h^+ pair recombination, reducing photoluminescence and favoring the migration of charges to the nanoparticle surface and generating more advanced oxidative species (ROS) to the dye surface oxidation. The photocatalytic kinetic constant was estimated by linearizing the catalytic data for better analysis of photocatalytic activity, as shown in Fig. 8b. The kinetic constant determination occurred similarly to previous works [12, 42]. Thus, kinetic constants $k = 0.28 \times 10^{-2}$, 5.46×10^{-2} , 1.21×10^{-2} and $1.79 \times 10^{-2} \text{ min}^{-1}$ were obtained for pure, Ag, Zn and Ag:Zn samples, respectively.

Insert Fig. 8

As seen in Fig 8b, the linear fit does not fit the data well as photocatalytic efficiency is increased, indicating that doping acts to reduce the continuous linearity of the catalytic process. The reduction in linearity is associated with variation in dye molecule concentration, where greater interaction with nanoparticles initially occurs due to higher concentration, thus increasing the catalytic efficiency [43]. The kinetic constant acts as an important tool for estimating the catalytic behavior of semiconductor materials. The values obtained in this study illustrate the positive effect of doping, where catalytic kinetics increase by 20x when doping CaWO_4 with silver. The photocatalytic results are consistent with the photoluminescent analyzes, indicating that doping reduces the recombination rate of e^-/h^+ pairs, favoring photocatalytic activity.

As discussed earlier, doping causes defects in the CaWO_4 lattice which act to prevent the recombination of photoexcited e^-/h^+ pairs. The performance of these charges in photocatalysis was studied through the use of scavengers to better explain the photocatalytic mechanism. Thus, Fig. 9 shows the variation curves of MB dye concentration by the assay time using charge scavengers. To do so, AgNO_3 (AG), EDTA and isopropyl alcohol (ISO) were used to inhibit the action of e^- , h^+ and $\cdot\text{OH}$, respectively. Fig. 9a shows the curves for the pure sample, indicating that the use of scavengers increases dye degradation. This fact is consistent with photocatalytic and photoluminescent analyzes, where the pure sample presents a high recombination rate of the e^-/h^+ pairs so that by inhibiting one of these in isolation it will make the other available to act on generating reactive oxygen species (ROS), thereby increasing the photocatalytic activity of the powders. The effect of the isolated mechanisms is less evident for doped samples (Fig. 9b-9d) which have a lower e^-/h^+ pair recombination rate due to the presence of defects in the material lattice.

The silver-doped sample (Fig. 9b) shows a reduction in photocatalytic activity with the addition of EDTA, indicating that holes play a major role in ROS generation. Similarly, zinc-doped and co-doped samples (Fig. 9c and 9d) indicate that holes play a major role in the photocatalytic process, but electrons also play a significant role. Thus, the results indicate that h^+ is the main mechanism acting in photocatalysis for all samples, being responsible for both directly oxidizing dye molecules on the surface of the powders, as well as interacting with the environment and generating hydroxyl radicals [44].

Insert Fig. 9

The use of particulate materials in photocatalytic activity requires their correct application so that there is no formation of secondary residues containing the photocatalyst. Thus, the ability of the material to be used in several consecutive catalytic cycles without the need for complex treatments is a prime factor for large-scale applications. Among the characteristics that make a material suitable for use in several consecutive cycles is the chemical stability and maintenance of the activity over the cycles [43]. The reuse tests in this work were performed by collecting the powders after the catalytic cycles by simple centrifugation which was then dried in the open air, and the powders were weighed and the catalyst/dye ratio maintained. Fig. 10a shows the degradation of the silver, zinc and co-doped samples which showed the best photocatalytic results, while Fig. 10b shows the diffractograms performed after the third cycle. As shown in Fig. 10a, the silver-doped sample loses its efficiency over the course of the cycles, so it loses 26% of its efficiency in the third cycle, while the zinc-doped and co-doped samples maintain virtually constant activity with each other. For the co-

doped sample, a slight increase in photocatalytic efficiency is observed in the second cycle, followed by a reduction in the third cycle. This increase is associated with the small amount of silver present in the sample, where the radiation incidence tends to reduce silver on the surface of the particles, generating Ag^0 and producing the surface plasmon effect (SPR), while the reduction in efficiency occurs by the subsequent oxidation of these particles in silver oxide nanoparticles (AgO). Tun *et al.* [44] also reported the positive effect of reducing metallic silver on the surface of AgBr powders for photocatalytic activity, accompanied by a reduction in subsequent cycles. According to the diffractograms shown in Fig. 10b, the silver-doped sample shows the formation of AgO and Ca , characterized by the ICSD 27669 card with monoclinic system and space group $C2/c$ (no. 15) and ICSD 44348 with cubic system and space group $Fm-3m$ (no. 225), respectively. The emergence of these phases indicates the low chemical stability for photocatalytic applications using ultraviolet radiation, thus indicating the use of the co-doped sample, which presented second-best photocatalytic response and good chemical stability without the formation of secondary phases.

Insert Fig. 10

4. Conclusion

Diffractograms indicate that sonochemical synthesis is a fast, simple and efficient methodology for obtaining bare CaWO_4 nanoparticles and doped with silver and zinc without the formation of secondary phases. Defects resulting from doping act in altering the growth kinetics of the crystallites, resulting in a reduction in nanoparticle average diameter from 71.76 to 16.76 nm for pure and co-doped samples, respectively. The occupation of Ag and Zn ions at levels close to the conduction band shifts the band to

higher energies, thus increasing the E_{gap} . The photocatalytic and photoluminescent properties of semiconductor materials are directly related to the recombination ability of the electron/hole pairs. Thus, it can be assumed that the occupancy of levels close to the CaWO_4 conduction band by Ag and Zn cations act to reduce the recombination rate of these pairs, improving photocatalytic activity and reducing CaWO_4 photoluminescent capacity. The photocatalytic capacity of Ag and Zn-doped CaWO_4 powders is strongly influenced by the action of the holes (h^+), which act by generating reactive oxygen species and directly oxidizing the methylene blue dye chains. Reuse tests indicate that the silver-doped sample does not have good chemical stability, generating secondary phases over the course of the cycles. Thus, the co-doped sample is best suited for photocatalytic applications, as it has a good ability to degrade the methylene blue dye and maintain its chemical composition.

Acknowledgment

This study was partially financed in part by the Coordenação de Aperfeiçoamento de Pessoal de Nível Superior - Brasil (CAPES/PROCAD) - Finance Code 2013/2998/2014 and the authors thanks to the financial support of the Brazilian research financing institution (CNPq) No. 307546/2014 and São Paulo Research Foundation (FAPESP - CDMF) No. 2013/07296-2.

References

[1] N.F.A. Neto, L.M.P. Garcia, E. Longo, M.S. Li, C.A. Paskocimas, M.R.D. Bomio, F.V. Motta, Photoluminescence and photocatalytic properties of Ag/AgCl synthesized by sonochemistry: statistical experimental design, *Journal of Materials Science: Materials in Electronics*, 28 (2017) 12273-12281.

- [2] D.S. Babu, V. Srivastava, P.V. Nidheesh, M.S. Kumar, Detoxification of water and wastewater by advanced oxidation processes, *Science of The Total Environment*, 696 (2019) 133961.
- [3] R. Anjali, S. Shanthakumar, Insights on the current status of occurrence and removal of antibiotics in wastewater by advanced oxidation processes, *Journal of Environmental Management*, 246 (2019) 51-62.
- [4] K. Sivagami, K.P. Sakthivel, I.M. Nambi, Advanced oxidation processes for the treatment of tannery wastewater, *Journal of Environmental Chemical Engineering*, 6 (2018) 3656-3663.
- [5] H. Su, C. Christodoulatos, B. Smolinski, P. Arienti, G. O'Connor, X. Meng, Advanced Oxidation Process for DNAN Using UV/H₂O₂, *Engineering*, 5 (2019) 849-854.
- [6] L.M.P. Garcia, M.T.S. Tavares, N.F. Andrade Neto, R.M. Nascimento, C.A. Paskocimas, E. Longo, M.R.D. Bomio, F.V. Motta, Photocatalytic activity and photoluminescence properties of TiO₂, In₂O₃, TiO₂/In₂O₃ thin films multilayer, *Journal of Materials Science: Materials in Electronics*, 29 (2018) 6530-6542.
- [7] N.F. Andrade Neto, P. Zanatta, L.E. Nascimento, R.M. Nascimento, M.R.D. Bomio, F.V. Motta, Characterization and Photoluminescent, Photocatalytic and Antimicrobial Properties of Boron-Doped TiO₂ Nanoparticles Obtained by Microwave-Assisted Solvothermic Method, *Journal of Electronic Materials*, 48 (2019) 3145-3156.
- [8] N.P. Singh, N.P. Singh, N.R. Singh, N.M. Singh, Photoluminescence studies of CdWO₄:Sm³⁺ phosphor: Concentration and annealing effect, *Optik*, 144 (2017) 490-497.

- [9] R.M. Abozaid, Z.Ž. Lazarević, N. Tomić, A. Milutinović, D. Šević, M.S. Rabasović, V. Radojević, Optical properties $\text{CaWO}_4:\text{Nd}^{3+}/\text{PMMA}$ composite layered structures, *Optical Materials*, 96 (2019) 109361.
- [10] I. Rodríguez-Gutiérrez, E. Djatoubai, M. Rodríguez-Pérez, J. Su, G. Rodríguez-Gattorno, L. Vayssieres, G. Oskam, Photoelectrochemical water oxidation at $\text{FTO}|\text{WO}_3@\text{CuWO}_4$ and $\text{FTO}|\text{WO}_3@\text{CuWO}_4|\text{BiVO}_4$ heterojunction systems: An IMPS analysis, *Electrochimica Acta*, 308 (2019) 317-327.
- [11] Y. Wu, S. Zhou, T. He, X. Jin, L. Lun, Photocatalytic activities of ZnWO_4 and $\text{Bi}@\text{ZnWO}_4$ nanorods, *Applied Surface Science*, 484 (2019) 409-413.
- [12] N.F. Andrade Neto, Y.G. Oliveira, J.H.O. Nascimento, B.R. Carvalho, M.R.D. Bomio, F.V. Motta, Synthesis, characterization, optical properties investigation and reusability photocatalyst capacity of AgCl-xGO composite, *Journal of Materials Science: Materials in Electronics*, 30 (2019) 15214-15223.
- [13] C. Ayappan, B. Palanivel, V. Jayaraman, T. Maiyalagan, A. Mani, One-step hydrothermal synthesis of $\text{CaWO}_4/\alpha\text{-Ag}_2\text{WO}_4$ heterojunction: An efficient photocatalyst for removal of organic contaminants, *Materials Science in Semiconductor Processing*, 104 (2019) 104693.
- [14] K. Somasundaram, C.K. Rastogi, I. Roy, P.C. Selvin, V. Sudarsan, Lanthanide ion induced phase decomposition of tetragonal CaWO_4 , *Materials Research Bulletin*, 113 (2019) 133-140.
- [15] Y. Song, S. Liang, F. Li, X. Wang, C. You, Y. Yang, The self-assembly mechanism of $\text{CaWO}_4@\text{CaWO}_4:\text{Dy}^{3+}$ core/shell microspheres via a simple surfactant-free hydrothermal route, *Materials Letters*, 161 (2015) 100-103.

- [16] R. Chai, Y. Liu, G. Zhang, J. Feng, Q. Kang, In situ preparation and luminescence properties of CaWO_4 and $\text{CaWO}_4\text{:Ln}$ ($\text{Ln}=\text{Eu}^{3+}$, Tb^{3+}) nanoparticles and transparent $\text{CaWO}_4\text{:Ln/PMMA}$ nanocomposites, *Journal of Luminescence*, 202 (2018) 65-70.
- [17] E. Palmieri, A. Marcucci, G. Marcheselli, A. De Stefanis, R. Polini, Carbothermic reduction of scheelite (CaWO_4) doped with cobalt or nickel, *International Journal of Refractory Metals and Hard Materials*, 59 (2016) 93-99.
- [18] Y. Zhang, R. Fan, Q. Zhang, Y. Chen, O. Sharifi, D. Leszczynska, R. Zhang, Q. Dai, Synthesis of CaWO_4 -biochar nanocomposites for organic dye removal, *Materials Research Bulletin*, 110 (2019) 169-173.
- [19] S. Huang, Z. Lou, N. Zhu, H. Yuan, Comparison of photocatalytic activities between $\text{Er}^{3+}/\text{Yb}^{3+}$ and $\text{Tm}^{3+}/\text{Yb}^{3+}$ codoped ($\text{CaWO}_4@(\text{TiO}_2/\text{CaF}_2)$) near-infrared photocatalysts, *Catalysis Communications*, 61 (2015) 6-10.
- [20] B. Toby, EXPGUI, a graphical user interface for GSAS, *Journal of Applied Crystallography*, 34 (2001) 210-213.
- [21] M. Patel, A. Chavda, I. Mukhopadhyay, J. Kim, A. Ray, Nanostructured SnS with inherent anisotropic optical properties for high photoactivity, *Nanoscale*, 8 (2016) 2293-2303.
- [22] B.D. Vezbicke, S. Patel, B.E. Davis, D.P. Birnie Iii, Evaluation of the Tauc method for optical absorption edge determination: ZnO thin films as a model system, *physica status solidi (b)*, 252 (2015) 1700-1710.
- [23] N.F. Andrade Neto, Y.G. Oliveira, C.A. Paskocimas, M.R.D. Bomio, F.V. Motta, Increase of antimicrobial and photocatalytic properties of silver-doped PbS obtained by sonochemical method, *Journal of Materials Science: Materials in Electronics*, 29 (2018) 19052-19062.

- [24] N.F. Andrade Neto, P.M. Oliveira, R.M. Nascimento, C.A. Paskocimas, M.R.D. Bomio, F.V. Motta, Influence of pH on the morphology and photocatalytic activity of CuO obtained by the sonochemical method using different surfactants, *Ceramics International*, 45 (2019) 651-658.
- [25] D. Kumar, B.P. Singh, M. Srivastava, A. Srivastava, P. Singh, A. Srivastava, S.K. Srivastava, Structural and photoluminescence properties of thermally stable Eu^{3+} activated CaWO_4 nanophosphor via Li^+ incorporation, *Journal of Luminescence*, 203 (2018) 507-514.
- [26] M.D.P. Silva, R.F. Gonçalves, I.C. Nogueira, V.M. Longo, L. Mondoni, M.G. Moron, Y.V. Santana, E. Longo, Microwave-assisted hydrothermal synthesis of $\text{Ag}_2(\text{W}_{1-x}\text{Mo}_x)\text{O}_4$ heterostructures: Nucleation of Ag, morphology, and photoluminescence properties, *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, 153 (2016) 428-435.
- [27] L.S. Cavalcante, V.M. Longo, J.C. Sczancoski, M.A.P. Almeida, A.A. Batista, J.A. Varela, M.O. Orlandi, E. Longo, M.S. Li, Electronic structure, growth mechanism and photoluminescence of CaWO_4 crystals, *CrystEngComm*, 14 (2012) 853-868.
- [28] Y. Su, G. Li, Y. Xue, L. Li, Tunable Physical Properties of CaWO_4 Nanocrystals via Particle Size Control, *The Journal of Physical Chemistry C*, 111 (2007) 6684-6689.
- [29] C.A. Schneider, W.S. Rasband, K.W. Eliceiri, NIH Image to ImageJ: 25 years of image analysis, *Nature methods*, 9 (2012) 671-675.
- [30] M.A. Ávila-López, E. Luévano-Hipólito, L.M. Torres-Martínez, CO_2 adsorption and its visible-light-driven reduction using CuO synthesized by an eco-friendly sonochemical method, *Journal of Photochemistry and Photobiology A: Chemistry*, 382 (2019) 111933.

- [31] Z. Lou, M. Cocivera, Cathodoluminescence of CaWO_4 and SrWO_4 thin films prepared by spray pyrolysis, *Materials Research Bulletin*, 37 (2002) 1573-1582.
- [32] R. Grasser, A. Scharmann, K.R. Strack, On the intrinsic nature of the blue luminescence in CaWO_4 , *Journal of Luminescence*, 27 (1982) 263-272.
- [33] Y. Zhang, N. Holzwarth, R. Williams, Electronic band structures of the scheelite materials and, *Physical Review B - Condensed Matter and Materials Physics*, 57 (1998) 12738-12750.
- [34] A. Sarkar, S. Ghosh, S. Chaudhuri, A.K. Pal, Studies on electron transport properties and the Burstein-Moss shift in indium-doped ZnO films, *Thin Solid Films*, 204 (1991) 255-264.
- [35] A. Taoufyq, V. Mauroy, T. Fiorido, F. Guinneton, J.-C. Valmalette, B. Bakiz, A. Benlhachemi, A. Lyoussi, G. Nolibe, J.-R. Gavarri, Photoluminescence properties of CaWO_4 and CdWO_4 thin films deposited on SiO_2/Si substrates, *Journal of Luminescence*, 215 (2019) 116619.
- [36] K.Y. Jung, J.C. Lee, D.S. Kim, B.-K. Choi, W.-J. Kang, Co-doping effect of monovalent alkali metals on optical properties of $\text{CeO}_2:\text{Eu}$ nanophosphor prepared by spray pyrolysis and application for preparing pearlescent pigments with red emission, *Journal of Luminescence*, 192 (2017) 1313-1321.
- [37] J. Xia, H. Li, H. You, Z. Wu, J. Chen, Z. Lu, L. Chen, M. Wang, Y. Jia, Effects of Fe doping on photoluminescent and magnetic properties of $\text{CaTiO}_3:\text{Eu}^{3+}$, *Ceramics International*, 44 (2018) 21530-21532.
- [38] L. Xu, G. Zheng, F. Xian, Y. Liu, Tailoring the photoluminescent property of ZnO/Ag nanocomposite thin films based on a thermal treatment, *Journal of Luminescence*, 198 (2018) 296-301.

- [39] K. Li, C. Dong, Y. Zhang, H. Wei, F. Zhao, Q. Wang, Ag–AgBr/CaWO₄ composite microsphere as an efficient photocatalyst for degradation of Acid Red 18 under visible light irradiation: Affecting factors, kinetics and mechanism, *Journal of Molecular Catalysis A: Chemical*, 394 (2014) 105-113.
- [40] B. An, Y. Xin, R. Niu, J. Lu, E. Wang, K. Han, Hardening Cu-Ag composite by doping with Sc, *Materials Letters*, 252 (2019) 207-210.
- [41] R.K. Mishra, V.B. Kumar, A. Victor, I.N. Pulidindi, A. Gedanken, Selective production of furfural from the dehydration of xylose using Zn doped CuO catalyst, *Ultrasonics Sonochemistry*, 56 (2019) 55-62.
- [42] A.A.G. Santiago, N.F. Andrade Neto, E. Longo, C.A. Paskocimas, F.V. Motta, M.R.D. Bomio, Fast and continuous obtaining of Eu³⁺ doped CeO₂ microspheres by ultrasonic spray pyrolysis: characterization and photocatalytic activity, *Journal of Materials Science: Materials in Electronics*, 30 (2019) 11508-11519.
- [43] R. Qian, H. Zong, J. Schneider, G. Zhou, T. Zhao, Y. Li, J. Yang, D.W. Bahnemann, J.H. Pan, Charge carrier trapping, recombination and transfer during TiO₂ photocatalysis: An overview, *Catalysis Today*, 335 (2019) 78-90.
- [44] J. Trawiński, R. Skibiński, Rapid degradation of clozapine by heterogeneous photocatalysis. Comparison with direct photolysis, kinetics, identification of transformation products and scavenger study, *Science of The Total Environment*, 665 (2019) 557-567.

Table captions

Table 1 - Microstructural and refinement parameters obtained through GSAS software with EXPGUI interface.

Table 2 – Position (x_c) and FWHM for the ν_1 and ν_2 symmetrical elongation peaks obtained through the GAUSS adjust.

Figure captions

Figure 1 - (a) Diffractograms of CaWO_4 samples and (b) Diffractogram enlargement near plane (112).

Figure 2 - Observed and calculated diffractograms obtained by the Rietveld refinement for (a) Pure, (b) Ag, (c) Zn and (d) Ag:Zn samples and tetragonal structure illustration for (e) Pure and (f) Ag:Zn samples.

Figure 3 - (a) FTIR and (b) Raman spectra for CaWO_4 samples.

Figure 4 - SEM images for (a) Pure, (b) Ag, (c) Zn and (d) Ag:Zn samples.

Figure 5 - TEM and HRTEM images for (a) Pure and (b) Ag:Zn samples

Figure 6 - Absorption spectrum obtained through the Kubelka-Munk equation and extrapolation of the linear portion of the α^2 curves by photon energy for (a) Pure, (b) Ag, (c) Zn and (d) Ag:Zn samples.

Figure 7 - (a) PL spectra and digital emission photography and (b) CIE diagram for CaWO_4 samples.

Figure 8 - (a) Variation of the methylene blue dye concentration (C/C_0) by the assay time and (b) your linearization ($\ln C/C_0$) for the determination of the photocatalytic kinetic constant.


Figure 9 - MB dye concentration variation using scavengers for (a) pure, (b) Ag, (c) Zn and (d) Ag:Zn samples.



Figure 10 - (a) Reuse cycles and (b) DRX pattern after the third cycle for Ag, Zn and Ag:Zn samples.


Sample	Pure	Ag	Zn	Ag:Zn
<i>a</i> (Å)	5.2439	5.2368	5.2413	5.2404
<i>c</i> (Å)	11.3777	11.3797	11.3799	11.3794
Volume (Å ³)	312.8695	312.0777	312.6198	312.4987
<i>c/a</i>	2.1697	2.1730	2.1712	2.1715
<i>R_p</i>	0.0892	0.0734	0.0716	0.0743
<i>Chi</i> ²	1.884	1.442	1.398	1.346
<i>R(F</i> ² <i>)</i>	0.0553	0.0425	0.0380	0.0439
Crystallite size (nm)	27.38	19.89	18.70	16.39
Microstrain	0.0003145	0.0004364	0.0004625	0.000526
% Ag	0	4.13	0	2.12
% Zn	0	0	4.71	2.21



Table 2 – Position (x_c) and FWHM for the ν_1 and ν_2 symmetrical elongation peaks obtained through the GAUSS adjust.


Sample	Pure	Ag	Zn	Ag:Zn	
ν_1	x_c (cm^{-1})	909.955	909.699	910.235	910.190
	FWHM	13.003	14.247	13.469	13.557
ν_2	x_c (cm^{-1})	331.015	330.495	330.887	330.866
	FWHM	16.168	17.661	17.662	17.672

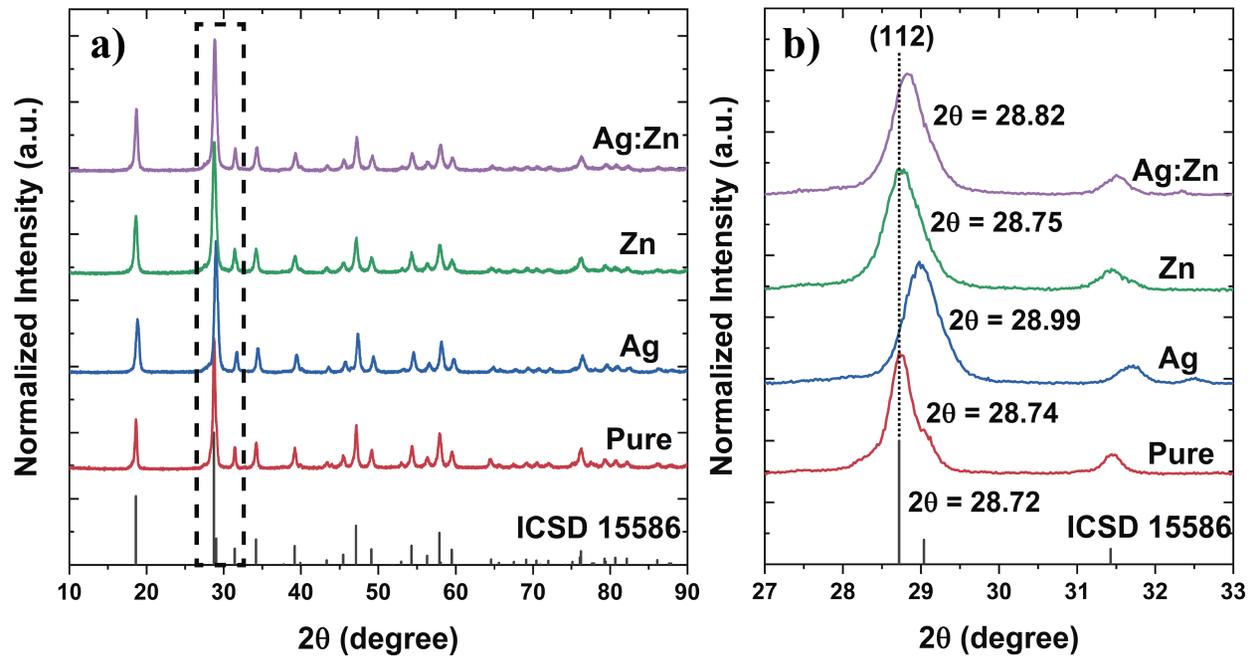


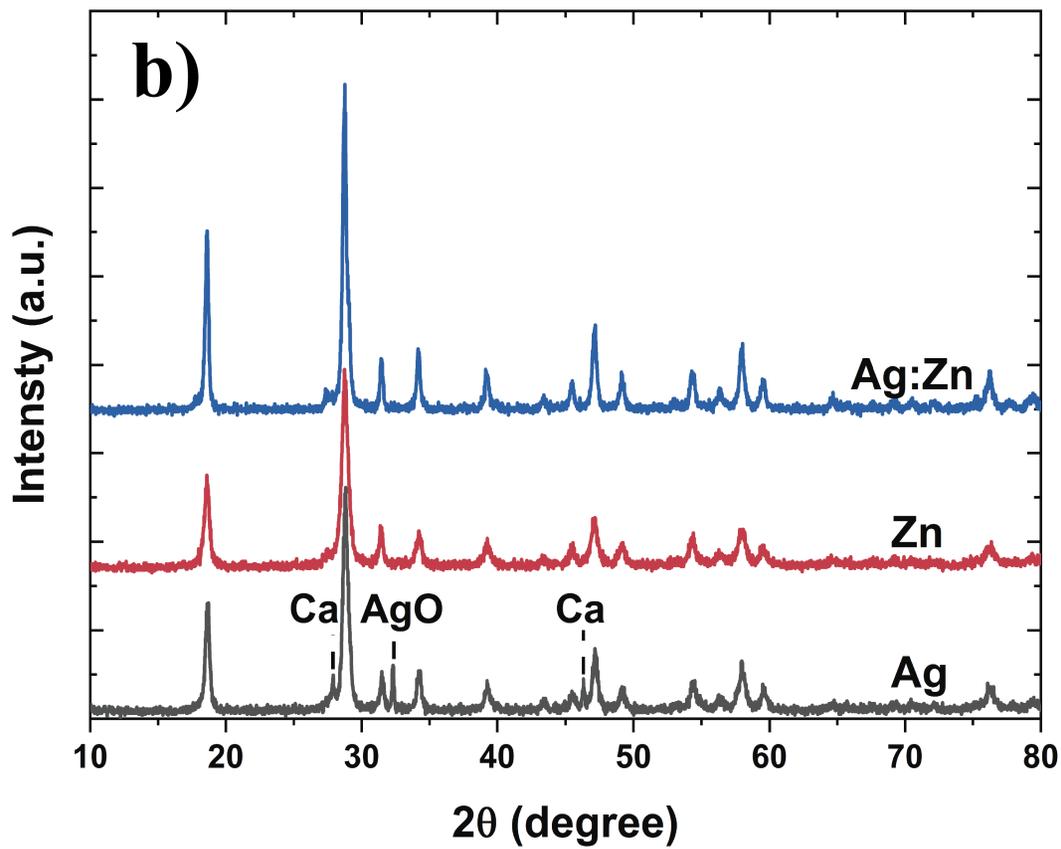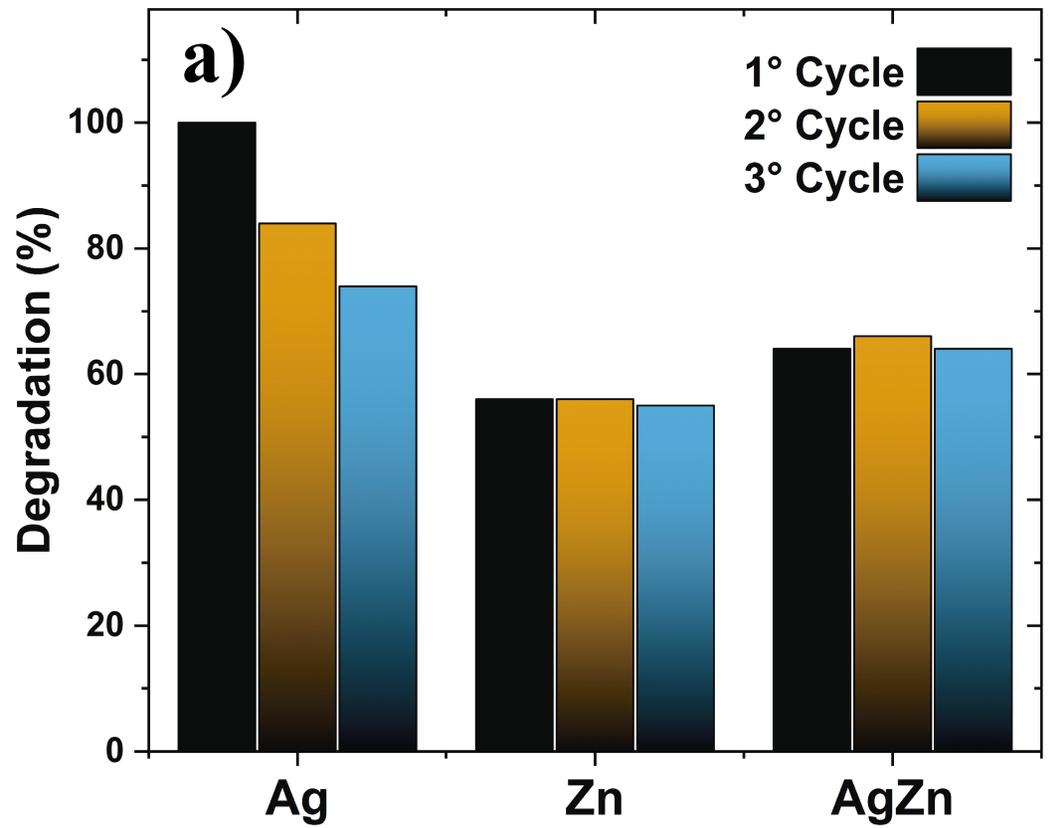



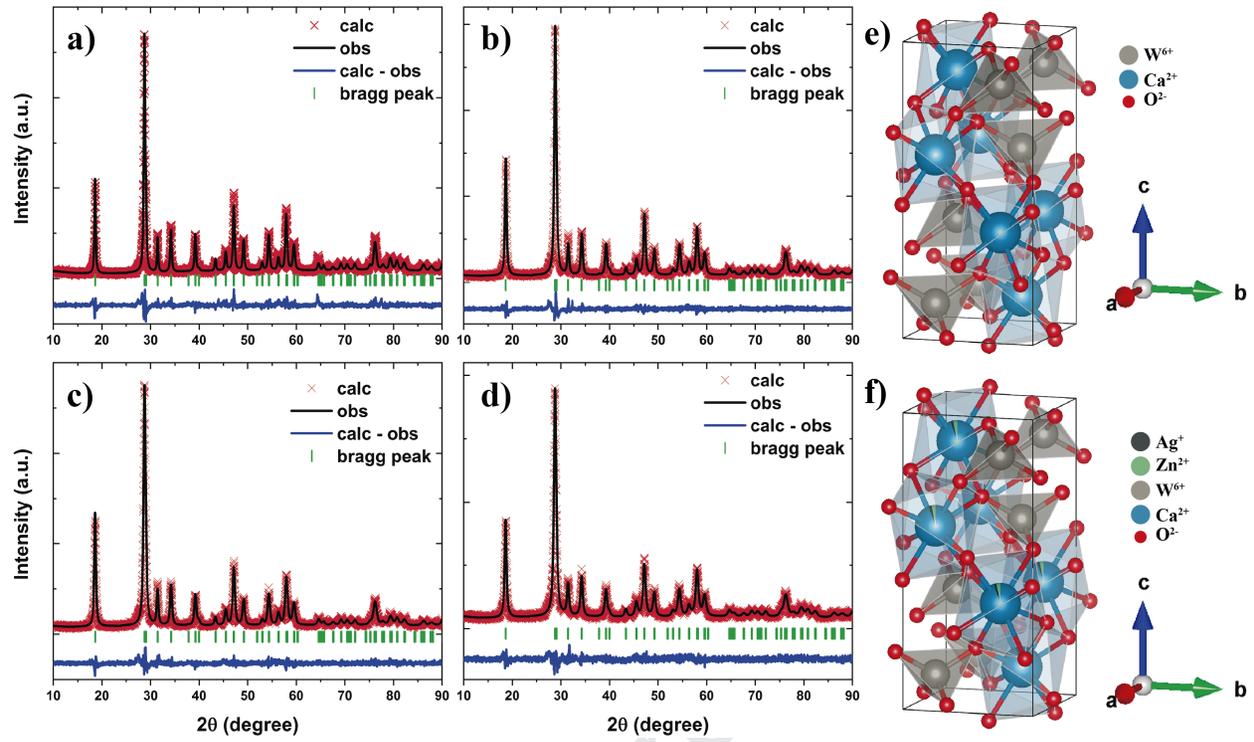


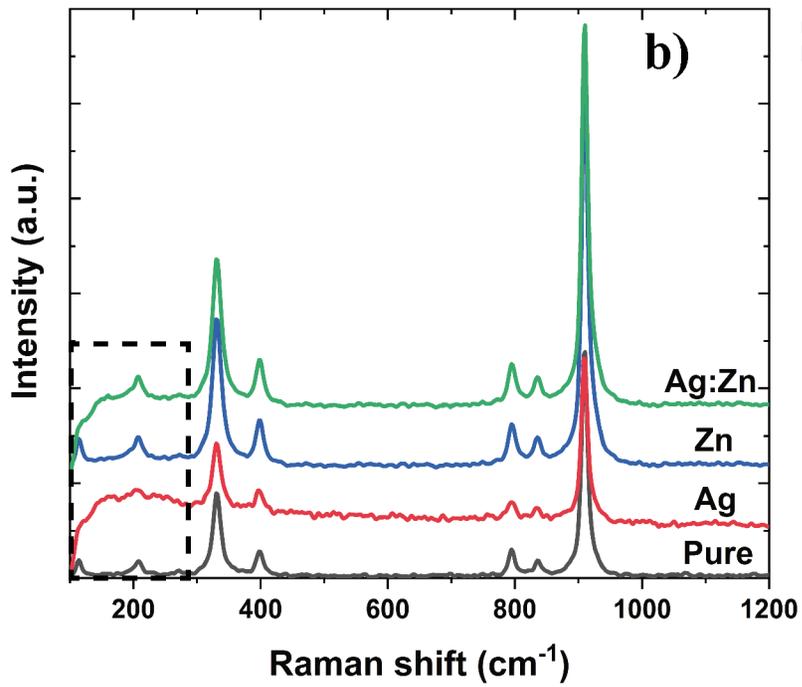
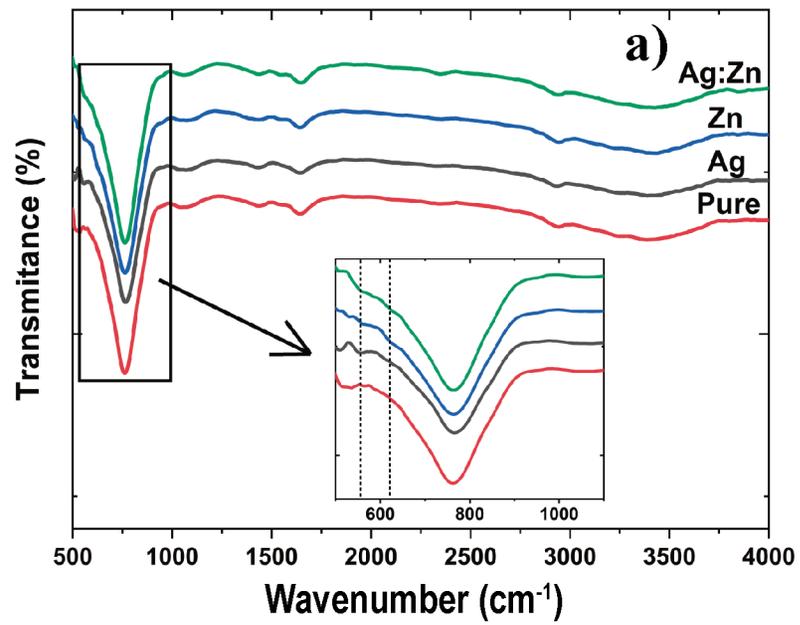


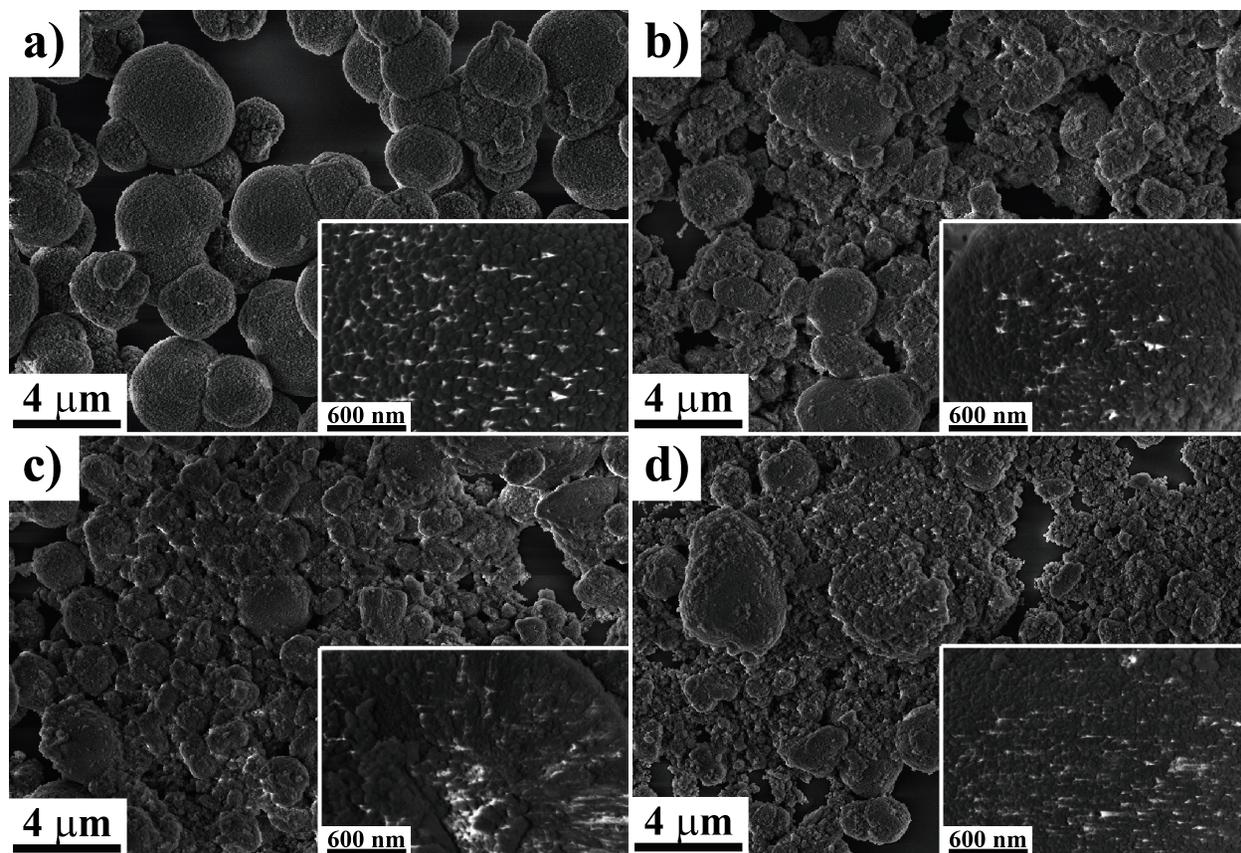


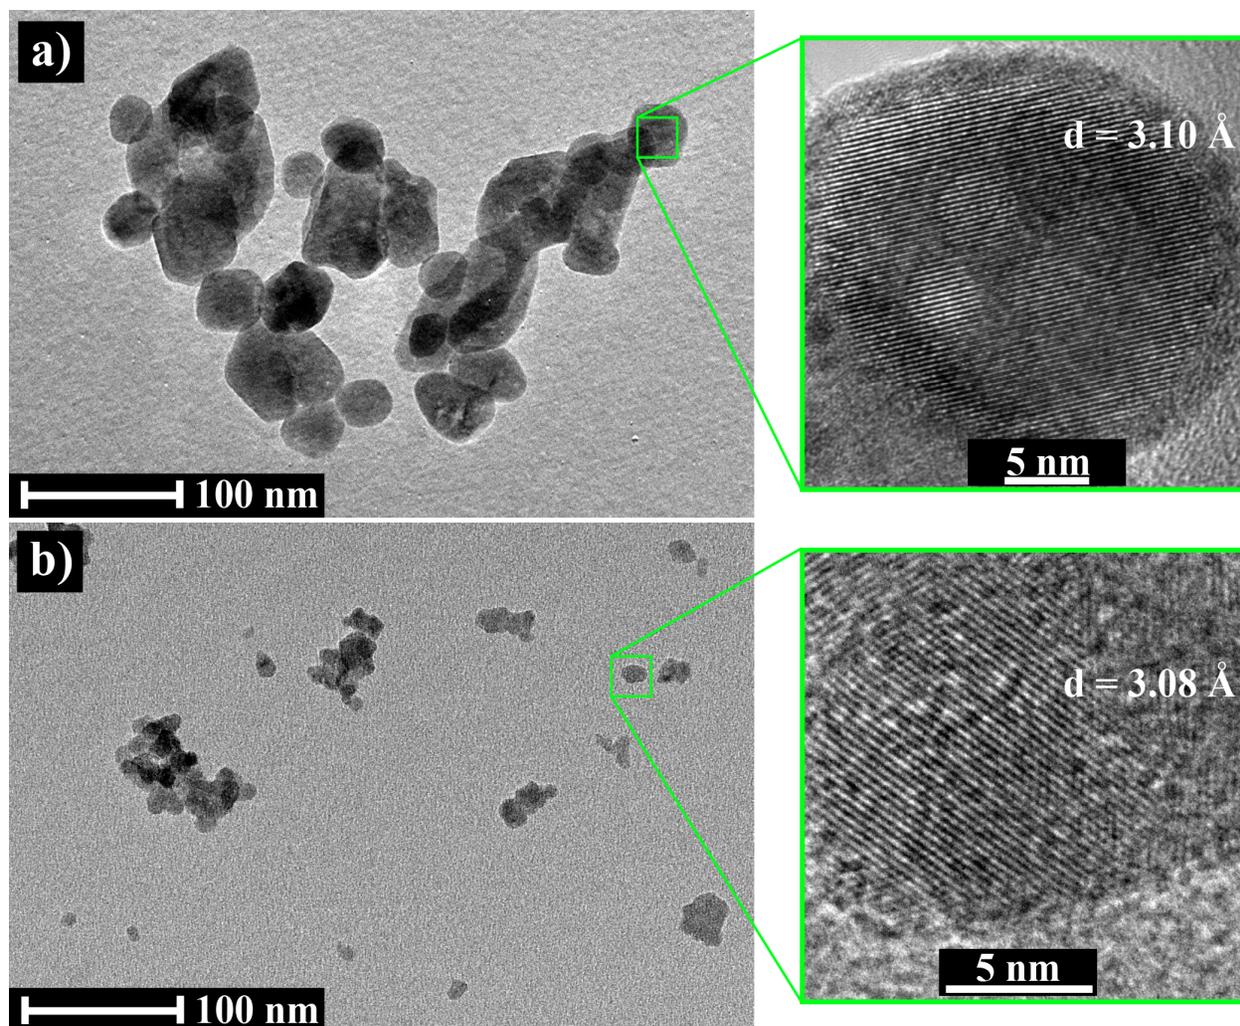

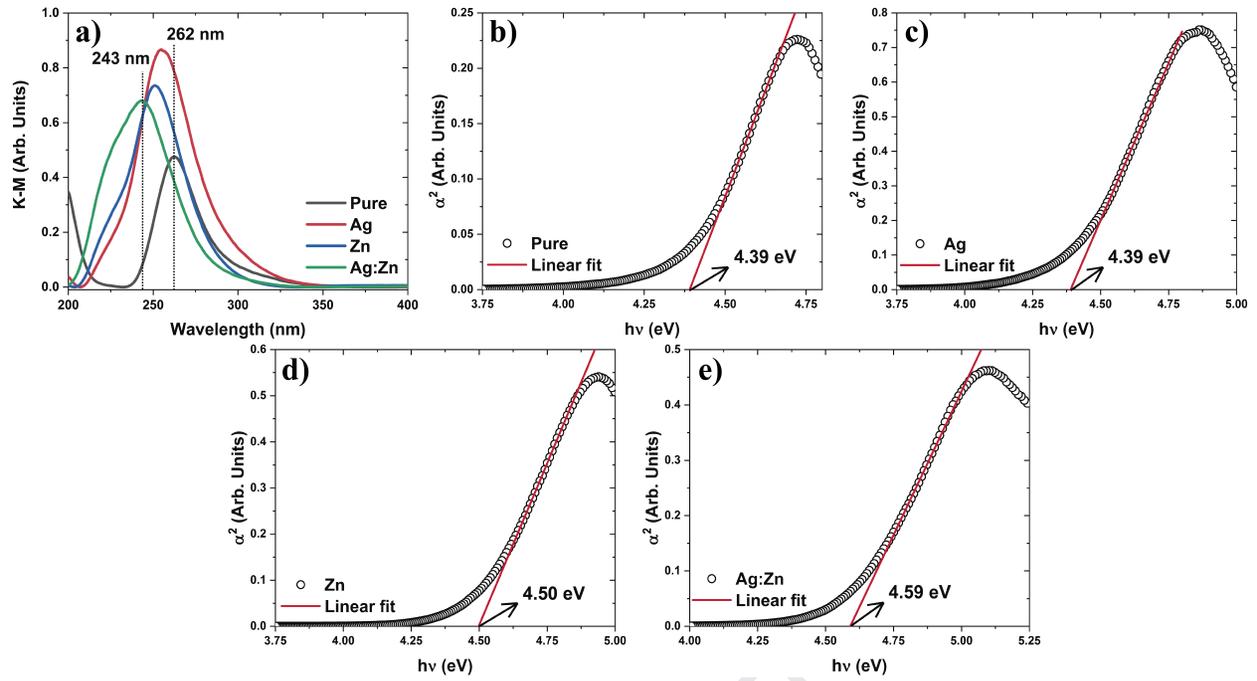

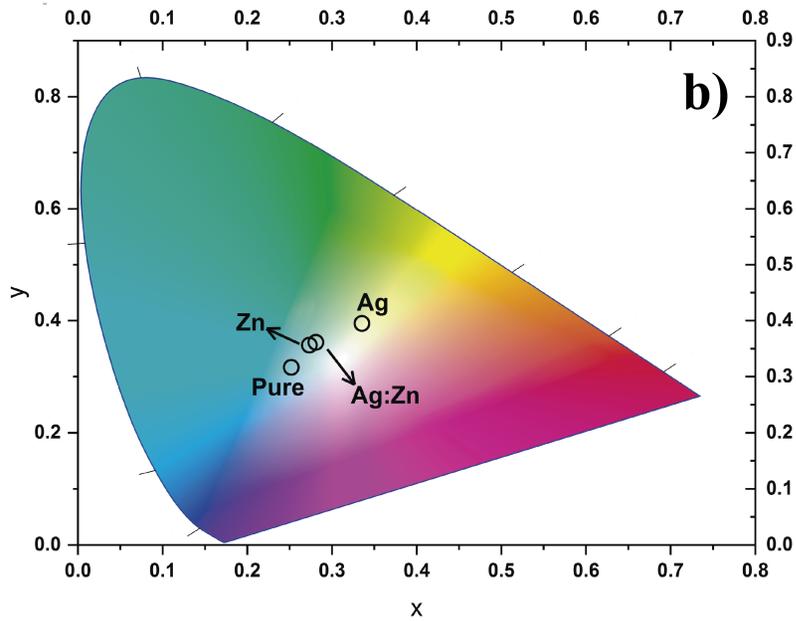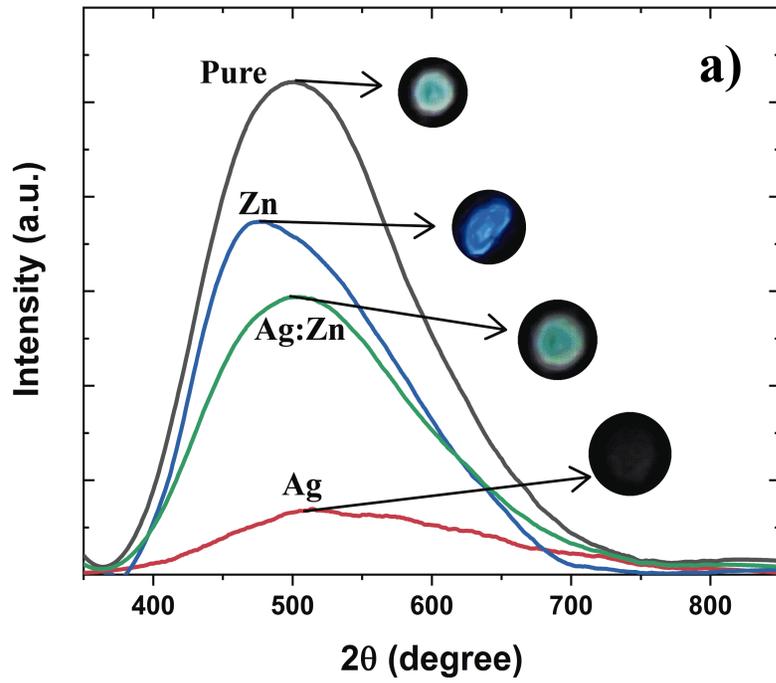

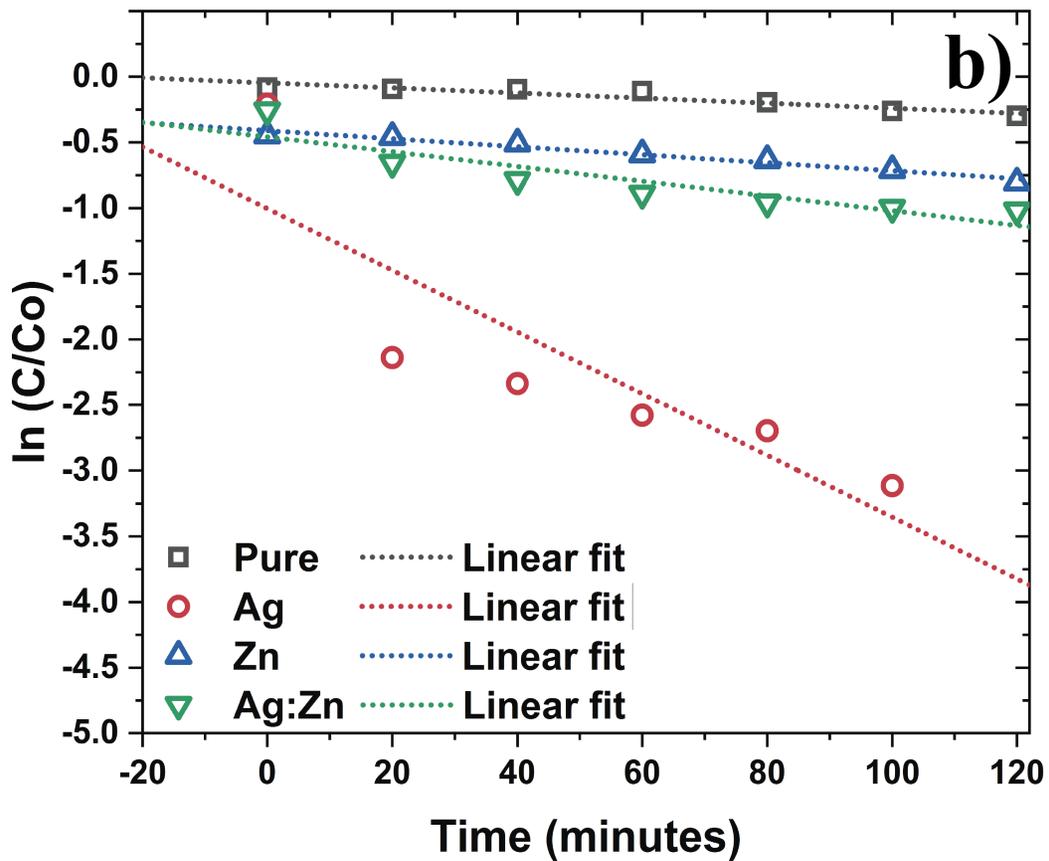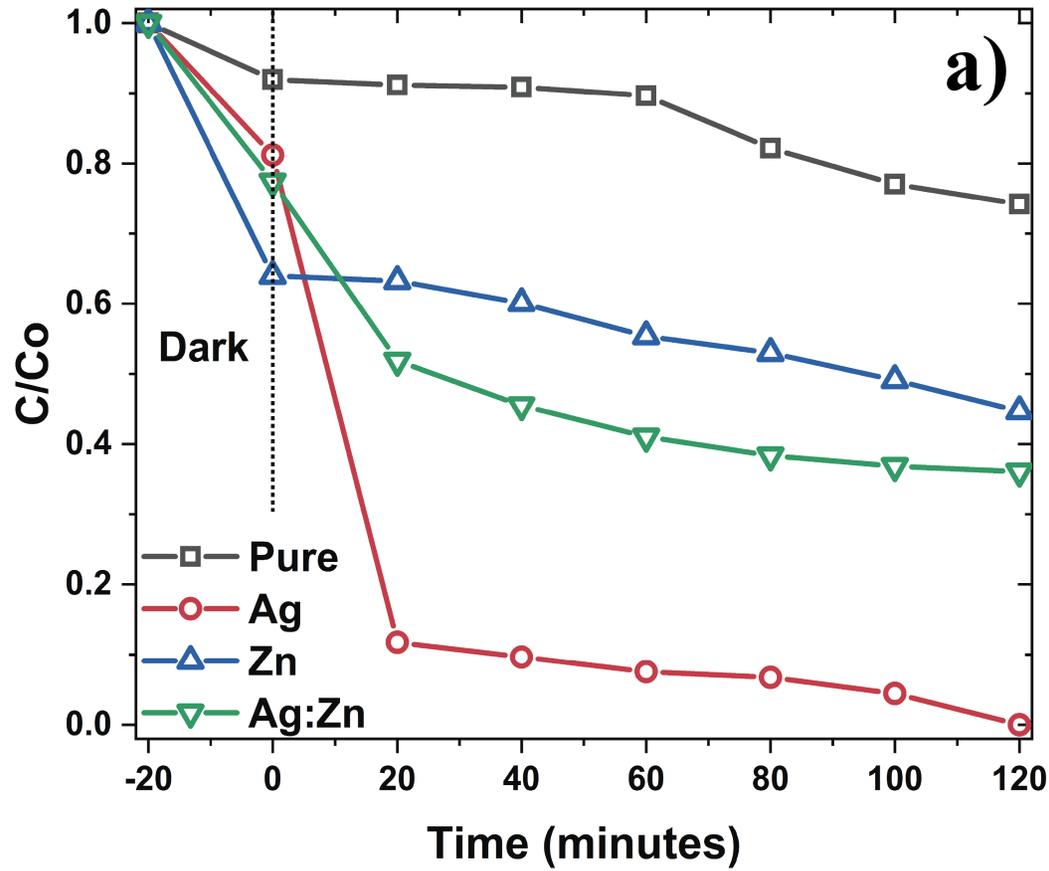

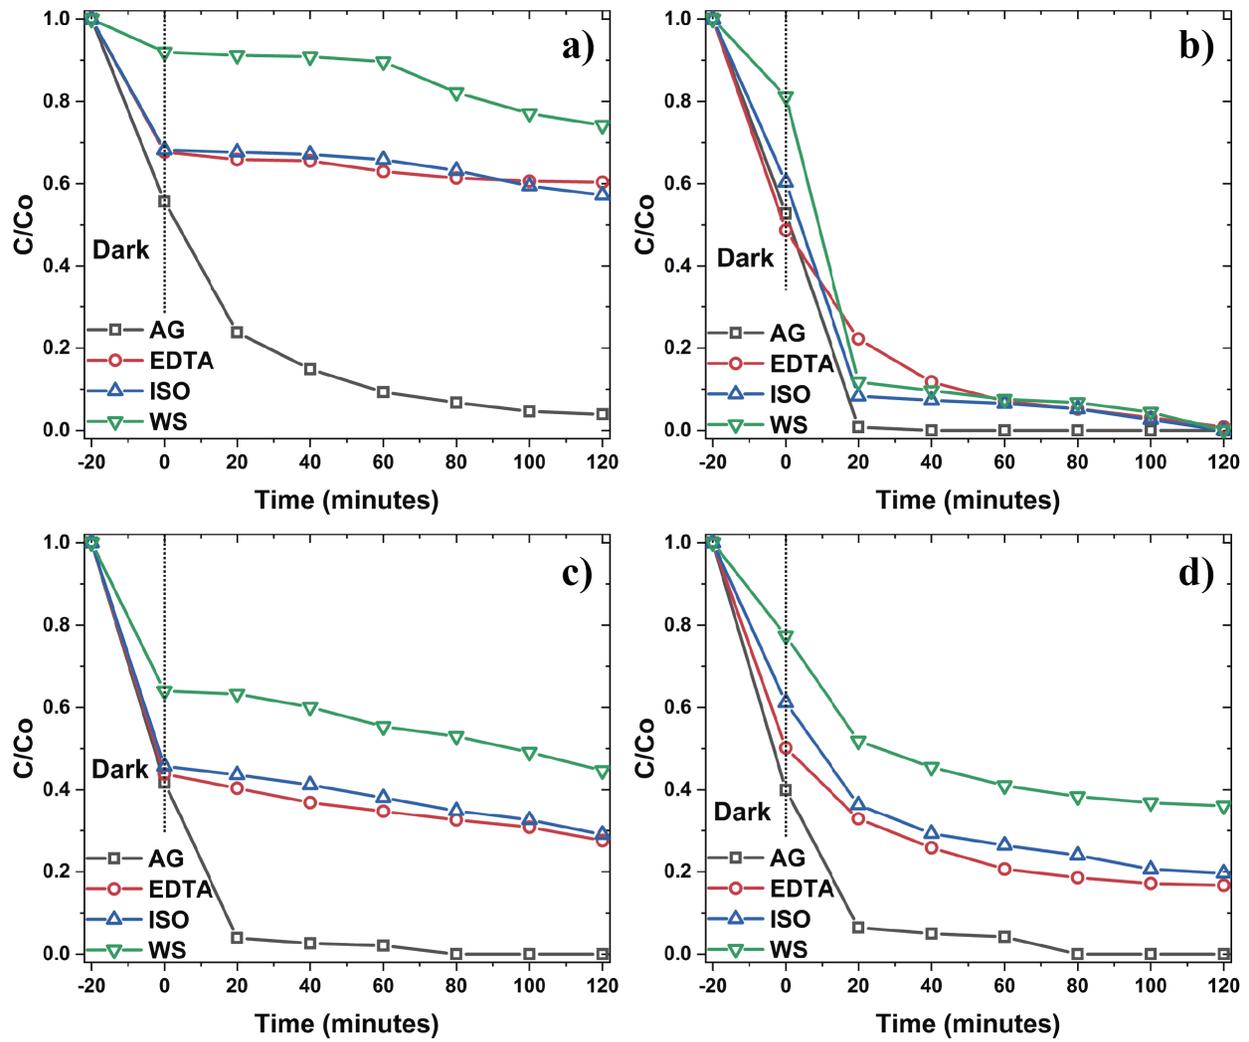

- **Highlights**

- Fast and facile sonochemical synthesis of Ag^+ and Zn^{2+} co-doped CaWO_4 nanoparticles.
- Increased absorption in the ultraviolet region with doping.
- Determination of doping changes in the crystalline and optical properties of materials.
- Change in photoluminescent emission color as doping is performed, theoretical and practical comparison.

Journal Pre-proof

Declaration of interests

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests: