

Synthesis of Oxygen-Containing Spirobipyrrolidinium Salts for High Conductivity Room Temperature Ionic Liquids

by Seiichiro Higashiya^{a)}, Thamarai Selvi Devarajan^{b)}, Manisha V. Rane-Fondacaro^{*b)}, Christopher Dangler^{b)}, Jeremy Snyder^{b)}, and Pradeep Haldar^{b)}

^{a)} Department of Chemistry, University at Albany, 1400 Washington Avenue, Albany, New York 12222, USA



^{b)} College of Nanoscale Science and Technology, University at Albany, 255 Fuller Road, Albany, New York 12203, USA

Synthesis of ionic liquids (IL) based on oxygen-containing spirobipyrrolidinium salts with BF₄, BF₃C₂F₅, and NTf₂ as counterions was undertaken. Their physical and electrochemical properties were evaluated for suitability for Room Temperature Ionic Liquids (RTIL) application. Reduction in melting point occurred upon exchange of C(2) by an O-atom of spirobipyrrolidinium, without sacrificing the electrochemical stability; while introduction of alkyl groups between the N- and O-atoms led to incorporation of asymmetry, and hence reduced the melting points, and viscosity.

Introduction. – Improvement of energy density of electric double layer capacitors (EDLCs) while maintaining the high power density, cycle life, and safety is one of the most awaited technological developments for sustainable society [1–4]. Electrolytes with wide operational (potential and temperature) window, high ion conductivity and concentration are important for further improvement. Several aspects of aliphatic room temperature ionic liquids (RTILs) meet these requirements; however, they have relatively low conductivity. Reduction in melting point and viscosity, upon introduction of O-atoms to aliphatic ammonium cations is well-known [5–9]. Meanwhile, 1,1'-spirobipyrrolidinium (SBP) salts of type **1** (*Table 1*) generally show high conductivity and solubility [10–18] and the application to EDLCs has been reported (for example [11–14][19–34]). Therefore, simultaneous implementation of these characters in cations depicted as type **2** in *Table 1* would lower the melting point and increase the conductivity of RTIL. In addition, introduction of alkyl groups in the molecules (R¹ to R³, *Table 1*) would lower the crystallinity by introduction of asymmetry and the ion-ion interaction by shielding the localized positive charges. In this article, we report the synthesis and characterization of oxygen-containing, alkyl group decorated spirobipyrrolidinium salts.


Results and Discussion. – *Synthesis of Oxygen-Containing Spirobipyrrolidinium Salts of Type 2.* There have been reports on the synthesis of oxygen-containing spirobipyrrolidinium salts [35][36]. *Cossar* and *Reynolds* used acetal exchange reaction of haloacetals with pyrrolidines. Our results show that a combination of aldehydes and haloalcohols instead of haloacetals also works well, and it provides flexibility in the synthesis (*Scheme 1*).

Table 1. Type 1: 1,1'-Spirobipyrrolidinium; Type 2: Various Functionalities Modifying the Parent Compound^{a)}

 1  2						
Salt	X	R ¹	R ²	R ³	A ⁻	Salt formation
SBP BF₄^{b)}	–	–	–	–	BF ₄	SBP Cl + HBF ₄ → SBP BF₄
OP BF₄	CH ₂	H	H	H	BF ₄	OP Cl + HBF ₄ → OP BF₄
OP BF₃C₂F₅	CH ₂	H	H	H	BF ₃ C ₂ F ₅	OP BF₄ + KBF ₃ C ₂ F ₅ → OP BF₃C₂F₅
OP NTf₂	CH ₂	H	H	H	NTf ₂	OP Cl + LiNTf ₂ → OP NTf₂
2MOP BF₄	CH ₂	Me	H	H	BF ₄	2MOP Cl + HBF ₄ → 2MOP BF₄
2MOP BF₃C₂F₅	CH ₂	Me	H	H	BF ₃ C ₂ F ₅	2MOP BF₄ + KBF ₃ C ₂ F ₅ → 2MOP BF₃C₂F₅
2MOP NTf₂	CH ₂	Me	H	H	NTf ₂	2MOP BF₄ + LiNTf ₂ → 2MOP NTf₂
2EOP BF₄	CH ₂	Et	H	H	BF ₄	2EOP Cl + HBF ₄ → 2EOP BF₄
4MOP BF₄	CH ₂	H	Me	H	BF ₄	4MOP Cl + HBF ₄ → 4MOP BF₄
5MOP BF₄	CH ₂	H	H	Me	BF ₄	5MOP Cl + HBF ₄ → 5MOP BF₄
5MOP NTf₂	CH ₂	H	H	Me	NTf ₂	5MOP BF₄ + LiNTf ₂ → 5MOP NTf₂
SBO BF₄	O	H	H	H	BF ₄	SBO Cl + HBF ₄ → SBO BF₄

^{a)} The table provides a list of ammonium salts with corresponding anionic functionalities. For the way of their preparation, see also *Scheme 1*. ^{b)} Type 1. Rest of the salts are of Type 2.

Scheme 1

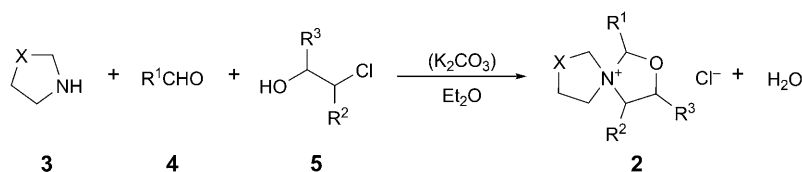

In the presence of K₂CO₃ except in the cases of paraformaldehyde (R¹=H), pyrrolidine was added at low temperature to improve the purity of the crude products. The crude chloride salts were washed with CH₂Cl₂. 2MOP Cl, 2EOP Cl, and SBO Cl were further purified using a cation exchange column (H⁺-form), which removes most of the color and basic by-products which cause the product to decompose at elevated temperatures. The chloride salts were subsequently treated with HBF₄ to generate BF₄ salts. Further purification of **2MOP BF₄** and **2EOP BF₄** was performed by acidic alumina column chromatography, which removed the protonated ammonium by-products. BF₃C₂F₅ and NTf₂ salts were prepared from Cl or BF₄ salts by the metathesis with KBF₃C₂F₅ [37–39] and LiNTf₂, respectively. The molecular weights and melting points are summarized in Table 2, along with the parent ammonium salt, 1,1'-spirobipyrrolidinium (SBP) tetrafluoroborate (**SBP BF₄**). The introduction of alkyl

Table 2. Characterization of Spiroammonium Salts

Salt	M_r	M.p. [°]	Conductivity [mS cm^{-1}]	Viscosity [cP]
SBP BF₄	213.02	189	^{a)}	^{a)}
OP BF₄	215.00	104	^{a)}	^{a)}
OP BF₃C₂F₅	315.01	155	^{a)}	^{a)}
OP NTf₂	408.34	78	^{a)}	^{a)}
2MOP BF₄	229.02	28	2.15	412.0
2MOP BF₃C₂F₅	329.04	142	^{a)}	^{a)}
2MOP NTf₂	422.36	22	2.62	57.3
2EOP BF₄	243.05	15	1.60	195.3
4MOP BF₄	229.02	243	^{a)}	^{a)}
5MOP BF₄	229.02	56	^{a)}	^{a)}
5MOP NTf₂	422.36	20	2.72	78.3
SBO BF₄	216.97	168	^{a)}	^{a)}

^{a)} Solid at r.t., hence the property was not determined.

groups next to the O-atom greatly reduced the melting points and they were below 30° in cases of **2MOP BF₄**, **2MOP NTf₂**, **2EOP BF₄**, and **5MOP NTf₂**. The conductivity and viscosity of these ionic liquids at 25° was 1.6 to 2.7 mS/cm as shown in Table 2. The ionic liquids except **2EOP BF₄** were purified by a low temperature recrystallization process down to –80° from MeOH, while **2EOP BF₄** showed liquid-liquid phase separation prior to the solidification with the contaminants. **2MOP BF₄** also showed partial phase separation by precipitating at the bottom of the flask along with crystallization from the rest of the solution. The crystalline part was repetitively collected from the precipitate.

Conductivity in MeCN. The measured conductivity of the electrolytes in MeCN at various concentrations at 25°, and the results are shown in Fig. 1.

Most of the new BF₄ salts exhibited highest conductivity around 2M, however, the conductivity was considerably lower than for **SBP BF₄**. The increased polarity of the fixed ring O-atom, and the ion-ion interaction in **OP BF₄** was responsible for lowering its conductivity. Conductivity measurement of **SBO BF₄** was not undertaken due to its low solubility in MeCN (<0.35M).

Potential Window in MeCN. The potential window of electrolytes at 0.65M in MeCN was measured using limiting current density of 1 mA/cm² [10]. The results are summarized in Table 3. A solution of 0.65M TEABF₄ (tetraethylammonium tetrafluoroborate) in MeCN is the industry standard for ultracapacitors, and the performance of electrolytes developed in house was compared with 0.65M TEABF₄/MeCN (potential window *ca.* 5.5 V).

The cathodic stability of the BF₄ salts of OP, 4MOP, and 5MOP was comparable with SBP in MeCN, but for the 2MOP and 2EOP salts, it was slightly lower. The alkyl group present between the N- and O-atoms was responsible for slight lowering of the stability. The instability seems to be a result of the β -elimination from the alkyl group between two electron-withdrawing atoms (Scheme 2).

Thermal Analysis. The thermal stability of the salts was estimated using thermogravimetric analysis. The results are shown in Fig. 2.

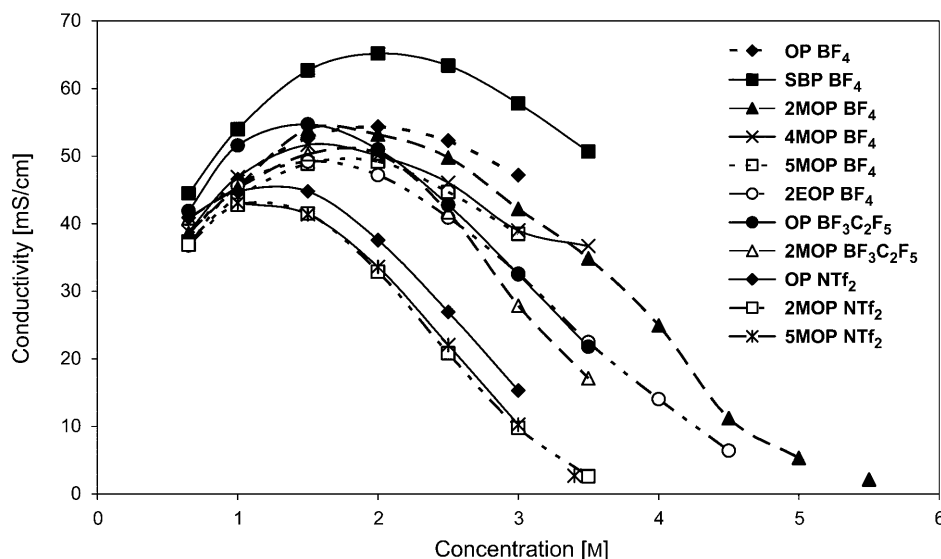



Fig. 1. Conductivity of electrolytes at various concentrations in MeCN

Table 3. Potential Window of Oxygenated Spiroammonium Salts at 0.65M in MeCN

Salt	Cathodic limit [V]	Anodic limit [V]	Potential window [V]
SBP BF₄	−2.7	4.6	7.3
OP BF₄	−2.8	4.5	7.3
OP BF₃C₂F₅	−2.7	3.4	6.1
OP NTf₂	−2.8	3.5	6.2
2MOP BF₄	−2.6	4.6	7.2
2MOP BF₃C₂F₅	−2.5	3.4	5.9
2MOP NTf₂	−2.7	3.4	6.1
2EOP BF₄	−2.6	4.6	7.2
4MOP BF₄	−2.7	4.6	7.3
5MOP BF₄	−2.7	4.5	7.2
5MOP NTf₂	−2.7	3.5	6.2
SBO BF₄^{a)}	−2.6	4.4	7.0

^{a)} 0.3M (maximum solubility).

Scheme 2

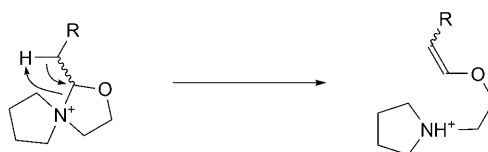

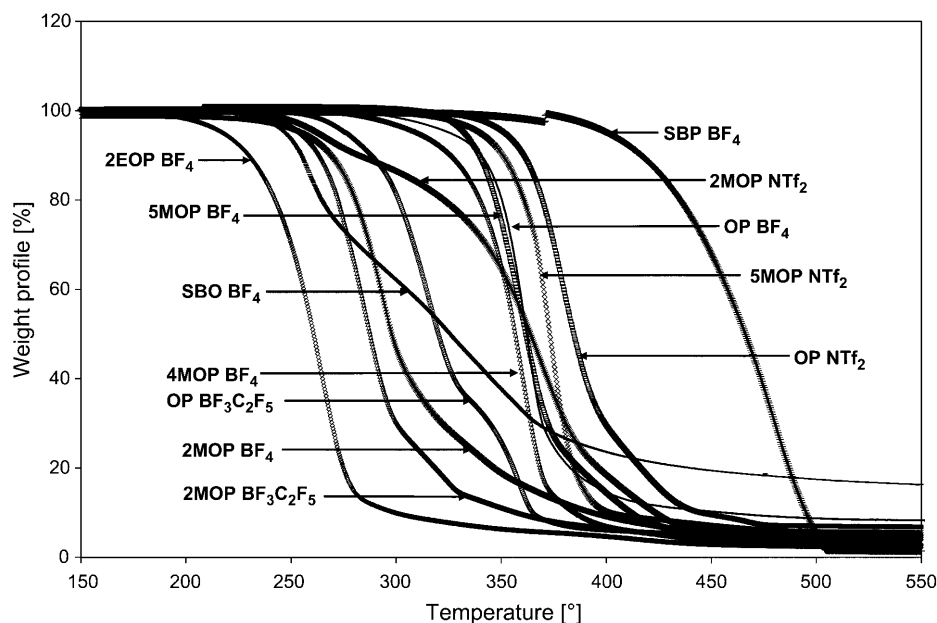


Fig. 2. TGA Analysis of the synthesized salts

The onset of the weight loss of each of the BF_4 salts occurred in the order of $2\text{EOP} < 2\text{MOP} \approx \text{SBO} < \text{OP} \approx 4\text{MOP} \approx 5\text{MOP} < \text{SBP}$. This trend is similar to that of the electrochemical stability. Reduction in thermal stability occurred upon introduction of the O-atom to the ring. The salts of OP, 2EOP, 2MOP, 4MOP, and 5MOP left a residue of carbonized material on the pan while the residue of SBP was colorless.

In summary, a variety of novel oxygen and alkyl group-containing spirobipyrrolidinium compounds were investigated for room temperature ionic liquid applications. Six novel cations, namely, OP, 2EOP, 2MOP, 4MOP, 5MOP, and SBO, were synthesized by employing aldehydes and haloalcohols. All together, eleven novel salts were produced. Three types of anions, BF_4^- , $\text{BF}_3\text{C}_2\text{F}_5^-$, and NTf_2^- were applied. The BF_4 and NTf_2 analogs were produced by conversion of chlorides, while the $\text{BF}_3\text{C}_2\text{F}_5$ analogs were generated by metathesis of BF_4 .

The melting points and voltage windows were determined from TGA and linear sweep voltammetry. The melting point reduced from 189° (**SBP BF₄**) to below 100° in six salts, and was even below 30° (RTIL) in four salts.

Potential window measurement was performed at 0.65M solution dissolved in MeCN for each salt. The parent compound **SBP BF₄** had a voltage window of 7.3 V. Six out of eleven salts had a potential window ≥ 7.0 V. The potential window varied from 5.9 to 7.3 V. The potential window of commercial workhorse 0.65M TEABF₄ in MeCN was *ca.* 5.5 V.

Conductivity measurement was performed at various concentrations (0.65 to 5.0M in MeCN), and a conductivity maximum was observed around a 2M concentration for

all salts. The conductivity (at 2M) of all the salts was in the range *ca.* 48–55 mS/cm, as compared with 65 mS/cm for **SBP BF₄**.

The thermal stability of various salts was found to reduce from *ca.* 500 to 300–420° range, which is more than adequate for most of the high temperature EDLC applications.

Experimental Part

General. An overview of ions that were synthesized is shown in *Table 1*. Salt of LiNTf₂ and aq. 50% HBF₄ were purchased from *TCI* and *Acros Organics*, resp. The cation chlorides were reacted with LiNTf₂ and HBF₄ to convert them into NTf₂ and BF₄ salts, resp. Aluminum oxide (activated, acidic, *Brockmann* Grade I, 58 Å) was purchased from *Alfa Aesar*. Regeneration of H⁺-form cation exchange resin (*BioRad* AG MP-50 H⁺-form) was undertaken as follows. Addition of 1M NaOH to the column until the eluent became basic, then H₂O was added to neutralize the eluent, subsequently 1M HCl in MeOH/H₂O (1:1) was added until the eluent became acidic, 1M HCl (two bed volume), and then H₂O until the eluent became neutral.

Characterizations. Measurement of NMR spectra of salts in CD₃OD unless specified, and the solvent peaks of ¹H- and ¹³C-NMR, and external CFC1₃ peak of ¹⁹F-NMR were used as references for the chemical shifts, resp. Linear sweep voltammetry of 0.65M electrolyte was performed using *Princeton Applied Research PARSTAT 2273A* potentiostat with glassy carbon working electrode (*AFEIE050GC E1 Series* Glassy Carbon electrode, *Pine Research Instrumentation*), Pt wire counter electrode, and Ag wire *quasi*-reference electrode at a scan rate of 5 mV/s in a dry box and the potential window was determined with a limiting current at 1 mA/cm² [10]. Conductivity and viscosity were measured using *Radiometer Analytical CDM230 Conductivity Meter* and *Brookfield DV-II + Pro*, resp., at 25°. TGA Data was recorded on a *TA Instruments TGA 2050* thermogravimetric analyzer under dynamic N₂ flow (total flow rate 100 cm³/min), using Pt pans and a ramp rate of 10°/min. DSC Data was recorded on a *TA Instruments DSC 2920* differential scanning calorimeter at 1 atm under dynamic N₂, using hermetically sealed Al pans, with a ramp rate of 10°/min.

Synthesis of KBF₃C₂F₅. KBF₃C₂F₅ was synthesized with slight modification of the previous method [37]. CF₃CF₂Br (43.8 g, 0.22 mmol) was condensed on a cold finger and introduced to anh. Et₂O (400 ml). PhMgBr (3M in Et₂O, 70 ml, 0.21 mol) was added dropwise to the mixture at a temp. below –65°, and stirred for 1 h. After dropwise addition of (MeO)₃B (24.9 g, 0.24 mol), the temp. was raised to –40°, subsequently, the bath temp. was lowered to dry ice temp., and stirred for 2 h. The mixture was decanted into cold 50% HF (100) in a high density polyethylene container, and stirred overnight at r.t. Then, ice-cold aq. KOH (100 g in 100 ml H₂O) was added while maintaining the temp. below 15°. The org. layer was separated. The aq. layer was extracted three times with Et₂O. The combined org. layers were dried over K₂CO₃ and MgSO₄. Filtration removed the desiccant material, and the volatiles by evaporation, the residual solid was washed with hexane and then recrystallized from i-PrOH/toluene to give the salt (17.86 g, 33%).

*Synthesis of 1,1'-Spirobipyrrolidinium Tetrafluoroborate (=5-Azoniaspiro[4.4]nonane Tetrafluoroborate; **SBP BF₄**).* Synthesis of **SBP BF₄** was attempted according to the previous report using pyrrolidine, 1,4-dibromobutane, K₂CO₃, and KBF₄ in MeCN [40]. However, due to inefficient anion exchange metathesis between Br and BF₄, the anion was converted to Cl using cation exchange resin, and subsequently converted to BF₄ using HBF₄ [23][41][42]. The resulting product was recrystallized from i-PrOH several times.

*Synthesis of 3-Oxazolidine-1'-spiropyrrolidinium Tetrafluoroborate (=2-Oxa-5-azoniaspiro[4.4]nonane Tetrafluoroborate; **OP BF₄**).* Pyrrolidine (28.45 g, 0.40 mol), was added to a mixture of paraformaldehyde (12.01 g, 0.40 mol), Et₂O (150 ml), and 2-chloroethanol (32.20 g, 0.40 mol), and mildly refluxed. Stirring overnight at r.t. resulted in layer separation. The top Et₂O layer was discarded, and the bottom layer was dissolved in H₂O and subsequently filtered. CH₂Cl₂ was used to wash the filtrate three times, and the aq. layer was evaporated, and the residue dried *in vacuo* at 100° to yield a crude chloride salt (OP Cl, 57.15 g, 0.35 mmol). It was converted to BF₄ salt by adding 50% HBF₄

(61.35 g, 0.35 mol) and MeOH (150 ml), followed by evaporation. EtOH (100 ml) was added and subsequently evaporated to azeotropically remove moisture. The residue was recrystallized from MeOH, and subsequently dissolved in MeCN and filtered through a membrane filter (Nylon, 0.22 μ). The solvent was evaporated, and the crude product was repeatedly recrystallized from MeOH and dried *in vacuo* at 100° overnight to give **OP BF₄** (64.0 g, 74% overall yield). ¹H-NMR: 4.87 (s, 2 H); 4.34 (t, *J* = 7.3, 2 H); 3.81 (t, *J* = 7.3, 2 H); 3.76–3.60 (m, 4 H); 2.24 (dd, *J* = 7.8, 16.9, 4 H). ¹³C-NMR: 92.6; 67.4; 62.7; 60.7; 23.2. ¹⁹F-NMR: –154.4 (m).

3-Oxazolidine-1'-spiropyrrolidinium Trifluoro(pentafluoroethyl)borate(1–) (=2-Oxa-5-azoniaspiro[4.4]nonane Trifluoro(pentafluoroethyl)borate(1–); **OP BF₃C₂F₅**). **OP BF₃C₂F₅** was synthesized by the metathesis of **OP BF₄** (24.34 g, 0.116 mol) and KBF₃C₂F₅ (26.17 g, 0.116 mol) by mixing the aq. solns. CH₂Cl₂ was added to extract **OP BF₃C₂F₅**. The org. layer was washed with two portions of H₂O. The solvent was removed by evaporation, and the residue was recrystallized from MeOH at –80° to give the product (17.2 g, 47%). ¹H-NMR: 4.87 (s, 2 H); 4.33 (t, *J* = 7.3, 2 H); 3.81 (t, *J* = 7.3, 2 H); 3.74–3.62 (m, 4 H); 2.24 (dd, *J* = 7.6, 17.2, 4 H). ¹³C-NMR: 92.5; 67.2; 62.7; 60.5; 23.0. ¹⁹F-NMR: –85.9 (*q*, *J* = 4.9); –139.1 (*q*, *J* = 20.0); –156.6 (*q*, *J* = 42.2).

3-Oxazolidine-1'-spiropyrrolidinium Bis[(trifluoromethyl)sulfonyl]azanide (=2-Oxa-5-azoniaspiro[4.4]nonane Bis[(trifluoromethyl)sulfonyl]azanide; **OP NTf₂**). **OP NTf₂** was prepared by the metathesis of crude OP Cl (29.6 g, 0.181 mol) and LiNTf₂ (51.9 g, 0.181 mol) in a similar way as described above and recrystallized from MeOH at –80° (63.0 g, 85%). ¹H-NMR: 4.87 (s, 2 H); 4.33 (t, *J* = 7.3, 2 H); 3.81 (t, *J* = 7.1, 2 H); 3.76–3.58 (m, 4 H); 2.24 (dd, *J* = 7.6, 17.2, 4 H). ¹³C-NMR: 121.3 (*q*, *J* = 320.4); 92.7; 67.5; 62.9 (br.); 60.8 (br.); 23.3. ¹⁹F-NMR: –81.1 (s).

Synthesis of 2-Methyl- (2MOP) and 2-Ethyl-3-oxazolidine-1'-spiropyrrolidinium (2EOP) Salts. 2-Methyl-3-oxazolidine-1'-spiropyrrolidinium Tetrafluoroborate (=1-Methyl-2-oxa-5-azoniaspiro[4.4]nonane Tetrafluoroborate; **2MOP BF₄**). Acetaldehyde (33.7 ml, 0.60 mol) was added to a chilled mixture of K₂CO₃ (20.7 g, 0.15 mol), Et₂O (150 ml), and 2-chloroethanol (48.3 g, 0.60 mol). To this mixture, pyrrolidine (42.7 g, 0.60 mol) was added dropwise while constantly stirring. Overnight, the temp. of the ice bath came to r.t. The volatile compounds were removed by evaporation, followed by addition of CH₂Cl₂ (200 ml) and subsequent filtration. H₂O (100 ml) was added, and the org. phase was removed. CH₂Cl₂ was used to wash the aq. phase twice, followed by subsequent evaporation. The residue was dissolved in H₂O to apply to H⁺-form cation exchange column chromatography (CC; 300 ml). The product was eluted with 0.2M aq. HCl (1 l) and the solvent was evaporated. The residue was dissolved in EtOH, and the insoluble material was filtered off. The solvent was evaporated, and the residue was dried *in vacuo* at r.t. to give the crude chloride salt (2MOP Cl, 77.9 g, 0.44 mol). The crude product was dissolved in 50% HBF₄ (77.3 g, 0.44 mol) and MeOH (200 ml) and subsequently evaporated. The residue was dried *in vacuo* overnight at 50° and then dissolved in CH₂Cl₂ (200 ml) and applied to acidic alumina CC (200 ml) and eluted with CH₂Cl₂ (800 ml). The eluent was evaporated, and the residue was dissolved in H₂O, then washed with 20% Et₂O in CH₂Cl₂ three times. The aq. layer was evaporated and dried *in vacuo* at 70° overnight to give a crude orange oil, **2MOP BF₄** (71.6 g, 52%). Crude **2MOP BF₄** (18.8 g) was further purified by acidic alumina CC (150 ml) with CH₂Cl₂ eluent (600 ml). The eluent was evaporated and the residue dissolved in H₂O followed by washing with 20% Et₂O in CH₂Cl₂. The aq. phase was filtered, evaporated, and subsequently dried *in vacuo* at 70° overnight to give **2MOP BF₄** (16.9 g). The product was dissolved in MeOH (800 ml) and allowed to crystallize at –80°. The soln. separated into two phases. Most of the impurities settled down, while the product formed a turbid soln. The turbid soln. was filtered using a chilled Büchner funnel at 4°, and the product dried *in vacuo* at 70° overnight. The filtrate soln. was poured back into the impure product to dissolve more salt to yield additional crop. ¹H-NMR: 5.09 (*q*, *J* = 5.4, H–C(1)); 4.34–4.20 (m, 2 H); 3.96–3.71 (m, 2 H); 3.71–3.47 (m, 3 H); 3.47–3.33 (m, 1 H); 2.23 (br. s, 4 H); 1.58 (d, *J* = 5.6, Me–C(1)). ¹³C-NMR: 99.0; 65.0; 61.5 (br.); 61.2 (br.); 57.5 (br.); 23.0; 22.6; 14.0. ¹⁹F-NMR: –153.6 (m).

2-Methyl-3-oxazolidine-1'-spiropyrrolidinium Trifluoro(pentafluoroethyl)borate(1–) (=1-Methyl-2-oxa-5-azoniaspiro[4.4]nonane Trifluoro(pentafluoroethyl)borate(1–); **2MOP BF₃C₂F₅**) and **2-Methyl-3-oxazolidine-1'-spiropyrrolidinium Bis[(trifluoromethyl)sulfonyl]azanide** (=1-Methyl-2-oxa-5-azoniaspiro[4.4]nonane Bis[(trifluoromethyl)sulfonyl]azanide; **2MOP NTf₂**). Equimolar amounts of crude **2MOP BF₄** and KBF₃C₂F₅ or LiNTf₂, resp., were mixed in H₂O/CH₂Cl₂. The org. phase was separated,

and the aq. phase was subsequently extracted with CH_2Cl_2 several times. The combined org. phase was washed eight times with H_2O . The solvent was evaporated, and the residue was dried *in vacuo* at 50° to give each of the crude products (68 and 91%, resp.). **2MOP BF₃C₂F₅** and **2MOP NTf₂** were further recrystallized from MeOH at -20° and -80° , resp., and the crystals filtered at 4° and then dried *in vacuo* at 70° .

Data of 2MOP BF₃C₂F₅. $^1\text{H-NMR}$: 5.08 (*q*, $\text{H-C}(1)$); 4.37–4.14 (*m*, 2 H); 3.93–3.69 (*m*, 2 H); 3.59 (*td*-like, 3 H); 3.44–3.32 (*m*, 1 H); 2.22 (*br. s*, 4 H); 1.58 (*d*, $J = 5.6$, $\text{Me-C}(1)$). $^{13}\text{C-NMR}$: 99.3; 65.1; 61.6 (*br.*); 61.5 (*br.*); 57.7 (*br.*); 23.2; 22.7; 14.0. $^{19}\text{F-NMR}$: -85.8 (*q*, $J = 4.9$); -138.9 (*q*, $J = 19.7$); -156.6 (*q*, $J = 41.8$).

Data of 2MOP NTf₂. $^1\text{H-NMR}$: 5.07 (*q*, $J = 5.6$, $\text{H-C}(1)$); 4.36–4.18 (*m*, 2 H); 3.90–3.68 (*m*, 2 H); 3.69–3.48 (*m*, 3 H); 3.43–3.33 (*m*, 1 H); 2.22 (*br. s*, 4 H); 1.57 (*d*, $J = 5.6$, $\text{Me-C}(1)$). $^{13}\text{C-NMR}$: 21.2 (*q*, $J = 320.4$); 65.2 (*m*); 61.2 (*m*); 57.3 (*m*); 23.0; 22.5; 14.0 (*m*). $^{19}\text{F-NMR}$: -80.9 (*s*).

2-Ethyl-3-oxazolidine-1'-spiropyrrolidinium Tetrafluoroborate (=1-Ethyl-2-oxa-5-azoniaspiro[4.4]nonane Tetrafluoroborate; 2EOP BF₄). The same method using propionaldehyde instead of acetaldehyde produced a yield of 11% of **2EOP BF₄**. The recrystallization from MeOH or EtOH was not successful. $^1\text{H-NMR}$: 4.87 (*d*, $J = 9.6$, $\text{H-C}(1)$); 4.34–4.22 (*m*, 2 H); 3.85–3.73 (*m*, 2 H); 3.69–3.51 (*m*, 3 H); 3.44–3.30 (*m*, 1 H); 2.22 (*br. s*, 4 H); 2.06–1.91 (*m*, 1 H); 1.78 (*ddd*, $J = 7.1, 10.1, 13.6$, 1 H); 1.10 (*t*, $J = 7.6$, Me). $^{13}\text{C-NMR}$: 102.8; 64.8; 61.8; 61.1; 57.9; 22.9; 22.2; 22.2; 9.8. $^{19}\text{F-NMR}$: -152.9 ; -153.0 .

Synthesis of 4-Methyl-3-oxazolidine-1'-spiropyrrolidinium Tetrafluoroborate (=3-Methyl-2-oxa-5-azoniaspiro[4.4]nonane Tetrafluoroborate; 4MOP BF₄). 2-Chloro-1-propanol was synthesized following the procedure described in [43]. To a mixture of NaBH_4 (14.19 g, 0.357 mol) and EtOH (150 ml), ethyl 2-chloropropionate (68.29 g, 0.50 mol) was added dropwise while maintaining the temp. below 45° . The mixture was stirred for 30 min and subsequently acidified using 2M HCl (200 ml) soln. Addition of CH_2Cl_2 (200 ml) separated the soln. into two layers. The org. phase was decanted and washed with H_2O (50 ml), followed by washing with aq. NaHCO_3 , and subsequently dried over anhyd. MgSO_4 . The solvent was gently evaporated after filtering off the drying reagent. The residue was subjected to fractional distillation ($65\text{--}68^\circ/70$ mmHg, 31.20 g, 65%). Pyrrolidine (36.82 g, 0.511 mol) was added to a mixture of paraformaldehyde (15.35 g, 0.511 mol), Et_2O (120 ml), and 2-chloro-1-propanol (48.78 g, 0.511 mol), and refluxed overnight to form two layers. H_2O was added to dissolve the salt, and the aq. layer was separated, which was then washed with CH_2Cl_2 three times. The aq. phase was filtered and the solvent evaporated. The residue was dried *in vacuo* at r.t. to give the crude chloride salt, 4MOP Cl (24.08 g, 27%). 50% HBF_4 (23.8 g, 0.136 mol) and MeOH (70 ml) were added to the crude product, and the solvent was evaporated. EtOH (50 ml) was added and subsequently evaporated. This process was repeated twice. The resulting residue was recrystallized from EtOH (200 ml) at -20° to give **4MOP BF₄** (26.4 g, 85%) as a viscous solid. The product was further recrystallized from MeOH. $^1\text{H-NMR}$: 4.87 (*br. s*, $\text{CH}_2(1)$); 4.53 (*t*, $J = 8.3$, 1 H); 4.13 (*qt*, $J = 7.1$, $\text{H-C}(3)$); 3.88–3.81 (*m*, 1 H); 3.73–3.64 (*m*, 1 H); 3.64–3.53 (*m*, 2 H); 3.51–3.43 (*m*, 1 H); 2.29–2.11 (*m*, 4 H); 1.47 (*d*, $J = 6.6$, Me). $^{13}\text{C-NMR}$: 91.7; 73.4; 67.1; 61.7; 55.0; 22.9; 22.3; 12.8. $^{19}\text{F-NMR}$: -154.4 ; -154.5 .

Synthesis of 5-Methyl-3-oxazolidine-1'-spiropyrrolidinium (5MOP) Salts. 5-Methyl-3-oxazolidine-1'-spiropyrrolidinium Tetrafluoroborate (=4-Methyl-2-oxa-5-azoniaspiro[4.4]nonane Tetrafluoroborate; 5MOP BF₄). Synthesis of crude 5MOP Cl was undertaken in a manner similar to OP Cl. The reaction between 1-chloro-2-propanol (technical grade, 75% purity, 18.91 g, 0.20 mol), paraformaldehyde (6.01 g, 0.20 mol), and pyrrolidine (14.22 g, 0.20 mol) in Et_2O (50 ml) gave crude 5MOP Cl as a waxy gel (29.53 g, 83%). 5MOP Cl was subsequently converted to **5MOP BF₄** with 50% HBF_4 (29.18 g, 0.166 mol) in MeOH (80 ml) followed by three sets of EtOH-evaporation procedure. Drying *in vacuo* overnight at r.t. gave the crude solid product (36.9 g, 81%), which was further recrystallized from MeOH at -80° in the same manner as **2MOP BF₄**. The product was dried *in vacuo* at 80° to yield **5MOP BF₄** (25.9 g, 55%). $^1\text{H-NMR}$ showed that the product contained about 6 mol-% of **4MOP BF₄** derived from the technical grade 1-chloro-2-propanol, and further recrystallization from MeOH did not remove **4MOP BF₄**. $^1\text{H-NMR}$: 5.03 (*d*, $J = 6.1$, $\text{H-C}(1)$); 4.79 (*d*, $J = 5.6$, $\text{H-C}(1)$); 4.59 (*qdd*, $J = 6.8$, $\text{H-C}(4)$); 3.96 (*dd*, $J = 7.3, 11.9$, $\text{H-C}(3)$); 3.80–3.55 (*m*, 4 H); 3.35 (*dd*, $J = 8.1, 11.6$, $\text{H-C}(3)$); 2.38–2.07 (*m*, 4 H); 1.44 (*d*, $J = 6.1$, Me). $^{13}\text{C-NMR}$: 92.2; 76.4; 66.5; 64.1; 62.4; 23.1; 23.0; 18.6. $^{19}\text{F-NMR}$: -154.1 ; -154.2 .

5-Methyl-3-oxazolidine-1'-spiropyrrolidinium Bis[(trifluoromethyl)sulfonyl]azanide (= *4-Methyl-2-oxa-5-azoniaspiro[4.4]nonane Bis[(trifluoromethyl)sulfonyl]azanide*; **5MOP NTf₂**). **5MOP NTf₂** was synthesized using metathesis of **5MOP BF₄** and LiNTf₂ in the same manner as the synthesis of **2MOP NTf₂** in 91% yield, and the product was further recrystallized from MeOH at -80° , in the same manner as **2MOP BF₄**. ¹H-NMR: 5.04 (*d*, *J* = 5.6, H–C(1)); 4.79 (*d*, *J* = 6.1, H–C(1)); 4.59 (*qdd*, *J* = 6.9, H–C(4)); 3.95 (*dd*, *J* = 7.1, 11.6, H–C(3)); 3.79–3.58 (*m*, 4 H); 3.35 (*dd*, *J* = 8.6, 11.6, H–C(3)); 2.30–2.14 (*m*, 4 H); 1.45 (*d*, *J* = 6.6, Me). ¹³C-NMR: 121.2 (*q*, *J* = 320.5, 1 H); 92.3 (*br.*); 76.4; 66.6 (*m*); 64.3 (*m*); 62.6 (*m*); 23.0; 23.0; 18.6; 18.6. ¹⁹F-NMR: -81.1 (*s*).

Synthesis of 3,3'-Spirobioxazolidinium Tetrafluoroborate (= *2,7-Dioxa-5-azoniaspiro[4.4]nonane Tetrafluoroborate*; **SBO BF₄**). 1,3-Oxazolidine was synthesized from paraformaldehyde (15.02 g, 0.50 mol) and 2-aminoethanol (30.54 g, 0.50 mol) [44]. The reaction between paraformaldehyde and aminoethanol yielded 1,3,5-tris(2-hydroxyethyl)hexahydro-1,3,5-triazine [45], which was thermally cracked to yield 1,3-oxazolidine. The crude distillate (34.4 g, 94%) was collected in a trap chilled at -78° and was used without further purification. Crude 1,3-oxazolidine (34.4 g, 0.47 mol) was added to paraformaldehyde (14.11 g, 0.47 mol) and 2-chloroethanol (37.8 g, 0.47 mol) in Et₂O (120 ml) at -78° . The temp. was raised to 0° and then slowly to r.t. overnight while stirring continuously. The volatile materials were removed by evaporation, and the residue was dissolved in H₂O. The insoluble material was filtered, and the filtrate was washed three times with CH₂Cl₂, and then applied to a column of H⁺-form cation exchange resin (250 ml). The column was washed with H₂O to neutralize the eluent, and subsequently eluted with 1 to 2M HCl. Solvent evaporation yielded a crude SBO Cl (51.04 g, 66%, 0.31 mol), which was converted to **SBO BF₄** with 50% HBF₄ (54.17 g, 0.31 mol) in MeOH (100 ml) to immediately generate a white precipitate. The product was filtered and subsequently recrystallized from H₂O, and dried *in vacuo* at 100° to yield **SBO BF₄** (23.55 g, 35%). ¹H-NMR ((D₆)DMSO): 5.27 (*d*, *J* = 5.6, 2 H); 5.13 (*d*, *J* = 5.6, 2 H); 4.50 (*t*, *J* = 7.1, 4 H); 4.19–4.07 (*m*, 4 H). ¹³C-NMR ((D₆)DMSO): 90.0 (*m*); 66.1 (*m*); 56.6 (*m*). ¹⁹F-NMR: -148.7 ; -148.7 .

We would like to thank the Chemistry Department for providing processing and characterization facilities.

REFERENCES

- [1] D.o.E. Office of Basic Energy Sciences, the United State of America, Basic Research Needs for Electrical Energy Storage, 2007.
- [2] A. Lewandowski, M. Galinski, *J. Power Sources* **2007**, *173*, 822.
- [3] A. Burke, *Electrochim. Acta* **2007**, *53*, 1083.
- [4] M. Galiński, A. Lewandowski, I. Stępnia, *Electrochim. Acta* **2006**, *51*, 5567.
- [5] T. Sato, G. Masuda, K. Takagi, *Electrochim. Acta* **2004**, *49*, 3603.
- [6] Z.-B. Zhou, H. Matsumoto, K. Tatsumi, *Chem. Lett.* **2004**, *33*, 886.
- [7] Z.-B. Zhou, H. Matsumoto, K. Tatsumi, *Chem. Lett.* **2004**, *33*, 1636.
- [8] K. Yuyama, G. Masuda, H. Yoshida, T. Sato, *J. Power Sources* **2006**, *162*, 1401.
- [9] Z.-B. Zhou, H. Matsumoto, K. Tatsumi, *Chem. – Eur. J.* **2006**, *12*, 2196.
- [10] M. Ue, K. Ida, S. Mori, *J. Electrochem. Soc.* **1994**, *141*, 2989.
- [11] K. Chiba, *Denkai Chikudenki Hyoron (Electrolytic Condenser Rev.)* **2006**, *57*, 94.
- [12] K. Chiba, R. Nagamatsu, JP2005175239, 2005.
- [13] Y. Watanuki, M. Nakano, S. Tanabe, JP2006024785, 2006.
- [14] S. Horikoshi, JP2008078349, 2008.
- [15] M. Shimizu, Y. Yokoyama, JP02054511, 1990.
- [16] M. Shimizu, Y. Yokoyama, A. Hirozawa, JP02069916, 1990.
- [17] T. Matsunaga, T. Kawahara, H. Matsumoto, WO2003012900, 2003.
- [18] N. Nagakura, JP2004175667, 2004.
- [19] K. Chiba, WO2005088656, 2005.
- [20] K. Chiba, WO2005022571, 2005.

- [21] K. Chiba, JP2005260030, 2005.
- [22] K. Chiba, T. Kamei, JP2005175513, 2005.
- [23] T. Higono, K. Sato, N. Suga, K. Chiba, T. Kamei, EP1583116, 2005.
- [24] H. Nakamura, K. Chiba, T. Kamei, M. Okamura, JP2005286177, 2005.
- [25] H. Nakamura, O. Kuwagaki, K. Tamura, M. Okamura, JP2005286178, 2005.
- [26] K. Chiba, T. Kamei, JP2006245357, 2006.
- [27] K. Chiba, T. Kamei, JP2006351915, 2006.
- [28] T. Higono, K. Sato, A. Takeshita, K. Chiba, T. Kamei, JP2006186052, 2006.
- [29] A. Kosuda, Y. Ohashi, EP1727165, 2006.
- [30] H. Norieda, K. Kobayashi, WO2006132444, 2006.
- [31] K. Chiba, H. Yamamoto, JP2007189024, 2007.
- [32] H. Nakajima, JP2007180055, 2007.
- [33] S. Horikoshi, JP2008034424, 2008.
- [34] H. Nakajima, JP2008066407, 2008.
- [35] N. J. Leonard, E. F. Kiefer, L. E. Brady, *J. Org. Chem.* **1963**, 28, 2850.
- [36] B. C. Cossar, D. D. Reynolds, *J. Heterocycl. Chem.* **1965**, 2, 430.
- [37] Z.-B. Zhou, M. Takeda, M. Ue, *J. Fluorine Chem.* **2003**, 123, 127.
- [38] Z.-B. Zhou, M. Takeda, T. Fujii, M. Ue, *J. Electrochem. Soc.* **2005**, 152, A351.
- [39] Z.-B. Zhou, M. Takeda, M. Ue, *J. Fluorine Chem.* **2004**, 125, 471.
- [40] A. Siggel, F. Nerenz, T. Palanisamy, A. Poss, S. Demel, US2007049750, 2007.
- [41] K. Chiba, H. Yamamoto, JP2007106750, 2007.
- [42] T. Baba, Y. Watanuki, Y. Kanokogi, S. Ueda, JP2007077046, 2007.
- [43] H. Tsuruoka, K. Shibayama, JP2003022711, 2000.
- [44] J. B. Lambert, S. M. Wharry, *J. Org. Chem.* **1982**, 47, 3890.
- [45] I. C. Popoff, P. G. Haines, US4008244, 1977.

Received February 11, 2009