

Decamethylnickelocenium hydrogen-7,7,8,8-tetracyanoperfluoro-*p*-quinodimethandiide: isolation of the protonated weak base [HTCNQF₄][−]

Xiaotai Wang,^{a,b} Louise M. Liable-Sands,^c Jamie L. Manson,^a Arnold L. Rheingold^{*c} and Joel S. Miller^{*a}

^a Department of Chemistry, University of Utah, Salt Lake City, Utah 84112, USA

^b Department of Chemistry, The Ohio State University, Columbus, Ohio 43210, USA

^c Department of Chemistry, University of Delaware, Newark, Delaware 19716, USA

Unprecedentedly stable hydrogen-7,7,8,8-tetracyanoperfluoro-*p*-quinodimethandiide, [HTCNQF₄][−], is isolated and crystallographically characterized.

The discoveries of the metamagnetic behaviour¹ of a one-dimensional phase [Fe(C₅Me₅)₂]⁺[TCNQ][−] (TCNQ = 7,7,8,8-tetracyano-*p*-quinodimethane) and the ferromagnetic behaviour² of [Fe(C₅Me₅)₂]⁺[TCNE][−] (TCNE = tetracyanoethylene) led to extensive studies of the electron-transfer salts comprising metallocenium cations and polycyano anions.^{3,4} As part of our program to understand the magnetic properties of metallocenium salts of radical anion acceptors, the reaction of decamethylnickelocene, [Ni(C₅Me₅)₂], with perfluoro-TCNQ, TCNQF₄,⁵ has been studied. TCNQF₄ is a strong electron acceptor, however, unlike TCNQ, its isolated radical anion has never been observed in the solid state, only as its *S* = 0 dimer, [TCNQF₄]₂^{2−}.⁶ Seven metallocene-based electron-transfer salts incorporating reduced TCNQF₄ as [TCNQF₄]₂^{2−} have been reported.^{6a,c,e,f} [Ni(C₅Me₅)₂] undergoes two reversible one-electron oxidations at −0.73 and 0.37 V,⁷ while TCNQF₄ undergoes two reversible one-electron reductions at 0.53 and 0.02 V⁸ (vs. SCE in MeCN). Thus, there are 0.90 and 0.39 V driving forces for forming [Ni(C₅Me₅)₂]⁺[TCNQF₄][−] and {[Ni(C₅Me₅)₂]⁺]₂[TCNQF₄]₂^{2−}, respectively.

Recrystallisation from MeCN of the precipitate formed upon the reaction of [Ni(C₅Me₅)₂] and TCNQF₄ (1 : 1) in thf led to the isolation of two phases. The β-phase precipitates first and has a characteristic IR (Nujol): ν(CN) 2181 ± 1 m and 2151 ± 1 m cm^{−1} (at 26 K: 2182s and 2150s cm^{−1}) (yield: 41%). After the β-phase was isolated, the remaining mother liquor was concentrated and cooled at −40 °C for several days, affording the α-phase in two crops (yield: 24%). IR (Nujol): ν(CN) 2182 ± 1 m and 2155 ± 1 m cm^{−1} (at 26 K: 2195w, 2183s, 2155s cm^{−1}).

Crystals of α-phase suitable for single-crystal X-ray diffraction were obtained upon refrigerating a MeCN solution at −40 °C. The structure determination[†] confirms [Ni(C₅Me₅)₂]⁺ and an unexpected polymeric anion. The cation, Fig. 1, has approximate *D*_{5d} molecular symmetry with Ni–C distances ranging between 2.082(7) and 2.117(7) Å and averaging 2.105 Å; 0.06 Å shorter than in [Ni(C₅H₅)₂].⁹ The C₅ rings have C–C distances averaging 1.420 Å. The Ni–C₅ ring centroid distance is 1.723₅ ± 0.003₅ Å while the angle between ring centroids and Ni is 178.9°. This is the second reported structure of [Ni(C₅Me₅)₂]⁺, the first being [Ni(C₅Me₅)₂]⁺[C₆₀][−],¹⁰ however, structural details of the cation were not reported.

The polymeric anion is [HTCNQF₄][−] (Fig. 1) which is reported for the first time and possesses a planar (NC)₂CC₆F₄ moiety typical of previously reported TCNQ¹¹ and TCNQF₄.^{6,12} compounds with an unprecedented nonplanar C(CN)₂H group. The ring C–C distances average 1.387 Å. The four CN groups average 1.138 Å. The unique feature is the sp³ C(27) with a C₆-ring C(21)–C(27) distance of 1.501(10) Å and C(27)–CN distances of 1.482 ± 0.012 Å which are distinctly longer than the those for sp² C(30). For example, the C(30)–C(24)

bond is 1.414(9) Å and the C(27)–H(27) bond distance is 1.00(7) Å. The bond angles of C(21)–C(27)–C(28), C(21)–C(27)–C(29) and C(28)–C(27)–C(29) sum to 331.9° characteristic of sp³ bonding about C(27). In contrast, the sum of the angles about C(30) is 360.1° characteristic of sp² bonding. Furthermore, the mean distance of the C(27)–C(28) and C(27)–C(29) bonds (1.482 Å) is significantly longer than that of the C(30)–C(31) and C(30)–C(32) bonds (1.428 Å). Except for the H atom and the CN groups bonded to C(27), all the atoms are essentially coplanar.

The solid is comprised of one-dimensional ...D⁺A[−]D⁺A[−]... chains {D⁺ = [Ni(C₅Me₅)₂]⁺, A[−] = [HTCNQF₄][−]} where the C₆-ring is essentially parallel to the C₅Me₅ plane, as observed for many [M(C₅Me₅)₂]⁺[A][−] electron-transfer salts that exhibit cooperative magnetic interactions.^{1–4} The intrachain Ni...Ni separation is 10.888 Å, while the interchain separations are 9.570, 9.733, 9.822, 10.025 and 11.579 Å. Unlike previously reported ...D⁺A[−]D⁺A[−]... structured salts, this salt has hydrogen-bonded chains of [HTCNQF₄][−] anions in the solid. Each C(27)–H(27) hydrogen bonds to N(3) on another [HTCNQF₄][−] with an sp²-C(27)···N(3) separation of 3.14 Å and a C(27)–N(3) distance of 2.084 Å which is significantly less than the sum of the N and H van der Waals radii,¹³ Fig. 2.

A detailed study of the ν(CH) region of the IR spectra (Fluorolube) reveals a room-temperature absorption at 2854 m cm^{−1} for the α-phase which is not present for either the β-phase or [Ni^{III}(C₅Me₅)₂]⁺ and is assigned to the (NC)₂C–H stretch. Comparable absorptions have been reported for CH₂(CN)₂,^{14a} H₂TCNQ,^{14b} HC(CN)₂(C₆H₄)C(CN)₂(C₆H₄)NMe₂,^{14a} HC(CN)₂(C₆H₄)C(CN)NC₆H₄OMe,^{14c} and H₂TCNE. At 26 K this band shifts to lower energy and splits into three absorptions

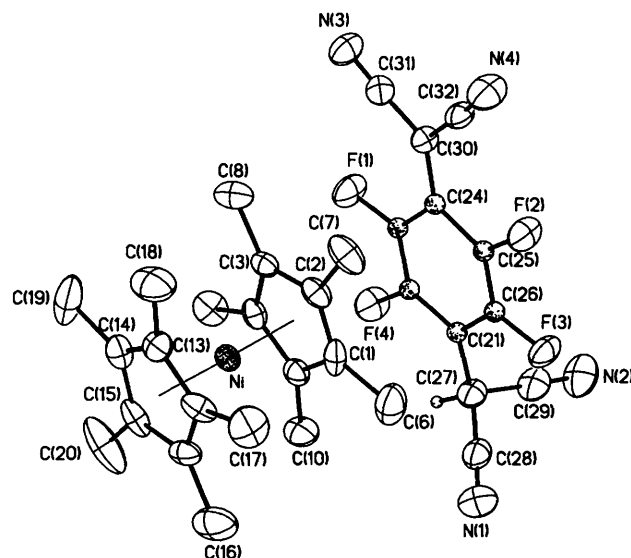


Fig. 1 ORTEP drawing depicting the atom labelling of [Ni(C₅Me₅)₂]⁺; atoms shown as 30% probability ellipsoids

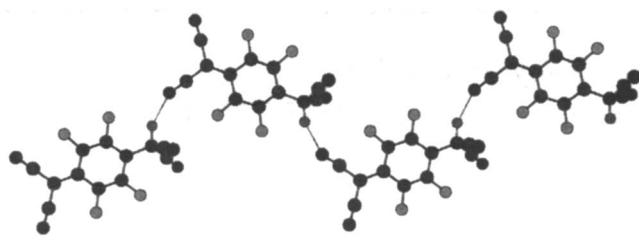


Fig. 2 Hydrogen-bonded chains of $[\text{HTCNQF}_4]^-$

at 2846m, 2837m and 2823w cm^{-1} consistent with a phase transition that is indicative from preliminary magnetic studies.

The hydrogen source is either H^+ or H^- ; the former requiring protonation of $[\text{TCNQF}_4]^{2-}$ and the latter requiring H^- addition to $[\text{TCNQF}_4]^{1-}$. H_2TCNQF_4 is an intermediate in the preparation of TCNQF_4 ,⁵ but unlike H_2TCNQ ,^{14b} it has neither been isolated or characterized.⁵ The computationally determined $\text{p}K_{\text{a}1}$ and $\text{p}K_{\text{a}2}$ are 4.0 and 7.2 for H_2TCNQF_4 ;¹⁵ hence strong acids are needed to protonate $[\text{TCNQF}_4]^{2-}$. Therefore, although formation of $\{[\text{Ni}(\text{C}_5\text{Me}_5)_2]^+\}_2[\text{TCNQF}_4]^{2-}$ is energetically allowed, it requires 2 equiv. of the donor^{16†} and a sufficiently strong acid to protonate $[\text{TCNQF}_4]^{2-}$;§ both of which are not present.

Since the first step is probably the formation of $[\text{Ni}^{\text{III}}(\text{C}_5\text{Me}_5)_2]^+[\text{TCNQF}_4]^{1-}$, H^- addition to $[\text{TCNQF}_4]^{1-}$ to form $[\text{HTCNQF}_4]^-$ is plausible even though formation of the $\text{sp}^3\text{-C}$ breaks the extended conjugation and stability of the radical anion.¶ The H^- source is most likely the thf solvent. This is consistent with the observation that only the β -phase is isolated from acetonitrile and that the α -phase requires thf.

The β -phase has not as yet yielded crystals of sufficient size to determine its structure. The β -phase undergoes a reversible phase transition at 42.5 °C ($\Delta H = 1.81 \text{ kJ mol}^{-1}$) without a change in the $\nu(\text{CN})$ absorptions. Therefore, the β -phase is not a metastable phase that has the same chemical composition as the α -phase. This is in accord with the IR spectra in the $\nu(\text{CH})$ region which lacks the 2854 cm^{-1} absorption and the $\nu(\text{CN})$ region of the two phases which are similar, but not identical. Consequently, based upon elemental analyses and IR data, the β -phase is formulated as $[\text{Ni}^{\text{III}}(\text{C}_5\text{Me}_5)_2][\text{TCNQF}_4]$. However, the $\nu(\text{CN})$ region of the two phases are different from those of previously characterized TCNQF_4 , $\{[\text{TCNQF}_4]_2\}^{2-}$ and $[\text{TCNQF}_4]^{2-}$.⁶ This suggests that some interactions between the acceptor and the donor exist, but requires a structural determination to elucidate.

The authors gratefully acknowledge support from the US Department of Energy Grant Nos. DE-FG03-93ER45504 and DE-FG02-86BR45271 (X.W.) and D. Beardall and C. A. Wight for assistance in obtaining IR spectra, A. Arif for the search of the Cambridge Crystallographic Database, and J. M. Mayer (U. Washington) for helpful discussions.

Footnotes

† Crystal data for a $0.2 \times 0.4 \times 0.4 \text{ mm}$ crystal of $\alpha\text{-}[\text{Ni}(\text{C}_5\text{Me}_5)_2]^+[\text{HTCNQF}_4]^-$, $\text{C}_{32}\text{H}_{31}\text{F}_4\text{N}_4\text{Ni}$, $M = 606.32$, orthorhombic space group $P2_12_12_1$ (no. 19); $a = 10.888(1)$, $b = 16.341(1)$, $c = 16.861(2) \text{ \AA}$, $U = 3000.0(3) \text{ \AA}^3$, $Z = 4$, $D_c = 1.342 \text{ Mg m}^{-3}$, $\mu = 0.699 \text{ cm}^{-1}$, $T = 296 \text{ }^\circ\text{C}$. 2882 measured reflections, 2702 unique reflections, 2137 with $I > 3\sigma(I)$ used for refinement. $R(F) = 4.27\%$. All atoms were refined anisotropically with the exception of the carbon atoms in the phenyl ring which were refined isotropically to conserve data. Hydrogen atom H(27A) was located from the difference map and refined with idealized thermal parameters. All other hydrogen atoms were treated as idealized contributions. Atomic coordinates, bond lengths, bond angles and thermal parameters have been deposited at the Cambridge Crystallographic Data Centre (CCDC). See Information for Authors, Issue No. 1. Any request to

the CCDC for this material should quote the full literature citation and the reference number 182/152.

‡ The reaction of $[\text{Ni}(\text{C}_5\text{Me}_5)_2]$ and TCNQF_4 (2:1) in MeCN forms $\{[\text{Ni}(\text{C}_5\text{Me}_5)_2]^+\}_2[\text{TCNQF}_4]^{2-}$ with $\nu(\text{CN})$ at 2167s and 2131s cm^{-1} characteristic of unbound $[\text{TCNQF}_4]^{2-}$.^{6b}

§ A potential H^+ source might be the disproportionation of $[\text{Ni}^{\text{III}}(\text{C}_5\text{Me}_5)_2]^+$ to $[\text{Ni}^{\text{II}}(\text{C}_5\text{Me}_5)_2]$ and $[\text{Ni}^{\text{IV}}(\text{C}_5\text{Me}_5)(\text{C}_5\text{Me}_4)(=\text{CH}_2)]^+$ + H^+ as reported for $[\text{Ru}^{\text{III}}(\text{C}_5\text{Me}_5)_2]^+$ ^{17a} and $[\text{Rh}^{\text{III}}\text{Cp}(\text{C}_5\text{Me}_5)]^+$.^{17b}

¶ The homolytic C–H bond strength is estimated to be 74 kcal mol^{-1} ($\text{cal} = 4.184 \text{ J}$) using the method developed by Bordwell *et al.* (see footnote ||).

|| This is 16 kcal mol^{-1} weaker than that reported for $\text{H}_2\text{C}(\text{CN})_2$,^{18b} but comparable to those reported for 4- $\text{RC}_6\text{H}_4\text{CH}(\text{CN})_2$.^{18c} It is, however, 18 kcal mol^{-1} less than that of thf,^{18d} the putative hydrogen source. The MeCN reduction potential (0.02 V vs. SCE) for $[\text{TCNQF}_4]^{1-}$ – $[\text{TCNQF}_4]^{2-}$ is -0.40 V vs. ferrocene–ferrocenium in Me_2SO and since $\text{p}K_{\text{a}}$ values for Me_2SO are unavailable, the computed value¹⁵ is used. The comparable value for $[\text{HTCNQ}]^-$ is 69 kcal mol^{-1} .

References

- G. A. Candela, L. J. Swartzendruber, J. S. Miller and M. J. Rice, *J. Am. Chem. Soc.*, 1979, **101**, 2755.
- J. S. Miller, J. C. Calabrese, H. Rommelmann, S. R. Chittipeddi, J. H. Zhang, W. M. Reiff and A. J. Epstein, *J. Am. Chem. Soc.*, 1987, **109**, 769.
- J. S. Miller and A. J. Epstein, *Adv. Chem. Ser.*, 1995, **245**, 161; D. Gatteschi, *Adv. Mater.*, 1994, **6**, 635. O. Kahn, *Molecular Magnetism*, VCH, New York, 1993; J. S. Miller and A. J. Epstein, *Chem. Eng. News*, 1995, **73**(40), 30.
- J. S. Miller and A. J. Epstein, *Angew. Chem., Int. Ed. Engl.*, 1994, **33**, 385; *Angew. Chem.*, 1994, **106**, 399.
- R. C. Wheland and E. L. Martin, *J. Org. Chem.*, 1975, **40**, 3101.
- (a) J. S. Miller, J. H. Zhang and W. M. Reiff, *Inorg. Chem.*, 1987, **26**, 600; (b) D. A. Dixon, J. C. Calabrese and J. S. Miller, *J. Phys. Chem.*, 1989, **93**, 2284; (c) J. S. Miller, unpublished work. These are isomorphous to $\{[\text{Fe}(\text{C}_5\text{Me}_5)_2]^+\}_2[\text{TCNQF}_4]^{2-}$ [J. S. Miller, J. H. Zhang, W. M. Reiff, L. D. Preston, A. H. Reis, Jr. E. Gerbert, M. Extine, J. Troup and M. D. Ward, *J. Phys. Chem.*, 1987, **91**, 4344]; (d) M. D. Ward and D. C. Johnson, *Inorg. Chem.*, 1987, **26**, 4213; (e) D. Stein, H. Sitzmann, R. Boese, E. Dormann and H. Winter, *J. Organomet. Chem.*, 1991, **412**, 143; (f) D. Stein, H. Sitzmann and R. Boese, *J. Organomet. Chem.*, 1991, **421**, 275.
- J. L. Robbins, N. Edelstein, B. Spencer and J. C. Smart, *J. Am. Chem. Soc.*, 1982, **104**, 1882.
- C. Vazquez, J. C. Calabrese, D. A. Dixon and J. S. Miller, *J. Org. Chem.*, 1993, **58**, 65.
- P. Seiler and J. D. Dunitz, *Acta Crystallogr., Sect. B*, 1980, **36**, 2255.
- W. H. Wan, X. Liu, G. M. Sweeny and W. E. Broderick, *J. Am. Chem. Soc.*, 1995, **117**, 9580.
- Over 550 TCNQ-based structures have been reported in the Cambridge Crystallographic Database version 5.10 (Oct. 1995).
- E. R. C. S. Hotta and H. Kobayashi, *Synth. Met.*, 1994, **66**, 117.
- CRC Handbook of Chemistry and Physics*, ed. R. C. Weast, 57th edn., Boca Raton, FL, pp. D-178.
- (a) *Aldrich Library of Infrared Spectra*, 2nd edn., ed. C. J. Pouchert, 1975, pp. 446; (b) D. S. Acker and W. R. Hertler, *J. Am. Chem. Soc.*, 1962, **84**, 3370; $\text{p}K_{\text{a}1}$ and $\text{p}K_{\text{a}2}$ values are computed to be 7.1 and 10.3 for H_2TCNQ ;¹⁵ (c) W. R. Hertler, H. D. Hartzler, D. S. Acker and D. E. Benson, *J. Am. Chem. Soc.*, 1962, **84**, 3387.
- T. Akutagawa and G. Saito, *Bull. Chem. Soc. Jpn.*, 1995, **68**, 1753.
- J. S. Miller and D. A. Dixon, *Science*, 1987, **235**, 871; D. A. Dixon, J. C. Calabrese and J. S. Miller, *J. Phys. Chem.*, 1988, **93**, 2284.
- (a) U. Kolle and J. Grub, *J. Organomet. Chem.*, 1985, **289**, 133; (b) J. A. Miguel-Garcia, H. Adams, N. A. Bailey and P. M. Maitlis, *J. Chem. Soc., Dalton Trans.*, 1992, 131.
- (a) F. G. Bordwell, J.-P. Cheng, G.-Z. Ji, A. V. Satish and X. Zhang, *J. Am. Chem. Soc.*, 1991, **113**, 9790; (b) X. J. Zhang and F. G. Bordwell, *Phys. Org. Chem.*, 1994, **7**, 751; (c) F. G. Bordwell, X. Zhang, A. V. Satish and J.-P. Cheng, *J. Am. Chem. Soc.*, 1994, **116**, 6605; (d) *Lange's Handbook of Chemistry*, ed. J. A. Dean, 14th edn., McGraw-Hill, New York, p. 4.29.

Received, 7th June 1996; Com. 6/03993F