



New NLO Stilbene Derivatives Bearing Phosphonate Ester Electron-Withdrawing Groups

Kevin D. Belfield,* Chandrasekhar Chinna and Katherine J. Schafer

Department of Chemistry, University of Detroit Mercy, Detroit, MI 48219

Abstract: The synthesis and characterization of a new class of electron donor-acceptor substituted stilbenes bearing a phosphonate ester as the electron-withdrawing functionality is described. Phosphorylation of aromatic rings was accomplished using Ni-catalyzed Arbuzov reactions, while Pd-catalyzed Heck-type coupling reactions were employed to construct the stilbene derivatives. Through determination of an electro-optic coefficient (r_{33}), it was demonstrated that the phosphonate ester group is effective as an electron-withdrawing group for stilbene-based second-order NLO materials.

© 1997 Elsevier Science Ltd.

INTRODUCTION

The photorefractive effect, found in materials that are both photoconductive and have nonlinear optical properties, is avidly being pursued for optical processing applications. When a photorefractive material is illuminated with light of nonuniform intensity, in the presence of an applied electric field, charges are photogenerated and subsequently transported and trapped at defects. This results in a nonuniform space-charge distribution, affording a refractive index distribution which can be modulated through the electro-optic effect. A phase grating is then created which can diffract light, affording a hologram.¹ Photorefractivity, thus, holds great potential in holographic optical data storage and processing, as well as frequency doubling of laser light.

In order to manifest the photorefractive effect, it is thought that these polymers must contain photocharge generating (CG) and transporting (CT) functionality, charge trapping sites, and nonlinear optical (NLO) chromophores. A number of systems have been reported in which a polymer possessing one of the requisite functionalities, e.g., covalently attached NLO chromophores, is doped with the others, e.g., CG and CT dopants (see, e.g., references 1-5). With the pressing technological demand for more efficient photorefractive and electro-optic materials, it is clear that new types of materials and new synthetic approaches are needed.

The phosphonate ester group is a strong electron-withdrawing functionality.⁶ An aniline derivative bearing a phosphonate ester was recently reported to exhibit second-order nonlinear optical properties comparable to the 4-nitroaniline NLO reference.⁶ Several stilbene derivatives displaying NLO properties are known but there have been no reports utilizing a phosphonate ester as an electron-withdrawing group for this purpose. Herein, we report the straightforward synthesis and characterization of a new class of electron donor-acceptor substituted stilbene derivatives bearing phosphonate groups (5 and 6). A multifunctional carbazole derivative (5), bearing two NLO moieties, was prepared, the carbazole core is intended to serve as the charge transporter.

EXPERIMENTAL

Materials. CH_2Cl_2 , hexanes, Et_2O , EtOAc , triethylphosphite, ethylene carbonate, Et_3N , DMF, THF, and toluene were distilled before use. EtOH was dried over 4 Å molecular sieves. 4-Bromo-N,N-dimethylaniline was recrystallized before use. 4-Bromoacetophenone, NaBH_4 , NaH , 3,6-dibromocarbazole, tri-*o*-tolylphosphine, $\text{Pd}(\text{OAc})_2$, NiCl_2 , and fused KHSO_4 were used as received from commercial suppliers.

Measurements. ^1H NMR spectra were recorded on a Bruker AM-300 spectrometer. UV-visible measurements were secured using a Hewlett-Packard model 8452A diode array spectrophotometer. High and low resolution mass spectra were obtained using JEOL model SX102A and AX505H mass spectrometers, respectively. 3-Nitrobenzyl alcohol doped with NaI was used as the matrix for fast atom bombardment (FAB) measurements. NH_3 was employed as reagent gas for chemical ionization (CI) measurements.

Synthesis of 3,6-bis(diethyl 4-phosphonatestyryl)carbazole (5). To a solution of N-(2-hydroxyethyl)-3,6-dibromocarbazole (**4**, 0.2 g, 0.54 mmol) in DMF was added $\text{Pd}(\text{OAc})_2$ (0.008 g, 0.036 mmol), tri-*o*-tolylphosphine (0.021 g, 0.07 mmol), Et_3N (0.253 g, 2.5 mmol), 4-vinylbenzenephosphonic acid diethyl ester (**3**, 0.36 g, 1.4 mmol). The yellow reaction mixture was stirred at 60 °C for 12 h. The solvent was removed, and the mixture was poured into water and extracted in CH_2Cl_2 . The crude product was purified on a silica gel column (1:20 hexanes/ EtOAc), resulting in a bright yellow solid (44% yield). ^1H NMR (300 MHz, CDCl_3): δ 1.36 (t, 12H, $-\text{OCR}_2\text{CH}_3$), 1.98 (s, 1H, $-\text{OH}$), 4.00–4.20 (m, 10H, $-\text{OCH}_2\text{CR}_3$ and $\text{N}-\text{CH}_2$), 4.50 (t, 2H, $\text{O}-\text{CH}_2$), 7.12, 7.17, 7.40, 7.45 (dd, 4H, *trans*-stilbene $-\text{CH}=\text{CH}-$), 7.48 (d, 2H, C1, C8 carbazole ArH), 7.64 (m, 6H, ArH *ortho* to $\text{C}=\text{C}$ and C2, C7 carbazole ArH), 7.78 (dd, 4H, *ortho* to $\text{P}(\text{O})(\text{OEt})_2$), 8.27 (s, 2H, C4, C5 carbazole ArH). High resolution MS (FAB, $[\text{M}+\text{Na}]$): calc 710.2410; actual: 710.2436. UV-vis: $\lambda_{\text{max}} = 340$ nm.


Synthesis of 4-diethyl 4'-N,N-dimethylaminostilbenephosphonate (6). 4-Bromo-N,N-dimethylaniline (0.64 g, 3.2 mmol), **3** (0.6 g, 2.64 mmol), $\text{Pd}(\text{OAc})_2$ (5.9 mg, 2.64×10^{-2} mmol), tri-*o*-tolylphosphine (16 mg, 5.28×10^{-2} mmol) and Et_3N (0.735 g, 5.28 mmol) were combined in a screw cap vial and heated to 100 °C for 12 h. The reaction mixture was cooled to room temperature, dissolved in acetonitrile, passed through a silica gel plug, washed with sat. NaCl, dried over MgSO_4 , concentrated, and washed with hexane, resulting in a fluorescent yellow solid (70% yield). ^1H NMR (300 MHz, CDCl_3): δ 1.36 (t, 6H, $-\text{OCR}_2\text{CH}_3$), 3.09 (s, 6H, $-\text{NCH}_3$), 4.15 (m, 4H, $-\text{OCH}_2\text{CR}_3$), 6.78 (m, 2H, ArH *ortho* to N), 6.92 and 7.16 (dd, 2H, *trans* stilbene $-\text{CH}=\text{CH}-$), 7.45 (d, 2H, ArH *meta* to N), 7.60 (m, 2H, ArH *meta* to $\text{P}(\text{O})(\text{OEt})_2$), 7.75 (dd, 2H, ArH *ortho* to $\text{P}(\text{O})(\text{OEt})_2$). High resolution MS (EI, 70 eV): calc 359.1650; actual 359.1644. UV-vis: $\lambda_{\text{max}} = 320$ nm.

RESULTS AND DISCUSSION

4-Vinylbenzenephosphonic acid diethyl ester (**3**) was prepared in three steps according to a previously reported procedure illustrated in Scheme 1, in 31% overall yield.^{7,8} This sequence involved a NiCl_2 -mediated Arbuzov-type reaction, reduction with NaBH_4 , and elimination over KHSO_4 . Hydroxyethylation of 3,6-dibromocarbazole was conducted with ethylene carbonate, by first forming the amine anion with NaH, affording N-(2-hydroxyethyl)-3,6-dibromocarbazole (**4**) in 80% yield.⁹

Pd-catalyzed Heck-type cross-coupling reactions¹⁰ were conducted on N-(2-hydroxyethyl)-3,6-dibromocarbazole (**4**) and 4-bromo-N,N-dimethylaniline, as shown in Schemes 2 and 3, respectively. The Heck reaction between **3** and **4** was carried out with $\text{Pd}(\text{OAc})_2$, tri-*o*-tolylphosphine, and Et_3N in DMF at 60 °C. 3,6-Bis(diethyl 4-phosphonatestyryl)carbazole (**5**) was isolated, and characterized by ^1H NMR and high resolution MS (FAB), confirming formation of the desired compound. FAB MS analysis showed $[\text{M}+\text{H}]^+ = 688$ and $[\text{M}+\text{Na}]^+ = 710$, high resolution FAB MS indicated $[\text{M}+\text{Na}]^+ = 710.2436$ (calc. 710.2410). NMR

chromophores are efficiently incorporated into one multifunctional unit. Furthermore, it was demonstrated that the phosphonate ester group is effective as an electron-withdrawing group for second-order NLO organic materials.

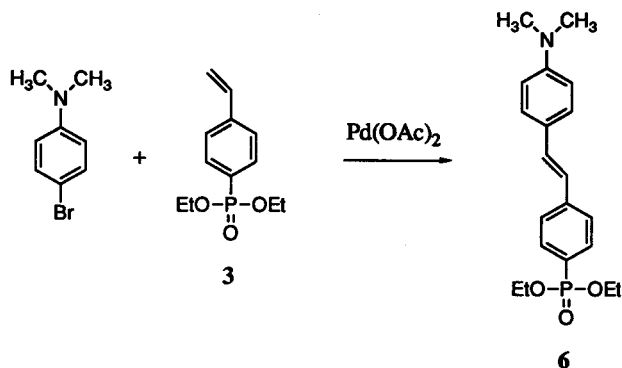

Scheme 3

ACKNOWLEDGMENTS

Financial support from the University of Detroit Mercy, College of Engineering and Science Research Initiation Program is acknowledged. The authors gratefully acknowledge Dr. Andrew Tyler of Harvard University for MS analyses and Dr. Richard Vaia of the USAF Wright Laboratories for electro-optic characterization. The Harvard University Department of Chemistry and Chemical Biology Mass Spectrometry Facility is supported by grants from NSF (CHE-900043) and NIH (SIO-RR06716).

REFERENCES AND NOTES

1. Moerner, W. E.; Silence, S. M. *Chem. Rev.* **1994**, *94*, 127.
2. Schildkraut, J. S. *Appl. Phys. Lett.* **1991**, *58*, 340.
3. Moerner, W. E. *Nature* **1994**, *371*, 475.
4. Meerholz, K.; Volodin, B. L.; Sandalphon; Kippelen, B.; Peyghambarian, N. *Nature* **1994**, *371*, 497.
5. Zobel, O.; Eckl, M.; Stroehriegl, P.; Haarer, D. *Adv. Mater.* **1995**, *7*, 911.
6. Hutchings, M. G.; Gordon, P. F.; Duggan, P. J.; Ledoux, I.; Puccetti, G.; Zyss, J. *Tetrahedron Lett.* **1994**, *35*, 9073.
7. Zhuang, H.; Pearce, E. M.; Kwei, T. K. *Macromolecules* **1994**, *27*, 6398.
8. Hartmann, M.; Hiplar, U.-CH.; Carlsohn, H. *Acta Polym.* **1980**, *31*, 165.
9. ^1H NMR (300 MHz, CDCl_3): δ 1.28 (s, 1H, OH), 4.00-4.10 (m, 2H, CH_2N), and 4.40-4.50 (m, 2H, CH_2O), 7.30-7.85 (m, 4H, ArH), 8.24 (s, 2H, C4, C5 ArH).
10. Belfield, K. D.; Chinna, C.; Najjar, O.; Sriram, S. *Polym. Preprints* **1997**, *38*(1), 203.
11. Poling temperature = 95 °C, $d_{\text{applied}} = 77 \text{ V}/\mu\text{m}$, $\lambda_{\text{measured}} = 676 \text{ nm}$.
12. Poling temperature = 95 °C, $d_{\text{applied}} = 106 \text{ V}/\mu\text{m}$, $\lambda_{\text{measured}} = 780 \text{ nm}$.

(Received in USA 24 June 1997; accepted 2 July 1997)