

## Production of Ethylene and Propylene by the Vapor-phase Catalytic Oxidative Dehydrogenation of Butane with Carbonyl Sulfide


Masamichi AKIMOTO,\* Takashi SAKATANI, and Etsuro ECHIGOYA

Department of Chemical Engineering, Tokyo Institute of Technology, Ookayama, Meguro-ku, Tokyo 152

(Received May 24, 1983)

**Synopsis.** Ethylene and propylene were produced at high yields, additionally to butenes and butadiene, by the vapor-phase oxidative dehydrogenation of butane with COS over SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, MgO, and TiO<sub>2</sub> catalysts at 873–923 K. The results of kinetic and mechanistic studies indicate that ethylene and propylene are produced by the oxidative dehydrogenation through a homolytic mechanism followed by  $\beta$ -scission of the carbon-carbon bond.

Carbonyl sulfide undergoes catalytic decomposition by either of the following two reactions.<sup>1)</sup>



Since the dissociation by the first reaction evolves reactive sulfur atoms, many studies have been made on the use of COS as an oxidant for the oxidative dehydrogenation of lower paraffinic hydrocarbons and alkyl-substituted aromatics.<sup>2,3)</sup> Some mechanistic studies have also been reported.<sup>4,5)</sup> In our recent study on the vapor-phase oxidative dehydrogenation of ethylbenzene by COS over SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, MgO, and TiO<sub>2</sub> catalysts, we showed that the role of the metal oxide catalysts is to decompose COS to CO+S, the formed sulfur (maybe sulfur atom) then dehydrogenating ethylbenzene in gaseous phase.<sup>5)</sup> We also showed that in addition to the thermocatalytic mechanism proposed by Haas and Khalafalla<sup>1)</sup> COS is decomposed to CO+S by the action of the reduction sites.<sup>5)</sup> In the present paper, we report the production of ethylene and propylene by the vapor-phase catalytic oxidative dehydrogenation of butane with COS and discuss the mechanism of the formation of these two olefins. The catalytic oxidative dehydrogenation of ethane, propane, and isobutane with COS has been reported.<sup>3,4)</sup> However, no studies have been reported on the catalytic oxidative dehydrogenation of butane with COS and hence no results have been reported of the formation of ethylene and propylene by the catalytic oxidative dehydrogenation with COS.

### Experimental

Vapor-phase catalytic oxidative dehydrogenation of hydrocarbons was carried out using a conventional flow fixed-

bed reactor under atmospheric pressure. The shape of reactor and method of reaction were the same as those in our previous paper.<sup>5)</sup> Purchased COS of greater than 97.5% purity and research grade paraffinic hydrocarbons (purity > 99%) were used without further purification. The catalysts (32–60 mesh) were prepared by the calcination of their corresponding metal hydroxides at 1073 K (873 K for TiO<sub>2</sub>) in air for 5 h. The surface areas determined by the conventional B.E.T. method were 167 m<sup>2</sup> g<sup>-1</sup> (SiO<sub>2</sub>), 178 m<sup>2</sup> g<sup>-1</sup> (Al<sub>2</sub>O<sub>3</sub>), 40 m<sup>2</sup> g<sup>-1</sup> (MgO), and 48 m<sup>2</sup> g<sup>-1</sup> (TiO<sub>2</sub>), respectively. The gaseous reaction products (paraffins, olefins, COS, CO, CO<sub>2</sub>, and H<sub>2</sub>S) were analyzed by gas chromatography using propylene carbonate (40 wt% on C-22, 17.0 m, room temperature), Porapak R (2.0 m, 363 K), and molecular sieve 13X (1.5 m, room temperature) as separating columns. Carbon disulfide was not analyzed.


### Results and Discussion

Table 1 summarizes the catalytic results obtained in the oxidative dehydrogenation of butane with COS at 873 K. No reaction took place when the mixture of butane and N<sub>2</sub> (butane 30.0 vol%) was fed over these four metal oxide catalysts at 873 K. However, such olefins as ethylene and propylene were produced additionally to butenes and butadiene with an accompanying formation of H<sub>2</sub>S when COS was added to the reactant mixture (Table 1. The yield of H<sub>2</sub>S is not presented for the sake of simplicity). Both the conversions of butane and COS decreased with time, due to the formation of carbonaceous materials at the surface of the catalysts,<sup>5)</sup> and leveled off after a preliminary period of 5 h. However, it is evident that Al<sub>2</sub>O<sub>3</sub> had the greatest catalytic activity at the initial stages of the reaction among these four metal oxide catalysts (Table 1, A). This greatest initial catalytic activity of Al<sub>2</sub>O<sub>3</sub> correlates its greatest concentration of the reduction sites reported in our previous paper<sup>5)</sup>, suggesting the preferential role of the reduction sites in the catalytic decomposition of COS to CO+S. For some catalytic results, the conversion of butane was greater than the yield of sulfur (= [conversion of COS] × [COS decomposition to CO+S]) (Table 1, SiO<sub>2</sub>-A,B, MgO-B, and TiO<sub>2</sub>-B). It seems that sulfur was also evolved by the catalytic decomposition of

TABLE 1. RESULTS OF THE CATALYTIC OXIDATIVE DEHYDROGENATION OF BUTANE BY COS<sup>a)</sup>

Catalyst	Conversion/%		COS decomposition to CO+S/%	Yield/%				Selectivity/%		
	n-C <sub>4</sub> H <sub>10</sub>	COS		C <sub>n</sub> H <sub>2n+2</sub> <sup>e)</sup>	C <sub>2</sub> H <sub>4</sub>	C <sub>3</sub> H <sub>6</sub>	C <sub>4</sub> olefins <sup>f)</sup>	C <sub>2</sub> H <sub>4</sub> +C <sub>3</sub> H <sub>6</sub>	olefins	
SiO <sub>2</sub>	(A <sup>b)</sup>	45.8	49.2	41.1	6.7	4.4	24.3	9.4	62.7	83.2
	(B <sup>c)</sup>	29.8	47.9	37.0	3.1	2.9	15.1	7.9	60.4	86.9
Al <sub>2</sub> O <sub>3</sub>	(A <sup>b)</sup>	53.4	96.5	97.7	4.8	2.2	14.3	15.5	30.9	59.9
	(B <sup>c)</sup>	26.6	42.0	61.4	2.7	1.4	7.3	13.5	32.7	83.5
MgO <sup>d)</sup>	(A <sup>b)</sup>	29.2	63.4	69.9	2.7	1.6	9.6	5.9	38.4	58.6
	(B <sup>c)</sup>	12.4	10.4	64.4	1.3	0.5	4.5	2.7	40.3	62.1
TiO <sub>2</sub>	(A <sup>b)</sup>	47.0	87.3	94.2	4.1	2.0	13.0	12.1	31.9	57.7
	(B <sup>c)</sup>	18.9	14.7	73.5	1.0	1.0	4.5	6.3	29.1	62.4

a) Reaction temperature: 873 K. Feed: 100 NTP cm<sup>3</sup> min<sup>-1</sup> (n-C<sub>4</sub>H<sub>10</sub> 30.0 vol%, COS 30.0 vol%, N<sub>2</sub> 40.0 vol%). Contact time: 11.2 g-catalyst·h·g-mol<sup>-1</sup>. b) At 10 min. c) At steady state. d) Contact time: 3.7 g-catalyst·h·g-mol<sup>-1</sup>. e) CH<sub>4</sub>+C<sub>2</sub>H<sub>6</sub>+C<sub>3</sub>H<sub>8</sub>. f) n-C<sub>4</sub>H<sub>8</sub>+C<sub>4</sub>H<sub>6</sub>.

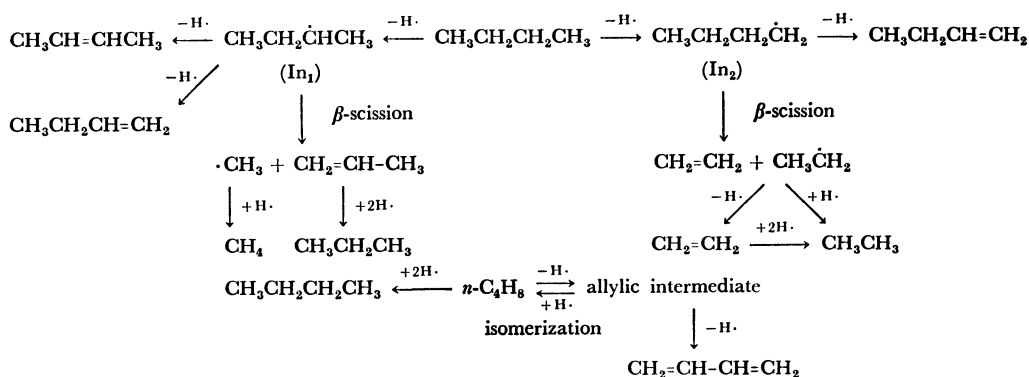

$\text{CS}_2$  formed during the catalytic oxidative dehydrogenation of butane by COS, as already seen in the reaction of ethylbenzene by COS.<sup>5)</sup>

The most important finding that Table 1 provides is that ethylene and propylene were produced additionally to butenes and butadiene in the catalytic oxidative dehydrogenation of butane by COS. The combined yield of ethylene and propylene was high, 18.0–28.7% (selectivity 60.4–62.7%) and 8.7–16.5% (30.9–32.7%), over  $\text{SiO}_2$  and  $\text{Al}_2\text{O}_3$  catalysts, respectively, and the total selectivity to olefins was also high, 83.2–86.9%, over  $\text{SiO}_2$  catalyst. It is to be noted that the yield of propylene was always greater than that of ethylene for all of the catalysts employed (Table 1). At 923 K, the combined yield of ethylene and propylene over  $\text{SiO}_2$  catalyst determined after a preliminary period of 10 min increased to 60.3% (selectivity 64.1%) whereas that of butenes and butadiene remained nearly unchanged, 8.2%. In contrast to the reaction of butane, no such olefins as ethylene and propylene were produced when *trans*-2-butene was similarly reacted at 873 K (e.g.,  $\text{SiO}_2$  catalyst, conversion 48.1%, total yield of butenes 33.2%, and yield of butadiene 10.0%).

In the oxidative dehydrogenation of butane by COS over  $\text{SiO}_2$  catalyst at 873 K, the reaction order in butane was unity and that in COS was 0.2–0.3. Assuming the first order kinetics for the oxidative dehydrogenation of paraffinic hydrocarbons, the rate constant for the oxidative dehydrogenation of ethane, propane, and isobutane by COS over  $\text{SiO}_2$  catalyst was determined at 873 K using an integral reactor (Table 2). The rate constant  $k$  for the paraffinic hydrocarbons follows the order: ethane < propane < isobutane. The order of the reactivity of these hydrocarbons is much more obvious when the value of the rate constant  $k$  is normalized to one most-reactive hydrogen ( $k'$ , Table 2). That is, the reactivity of hydrogen for the oxidative dehydrogenation by sulfur follows the order: primary hydrogen < secondary hydrogen < tertiary hydrogen. This order of the reactivity of hydrogen correlates the value of the C–H bond dissociation energy (Table 2). As reported previously by Haag and Miale,<sup>4)</sup> we may thus conclude that the oxidative dehydrogenation of these paraffinic hydrocarbons by sulfur proceeds through a homolytic mechanism. On the other hand, no formation of olefins other than isobutene in the reaction of isobutane (Table 2) indicates that no  $\alpha$ -scission of the carbon-carbon bond took place during the oxidative dehydrogenation of paraffinic hydrocarbons by COS at 873 K.

TABLE 2. SUMMARY OF THE RATE CONSTANTS FOR THE CATALYTIC OXIDATIVE DEHYDROGENATION OF LOWER PARAFFINIC HYDROCARBONS BY COS<sup>a)</sup>

Paraffin	Number and type of hydrogen <sup>b)</sup>	B.D.E. <sup>c)</sup> kJ mol <sup>-1</sup>	Conversion %	$k^d)$ $\times 10^3$	$k'^e)$ $\times 10^3$
$\text{C}_2\text{H}_6$	6 p	410	22.3	2.25	0.38
$\text{C}_3\text{H}_8$	2 s	395	23.9	2.44	1.22
<i>i</i> - $\text{C}_4\text{H}_{10}$	1 t	380	24.9	2.56	2.56

a) Catalyst:  $\text{SiO}_2$ . Reaction temperature: 873 K. Feed: 100 NTP cm<sup>3</sup> min<sup>-1</sup> (paraffin 30.0 vol%, COS 30.0 vol%,  $\text{N}_2$  40.0 vol%). Contact time: 11.2 g-catalyst · h · g-mol<sup>-1</sup>. Product:  $\text{C}_2\text{H}_6 \rightarrow \text{C}_2\text{H}_4$ ,  $\text{C}_3\text{H}_8 \rightarrow \text{C}_3\text{H}_6$ , *i*- $\text{C}_4\text{H}_{10} \rightarrow i\text{-C}_4\text{H}_8$ . b), c) For the weakest C–H bond. C–H bond dissociation energy (B.D.E.): Ref. 6. d) g-mol (g-catalyst · h · atm)<sup>-1</sup>. e) Normalized to one most-reactive hydrogen.

drogenation of paraffinic hydrocarbons by COS at 873 K.

Based on the above findings made in the present work, we propose the following reaction scheme for the oxidative dehydrogenation of butane by COS over these metal oxide catalysts. The oxidative dehydrogenation of butane by sulfur takes place mainly in gaseous phase and it proceeds more preferentially *via* an intermediate  $\text{In}_1$  than *via* the another  $\text{In}_2$ , as indicated by the relative reactivity of the hydrogens (Table 2). The greater yields of propylene than ethylene and no formation of these two olefins from *trans*-2-butene found in the present work (Table 1) support this reaction scheme. The hydrogenation of hydrocarbon species does not take place extensively as seen in the small values of the combined yield of methane, ethane, and propane (Table 1). The hydrogens used for the hydrogenations must have been supplied from  $\text{HS}_x$  (maybe  $x=1$  and/or 2). The mechanism of the formation of carbonyneous materials at the surface of the catalysts remains unknown.

## References

- 1) L. A. Haas and S. E. Khalafalla, *J. Catal.*, **30**, 451 (1973).
- 2) D. E. Boswell, U. S. Patent 3 399 243 (1968), Mobil Oil Corporation.
- 3) W. O. Haag and J. N. Miale, U. S. Patent 3 787 517 (1974), 3 821 278 (1974), and 3 875 252 (1975), Mobil Oil Corporation.
- 4) W. O. Haag and J. N. Miale, "Proc. 6th Intern. Congr. Catal.," Elsevier, London (1976), Vol. 1, p. 397.
- 5) M. Akimoto, K. Yamagami, and E. Echigoya, *Chem. Lett.*, **1982**, 479.
- 6) C. R. Noller, "Chemistry of Organic Compounds," 3rd ed, Saunders, Philadelphia (1965), p. 993.