

Photodegradative Surfactants: *p*-Dodecylbenzyltrimethylammonium Bromide as a Photodegradative Emulsifier for Microemulsion Polymerization

Yoshihiro Itoh,* Satoshi Horiuchi, and Kenji Yamamoto


Department of Functional Polymer Science, Faculty of Textile Science and Technology,
Shinshu University, 3-15-1 Tokida, Ueda 386-8567

(Received March 29, 2005; CL-050419)

A photodegradative surfactant, *p*-dodecylbenzyltrimethylammonium bromide, was used as an emulsifier for micro-emulsion polymerization of methyl methacrylate in water. The resulting polymer latex was coagulated during UV irradiation. The analysis of the centrifuged solid after irradiation indicated almost perfection of both recovery of the polymer and removal of surface-active species from it.

In emulsion polymerization, surfactants are essential for emulsification of monomer droplets and stabilization of latex particles, but they have drawbacks in latex applications such as reduced water-resistance and electrical insulation of coatings. A simple way to overcome these problems is emulsifier-free polymerization. In most cases, however, small or moderate amounts of additives (e.g., polymerizable emulsifiers) have been added,¹ and then “truly” surfactant-free polymers have been scarcely obtained. An alternative and promising approach involves the use of cleavable surfactants.² Yamamura et al.³ demonstrated that acid-hydrolyzable surfactants containing ketal and sulfonate groups lower the content of ionic species in the resulting polymer. Nuyken et al.⁴ reported that *p*-dodecylphenyldiazosulfonate can control the latex coagulation process simply by exposing the dispersion to UV irradiation.⁵

In this paper, we report that a photodegradative surfactant, *p*-dodecylbenzyltrimethylammonium bromide (C₁₂BA) (Scheme 1),⁶ can be used not only as an emulsifier for micro-emulsion polymerization of methyl methacrylate (MMA) but also as a useful “floculant” of latices that gives surfactant-free polymers.



Scheme 1.

Poly(MMA) (PMMA) latices were prepared according to the method of Ming et al.⁷ with some modification.⁸ The polymerization proceeded smoothly and the conversion went up to over 95%. The resulting transparent latex solution was stable over several weeks.

The latex solution became turbid after UV irradiation for 20 min, its turbidity reached to the maximum after 45 min, and then the polymer was partially precipitated (Figure 1).⁹ This clearly indicates that in the time range the conversion of C₁₂BA to a non-surfactant labilizes the latices, promoting their coagulation. By contrast, no apparent change was observed for the latices prepared with a non-degradative surfactant, hexadecyltrimethylammonium chloride, or a photodegradative one, hexade-

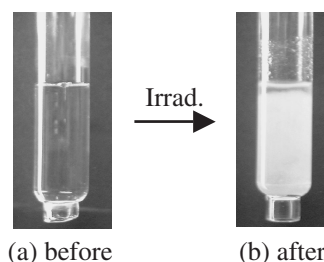


Figure 1. Photographs of PMMA/C₁₂BA latex solution (a) before and (b) after UV irradiation for 90 min.

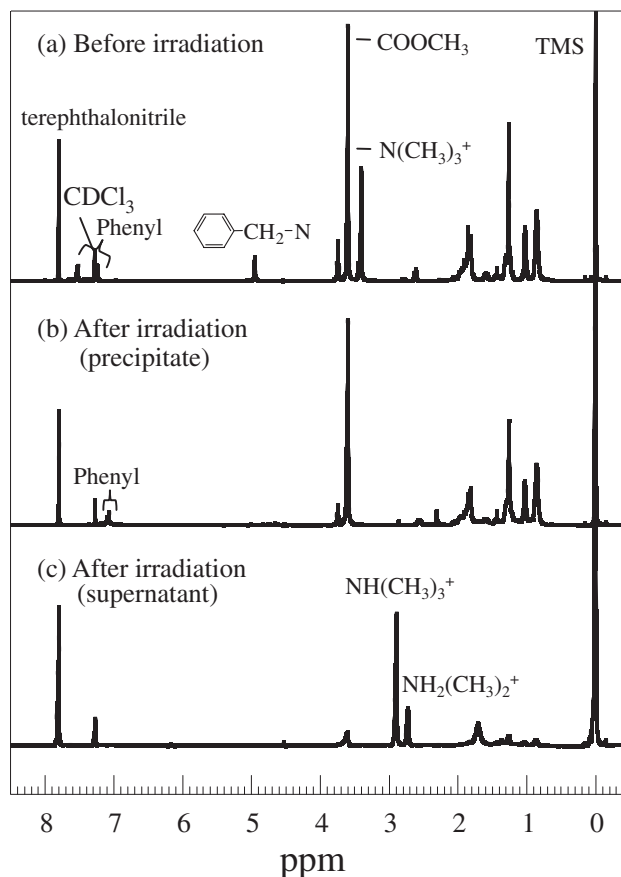


Figure 2. ¹H NMR spectra of PMMA/C₁₂BA lattices dissolved in CDCl₃ (a) before irradiation, (b) precipitate after irradiation, and (c) supernatant after irradiation: terephthalonitrile (δ 7.80 ppm) and tetramethylsilane (TMS: δ 0.00 ppm) were added as internal standards.

Table 1. Yields (%) of species in irradiated C₁₂BA/PMMA latex solution

Irrad. ^a	Fraction	PMMA ^b	C ₁₂ BA ^c	Hydrophobe ^d	Ion ^e
Before	Total	100	100	—	—
After	Total	100	4	86	93
	Precipitate	96	3	79	3
	Supernatant	4	0	0	68 ^f

^a[C₁₂BA] = 3 mM; [PMMA] = 29 mM; irradiation time, 90 min; products yields are based on the initial C₁₂BA concentration. ^bDetermined by peak area at 3.60 ppm. ^cDetermined by peak area at 3.42 ppm. ^dTotal yield of *p*-dodecylbenzyl alcohol, *p*-dodecyltoluene, and other minor products determined by peak area at 2.55 ppm. ^eTotal yield of dimethyl- and trimethylammonium bromides, determined by peak areas at 2.73 and 2.89 ppm, respectively. ^fPartially insoluble in CDCl₃.

cybenzyltrimethylammonium chloride.⁶ This is because the latices still hold a surface-activity after irradiation.

After irradiation for 90 min (almost 100% conversion), the suspended PMMA/C₁₂BA solutions were centrifuged and the precipitate and supernatant were analyzed by ¹H NMR spectroscopy.¹⁰ Figure 2 shows the spectra where some of assigned structures are indicated. Table 1 summarizes the quantitative data. As described below, the photoproducts of C₁₂BA obtained in the latex were the same as those in water. The signals of PMMA (δ 0.8–2.1 ppm and 3.60 ppm) were observed in the precipitate (Figure 2b), whereas those in the supernatant were little (Figure 2c). In fact, the recovery of the polymer, calculated from the area for the methyl proton at 3.60 ppm, was 96% of the total. Most of the signal of the *N*-methyl proton in C₁₂BA at 3.42 ppm disappeared both in the precipitate and supernatant, and those of the corresponding water-soluble products, dimethyl- and trimethylammonium bromides (2.73 ppm and 2.89 ppm, respectively) in the supernatant. In the same manner, the benzene protons in C₁₂BA (7.2–7.6 ppm) disappeared, and those of the corresponding hydrophobic products, *p*-dodecylbenzyl alcohol, *p*-dodecyltoluene, and others (7.0–7.2 ppm), appeared in the precipitate. From those data, the conversion of C₁₂BA was determined to be 96% and the removal of ionic species from the precipitate to be at least 94% (Table 1). Therefore, the photolysis of C₁₂BA not only can recover the polymer but also can remove ionic species from it almost perfectly. It should be noted that salting-out of the unirradiated PMMA/C₁₂BA latex with aqueous saturated NaCl solution recovered 87% of the total polymer and removed only 15% of C₁₂BA from it. Such a large difference in ionic content would affect the performances of the resulting polymers. Preliminary experiments showed that ionic dyes were little adsorbed on the film and solid of the “photo”-precipitated polymer, though, containing some photo-products. This might be indicative of improved water-resistance or electrical insulation of the polymer coating.¹¹

The photoreactivities of C₁₂BA in the latex and H₂O are compared in Table 2.¹² Although the conversion of C₁₂BA slightly decreased in the latex, the same products were obtained and their yields were not much different. It is thus concluded that C₁₂BA in the polymer latex is photodegraded similarly to that in water (quantum yield = 0.45).⁶

In conclusion, the irradiation of the PMMA/C₁₂BA latex can precipitate the polymer and can remove ionic species from it almost quantitatively, which may find various applications in

Table 2. Product yields (%) for photolysis of C₁₂BA in PMMA latex and H₂O^a

Sample	Conversion ^b	Alcohol	Alkyl	sec-A	tert-A
latex	85	7	26	32	4
C ₁₂ BA	95	9	23	37 ^c	57 ^c

^a[C₁₂BA] = 10 mM; [PMMA] = 26 mM; irradiation time, 60 min; products yields are based on the initial C₁₂BA concentration; Alcohol, *p*-dodecylbenzyl alcohol; Alkyl, *p*-dodecyltoluene; sec-A, dimethylammonium bromide; tert-A, trimethylammonium bromide. ^bConversion yield of C₁₂BA in %. ^cIrradiation time, 90 min.

polymer industry. For improvement of the reactivity and the sensitivity to a longer-wavelength light (>300 nm), the synthesis of different surfactants is in progress.

This work was supported by a Grant-in-Aid for 21st Century COE Program from the Ministry of Education, Science, Sports, and Culture of Japan.

References and Notes

- X. J. Xu, H. L. Goh, K. S. Siow, and L. M. Gan, *Langmuir*, **17**, 6077 (2001).
- M. Stjern Dahl, D. Lundberg, and K. Holmberg, *Surf. Sci. Ser.*, **114**, 317 (2003).
- S. Yamamura, M. Nakamura, K. Kasai, H. Satoh, and T. Takeda, *Yukagaku*, **40**, 1002 (1991).
- O. Nuyken, K. Meindl, A. Wokaun, and T. Mezger, *Macromol. Rep.*, **A32**, 447 (1995).
- Characterization of precipitates (polymers) such as surfactant content has not been reported.
- Y. Itoh, K. Yamamoto, and H. Shirai, *Chem. Lett.*, **32**, 8 (2003).
- W. Ming, F. N. Jones, and S. Fu, *Polym. Bull.*, **40**, 749 (1998).
- A typical polymerization procedure was as follows: To a mixture of 0.5 g of MMA, 0.6 g of C₁₂BA, and 45 g of water a 0.04 g of 2,2'-azobis(2-isobutylamidine) dihydrochloride in 5 g of water was added and heated to 60 °C under nitrogen atmosphere. Then 1 g of MMA was slowly added into the solution, which was kept at 60 °C for another 3.5 h. A portion of the resulting latex solution was lyophilized and weighed. The polymerization yield was 97%. The weight-average molecular weight of the obtained polymer was determined to be 80,000 by GPC.
- The diluted polymer latex solution ([C₁₂BA] = 3 mM) in a quartz tube (13 mm ϕ) was irradiated without deaeration at 25 °C with all light emitted from a 500-W high-pressure mercury lamp in a merry-go-round apparatus.
- Irradiated samples were prepared as follows: the suspended solutions were centrifuged and the precipitate was dissolved in CDCl₃ containing a known amount of terephthalonitrile as an internal standard (δ 7.80 ppm). The supernatant solution was lyophilized and then re-dissolved in the above CDCl₃ solution. Non-irradiated samples were obtained by direct lyophilization or salting-out with NaCl followed by dissolution in CDCl₃.
- Detailed characterization of the polymers is in progress.
- The latex composition was slightly different from the above case.