

Bimetallic Zn and Hf on silica catalysts for the conversion of ethanol to 1,3-butadiene

Trees De Baerdemaeker, Mathias Feyen, Ulrich Mueller, Bilge Yilmaz, Feng-Shou Xiao, Weiping Zhang, Toshiyuki Yokoi, Xinhe Bao, Hermann Gies, and Dirk E. De Vos

ACS Catal., **Just Accepted Manuscript** • DOI: 10.1021/acscatal.5b00376 • Publication Date (Web): 24 Apr 2015

Downloaded from <http://pubs.acs.org> on May 3, 2015

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.



Bimetallic Zn and Hf on silica catalysts for the conversion of ethanol to 1,3-butadiene

Trees De Baerdemaeker ^a, Mathias Feyen ^b, Ulrich Müller ^b, Bilge Yilmaz ^c, Feng-Shou Xiao ^d, Weiping Zhang ^e, Toshiyuki Yokoi ^f, Xinhe Bao ^g, Hermann Gies ^h and Dirk E. De Vos ^{a,*}

^a Centre for Surface Chemistry and Catalysis, KU Leuven, 3001, Leuven, Belgium; ^b Process Research and Chemical Engineering, BASF SE, 67056, Ludwigshafen, Germany; ^c Process Catalysts & Technologies, BASF Corporation, Iselin, New Jersey 08830, United States; ^d Zhejiang University, 310028, Hangzhou, China;

^e State Key Laboratory of Fine Chemicals, Dalian University of Technology, 116024, Dalian, China;

^f Chemical Resources Laboratory, Tokyo Institute of Technology, 226-8503, Yokohama, Japan; ^g State Key Laboratory of Catalysis, Dalian Institute of Chemical Physics, 116023, Dalian, China; ^h Institute of Geology, Mineralogy and Geophysics, Ruhr-University Bochum, 44780, Bochum, Germany

Corresponding author: dirk.devos@biw.kuleuven.be


Abstract: Silica supported catalysts for the conversion of ethanol to 1,3-butadiene were investigated. The combination of Hf(IV) and Zn(II) resulted in a stable, active and selective catalyst in which the Zn(II) effectively suppressed the dehydration activity of Hf(IV); the catalyst preparation method plays a crucial role. Using the crystalline Zn-silicate hemimorphite as an alternative Zn(II) source proved to be even more successful in suppressing ethanol dehydration.

Keywords: 1,3-butadiene - ethanol – zinc silicate – hemimorphite – heterogeneous catalysis – silica impregnation

1
2
3 1,3-Butadiene (BD) is a frequently used building block in polymer chemistry. It is typically obtained as a
4
5 by-product from steam cracking where ethene and propene are the main products. However, the recent
6
7 changes to the use of a lighter feedstock for steam cracking and the increased usage of shale gas as an
8
9 alternative source for ethene have resulted in a price increase for BD.¹ To meet the global demand for
10
11 BD, alternative synthesis routes that preferentially do not rely on fossil fuels are being investigated. One
12
13 of these routes that has received an increasing amount of attention over the past years is the conversion
14
15 of ethanol to BD.²⁻¹² This reaction, which is also known as the Lebedev process, has already been
16
17 described in the early twentieth century using mixed metal oxides as catalysts, typically MgO/SiO₂ or
18
19 ZnO/Al₂O₃.¹³⁻¹⁶

20
21
22
23
24
25 The mechanism of the multistep reaction of ethanol to butadiene is complex and has not yet been fully
26
27 elucidated, in spite of large research efforts, e.g., in a recent publication by Chierogato et al.¹⁷
28
29 Nevertheless, there is a consensus on a number of key steps (Scheme 1): (1) the dehydrogenation of
30
31 ethanol to acetaldehyde catalyzed by basic or redox sites, (2) the aldol condensation of acetaldehyde, (3)
32
33 dehydration and a Meerwein-Ponndorf-Verley type reduction on basic or Lewis acid sites resulting in
34
35 crotyl alcohol, and (4) a final dehydration step to 1,3-BD, possibly on weak acid sites.^{4, 9, 18-22} The
36
37 acetaldol and crotonaldehyde products are not always observed, presumably due to their short lifetime
38
39 under reaction conditions.⁸ On the other hand, ethene and diethylether are frequently detected as side
40
41 products, resulting from reactions promoted by Brønsted acid sites.^{8, 23} The different types of catalysts
42
43 used for this reaction have recently been reviewed by Makshina et al.¹⁶ For instance, MgO/SiO₂ systems,
44
45 as studied by Ohnishi et al.,²⁴ or by Kvisle et al.,¹⁸ are a well-studied class of catalysts, which, for a long
46
47 time, had the highest reported butadiene selectivities (up to 87 %).²⁴ However, the compositional
48
49 optimum seems narrow and catalyst stability is uncertain. Considerable improvements were realized by
50
51 adding Ni or Ag to the catalyst to facilitate the dehydrogenation.^{5, 12, 25} Such recent work shows that
52
53 correct tuning of the transition metal composition allows significant progress in comparison with the
54
55
56
57
58
59
60

binary MgO/SiO₂ systems. A related type of catalyst comprises a combination of transition metal oxides deposited on a silica support without the use of MgO. This approach has for instance been investigated by Jones et al.,⁴ where the highest selectivity to BD (67 % at 45 % ethanol conversion) was obtained using a trimetallic combination of Cu(II), Zr(IV) and Zn(II) (1 wt% each). In the present work, a fumed silica support was doped with different transition metal combinations; the catalytic function of each compound in the conversion of ethanol to butadiene was investigated, and the influence of the deposition method on catalyst performance was studied. Special attention was devoted to maximizing the butadiene effluent concentration and to minimizing the loss of ethanol to by-products from acid-catalyzed reactions like ethene and diethylether.

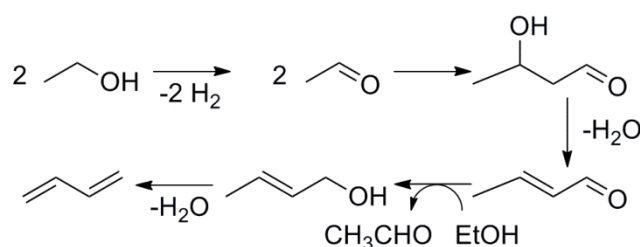

Scheme 1. Generally accepted overall scheme for the formation of BD from ethanol.

As a starting point, the trimetallic Cu(II)-Zn(II)-Zr(IV) system of Jones et al.⁴ was taken (Table 1, entry 1, Figure S1, S2). With this catalyst, a high selectivity of 61 % to BD at nearly full conversion was obtained, which remained stable after 10 h of reaction in spite of a small decrease in conversion. Unfortunately, this system still produces a significant amount of ethene (>10%) and related acid-catalyzed by-products. Therefore, Hf(IV) was chosen as a softer metal to replace Zr. This resulted in a much lower ethene production and an even higher selectivity to BD (Table 1, entry 2, Figure S3, S4, Table S1). By replacing ZrO(NO₃)₂·H₂O in the synthesis by HfCl₄, the counteranion of the metal precursor salt was simultaneously changed to chloride. To investigate the influence of the presence of chloride anions in the impregnation slurry, the Zr(IV)-containing system was prepared using ZrCl₄. This catalyst (Table 1, entry 3) shows a higher stability and BD selectivity and a lower selectivity to ethene compared to the Cl-free system

(Table 1, entry 1), indicating a beneficial effect of changing the metal source. However, the ethene production is still higher than in the case of HfCl₄, demonstrating the beneficial effect of the latter metal on decreasing acid catalyzed by-product formation. With increasing Hf(IV)-content of the catalysts (Table 1, entries 2, 4, 5) the BD selectivity increases further at the expense of the acetaldehyde production. Clearly, increasing the Hf(IV) content enhances the capacity of the catalyst for the aldol condensation step and increases the BD-productivity.

Table 1. Catalytic performance of trimetallic silica-supported catalysts. Catalytic results are shown after 0.5 h and 10 h reaction at 360°C preceded by a 3 h reaction period at 300°C using a feed rate of 0.21 g_{EtOH} g_{cat}⁻¹ h⁻¹. Catalysts were prepared using Cu(OAc)₂, Zn(NO₃)₂·6H₂O, ZrO(NO₃)₂·H₂O and HfCl₄ as metal precursors.

Catalyst ^a	TOS (h)	X _{EtOH} (%)	Selectivity (%) ^b									Yield _{BD} (%)	g _{BD} g _{cat} ⁻¹ h ⁻¹	BD (ppm)
			C ₂ ⁼	C ₃ ⁼	Ac.	BD	C ₄ ⁼	DEE	BuOH	BuO	Other			
1 Cu _{1.0} Zr _{1.0} Zn _{0.5}	0.5	98	16	2.8	5.8	61	6.6	2.3	0.49	<0.01	4.8	59.5	0.074	16500
	10	79	15	2.2	8.4	61	5.3	2.7	0.50	<0.01	5.3	48.0	0.060	13400
2 Cu _{1.0} Hf _{1.5} Zn _{0.5}	0.5	96	7.3	2.8	9.8	65	6.0	1.3	0.50	<0.01	7.9	61.8	0.077	17200
	10	95	6.5	2.8	11	65	4.0	1.1	0.62	<0.01	8.7	61.9	0.077	17300
3 ^c Cu _{1.0} Zr _{1.5} Zn _{0.5}	0.5	96	9.5	2.4	7.9	66	5.3	2.1	0.41	<0.01	6.3	63.3	0.079	17600
	10	91	9.0	2.3	10	64	4.8	2.1	0.44	<0.01	7.3	58.4	0.073	16300
4 Cu _{1.0} Hf _{0.75} Zn _{0.5}	0.5	99	6.2	3.7	22	52	2.6	0.5	0.62	<0.01	12	51.8	0.065	14400
	10	96	5.1	3.4	29	46	2.2	0.4	0.36	<0.01	14	44.6	0.056	12400
5 Cu _{1.0} Hf _{3.0} Zn _{0.5}	0.5	99	7.9	3.4	2.6	72	6.4	1.0	0.28	0.27	6.4	71.6	0.090	19900
	10	99	7.2	3.1	4.2	71	5.5	1.1	0.30	0.16	7.2	71.1	0.089	19800

^aSubscript refers to the metal content (wt%). ^bSelectivity to ethene, propene, acetaldehyde, BD, butenes, diethylether, butanol, butanal and other condensation products, respectively. ^cPrepared with ZrCl₄.

To further investigate the role of each compound in the Cu(II)-Zn(II)-Hf(IV) system, mono- and bimetallic catalysts were prepared (Table 2, Figure S5). If Hf(IV) is the only compound deposited on the silica support (Table 2, entry 1), hardly any ethanol dehydrogenation takes place and ethene and diethylether are the main products, resulting from acid catalysis. Adding Cu(II) to the catalyst alters the selectivity entirely (Table 2, entry 2). In this case, there is sufficient dehydrogenation capacity to obtain a catalyst with all required functionalities for the synthesis of butadiene. The ethene and diethylether formation is correspondingly diminished but they are still produced in larger amounts than in the trimetallic system (Table 1, entry 5). Additionally, the stability of the catalyst is much lower than in the Zn(II)-containing

1
2
3 trimetallic system. On the other hand, deposition of only Zn(II) on the silica support results in a low
4 (<10%) selectivity to ethene and diethylether (Table 2, entry 3). A small amount of BD is formed but the
5 selectivity is low; most of the ethanol is converted to acetaldehyde without further condensation. This
6 clearly demonstrates the contribution of Zn(II) to the dehydrogenation capacity of the catalyst; unlike
7 Hf(IV), Zn(II) does not hydrolyze to form acid sites that give rise to large amounts of ethene or
8 diethylether. The combination of Zn, which strongly increases the ethanol dehydrogenation, and Hf(IV),
9 which catalyzes the subsequent aldol condensation finally results in a catalyst with a good BD selectivity
10 and a stable performance for many hours on stream (Table 2, entry 4, Table S1, entry 9). Remarkably, it
11 is important that Hf(IV) and Zn(II) are impregnated simultaneously on the same silica support: separate
12 impregnations of silica powders with these compounds, followed by physically mixing them together in a
13 mortar to obtain a catalyst with the same overall metal loading resulted in an inferior catalyst with lower
14 BD selectivities and a low stability (Table 2, entry 5). Clearly, both metals should be present in sufficient
15 proximity to each other in order to suppress the ethene and diethylether formation and to balance the
16 different catalytic functions resulting in BD formation.

Table 2. Catalytic performance of mono- and bimetallic silica-supported catalysts. Catalytic results are shown after 0.5 h and 10 h reaction at 360°C preceded by a 3 h reaction period at 300°C using a feed rate of $0.64 \text{ g}_{\text{EtOH}} \text{ g}_{\text{cat}}^{-1} \text{ h}^{-1}$. Catalysts were prepared using $\text{Cu}(\text{OAc})_2$, $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, and HfCl_4 as metal precursors.

Catalyst ^a	TOS (h)	X_{EtOH} (%)	Selectivity ^b										Yield _{BD} (%)	$g_{\text{BD}}g_{\text{cat}}^{-1} \text{ h}^{-1}$	BD (ppm)
			$\text{C}_2^=$	$\text{C}_3^=$	Ac.	BD	$\text{C}_4^=$	DEE	BuOH	BuO	Other				
1 Hf _{3.0}	0.5	48	82	0.1	1.0	0.4	0.1	17	<0.01	<0.01	0.0	0.2	0.001	48	
	10	43	82	0.0	0.6	0.1	0.1	17	<0.01	<0.01	0.0	0.0	<0.001	10	
2 ^c Cu _{1.0} Hf _{3.0}	0.5	99	29	2.2	3.2	49	7.7	5.3	0.27	<0.01	2.8	48.9	0.061	13600	
	10	75	52	1.0	5.1	25	3.0	12	0.17	<0.01	2.0	18.8	0.023	5200	
3 Zn _{0.5}	0.5	66	10	1.2	57	14	0.4	0.7	2.5	1.3	12	9.5	0.036	2640	
	10	67	7.5	1.0	62	12	0.2	0.6	2.6	1.2	13	7.6	0.029	2100	
4 Hf _{3.0} Zn _{0.5}	0.5	72	7.7	2.0	13	63	4.1	2.0	2.6	0.37	6.0	45.3	0.179	12600	
	10	68	7.0	1.9	15	60	4.0	1.9	3.0	0.50	6.5	41.0	0.154	11400	
5 ^d Hf _{3.0} Zn _{0.5}	0.5	60	26	1.5	21	36	5.1	5.4	0.32	1.5	2.9	21.6	0.081	6000	
	10	34	21	1.1	34	29	2.9	6.6	0.46	2.5	3.0	9.8	0.037	2700	

^aSubscript refers to the metal content (wt%). ^bSelectivity to ethene, propene, acetaldehyde, BD, butenes, diethylether, butanol, butanal and other condensation products, respectively. ^cFeed rate $0.21 \text{ g}_{\text{EtOH}} \text{ g}_{\text{cat}}^{-1} \text{ h}^{-1}$. ^dAs a 1:1 mixture of silica containing 6.0 wt% Hf and silica containing 1.0 wt% Zn.

1
2
3 To better understand the interaction between Hf(IV) and Zn(II), the zinc silicate hemimorphite (HM) was
4
5 used, both as support and as Zn(II)-source. Hemimorphite ($\text{Zn}_4\text{Si}_2\text{O}_7(\text{OH})_2\cdot\text{H}_2\text{O}$) is a zinc silicate which, for
6
7 instance, can be used to catalyze the addition of methanol to propyne, using Zn^{2+} ions with open
8
9 coordination sites at the outer surface.²⁶ In the conversion of ethanol to BD, it catalyzes the
10
11 dehydrogenation to acetaldehyde, but it hardly enables the subsequent reaction steps (Table 3, entry 1)
12
13 resulting in a similar performance as with the Zn(II)-on-silica catalyst (Table 2, entry 3). Using it as a
14
15 support for Hf(IV) barely improves the selectivity to BD but the ethene production is still strikingly low
16
17 (Table 3, entry 2). Remarkably, when HM is deposited onto silica, i.e. when it is used as a Zn(II) precursor
18
19 instead of the previously used $\text{Zn}(\text{NO}_3)_2\cdot 6\text{H}_2\text{O}$, the observed selectivities change entirely. In a first
20
21 experiment, the HM was contacted with a Hf(IV)-containing silica support under reflux conditions (Table
22
23 3, entry 3). This already decreased the accumulation of acetaldehyde in the product stream and resulted
24
25 in an increased butadiene selectivity, but it also increased the ethene formation. Using this method of
26
27 combining Hf(IV) and Zn(II) on silica, the ethanol dehydration could not be sufficiently suppressed. On
28
29 the other hand, simply contacting both compounds (HM, Hf(IV) deposited on SiO_2) in suspension at room
30
31 temperature largely suppresses the ethene formation ($\approx 5\%$ selectivity) and, depending on the precise
32
33 composition, results in a stable BD selectivity of 70 % at nearly full ethanol conversion (Table 3, entries 4-
34
35 6).
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table 3. Catalytic performance of HM-containing silica-supported catalysts (HM = hemimorphite). Catalytic results are shown after 0.5 h and 10 h reaction at 360°C preceded by a 3 h reaction period at 300°C using a feed rate of $0.64 \text{ g}_{\text{EtOH}} \text{ g}_{\text{cat}}^{-1} \text{ h}^{-1}$. Catalysts were prepared using HfCl_4 as metal precursor and HM as the sole Zn source.

Catalyst ^a	TOS (h)	X_{EtOH} (%)	Selectivity ^b										Yield _{BD} (%)	$\text{g}_{\text{BD}} \text{ g}_{\text{cat}}^{-1} \text{ h}^{-1}$	BD (ppm)
			C_2^-	C_3^-	Ac.	BD	C_4^-	DEE	BuOH	BuO	Other				
1 ^c HM	0.5	76.2	4.6	2.0	60	5.5	0.1	0.2	3.1	1.1	24	4.2	0.016	1170	
	10	78.3	3.9	1.6	62	4.3	0.1	0.2	3.3	0.95	24	3.4	0.013	950	
2 ^c $\text{Hf}_{3.0}$ on HM	0.5	75.6	4.3	1.4	60	12	0.2	0.6	3.2	1.1	18	8.7	0.033	2400	
	10	77.3	3.8	1.2	61	8.8	0.2	0.7	3.6	1.1	19	6.8	0.025	1900	
3 ^d $\text{Hf}_{3.2}\text{Zn}_{5.1}$	0.5	97.6	18	11	0.8	39	27	0.2	<0.01	0.45	4.6	37.5	0.141	10500	
	10	99.4	16	14	0.3	18	32	0.1	0.23	0.83	20	17.5	0.066	4900	
4 ^e $\text{Hf}_{3.2}\text{Zn}_{5.1}$	0.5	88.1	5.3	2.6	9.2	66	3.2	0.8	0.41	2.8	11	57.7	0.217	16100	
	10	90.6	4.1	2.5	11	61	3.3	0.9	0.79	3.3	13	55.3	0.208	15400	
5 ^e $\text{Hf}_{2.5}\text{Zn}_{16}$	0.5	99.2	5.8	3.6	4.0	71	3.8	0.7	0.42	2.5	8.1	70.2	0.264	19500	
	10	97.3	4.9	3.6	6.5	67	4.3	1.1	0.48	3.2	9.4	65.2	0.245	18200	
6 ^e $\text{Hf}_{3.0}\text{Zn}_{9.3}$	0.5	98.8	10	3.6	2.4	70	5.0	1.4	0.06	1.8	5.4	69.3	0.260	19300	
	10	98.6	7.5	3.3	3.3	69	5.2	1.3	0.26	2.3	7.4	68.4	0.257	19100	

^aSubscript refers to the metal content (wt%). ^bSelectivity to ethene, propene, acetaldehyde, BD, butenes, diethylether, butanol, butanal and other condensation products, respectively. ^cHM as support, no silica. ^dThe appropriate amount of Hf was first impregnated onto the silica support and then contacted with HM in suspension under reflux conditions for 3 h. ^eThe appropriate amount of Hf was first impregnated onto the silica support and then contacted with HM in suspension at room temperature for 0.5 h.

Characterization of the catalysts with FTIR using pyridine as probe molecule provided further insights into the catalyst performance (Table 4, Figure S6). The impregnation of Hf(IV) onto silica clearly introduced Brønsted acidity (Table 4, entry 1), but this was significantly suppressed by the presence of Zn(II) – either introduced as $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, or admixed using hemimorphite as the Zn(II) source (Table 4, entries 3, 7-9). Adding Cu(II) to the catalyst only had a minor influence on the amount and type of acid sites (Table 4, entries 3, 5). Catalysts consisting only of Zn^{2+} and silica (Table 4, entries 2, 6) show an almost negligible Brønsted acidity and correspondingly low ethene formation. While ZnO has been described by Tanabe as being amphoteric,²⁷ various studies have shown that in the interaction with alcohols, ZnO primarily acts as a basic material.²⁸⁻³⁰ For materials loaded with both Hf(IV) and Zn(II), it is therefore well conceivable that the Brønsted acidity generated by hydrolysis on Hf(IV), is neutralized by neighbouring O-Zn groups, either on well-dispersed ZnO, or as Si-O-Zn moieties at the hemimorphite surface. Remarkably, the mixture of Hf(IV) and Zn(II), impregnated separately onto silica (Table 4, entry

4) has a limited number of Brønsted acid sites but still produces a significant amount of ethene (26 % selectivity). This again demonstrates the significance of the impregnation procedure to balance not only the amounts, but also the proximity to one another of the different catalytic functions.

Table 4. Acid properties of selected catalysts determined via FTIR spectroscopy using pyridine as probe molecule. Catalytic data are given for comparison.

Entry	Catalyst	BAS ($\mu\text{mol/g}$) ^a	LAS ($\mu\text{mol/g}$) ^a	L/B	Y(BD,%)	S(BD,%)	S(C ₂ ,%)
1 ^b	Hf _{3,0}	5.0	47.3	9.4	0.2	0.4	82
2 ^b	Zn _{0,5}	<0.1	13.9	-	7.1	9.5	6.6
3 ^b	Hf _{3,0} Zn _{0,5}	2.0	67.9	34.4	45.3	63	7.7
4 ^{b,c}	Hf _{3,0} Zn _{0,5}	1.2	21.3	18.1	21.6	36	26
5 ^b	Cu _{1,0} Hf _{3,0} Zn _{0,5}	1.5	53.0	36.2	71.6	72	7.9
6 ^d	HM	<0.1	13.0	-	4.2	5.5	4.6
7 ^d	Hf _{3,2} Zn _{5,1}	0.7	40.6	54.5	57.7	66	5.3
8 ^d	Hf _{2,5} Zn ₁₆	<0.1	44.1	-	70.2	71	5.8
9 ^d	Hf _{3,0} Zn _{9,3}	<0.1	25.5	-	69.3	70	10

^aAmount of pyridine adsorbed on Brønsted acid sites (BAS) and Lewis acid sites (LAS) at 150°C as determined from the IR absorption band of chemisorbed pyridine. ^bFrom impregnation of the appropriate amount of Cu(OAc)₂, Zn(NO₃)₂·6H₂O and HfCl₄ on silica. ^cAs a 1:1 mixture of silica containing 6.0 wt% Hf and silica containing 1.0 wt% Zn. ^dThe appropriate amount of Hf was first impregnated onto the silica support and then contacted with HM in suspension at room temperature for 0.5h.

While suppression of Brønsted acidity is clearly beneficial for the BD selectivity, Lewis acid sites are needed both for the aldol condensation and for the Meerwein type reduction of the putative crotonaldehyde intermediate. For the ethanol dehydrogenation, Zn-O moieties are effective, but for the aldol reaction the Zn(II) centres are nearly inactive. In contrast, Hf(IV) is not only effective for the aldol condensation, but it is also well known to promote hydrogen transfer reactions in MPV reactions. In the latter, Hf(IV) is even more active than Zr(IV), which has at least partly been ascribed to the facile displacement of –OH groups on the Hf(IV) by incoming alcohol reactants, at least for MPV reactions in mild conditions.³¹

With the best HM-based catalysts of the present study, the ethene selectivity is 10% or even significantly lower. While hardly any Brønsted acidity could be detected on these materials using the pyridine probe method, it is probable that some of the water, produced during the reaction, causes a mild hydrolysis of

1
2
3 the Hf(IV). This generates Brønsted acidity under reaction conditions, which is the likely cause for the
4
5 observed, limited ethanol dehydration.
6

7
8 In summary, we demonstrated that bimetallic mixtures of Hf(IV)-Zn(II) and trimetallic mixtures of Cu(II)-
9
10 Hf(IV)-Zn(II) and Cu(II)-Zr(IV)-Zn(II) give remarkably active, selective and stable catalysts for the ethanol
11
12 to butadiene reaction. In these trimetallic catalysts, Cu(II) acts as a dehydrogenation catalyst. However,
13
14 the synthesis of bimetallic catalysts has shown that this function can also be performed by Zn(II), which,
15
16 in addition, also increases the stability of the catalysts. Hf(IV) is preferred over Zr(IV), especially in order
17
18 to avoid the competitive ethanol dehydration. Adding Zn(II) to the Hf(IV) containing catalyst is crucial to
19
20 obtain dehydrogenation capacity and to force the Hf(IV) into catalyzing the condensation of
21
22 acetaldehyde rather than the ethanol dehydration. In order to achieve this high BD selectivity, the
23
24 deposition method is crucial. The use of hemimorphite as Zn(II) source was particularly successful in
25
26 suppressing the ethene formation while simultaneously producing high concentrations of BD.
27
28
29
30

31 **Acknowledgement**

32
33
34
35 T.D.B. is grateful for a PhD fellowship from F.W.O. - Vlaanderen (Research Foundation Flanders). The
36
37 authors acknowledge the support from BASF SE under the INCOE framework. We thank Sabina Accardo
38
39 for technical assistance.
40
41

42
43 **Supporting information:** experimental procedures, SEM, EDX, EPR, FTIR characterization, TG analysis.

44
45 This information is available free of charge via the Internet at <http://pubs.acs.org/>.

51 **References**

- 52
53
54 (1) Angelici, C.; Weckhuysen, B. M.; Bruijninx, P. C. A. *ChemSusChem* **2013**, *6*, 1595-1641.
55
56 (2) Tsuchida, T.; Sakuma, S.; Takeguchi, T.; Ueda, W. *Ind. Eng. Chem. Res.* **2006**, *45*, 8634-8642.
57
58
59
60

- 1
2
3 (3) Tsuchida, T.; Kubo, J.; Yoshioka, T.; Sakuma, S.; Takeguchi, T.; Ueda, W. *J. Catal.* **2008**, *259*, 183-
4
5 189.
6
7
8 (4) Jones, M. D.; Keir, C. G.; Iulio, C. D.; Robertson, R. A. M.; Williams, C. V.; Apperley, D. C. *Catal. Sci.*
9
10 *Technol.* **2011**, *1*, 267-272.
11
12 (5) Makshina, E. V.; Janssens, W.; Sels, B. F.; Jacobs, P. A. *Catal. Today* **2012**, *198*, 338-344.
13
14 (6) Chae, H.-J.; Kim, T.-W.; Moon, Y.-K.; Kim, H.-K.; Jeong, K.-E.; Kim, C.-U.; Jeong, S.-Y. *Appl. Catal., B*
15
16 **2014**, *150–151*, 596-604.
17
18 (7) Ezinkwo, G. O.; Tretjakov, V. F.; Talyshinky, R. M.; Ilolov, A. M.; Mutombo, T. A. *Catal. Commun.*
19
20 **2014**, *43*, 207-212.
21
22 (8) Lewandowski, M.; Babu, G. S.; Vezzoli, M.; Jones, M. D.; Owen, R. E.; Mattia, D.; Plucinski, P.;
23
24 Mikolajska, E.; Ochendusko, A.; Apperley, D. C. *Catal. Commun.* **2014**, *49*, 25-28.
25
26 (9) Sushkevich, V. L.; Ivanova, I. I.; Tolborg, S.; Taarning, E. *J. Catal.* **2014**, *316*, 121-129.
27
28 (10) Ivanova, I. I.; Ordonskiy, V. V.; Sushkevich, V. L. WO2012/015340, 2012.
29
30 (11) Tret'yakov, V. F.; Talyshinskii, R. M.; Ilolov, A. M.; Maksimov, A. L.; Khadzhiev, S. N. *Pet. Chem.*
31
32 **2014**, *54*, 195-206.
33
34 (12) Janssens, W.; Makshina, E. V.; Vanelderen, P.; De Clippel, F.; Houthoofd, K.; Kerkhofs, S.;
35
36 Martens, J. A.; Jacobs, P. A.; Sels, B. F. *ChemSusChem* **2015**, *8*, 994-1008.
37
38 (13) Lebedev, S. GB331482, 1930.
39
40 (14) Lebedev, S. FR665917, 1929.
41
42 (15) Szukiewicz, W. US2357855, 1944.
43
44 (16) Makshina, E. V.; Dusselier, M.; Janssens, W.; Degreve, J.; Jacobs, P. A.; Sels, B. F. *Chem. Soc. Rev.*
45
46 **2014**, *43*, 7917-7953.
47
48 (17) Chieriegato, A.; Velasquez Ochoa, J.; Bandinelli, C.; Fornasari, G.; Cavani, F.; Mella, M.
49
50 *ChemSusChem* **2015**, *8*, 377-388.
51
52
53
54
55
56
57
58
59
60

- 1
2
3 (18) Kvisle, S.; Agüero, A.; Sneed, R. P. A. *Appl. Catal.* **1988**, *43*, 117-131.
4
5 (19) Sushkevich, V. L.; Ivanova, I. I.; Taarning, E. *ChemCatChem* **2013**, *5*, 2367-2373.
6
7 (20) Takezawa, N.; Hanamaki, C.; Kobayashi, H. *J. Catal.* **1975**, *38*, 101-109.
8
9 (21) Ivanov, V. A.; Bachelier, J.; Audry, F.; Lavalley, J. C. *J. Mol. Catal.* **1994**, *91*, 45-59.
10
11 (22) Sushkevich, V. L.; Ivanova, I. I.; Taarning, E. *Green Chem.* **2015**, *17*, 2552-2559.
12
13 (23) León, M.; Díaz, E.; Ordóñez, S. *Catal. Today* **2011**, *164*, 436-442.
14
15 (24) Ohnishi, R.; Akimoto, T.; Tanabe, K. *J. Chem. Soc., Chem. Commun.* **1985**, 1613-1614.
16
17 (25) Kitayama, Y.; Satoh, M.; Kodama, T. *Catal. Lett.* **1996**, *36*, 95-97.
18
19 (26) Breuer, K.; Teles, J. H.; Demuth, D.; Hibst, H.; Schäfer, A.; Brode, S.; Domgörgen, H. *Angew.*
20
21 *Chem., Int. Ed.* **1999**, *38*, 1401-1405.
22
23 (27) Tanabe, K.; Misono, M.; Hattori, H.; Ono, Y. *New solid acids and bases: their catalytic properties*,
24
25 Elsevier, Amsterdam, 1989; pp 73-77.
26
27 (28) Drouilly, C.; Krafft, J.-M.; Averseng, F.; Lauron-Pernot, H.; Bazer-Bachi, D.; Chizallet, C.; Lecocq,
28
29 V.; Costentin, G. *Appl. Catal., A* **2013**, *453*, 121-129.
30
31 (29) Lahousse, C.; Bachelier, J.; Lavalley, J.-C.; Lauron-Pernot, H.; Le Govic, A.-M. *J. Mol. Catal.* **1994**,
32
33 *87*, 329-332.
34
35 (30) Vohs, J. M.; Barteau, M. A. *J. Phys. Chem.* **1991**, *95*, 297-302.
36
37 (31) Quignard, F.; Graziani, O.; Choplin, A. *Appl. Catal., A* **1999**, *182*, 29-40.
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

TOC graphic

