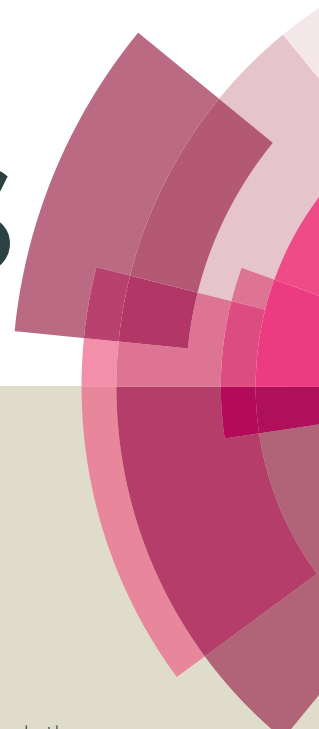


# RSC Advances



This article can be cited before page numbers have been issued, to do this please use: A. Shaabani, Z. Hezarkhani and E. Badali, *RSC Adv.*, 2015, DOI: 10.1039/C5RA10522F.



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

# Wool supported manganese dioxide nano-scale dispersion: As a biopolymer based catalyst for the aerobic oxidation of the organic compounds

Ahmad Shaabani\*, Zeinab Hezarkhani, and Elham Badali

*Faculty of Chemistry, Shahid Beheshti University, G. C., P. O. Box 19396-4716, Tehran, Iran*

Email: [a-shaabani@sbu.ac.ir](mailto:a-shaabani@sbu.ac.ir)

## Abstract

Wool supported manganese dioxide nano-scale dispersion ( $\text{MnO}_2@$ wool) were synthesized by soaking wool in a potassium permanganate solution and characterized by x-ray diffraction (XRD), thermogravimetric analysis (TGA), and scanning electron microscopy (SEM). The synthesized catalyst,  $\text{MnO}_2@$ wool complex, has been found to be able to catalyze the selectively aerobic oxidation of alkyl arenes, alcohols, oximes, and sulfides to their corresponding carbonyl and sulfoxide compounds in the absence of additional oxidizing reagent. The selectively conversion of thiols to disulfides was carried on by this biopolymer based supported catalyst, too.

## Introduction

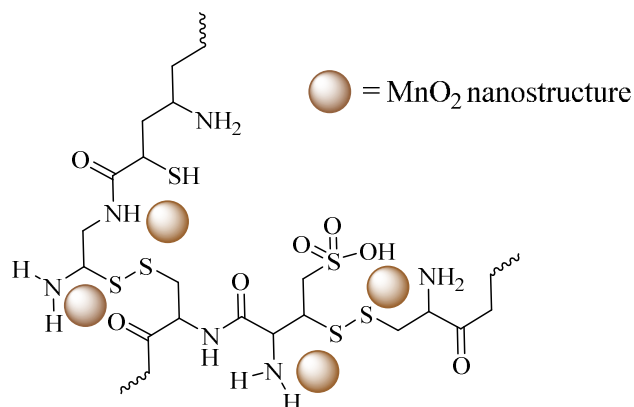
Manganese dioxide occurs naturally as the mineral pyrolusite. This blackish or brown solid is a cheap, renewable, mild, easily handled, and low toxic reagent, which has been extensively used as catalyst for the oxidations of a variety of functional groups.<sup>1-3</sup>  $\text{MnO}_2$  usually provides a relatively low surface area ( $10\text{--}80\text{ m}^2\text{ g}^{-1}$ ) because of its aggregation which impresses its catalytic activities.<sup>4</sup> Producing of manganese dioxide nanostructures provides the large surface area of catalyst.<sup>5</sup> By using of supports for the distribution of  $\text{MnO}_2$  nanostructures, aggregation of  $\text{MnO}_2$  is prevented and high catalytic activity is accessible.<sup>4,6</sup>

Industrial applications of  $\text{MnO}_2$  have become more attractive environmentally by the introduction of a process for recycling  $\text{MnO}_2$ .<sup>7</sup> For this reason, it is important that at the end of the catalytic oxidation process, the  $\text{MnO}_2$  is separable from supports. Although the procedure for separating  $\text{MnO}_2$  from supports such as kieselguhr,<sup>8</sup> aluminum silicate,<sup>9</sup> alumina,<sup>10</sup> or silica,<sup>11</sup> has not

been described before, but in our previous work<sup>6</sup> it was suggested that it possible to separate the MnO<sub>2</sub> from a bio-support by burning or chemical decomposing of bio-support.

The oxidation of organic compounds to their corresponding oxygenated compounds by air as green oxidant using a bio-support catalyst is of main importance for both economic and environmental reasons.<sup>12</sup> Natural biopolymers such as cellulose,<sup>5, 6</sup> chitosan,<sup>13</sup> starch,<sup>14</sup> and protein<sup>15</sup> with emphasis on environmentally friendly, sustainable resources and reusable catalytic processes have been used as supports in various oxidation processes. However, to the best of our knowledge, the use of natural wool as attractive candidate to be solid support for oxidation reactions has not been explored until now.

Wool is a very cheap natural biopolymer of amino acids cross-linked by S–S bonds and its main component is keratin. The mentioned biopolymer contains numerous amino acids units with –NH–CO–, –NH<sub>2</sub>, and –S–S– functional groups.<sup>16</sup> The metal uptake by wool fibers can be enhanced by chemically modifying the fibers with oxidation of –S–S– and –NH–CO– to –SO<sub>3</sub>H, –NH<sub>3</sub><sup>+</sup> and –CO<sub>2</sub><sup>–</sup> groups that able to coordinate metals in the surface of the wool.<sup>17</sup> Furthermore, the loaded metal particles could be distributed evenly on the surface of the wool.<sup>18</sup> As mentioned the aggregation and agglomeration of MnO<sub>2</sub> particles into less active large particles and bulk MnO<sub>2</sub> during the reaction decreased its catalytic activities. To settle the matter, wool can be used as support for manganese dioxide nanostructures. Due to the structurally ordered amino acid chains, the aggregation of MnO<sub>2</sub> could be prevented. The structure of MnO<sub>2</sub>@wool complex is shown in Scheme 1.



**Scheme 1** The possible structure of  $\text{MnO}_2@\text{wool}$

As part of our ongoing program related to developing new methods using heterogeneous catalysts for organic transformations,<sup>19, 20</sup> and based on our previous investigations on  $\text{MnO}_2$ ,<sup>6, 21, 22</sup> and due to the importance of the using wool as a bio-support,<sup>16-18</sup> heterogeneous catalyst based on immobilization of  $\text{MnO}_2$  nanoparticles on wool was synthesized and applied for selective aerobic oxidative transformations of alkyl arenes, alcohols, oximes, and sulfides into the corresponding carbonyl compounds and sulfoxides, in the absence of any other oxidizing reagent or initiator. Disulfides can also be prepared by aerobic oxidation of thiols using  $\text{MnO}_2@\text{wool}$  catalyst. It is important to note that these aerobic transformations did not proceed without air blowing.

## Materials and methods

### 1 General

Natural white wool (sheep of Kangavar/Iran) was washed with NaOH solution, distilled water and methanol, and then cut into very short pieces. All reagents were obtained from Aldrich or Merck and used without further purification. Mn(IV) determination was carried out on an FAAS (Shimadzu model AA-680 flame atomic absorption spectrometer) with a Mn hollow cathode lamps at 279.5 nm, using an air-acetylene flame. Thermogravimetric analysis (TGA) was carried out using STA 1500 instrument at a heating rate of  $10\text{ }^\circ\text{C min}^{-1}$  in air. Products were analyzed using a Varian 3900 GC. X-ray diffraction (XRD) pattern of catalyst was recorded on a STOE STADI P with


scintillation detector, secondary monochromator using Cu K $\alpha$  radiation ( $\lambda = 0.1540$  nm). Scanning electron microscopy (SEM) observations were carried out on an electron microscopy Philips XL-30 ESEM. All samples were sputtered with gold before observation.

## 2 Experimental: preparation of supported manganese dioxide nanostructures on wool

Natural white wool was washed with NaOH solution (0.01 M), distilled water and methanol and dried at 60 °C, then cut with scissors to very short pieces (about 20-500  $\mu\text{m}$ , based on SEM images). To a magnetically stirred mixture of the wool pieces (1.00 g) in 200 mL of H<sub>2</sub>O, a 0.01 M solution of KMnO<sub>4</sub> (130 mL) was added dropwise during 12 h at room temperature and stirring was continued at room temperature for 12 h. Then, the mixture was filtered and washed with CHCl<sub>3</sub> (3  $\times$  7 mL) and EtOH (3  $\times$  10 mL), successively and dried under vacuum at 60 °C for 12 h to give MnO<sub>2</sub>@wool (as brown color, 1.1 g).


## 3 Analysis and results

The Mn(IV) content of the MnO<sub>2</sub>@wool catalyst was determined using FAAS method and the amount of MnO<sub>2</sub> was determined 7.9% in this catalyst. The XRD patterns of wool fibers and MnO<sub>2</sub>@wool were employed to investigate the structure of the synthetic catalyst. As shown in Fig. 1-I, two broad peaks of wool fibers are observed around  $2\theta$  of 9° and 21° that clearly these peaks exist in the diagram II of Fig.1. It can be seen from Fig. 1-II that all the diffraction peaks of MnO<sub>2</sub> nanostructures rather than the peak of wool fibers are extremely weak in intensity and four weak peaks at  $2\theta = 13.90^\circ$ ,  $24.28^\circ$ ,  $34.60^\circ$ , and  $65.26^\circ$  can be ascribed to the MnO<sub>2</sub> nanostructures dispersed onto the surface of wool fibers.

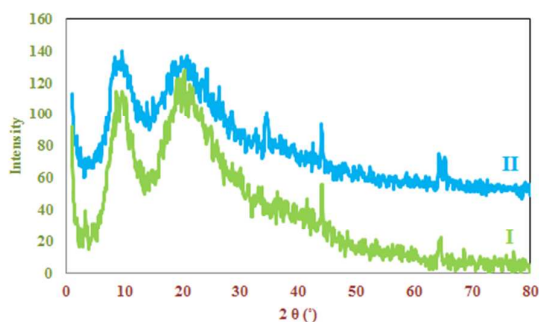

**Fig. 1** XRD patterns of wool fibers (I) and MnO<sub>2</sub> nanoparticle coated wool fibers (II).

TGA demonstrated that wool was decomposed in three stages (Fig. 2-I): the removal of adsorbed water (stage 1) and decomposition of wool (stages 2 and 3). In fact, decomposition of wool was happened in two stages above 241 °C and 487 °C, which showed relatively high thermal stability of the wool fibers in air (Fig. 2-I). High thermal stability was observed for MnO<sub>2</sub>@wool (Fig. 2-II), too. In the TGA curve of MnO<sub>2</sub>@wool catalyst, three stages could be observed. In the low temperature range (up to 242 °C), the mass slowly decreased by 1.9% that should be related to the removal of adsorbed water on the surface in MnO<sub>2</sub>@wool. In the range of 242-516 °C and 516-735 °C in two stages large weight loss for this catalyst was observed, which is attributed to the decomposition of wool.

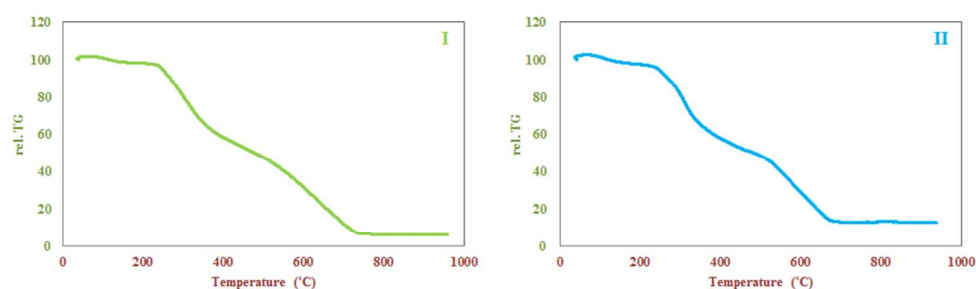

**Fig. 2** TG curves of wool (I) and MnO<sub>2</sub> nanoparticle coated wool fibers (II) in air.

Fig. 3 reveals the surface morphology of the wool fibers and MnO<sub>2</sub>@wool. Clearly, the wool fibers have a length of about 20-500 μm (Fig. 3a) and its surface has a wrinkled structure (Fig. 3b). The structure and morphology of the obtained MnO<sub>2</sub>@wool composites were illustrated by SEM (Fig. 3c, d) and MnO<sub>2</sub> nanostructures could be observed on the wool fiber surface which nanoparticles are well dispersed on the wool fiber surface (Fig. 3d).

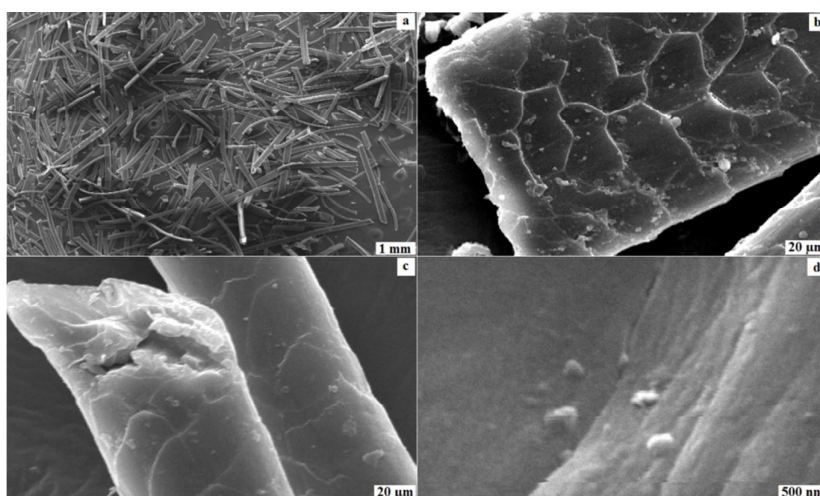


Fig. 3 SEM images of wool (a, b) and MnO<sub>2</sub>@wool (c, d).

Additionally, for determination of the chemical composition of MnO<sub>2</sub>@wool composite, the energy dispersive spectroscopy (EDS) analysis was employed that proves the presence of manganese in the MnO<sub>2</sub>@wool composite (Fig. 4).

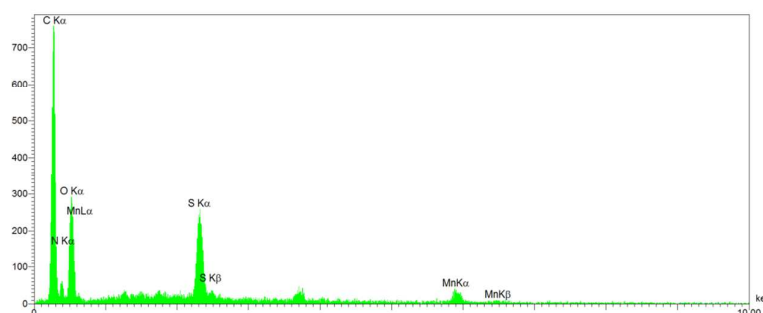


Fig. 4 SEM-EDS results for MnO<sub>2</sub>@wool catalyst.

#### 4 Oxidation of alkyl arenes; General procedure

In a typical reaction, an alkyl arene (1.00 mmol), MnO<sub>2</sub>@wool (0.11 g, 10 mol% of MnO<sub>2</sub>), and *o*-xylene (5.00 mL) were added to a two-necked flask. The mixture was stirred under reflux conditions and air blowing for the indicated time in Table 2. The thin layer chromatography (TLC) method was used to investigate the progress of the reaction. Upon completion, analysis of the crude product has been done by GC method.



## 5 Oxidation of alcohols; General procedure

In a typical reaction, an alcohol (1.00 mmol) was added to a two-necked flask containing  $\text{MnO}_2@$ wool (0.11 g, 10 mol% of  $\text{MnO}_2$ ),  $\text{K}_2\text{CO}_3$  (0.50 mmol), and *o*-xylene (5.00 mL) and stirred under room temperature and air blowing for the indicated time in Table 4. The progress of the reaction was followed by TLC. After completion of reaction and then filtration, the filtrate was analyzed by GC method.

## 6 Oxidation of oximes; General procedure

$\text{MnO}_2@$ wool (0.11 g, 10 mol% of  $\text{MnO}_2$ ) and an oxime (1.00 mmol) were well ground at room temperature using a pestle. The progress of the reaction was monitored by TLC. After the indicated time in Table 6 which the reaction was complete, the solid was washed with dichloromethane ( $3 \times 5$  mL). After the filtration of the reaction mixture, the filtrate were evaporated to give crude product. Analysis of the crude product has been done by GC method.

## 7 Oxidation of sulfides and thiols; General procedure

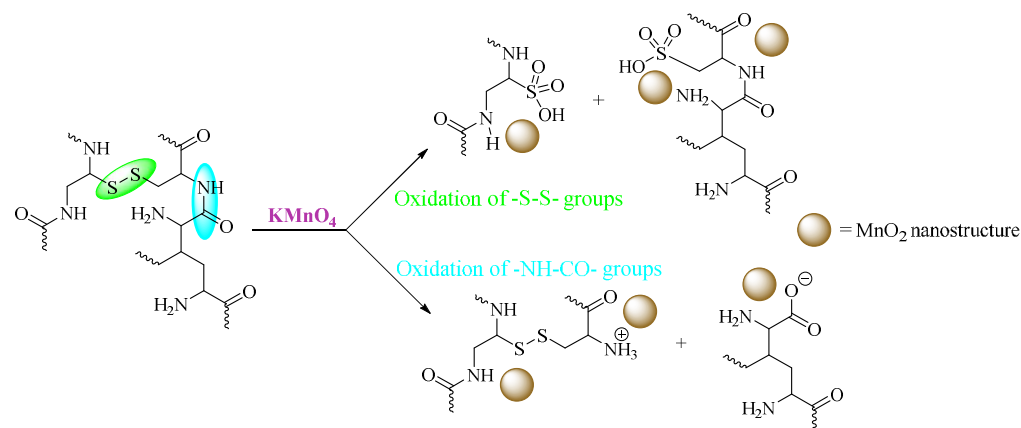
In a round bottom flask, to a solution of sulfide or thiol (1.00 mmol) in *o*-xylene (5.00 mL),  $\text{MnO}_2@$ wool catalyst (0.11 g, 10 mol% of  $\text{MnO}_2$  for oxidation of sulfides and 0.22 g, 20 mol% of  $\text{MnO}_2$  for oxidation of thiols) was added and the mixture was stirred magnetically at room temperature for the indicated time in Table 5. the progress of the reaction was monitored by TLC. After completion, the reaction mixture was filtered and the filtrate was evaporated under reduced pressure to give the corresponding pure sulfoxide or disulfide. All of the products were characterized by melting points which were compared with those obtained from authentic samples.<sup>23-25</sup>

## Results and discussion

The natural wool was treated by potassium permanganate. The  $\text{KMnO}_4$  is able to oxidize and modify the surface of wool, and *in situ* was reduce to  $\text{MnO}_2$  nanostructures as a catalyst.  $\text{KMnO}_4$  molecules were adsorbed by the wool fibers and the maximum absorption of  $\text{KMnO}_4$  is at the edge of scale layer. The  $\text{KMnO}_4$  can attack the disulfides linkage and the peptide bonds of the wool fiber and



reduced to  $\text{MnO}_2$  covering on the surface of this fiber.<sup>26</sup> In fact, the wool fibers act not only as a reduction agent to produce  $\text{MnO}_2$ , but also has support role to impregnate  $\text{MnO}_2$  nanostructures on its surface (Scheme 2).



**Scheme 2** The preparation of  $\text{MnO}_2$ @wool catalyst.

After the successful production of catalytic systems in which wool plays dual role: as a *in situ* reducing agent of  $\text{KMnO}_4$  to generate  $\text{MnO}_2$  nanostructures and as the support to achieve a suitable catalytic system for aerobic oxidation, we examined  $\text{MnO}_2$ @wool catalyst in the reaction media. Aerobic oxidation of indane was selected as a model reaction. Indane (0.12 g, 1.00 mmol),  $\text{MnO}_2$ @wool, solvent (5.00 mL) were added to a two-necked flask equipped with a gas bubbling tube. Air that used as an environment friendly oxidant, was bubbled at a rate of  $5 \text{ mL min}^{-1}$ . After completion of reaction, as indicated by TLC or GC method, catalyst was filtered and washed with acetone ( $2 \times 5 \text{ mL}$ ), and EtOH ( $2 \times 5 \text{ mL}$ ). The analysis of the crude product using GC method showed that corresponding aldehydes and ketones was produced.

In order to find the best reaction conditions, optimization studies were performed in various solvents (Table 1, Entries 2-10). The efficiency of  $\text{MnO}_2$ @wool catalyst in *o*-xylene was higher than other solvents (Table 1, Entries 10). Therefore *o*-xylene was selected as the preferred solvent for the aerobic oxidation of indane.

From the data presented in the Table 1, it is clear that the prepared catalyst,  $\text{MnO}_2$ @wool, has better catalytic role than aggregated  $\text{MnO}_2$  (Entries 1 and 10).

The comparison of the results related to the effect of various amounts of MnO<sub>2</sub>@wool revealed that the 10 mol% of MnO<sub>2</sub> is providing the best result (Table 1, Entries 10-12).

**Table 1** Optimization of the reaction conditions for aerobic oxidation of alkyl arenes by MnO<sub>2</sub>@wool catalyst<sup>a</sup>





















Entry	Catalyst	Amount of catalyst (MnO <sub>2</sub> content/mol%)	Solvent	Yield (%) <sup>b</sup>
1	MnO <sub>2</sub>	0.01 g (10)	<i>o</i> -xylene	24
2	MnO <sub>2</sub> @wool	0.11 g (10)	n-hexane	61
3	MnO <sub>2</sub> @wool	0.11 g (10)	CH <sub>2</sub> Cl <sub>2</sub>	49
4	MnO <sub>2</sub> @wool	0.11 g (10)	CH <sub>3</sub> CN	22
5	MnO <sub>2</sub> @wool	0.11 g (10)	THF	19
6	MnO <sub>2</sub> @wool	0.11 g (10)	MeOH	Trace
7	MnO <sub>2</sub> @wool	0.11 g (10)	EtOH	Trace
8	MnO <sub>2</sub> @wool	0.11 g (10)	DMF	25
9	MnO <sub>2</sub> @wool	0.11 g (10)	toluene	83
10	<b>MnO<sub>2</sub>@wool</b>	<b>0.11 g (10)</b>	<b><i>o</i>-xylene</b>	<b>99</b>
11	MnO <sub>2</sub> @wool	0.09 g (8)	<i>o</i> -xylene	63
12	MnO <sub>2</sub> @wool	0.07 g (6)	<i>o</i> -xylene	46

<sup>a</sup> Reaction conditions for MnO<sub>2</sub>@wool catalyst: indane (1.00 mmol), solvent (5.00 mL), air as oxidant, reflux, 10 h.

<sup>b</sup> Yield determined by GC analysis.

Finally, the oxidation of the various alkyl arenes to related carbonyl compounds using MnO<sub>2</sub>@wool catalyst in *o*-xylene as the preferred solvent under reflux conditions was studied. The oxidation of the alkyl arenes was proceeded effectively and selectively without any overoxidation to carboxylic acid during the reaction (Table 2).

**Table 2** Aerobic oxidation of variuos alkyl arenes to corresponding ketones<sup>a</sup>

Entry	Alkyl arene	Product	Time (h)	Yeild (%) <sup>b</sup>	Entry	Alkyl arene	Product	Time (h)	Yeild (%) <sup>b</sup>
1			10	93	6			10	91
2			12	95	7			12	84
3			12	86	8			9	99
4			9	100	9			9	94
5			10	99	10			10	89

<sup>a</sup> Reaction conditions: alkyl arene (1.00 mmol), MnO<sub>2</sub>@wool (0.11 g), *o*-xylene (5.00 mL), air as oxidant, reflux.

<sup>b</sup> Yield determined by GC analysis.

The oxidation of the alkyl arenes has been carried out successfully using the MnO<sub>2</sub>@wool catalyst, therefore the usability of this catalytic system has been examined for the oxidation of the alcohols, as well. Optimization studies were performed with aerobic oxidation of 1-indanol, as a model substrate. As

indicated in Table 3, the best result is related to the 10 mol% of  $\text{MnO}_2$ , *o*-xylene as a preferred solvent, and  $\text{K}_2\text{CO}_3$  as base (Entry 10).

**Table 3** Optimization of the reaction conditions for aerobic oxidation of alcohols by  $\text{MnO}_2@$ wool catalyst<sup>a</sup>





























Entry	Catalyst	Amount of catalyst ( $\text{MnO}_2$ content/mol%)	Solvent	Base (mmol)	Yield (%) <sup>b</sup>
1	$\text{MnO}_2$	0.01 g (10)	<i>o</i> -xylene	$\text{K}_2\text{CO}_3$ (0.5)	32
2	$\text{MnO}_2@$ wool	0.11 g (10)	n-hexane	$\text{K}_2\text{CO}_3$ (0.5)	91
3	$\text{MnO}_2@$ wool	0.11 g (10)	$\text{CH}_2\text{Cl}_2$	$\text{K}_2\text{CO}_3$ (0.5)	48
4	$\text{MnO}_2@$ wool	0.11 g (10)	$\text{CH}_3\text{CN}$	$\text{K}_2\text{CO}_3$ (0.5)	19
5	$\text{MnO}_2@$ wool	0.11 g (10)	THF	$\text{K}_2\text{CO}_3$ (0.5)	28
6	$\text{MnO}_2@$ wool	0.11 g (10)	MeOH	$\text{K}_2\text{CO}_3$ (0.5)	trace
7	$\text{MnO}_2@$ wool	0.10 g (10)	EtOH	$\text{K}_2\text{CO}_3$ (0.5)	trace
8	$\text{MnO}_2@$ wool	0.09 g (10)	DMF	$\text{K}_2\text{CO}_3$ (0.5)	33
9	$\text{MnO}_2@$ wool	0.11 g (10)	toluene	$\text{K}_2\text{CO}_3$ (0.5)	89
10	<b><math>\text{MnO}_2@</math>wool</b>	<b>0.11 g (10)</b>	<b><i>o</i>-xylene</b>	<b><math>\text{K}_2\text{CO}_3</math> (0.5)</b>	<b>98</b>
11	$\text{MnO}_2@$ wool	0.09 g (8)	<i>o</i> -xylene	$\text{K}_2\text{CO}_3$ (0.5)	69
12	$\text{MnO}_2@$ wool	0.07 g (6)	<i>o</i> -xylene	$\text{K}_2\text{CO}_3$ (0.5)	44
13	$\text{MnO}_2@$ wool	0.11 g (10)	<i>o</i> -xylene	KOH (0.5)	54
14	$\text{MnO}_2@$ wool	0.08 g (10)	<i>o</i> -xylene	$\text{Na}_2\text{CO}_3$ (0.5)	36
15	$\text{MnO}_2@$ wool	0.11 g (10)	<i>o</i> -xylene	-	27













<sup>a</sup> Reaction conditions: 1-indanol (1.00 mmol), solvent (5.00 mL), air as oxidant, r.t., 8 h.

<sup>b</sup> Yield determined by GC analysis.

To extend the scope of the prepared catalyst, the oxidation of the alcohols to the related carbonyl compounds have been investigated. The results of the mentioned reactions have been presented in the Table 4. The reactions were done under air blowing at room temperature with good to high yields. Selectivity for the oxidation of the alcohols to the corresponding carbonyl compounds had been observed, too (Table 4).

**Table 4** Selective aerobic oxidation of various alcohols to corresponding aldehydes and ketones<sup>a</sup>

Entry	Alcohol	Product	Time (h)	Yield (%) <sup>b</sup>	Entry	Alcohol	Product	Time (h)	Yield (%) <sup>b</sup>
1			8	98	11			12	96
2			8	93	12			14	89
3			8	92	13			13	90
4			8	93	14			14	85
5			8	95	15			13	93
6			7	98	16			13	88
7			8	98	17			13	86

8			6	99	18			6	94 <sup>c</sup>
9			6	97	19			13	87 <sup>c</sup>
10			9	87	20			13	89 <sup>c</sup>

<sup>a</sup> Reaction conditions: alcohol (1.00 mmol), MnO<sub>2</sub>@wool (0.11 g), K<sub>2</sub>CO<sub>3</sub> (0.50 mmol), o-xylene (5.00 mL), air as oxidant, r.t.

<sup>b</sup> Yield determined by GC analysis.

<sup>c</sup> The yield of only ketone product determined by GC analysis and the integrals of the <sup>1</sup>H NMR.

According to Table 4, MnO<sub>2</sub>@wool catalyst showed high selectivity for the oxidation of the benzylic alcohols to the related carbonyl compound, and no carboxylic acid was produced (Entries 1-10). The prepared catalyst has same selectivity for the oxidation of allylic and aliphatic alcohols to corresponding aldehydes and ketones (Entries 11-17).











Variety of reagents are available to selectively oxidize a secondary alcohol in the presence of primary alcohol. The rate of these used reagents to oxidize secondary alcohols is slightly faster than primary alcohols but some of reagents have not been highly selective for oxidation of secondary alcohols because of the small magnitudes of rate differences. In fact, when the substrate structure is compatible with the reaction mechanism of the reagent, high selectivity is possible.<sup>27</sup> Between these reagents, MnO<sub>2</sub> acts highly selective for the oxidation of secondary aliphatic and benzylic alcohols in the presence of primary ones.<sup>6</sup> In our previous work, examples of inter- and intramolecular competition experiments and regioselective oxidations was shown basis on the evidence for secondary-primary selectivity of MnO<sub>2</sub> stable nano-scale dispersion.<sup>6</sup>

In this report, mixed primary and secondary benzyl alcohols (Entry 18) and alkylalcohols (Entry 19) as the reactants was used to investigate the selectivity of the MnO<sub>2</sub>@wool catalytic system. The results showed that the oxidation of the secondary functional group is favored and only one of the reactants undergoes oxidation reaction. The oxidation of 2-ethylheptane-1,3-diol, a diol with both primary and secondary hydroxyl functional groups revealed that only product 3-(hydroxymethyl)octan-4-one was obtained (Entry 20). In both cases (inter- and intramolecular competition experiments), at first step the oxidation of the

secondary functional group was done and in continue after the completion of this reaction, the transformation of the primary alcohol was started.

The production of sulfoxide containing compounds as important intermediates in organic chemistry, medicinal chemistry and drug metabolism are very important.<sup>28</sup> Since oxidation of sulfides with manganese dioxide is known to give only sulfoxides,<sup>22</sup> the oxidation of the sulfides to the related sulfoxides compounds using MnO<sub>2</sub>@wool has been investigated as well. The obtained results (Table 5, Entries 1-7) showed that the oxidation of sulfides to sulfoxides has been carried out without any overoxidation to sulfones. Aerobic oxidation of thiols to the related disulfides using MnO<sub>2</sub>@wool catalyst was done and the obtained data have been shown in the Table 5 (Entries 8-10).

**Table 5** Selectively aerobic oxidation of variuos sulfides to corresponding sulfoxides<sup>a</sup>

$\text{R}^1\text{-S-R}^1 \xleftarrow[\text{if R}^2=\text{H}]{\text{MnO}_2@\text{wool}} \text{R}^1\text{-S-R}^2 \xrightarrow{\text{MnO}_2@\text{wool}} \text{R}^1\text{-S(=O)-R}^2$							
Entry	Sulfide or thiol	Time (h)	Yield (%) <sup>b</sup>	Entry	Sulfide or thiol	Time (h)	Yield (%) <sup>b</sup>
1		3	97	6		5	96
2		4	94	7		6	88
3		7	90	8		1	93
4		7	87	9		1.5	96
5		5	91	10		1.5	87

<sup>a</sup> Reaction conditions: sulfide or thiol (1.00 mmol), MnO<sub>2</sub>@wool (0.11 g, 10 mol% of MnO<sub>2</sub> for oxidation of sulfides and 0.22 g, 20 mol% of MnO<sub>2</sub> for oxidation of thiols), *o*-xylene (5.00 mL), air as oxidant, r.t.









<sup>b</sup> Yield determined by GC analysis.

Imine derivatives of carbonyl compounds (such as oximes, semicarbazones and phenylhydrazones) are used extensively for the characterization, isolation, and purification of carbonyl compounds. Oximes are also used as carbonyl protectors of parent carbonyl compounds<sup>29, 30</sup> because of their hydrolytic stability and could be regenerated at the completion of a synthetic procedure. On the other side oximes can also be prepared from noncarbonyl compounds. The carbonyl generation from these compounds provides an alternative method for the preparation of aldehydes and ketones<sup>31</sup>. Many methods such as hydrolytic, reductive, and oxidative reactions and reagents have been reported for

regeneration of carbonyl compounds from oxime derivatives. Using mild reagents and reaction conditions will cause the regeneration of the carbonyl compound to be done without modification to the rest of the molecule.

Thus, oxidation of oximes to the related carbonyl compounds has been studied under solvent-free conditions at room temperature with the yields between 87 and 99. The obtained results have been presented in the Table 6. It is important to note that with adding several drops of any solvent which can solve the oximes, and oxidation reactions were accelerated.


**Table 6** Selectively oxidation of variuos oximes to corresponding aldehydes and ketones<sup>a</sup>

$\text{R}^1\text{-CHO} \xleftarrow[\text{if R}^2 = \text{H}]{\text{MnO}_2@\text{wool}} \text{R}^1\text{-C(=NOH)-R}^2 \xrightarrow{\text{MnO}_2@\text{wool}} \text{R}^1\text{-C(=O)-R}^2$							
Entry	Alcohol	Time (min)	Yield (%) <sup>b</sup>	Entry	Alcohol	Time (min)	Yield (%) <sup>b</sup>
1		7	94	5		7	96
2		7	91	6		7	94
3		9	87	7		6	97
4		9	90	8		5	99

<sup>a</sup> Reaction conditions: oxime (1.00 mmol), MnO<sub>2</sub>@wool (0.11 g), room temperature.

<sup>b</sup> Yield determined by GC analysis.

Recyclability of the MnO<sub>2</sub>@wool catalyst was examined in the oxidation reaction of indane, 1-indanol, 2,3-dihydro-1H-inden-1-one oxime, and methyl phenyl sulfide. Catalyst was recovered from reaction media by filtration and reused for three repetitive cycles in the reaction. The results revealed that the activity of the MnO<sub>2</sub>@wool was saved during successive uses (Fig. 5).

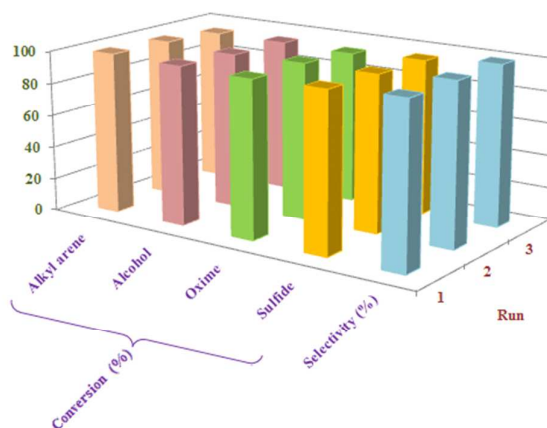

**Fig. 5** Successive use of the prepared catalyst for the oxidation of indane, 1-indanol, 2,3-dihydro-1H-inden-1-one oxime, and methyl phenyl sulfide.

The results of our investigations have been compared to previous reports of  $\text{MnO}_2$ .<sup>6, 8, 9, 11, 32-35</sup> The results show that  $\text{MnO}_2$  impregnated on wool is one of the best oxidant systems in reaction times and yield viewpoints (Table 7).

**Table 7** Comparison of the results obtained from active  $\text{MnO}_2$ ,  $\text{MnO}_2$  on different supports and nano  $\text{MnO}_2$  impregnated on wool for the oxidation of benzylalcohol

Entry	Catalyst	Conditions	Molar ratio substrate to $\text{MnO}_2$	Time (h)	Yield (%)	Ref.
1	active $\text{MnO}_2$	solvent free/ r.t.	1:0.08	48	77	[32]
2	active $\text{MnO}_2$	toluene/ $\text{O}_2$ /110 °C	1:0.80	4	85	[33]
3	$\text{MnO}_2$ /Graphite	$\text{CH}_2\text{Cl}_2$ /ref.	1:2.00	10	92	[34]
4	$\text{MnO}_2$ /Kieselguhr	$\text{CH}_2\text{Cl}_2$ /ref.	1:2.00	10	90	[35]
5	$\text{MnO}_2$ /Kieselguhr	solvent free/50-55 °C/grind	1:2.00	3	95	[8]
6	$\text{MnO}_2$ /Aluminum Silicate	$\text{CH}_2\text{Cl}_2$ /ref.	1:3.00	12	96	[9]
7	$\text{MnO}_2$ /Silica	solvent free/ref./Microwave irradiations	1:5.00	0.3	88	[11]
8	Nano $\text{MnO}_2$ /Cellulose	<i>o</i> -xylene/air/r.t.	1:0.10	7	99	[6]
9	Nano $\text{MnO}_2$ @wool	<i>o</i> -xylene/air/r.t.	1:0.10	8	98	This work

## Conclusion

Manganese dioxide nanostructures supported on wool which composed of protein with repeated unit of amino acid, as bio-supported heterogeneous catalyst, were synthesized and used for the selective oxidation of a variety of functional groups. The distribution of  $\text{MnO}_2$  on the surface of wool fibers gave an active catalytic system. The prepared catalyst showed high selectivity for the aerobic oxidation of the alkyl arenes, alcohols, and sulfides to the related carbonyl and sulfoxide compounds without any overoxidation. Use of air as oxidant (inexpensive oxidant), the absence of any co-promoter and additional oxidizing



reagent, the recyclability of catalyst with no loss in its activity, excellent yield, and easy workup are several advantages of MnO<sub>2</sub>@wool catalyst. This catalyst has high selectivity for the oxidation of oximes to related aldehydes and ketones.

## Acknowledgements

We gratefully acknowledge financial support from the Iran National Science Foundation (INSF), the Research Council of Shahid Beheshti University and Catalyst Center of Excellence (CCE) at Shahid Beheshti University.

## References

1. J. Mei and L. Zhang, *RSC Adv.*, 2015, **5**, 14843-14850.
2. S. Kumari, A. Shekhar and D. D. Pathak, *RSC Adv.*, 2014, **4**, 61187-61192.
3. R. J. K. Taylor, M. Reid, J. Foot and S. A. Raw, *Acc. Chem. Res.*, 2005, **38**, 851-869.
4. R. Nie, J. Shi, S. Xia, L. Shen, P. Chen, Z. Hou and F.-S. Xiao, *J. Mater. Chem.*, 2012, **22**, 18115-18118.
5. L. Zhou, J. He, J. Zhang, Z. He, Y. Hu, C. Zhang and H. He, *J. Phys. Chem. C*, 2011, **115**, 16873-16878.
6. A. Shaabani, Z. Hezarkhani and S. Shaabani, *RSC Adv.*, 2014, **4**, 64419-64428.
7. N. Singh and D. G. Lee, *Org. Process Res. Dev.*, 2001, **5**, 599-603.
8. L.-Y. Zhu, Z. Lou, J. Lin, W. Zheng, C. Zhang and J.-D. Lou, *Res. Chem. Intermed.*, 2013, **39**, 4287-4292.
9. L.-H. Huang, Y.-C. Ma, C. Zhang, Q. Wang, X.-N. Zou and J.-D. Lou, *Synth. Commun.*, 2011, **42**, 3377-3382.
10. S. M. Maliyekkal, A. K. Sharma and L. Philip, *Water res.*, 2006, **40**, 3497-3506.
11. R. S. Varma, R. K. Saini and R. Dahiya, *Tetrahedron lett.*, 1997, **38**, 7823-7824.
12. *Handbook of Reagents for Organic Synthesis, Oxidizing and Reducing Agents*, ed. S. D. Burke and R. L. Danheiser, John Wiley and Sons, Chichester, UK, 1999.
13. E. Guibal, *Prog. Polym. Sci.*, 2005, **30**, 71-109.
14. Y. Zhao, X. Yang, L. Zhan, S. Ou and J. Tian, *J. Mater. Chem.*, 2011, **21**, 4257-4263.
15. S. Kanbak-Aksu, M. Nahid Hasan, W. R. Hagen, F. Hollmann, D. Sordi, R. A. Sheldon and I. W. C. E. Arends, *Chem. Commun.*, 2012, **48**, 5745-5747.
16. L. Xue, B. Jia, L. Tang, X. F. Ji, M. Y. Huang and Y. Y. Jiang, *Polym. Adv. Technol.*, 2004, **15**, 346-349.

17. S. Wu, H. Ma, X. Jia, Y. Zhong and Z. Lei, *Tetrahedron*, 2011, **67**, 250-256.
18. H.-c. Ma, W. Cao, Z.-k. Bao and Z.-Q. Lei, *Catal. Sci. Technol.*, 2012, **2**, 2291-2296.
19. M. Mahyari, M. S. Laeini and A. Shaabani, *Chem. Commun.*, 2014, **50**, 7855-7857.
20. M. Mahyari, A. Shaabani and Y. Bide, *RSC Adv.*, 2013, **3**, 22509-22517.
21. A. Shaabani, P. Mirzaei, S. Naderi and D. G. Lee, *Tetrahedron*, 2004, **60**, 11415-11420.
22. A. Shaabani, P. Mirzaei and D. G. Lee, *Catal. Lett.*, 2004, **97**, 119-123.
23. K. Sato, M. Hyodo, M. Aoki, X.-Q. Zheng and R. Noyori, *Tetrahedron*, 2001, **57**, 2469-2476.
24. L. Field and J. E. Lawson, *J. Am. Chem. Soc.*, 1958, **80**, 838-841.
25. N. Iranpoor and B. Zeynizadeh, *Synthesis*, 1999, 49-50.
26. H. Y. Zhang and X. M. Hu, *Adv. Mater. Res.*, 2013, **739**, 57-60.
27. J. B. Arterburn, *Tetrahedron*, 2001, **57**, 9765-9788.
28. *The Chemistry of Sulphones and Sulphoxides*, ed. S. Patai, Z. Rappoport and C. J. M. Stirling, John Wiley, New York, 1988.
29. P. G. Wuts and T. W. Greene, in *Greene's protective groups in organic synthesis*, John Wiley & Sons, 2006.
30. A. Corsaro, U. Chiacchio and V. Pistarà, *Synthesis*, 2001, **2001**, 1903-1931.
31. D. H. R. Barton and J. M. Beaton, *J. Am. Chem. Soc.*, 1961, **83**, 4083-4089.
32. J.-D. Lou and Z.-N. Xu, *Tetrahedron Lett.*, 2002, **43**, 6149-6150.
33. A. Kamimura, H. Komatsu, T. Moriyama and Y. Nozaki, *Tetrahedron*, 2013, **69**, 5968-5972.
34. J.-D. Lou, X. L. Lu, L.-H. Huang, Q. Wang and X.-N. Zou, *Synth. React. Inorg., Metal-Org., Nano-Metal Chem.*, 2011, **41**, 1342-1345.
35. J.-D. Lou, J. Ge, X.-N. Zou, C. Zhang, Q. Wang and Y.-C. Ma, *Oxid. Commun.*, 2011, **34**, 361-365.