

ChemComm

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: S. Shibata, K. Sugahara, K. Kamata and M. Hara, *Chem. Commun.*, 2018, DOI: 10.1039/C8CC02185F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Liquid-phase oxidation of alkanes with molecular oxygen catalyzed by high valent iron-based perovskite

Received 00th January 20xx,
Accepted 00th January 20xx

Satomi Shibata,^a Kosei Sugahara,^a Keigo Kamata^{*a,b} and Michikazu Hara^{a,c}

DOI: 10.1039/x0xx00000x

www.rsc.org/

Hexagonal BaFeO_{3-δ} containing high valent iron species acted as an efficient heterogeneous catalyst for the aerobic oxidation of alkanes without the need for additives. The activity of BaFeO_{3-δ} was much higher than that of typical Fe³⁺/Fe²⁺-containing iron oxide-based catalysts, and the recovered catalyst could be reused without significant loss of catalytic performance.

Catalytic oxidation of the aliphatic C–H bond of alkanes to produce useful chemicals remains a significant and challenging subject of research in the chemical industry.¹ The development of effective catalysts with well-defined active sites for the oxidation of alkanes using activated oxidants such as organic peroxides/peracids and hydrogen peroxide is expected to lead to remarkable activity and selectivity.² In contrast to such processes, catalytic oxidation with molecular oxygen (O₂) as an oxidant offers environmental and economic advantages; however, the control of O₂ activation and selectivity remains a problem to be solved.³ Functionalized adamantane derivatives can be biologically active compounds and functionally hybrid materials;⁴ therefore, several catalytic systems for the aerobic oxidation of adamantane have been developed (Table S1, ESI).^{5,6} Most of these systems are homogeneous and typically require additives (radical initiator, reductant, etc.) or photo- or microwave irradiation.⁵ There are only a few examples of recoverable and reusable heterogeneous Ru- and V-based catalysts with O₂ as the sole oxidant.⁶

The versatility of perovskite oxides with formula ABO₃ has led to various applications in the fields of structural chemistry, magnetism, superconductivity, and piezoelectrics.^{7a} In particular, the catalytic function of perovskite oxide-based materials has attracted much attention because their

structures and physicochemical properties can be controlled by changing the composition.^{7b,7c} Despite their superiority, application to perovskite-catalyzed liquid-phase organic reactions is still limited. We have very recently reported the amino acid-aided synthesis of high-surface-area perovskite catalysts that contain alkaline earth metals as A-site elements.⁸ Hexagonal SrMnO₃ could act as an efficient heterogeneous catalyst for the aerobic oxidation of various substrates.⁸ We envisaged that an iron-based perovskite containing Fe⁴⁺ would likely act as an efficient catalyst for alkane oxidation because high valent iron-oxo species have been postulated to be strong active oxidants under mild conditions.⁹ Here, we report that hexagonal 6H-BaFeO_{3-δ}, which consists of face-sharing dimeric Fe₂O₉ units linked by single corner-sharing FeO₆ units along the *c* axis (Fig. 1(a)), could act as an efficient, recyclable and heterogeneous catalyst for the oxidation of adamantane (**1a**) with 0.1 MPa of O₂ as the sole oxidant. This study provides the first example of a naturally abundant iron oxide-based heterogeneous catalyst for the aerobic oxidation of **1a** without the need for any additives.

Perovskite BaFeO_{3-δ} was prepared by the amino acid-aided method (see ESI).^{8b} Fig. 1(b) shows a powder X-ray diffraction

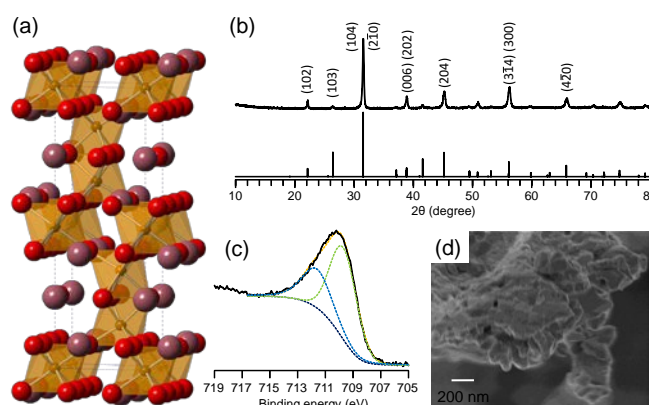


Fig. 1 (a) Structure of BaFeO₃. Brown, purple, and red spheres represent the Fe, Ba, and O atoms, respectively. (b) XRD patterns for BaFeO_{3-δ} (upper) and BaFeO₃ (lower, ICSD 50869). (c) XPS Fe 3p_{3/2} spectrum for BaFeO_{3-δ} and (d) SEM image.

^a Laboratory for Materials and Structures, Institute of Innovative Research, Tokyo Institute of Technology, 4259 Nagatsuta-cho, Midori-ku, Yokohama 226-8503, Japan. E-mail: kamata.k.ac@m.titech.ac.jp; Fax&Tel: +81-45-924-5338

^b Japan Science and Technology Agency (JST), Precursory Research for Embryonic Science and Technology (PRESTO), 4-1-8 Honcho, Kawaguchi 332-0012, Japan.


^c JST, Advanced Low Carbon Technology Research and Development Program (ALCA), 4-1-8 Honcho, Kawaguchi 332-0012, Japan.

† Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: [Experimental details, 6 Figures, 4 Tables]. See DOI: 10.1039/x0xx00000x

(XRD) pattern for BaFeO_{3-6} , which is in good agreement with that for hexagonal 6H-BaFeO_{3-x} [space group $P6_3/mmc$ (No. 194)].¹⁰ Impurity phases of other iron oxide species (FeO , Fe_3O_4 , Fe_2O_3 , and Ba_2FeO_4) were not observed. Elemental analysis of BaFeO_{3-6} using inductively coupled plasma atomic emission spectroscopy (ICP-AES) revealed that the molar ratio of Ba:Fe was 1:1. The average oxidation state of Fe species was determined to be 3.8 by iodometry, which indicates that the δ value in BaFeO_{3-6} is ca. 0.1. The X-ray photoelectron spectroscopy (XPS) Fe 2p spectrum of BaFeO_{3-6} showed peaks with binding energies of 709.7 and 711.6 eV, which correspond to Fe^{3+} and Fe^{4+} species, respectively (Fig. 1(c)).^{10,11} The specific surface area of BaFeO_{3-6} was $11 \text{ m}^2 \text{ g}^{-1}$, and this value was larger than those ($0.2\text{--}6.6 \text{ m}^2 \text{ g}^{-1}$) reported for BaFeO_{3-6} (Table S2, ESI).¹⁰ Fig. 1(d) shows a scanning electron microscopy (SEM) image of BaFeO_{3-6} , where the particle sizes were estimated to be 50–200 nm. Cubic SrFeO_3 and orthorhombic $\text{CaFeO}_{2.5}$ were also successfully synthesized by the amino acid-aided method and were characterized by XRD, N_2 -adsorption, and elemental analyses (Table S3 and Figs. S1 and S2, ESI).

Table 1 Effects of catalysts on the oxidation of **1a** with O_2^a

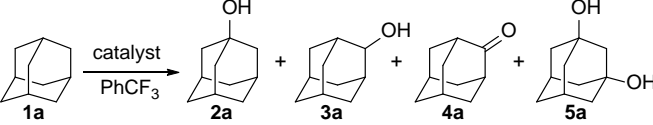

Entry	Catalyst	S_{BET} ($\text{m}^2 \text{ g}^{-1}$)	Yield (%)	Selectivity (%)			
				2a	3a	4a	5a
1	BaFeO_{3-6}	11	29	76	7	11	6
2 ^b	BaFeO_{3-6}	11	30	82	7	6	5
3 ^{b,c}	BaFeO_{3-6}	11	30	79	7	7	7
4 ^{b,d}	BaFeO_{3-6}	11	31	77	8	7	7
5	SrFeO_3	20	27	76	8	10	6
6	$\text{CaFeO}_{2.5}$	28	<1	—	—	—	—
7	LaFeO_3	18	<1	—	—	—	—
8	BaFe_2O_4	14	<1	—	—	—	—
9	Fe_2O_3	39	<1	—	—	—	—
10	Fe_3O_4	12	<1	—	—	—	—
11	FeO	1	<1	—	—	—	—
12	$\text{Fe}(\text{OAc})_2$	—	<1	—	—	—	—
13	$\text{Ba}(\text{OAc})_2$	—	<1	—	—	—	—
14	BaCoO_3	19	<1	—	—	—	—
15	BaMnO_3	25	<1	—	—	—	—
16	SrMnO_3	47	<1	—	—	—	—
17	CaMnO_3	11	<1	—	—	—	—
18	BaRuO_3	25	1	>99	—	—	—
19	without	—	<1	—	—	—	—

^a Reaction conditions: catalyst (0.1 g), **1a** (0.5 mmol), PhCF_3 (1 mL), $p\text{O}_2$ (0.1 MPa), 363 K, 48 h. Yield and selectivity were determined by gas chromatography (GC) analysis. Yield (%) = $(2\text{a}+3\text{a}+4\text{a}+5\text{a}) \text{ (mol)} / \text{initial } 1\text{a} \text{ (mol)} \times 100$. Selectivity (%) = $\text{product (mol)} / (2\text{a}+3\text{a}+4\text{a}+5\text{a}) \text{ (mol)} \times 100$. ^b **1a** (1 mmol). ^c Reuse (1st). ^d Reuse (2nd).

The aerobic oxidation of **1a** in benzotrifluoride (PhCF_3) at 0.1 MPa of O_2 without any additives was performed using

various perovskites and iron oxides (Tables 1 and S4, ESI). Four products, 1-adamantanol (**2a**), 2-adamantanol (**3a**), 2-adamantanone (**4a**), and 1,3-adamantanediol (**5a**), were mainly formed. The reaction did not proceed in the absence of a catalyst (entry 19). Among the catalysts tested, Fe^{4+} -containing BaFeO_{3-6} and SrFeO_3 exhibited high catalytic activity (entries 1 and 5), and the intrinsic activity of BaFeO_{3-6} (with face-sharing octahedra) per surface was approximately two times higher than that of SrFeO_3 (with the corner-sharing octahedra). Other $\text{Fe}^{3+}/\text{Fe}^{2+}$ -containing oxides such as $\text{CaFeO}_{2.5}$, LaFeO_3 , BaFe_2O_4 , and simple iron oxides (FeO , Fe_3O_4 , and Fe_2O_3) and catalyst precursors of $\text{Fe}(\text{OAc})_2$ and $\text{Ba}(\text{OAc})_2$ were almost inactive (entries 6–13). In the presence of Ba- and Mn-based perovskites (BaBO_3 (B = Mn, Co, and Ru) and AMnO_3 (A = Ca and Sr)), oxidation did not proceed (entries 14–18). The total yield of **2a–5a** reached 67% for the oxidation of **1a** under optimum conditions (entry 1 in Table 2), and the value was the second highest among the heterogeneous systems without additives (Table S1, ESI). In this case, the selectivity ratio of tertiary/secondary ($3^\circ/2^\circ$) C–H activation normalized to the number of C–H bonds was 29. This value is comparable to those of metal-catalyzed radical-mediated oxidation catalysts with O_2 .^{5,6,9c} Although BaFeO_3 -based materials have been investigated for the catalytic combustion of CH_4 and CO, NO_x decomposition, and electrochemical reaction,¹⁰ their application to liquid-phase organic reactions has not been reported.

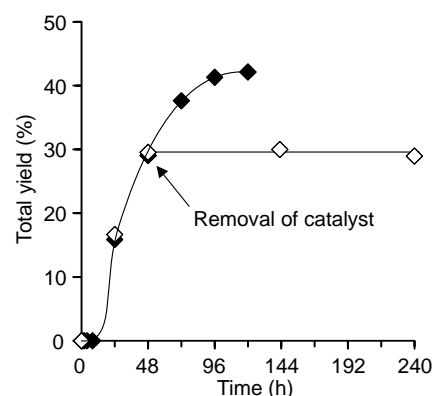


Fig. 2 Effect of BaFeO_{3-6} removal on the oxidation of **1a**. \blacklozenge , with BaFeO_{3-6} ; \diamond , without BaFeO_{3-6} as indicated by the arrow. Reaction conditions: BaFeO_{3-6} (0.1 g), **1a** (0.5 mmol), PhCF_3 (1 mL), $p\text{O}_2$ (0.1 MPa), 363 K.

To verify whether the observed oxidation catalysis is due to solid BaFeO_{3-6} or leached Fe or Ba species, the oxidation of **1a** was performed under the conditions described in Fig. 2. When BaFeO_{3-6} was removed by hot filtration after 48 h, no further oxidation proceeded (Fig. 2). In addition, no leaching of Fe or Ba species in the filtrate was determined by ICP-AES analysis. These results suggest that the observed catalysis is heterogeneous. The BaFeO_{3-6} used could readily be recovered from the reaction mixture by simple filtration. There was no significant difference in the XRD patterns of the fresh and recovered BaFeO_3 catalyst (Fig. S3, ESI).[†] The recovered catalyst could be reused twice without significant change in

the total yield or the selectivity: e.g., 82% selectivity to **2a** at 30% total yield (fresh), 79% selectivity to **2a** at 30% total yield (reuse 1st), and 77% selectivity to **2a** at 31% total yield (reuse 2nd) (entries 2–4 in Table 1),⁵ which indicates the durability of BaFeO_{3-δ}.

Table 2 Oxidation of various substrates catalyzed by BaFeO_{3-δ} with O₂^a

Entry	Substrate	Time (h)	Product (Yield (%))
1	1a	96	2a (48), 3a (3), 4a (5), 5a (11)
2 ^b	1b	72	2b (36)
3 ^c	1c	96	2c (36)
4 ^c	1d	96	2d (14) cis/trans = 26/74
5	1e	72	2e (3), 3e (11)
6 ^d	1f	96	2f (59)
7	1g	96	2g (95)
8	1h	30	2h (12), 3h (39)
9	1i	30	2i (6), 3i (37)

^a Reaction conditions: BaFeO_{3-δ} (0.2 g), **1** (1.0 mmol), PhCF₃ (1 mL), *p*O₂ (0.1 MPa), 363 K. ^b Ketones (6% yield). ^c Ketones (5% yield). ^d *n*-Octane (1 mL), 353 K.

The present system could be applied to the oxidation of various hydrocarbon substrates with O₂ as the sole oxidant (Table 2). The tertiary C–H bonds of **1a**, as well as its derivatives (1-ethyladamantane (**1b**) and 1,3-dimethyladamantane (**1c**)), were mainly oxidized, and the yields of the corresponding alcohols were 42% and 31%, respectively (entries 2 and 3). In the case of *cis*-decalin (**1d**), the stereoisomeric mixture of 9-decalol (**2e**, *cis/trans* = 26/74) was obtained (entry 4), which indicates the formation and the substantial inversion of the 9-decalyl radical intermediate in this reaction.^{2b,3a,9c,13} The secondary C–H bonds of cyclooctane (**1e**) was also oxidized to the corresponding alcohol and ketone (**2e** and **3e**), while the yields were low (entry 5). This catalyst system also efficiently catalyzed the oxidation of alkylarenes. Fluorene (**1f**) and xanthene (**1g**) with two benzene rings were oxidized to the corresponding ketones in 59% and 95% yields, respectively (entries 6 and 7). In the case of tetralin (**1h**) and indan (**1i**) with one benzene ring, the corresponding

oxygenated products (alcohols and ketones) were obtained (entries 8 and 9).

DOI: 10.1039/C8CC02185F

The BaFeO_{3-δ}-catalyzed oxidation of **1a** under the conditions of entry 1 in Table 1 proceeded with an induction period and was completely suppressed by the presence of a radical scavenger (2,6-di-*tert*-butyl-4-methylphenol, 1 equiv. with respect to **1a**). The oxidation of **1a** did not proceed under an Ar atmosphere (Fig. S4, ESI), which indicates that BaFeO_{3-δ} did not act as a stoichiometric oxidant but as a catalyst. A good correlation between the logarithm of the reaction rate normalized on a per hydrogen basis ($\log R_0'$) for the oxidation of alkylarenes and C–H bond dissociation energy (BDE) was observed (Fig. 3).¹⁴ A kinetic isotope effect (k_H/k_D) value of 5.0 was observed for the oxidation of **1f** and **1f-d**₁₀ at 363 K. All these data including the catalyst effect, 3°/2° value for **1a**, and the stereospecificity for **2d** indicate that the present oxidation proceeds via a radical-mediated oxidation mechanism and that H-abstraction (likely by high valent iron oxo species in BaFeO_{3-δ}) is the rate-determining step (Fig. S5). The high ¹⁸O content (96–97 %) in **2a** (¹⁸O-labeled **2a**/total **2a**) was observed from the initial stage of the BaFeO_{3-δ}-catalyzed oxidation of **1a** at 0.1 MPa of ¹⁸O₂ (97 atom%, Fig. S6),⁵⁵ supporting the reaction mechanism.

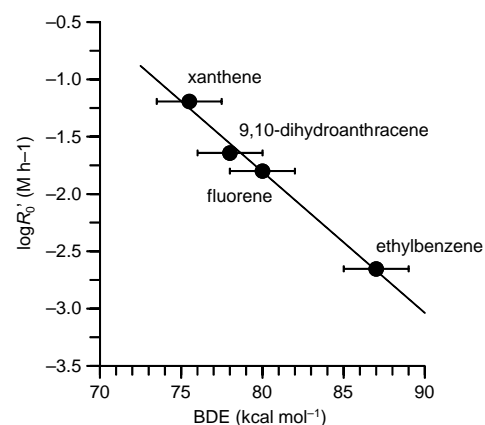


Fig. 3 Plot of $\log R_0'$ versus BDE for the oxidation of alkylarenes. Reaction conditions: BaFeO_{3-δ} (0.1 g), substrate (1 mmol), PhCF₃ (1 mL), *p*O₂ (0.1 MPa), 363 K.

In conclusion, hexagonal iron-based perovskite BaFeO_{3-δ} synthesized by the amino acid-aided method could heterogeneously catalyze the aerobic oxidation of various alkanes and alkylarenes without the need for any additives. This work was supported by the PRESTO program (No. JPMJPR15S3) of the Japan Science and Technology Agency (JST).

Conflicts of interest

There are no conflicts to declare.

Notes and references

† The slight peak shifts due to the increase of oxygen vacancies were observed.

§ The total turnover number (TON) was estimated to be 124 based on surface Fe (see details in ESI). For oxygenation of **1a** using 0.1 MPa of O₂ without any additives, the value is higher than or comparable to those (25–162) of homogeneous iron-based catalysts,¹² but lower than those (247–3300) of Ru- and V-based homogeneous and heterogeneous catalysts.^{5,6}

§§ The gradual decrease of the ¹⁸O contents in **4a** is probably caused by the different reaction mechanism for oxidation of **3a** into **4a** and/or exchange with ¹⁶O oxygen (lattice, water, etc.).

- 1 (a) T. Punniyamurthy, S. Velusamy and J. Iqbal, *Chem. Rev.*, 2005, **105**, 2329–2363; (b) M. Sankar, N. Dimitratos, P. J. Miedziak, P. P. Wells, C. J. Kiely and G. J. Hutchings, *Chem. Soc. Rev.*, 2012, **41**, 8099–8139.
- 2 (a) T. A. van den Berg, J. W. de Boer, W. R. Browne, G. Roelfes and B. L. Feringa, *Chem. Commun.*, 2004, 2550–2551; (b) K. Kamata, K. Yonehara, Y. Nakagawa, K. Uehara and N. Mizuno, *Nat. Chem.*, 2010, **2**, 478–483; (c) M. S. Chen and M. C. White, *Science*, 2010, **327**, 566–571; (d) R. V. Ottenbacher, D. G. Samsonenko, E. P. Talsi and K. P. Bryliakov, *ACS Catal.*, 2014, **4**, 1599–1606.
- 3 (a) Y. Ishii, S. Sakaguchi and T. Iwahama, *Adv. Synth. Catal.*, 2001, **343**, 393–427; (b) R. Neumann and A. M. Khenkin, *Chem. Commun.*, 2006, 2529–2538; (c) S. Ishikawa and W. Ueda, *Catal. Sci. Technol.*, 2016, **6**, 617–629.
- 4 E. A. Shokova and V. V. Kovalev, *Russ. J. Org. Chem.*, 2012, **48**, 1007–1040.
- 5 (a) Y. Ishii, K. Nakayama, M. Takeno, S. Sakaguchi, T. Iwahama and Y. Nishiyama, *J. Org. Chem.*, 1995, **60**, 3934–3935; (b) R. Neumann and M. Dahan, *J. Am. Chem. Soc.*, 1998, **120**, 11969–11976; (c) S. Shinachi, M. Matsushita, K. Yamaguchi and N. Mizuno, *J. Catal.*, 2005, **233**, 81–89; (d) H. Kobayashi and I. Yamanaka, *Chem. Lett.*, 2007, **36**, 114–115; (e) S. Ikurumi, S. Okada, K. Nakatsuka, T. Kamegawa, K. Mori and H. Yamashita, *J. Phys. Chem. C*, 2014, **118**, 575–581.
- 6 (a) K. Yamaguchi and N. Mizuno, *New J. Chem.*, 2002, **26**, 972–974; (b) T. Mitsudome, N. Nosaka, K. Mori, T. Mizugaki, K. Ebitani and K. Kaneda, *Chem. Lett.*, 2005, **34**, 1626–1627; (c) E. Kockrick, T. Lescouet, E. V. Kudrik, A. B. Sorokin and D. Farrusseng, *Chem. Commun.*, 2011, **47**, 1562–1564; (d) X.-H. Li, J.-S. Chen, X. Wang, J. Sun and M. Antonietti, *J. Am. Chem. Soc.*, 2011, **133**, 8074–8077.
- 7 (a) M. A. Pena and J. L. G. Fierro, *Chem. Rev.*, 2001, **101**, 1981–2017; (b) J. Zhu, H. Li, L. Zhong, P. Xiao, X. Xu, X. Yang, Z. Zhao and J. Li, *ACS Catal.*, 2014, **4**, 2917–2940; (c) S. Royer, D. Duprez, F. Can, X. Courtois, C. Batiot-Dupeyrat, S. Laassiri and H. Alamdari, *Chem. Rev.*, 2014, **114**, 10292–10368.
- 8 (a) S. Kawasaki, K. Kamata and M. Hara, *ChemCatChem*, 2016, **8**, 3247–3253; (b) K. Sugahara, K. Kamata, S. Muratsugu and M. Hara, *ACS Omega*, 2017, **2**, 1608–1616.
- 9 (a) J. T. Groves, *J. Inorg. Biochem.*, 2006, **100**, 434–447; (b) W. Nam, *Acc. Chem. Res.*, 2007, **40**, 522–531; (c) M. Costas, K. Chen and L. Que Jr, *Coord. Chem. Rev.*, 2000, **200–202**, 517–544.
- 10 (a) H. Xian, X. Zhang, X. Li, L. Li, H. Zou, M. Meng, Q. Li, Y. Tan and N. Tsubaki, *J. Phys. Chem. C*, 2010, **114**, 11844–11852; (b) F. Dong, D. Chen, Y. Chen, Q. Zhao and Z. Shao, *J. Mater. Chem.*, 2012, **22**, 15071–15079; (c) A. el Hadri, I. Gomez-Recio, E. del Rio, J. C. Hernandez-Garrido, R. Cortes-Gil, M. Hernando, A. Varela, A. Gutierrez-Alonso, M. Parras, J. J. Delgado, J. A. Perez-Omil, G. Blanco, J. J. Calvino and J. M. Gonzalez-Calbet, *ACS Catal.*, 2017, **7**, 8653–8663; (d) C. Huang, Y. Zhu, X. Wang, X. Liu, J. Wang and T. Zhang, *J. Catal.*, 2017, **347**, 9–20.
- 11 (a) M. Florea, M. Alifanti, V. Kuncser, D. Macovei, N. Apostol, P. Granger and V. I. Parvulescu, *J. Catal.*, 2014, **316**, 130–140; (b) K. Zhu, H. Liu, X. Li, Q. Li, J. Wang, X. Zhu and W. Yang, *Electrochim. Acta*, 2017, **241**, 433–439.
- 12 (a) N. Mizuno, M. Tateishi, T. Hirose and M. Iwamoto, *Chem. Lett.*, 1993, 2137–21410; (b) M. Bonchio, M. Carraro, A. Farinazzo, A. Sartorel, G. Scorrano and U. Kortz, *J. Mol. Catal. A*, 2007, **262**, 36–40.
- 13 L. Saussine, E. Brazi, A. Robine, H. Mimoun, J. Fischer and R. Weiss, *J. Am. Chem. Soc.*, 1985, **107**, 3534–3540.
- 14 (a) J. R. Bryant and J. M. Mayer, *J. Am. Chem. Soc.*, 2003, **125**, 10351–10361; (b) J. M. Mayer, *Acc. Chem. Res.*, 1998, **31**, 441–450; (c) X.-S. Xue, P. Ji, B. Zhou and J.-P. Cheng, *Chem. Rev.*, 2017, **117**, 8622–8648.