

Cite this: *RSC Adv.*, 2017, 7, 20451

# Facile synthesis of spinel $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$ microspheres with high activity for the catalytic combustion of diesel soot†

H. Zhao,<sup>ab</sup> X. X. Zhou,<sup>a</sup> L. Y. Pan,<sup>ab</sup> M. Wang,<sup>ab</sup> H. R. Chen<sup>id</sup>\*<sup>ac</sup> and J. L. Shi<sup>ac</sup>

A series of Cu–Mn mixed oxides were prepared *via* a facile co-precipitation method and used as catalysts for diesel soot combustion in  $\text{NO}_x/\text{O}_2/\text{N}_2$ . It is found that the chemical composition in the Cu–Mn mixed oxides has a significant influence on both morphology and catalytic activity. When the Cu/Mn atomic ratio was optimized to be 1, a distinctive pure spinel phase of  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  was obtained (named Cu1Mn1), which exhibited superior catalytic activity (e.g., finishing combustion temperature ( $T_f$ ) = 360 °C, in loose contact mode). The excellent catalytic activity of Cu1Mn1 was mainly attributed to the following aspects: (1) distinct morphological features: the well-dispersed Cu1Mn1 microspheres with a rough surface could contact soot particles sufficiently, and the stacked pores between the loosely packed nanoparticles within the microspheres could facilitate the diffusion of gaseous  $\text{O}_2$ , NO and  $\text{NO}_2$ ; and (2) the high intrinsic activity of the  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase: the abundant adsorbed oxygen species ( $\text{O}_{\text{ads}}$ ) is beneficial to the direct oxidation of soot into  $\text{CO}_2$ , and the enormous  $\text{Cu}^+-\text{Mn}^{\lambda+}$  ( $\lambda = 3, 4$ , hereinafter inclusive) cation pairs could facilitate the production of the strong oxidant  $\text{NO}_2$ , and the interaction between  $\text{Cu}^{2+}$  and  $\text{NO}_2$  would lead to high enhancement efficiency of  $\text{NO}_2$  for soot combustion. This facile strategy for the high activity spinel phase towards catalytic soot combustion shows great promise for practical applications.

Received 16th February 2017  
Accepted 4th April 2017

DOI: 10.1039/c7ra01971h

rsc.li/rsc-advances

## Introduction

The diesel particulate filter (DPF) has been developed for many years as an effective device to trap over 90% of diesel soot, which would otherwise lead to a rise in  $\text{PM}_{2.5}$  and thus serious health problems in human beings.<sup>1,2</sup> DPF with trapped soot is usually regenerated in a positive way, such as fuel post-injection, which is applied to increase the exhaust temperature (usually below 400 °C) up to the soot ignition temperature (~600 °C).<sup>3,4</sup> But there remain several limitations for industrial application, such as fuel overconsumption and thermal damage to the filter.

Hence, reforming of DPF with a catalyst coating has been proposed to reduce the ignition temperature of the trapped soot. Many kinds of catalysts have been proposed and investigated, e.g. the noble metals,<sup>5</sup> transition metal oxides,<sup>6</sup> perovskite and/or perovskite-like mixed oxides,<sup>7</sup> spinel mixed oxides,<sup>8</sup> alkaline/alkaline-earth metal oxides,<sup>9</sup> ceria-based oxides,<sup>10</sup> *etc.* Thereinto, noble metal-based catalysts with a three-dimensional ordered macroporous (3DOM) support<sup>11</sup> or a cordierite support<sup>12</sup> are among the best candidates with outstanding catalytic performance, which can decrease the  $T_f$  of soot combustion to as low as 400 °C. Nevertheless, the high cost and sulfur sensitivity of noble metal,<sup>13,14</sup> would impose a severe restriction on its industrial application.

As one of the promising substitutes for noble metal based catalysts, copper manganese spinel-type mixed oxides have been reported to be well suitable for various catalytic processes, e.g., total oxidation of volatile organic compounds,<sup>15</sup> steam reforming of methanol,<sup>16</sup> water gas shift reaction,<sup>17</sup> and low temperature reduction of  $\text{NO}$ ,<sup>18</sup> demonstrating versatile application potential. The physicochemical properties of these spinel-type compounds mainly depend on the type, charge and distribution in tetrahedral/octahedral sites of the cations.<sup>19</sup> Spinel can be divided into stoichiometric ( $\text{AB}_2\text{O}_4$ ) and non-stoichiometric spinels ( $\text{A}_x\text{B}_{3-x}\text{O}_4$ ) types, where A, B stand for two kinds of cations, and the subscripts are the atomic ratio of A, B and O atom. The ion distribution in  $\text{A}_x\text{B}_{3-x}\text{O}_4$  is rather complex, e.g.,

<sup>a</sup>State Key Laboratory of High Performance Ceramics and Superfine Microstructure, Shanghai Institute of Ceramics Chinese Academy of Sciences, 1295 Ding-Xi Road, Shanghai 200050, P. R. China. E-mail: hrchen@mail.sic.ac.cn


<sup>b</sup>University of Chinese Academy of Sciences, Beijing, 100049, P. R. China

<sup>c</sup>Jiangsu National Synergetic Innovation Center for Advanced Materials (SICAM), Nanjing, P. R. China

† Electronic supplementary information (ESI) available: Characteristic temperatures ( $T_i$ ,  $T_m$  and  $T_f$ ) and selectivity to  $\text{CO}_2$  for catalytic soot combustion over all studied catalysts and non-catalyzed reference;  $\text{N}_2$  adsorption/desorption isotherms & pore size distributions of all studied catalysts; specific surface areas, pore volumes and average pore diameters of all studied catalysts; SEM image and corresponding EDS spectrum of Cu1Mn2; SEM image and corresponding EDS spectrum of Cu1Mn1; STEM image of Cu1Mn1; catalytic soot oxidation in  $\text{O}_2/\text{N}_2$  under loose contact mode over all studied catalysts; catalytic NO oxidation over CuO, Cu1Mn1 and  $\text{MnO}_2$ ; catalytic soot combustion over CuO, Cu1Mn1 and  $\text{MnO}_2$  with or without NO. See DOI: 10.1039/c7ra01971h



$\text{Cu}_x\text{Mn}_{3-x}\text{O}_4$  with four kinds of cations, shows a configuration of  $[\text{Cu}_a^{+}\text{Mn}_b^{2+}\text{Cu}_c^{2+}\text{Mn}_{1-a-b-c}^{3+}]_\alpha[\text{Cu}_{x-a-c}^{2+}\text{Mn}_{3-2x-b+c}^{3+}\text{Mn}_{x+a+b-1}^{4+}]_\beta\text{O}_4$ , where the subscripts except  $\alpha$  and  $\beta$  are for the atomic ratios of the ions in specific sites.<sup>20</sup> When  $x$  in  $\text{Cu}_x\text{Mn}_{3-x}\text{O}_4$  is adjusted, different structural, electrical or magnetic properties can be realized. For example,  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  ( $[\text{Cu}^{+}]_\alpha[\text{Cu}_{0.5}^{2+}\text{Mn}_{1.5}^{4+}]_\beta\text{O}_4$ ) contains abundant  $\text{Cu}^{+}$  and  $\text{Mn}^{4+}$  cations (arising from reaction (1)),<sup>21,22</sup> which are respectively stabilized in the tetrahedral and octahedral sites without the need of a stabilizing agent.<sup>20</sup> This  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase is expected to be much beneficial for diesel soot combustion, since the high concentration of  $\text{Cu}^{+}$  and  $\text{Mn}^{4+}$  cations could activate  $\text{O}_2$  and  $\text{NO}_x$  in the diesel exhaust, respectively, thus facilitating  $\text{NO}_2$  production.



Our previous work confirmed that the spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  loaded on zeolite beta could exhibit excellent activity for catalytic soot combustion, which was partially attributed to the synergetic catalytic effect between the valence-changeable copper and manganese cations within the spinel phase.<sup>23</sup> However, there still remain several drawbacks, such as complexity in preparation and the limited loading amount of active spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$ . In this work, a facial, scalable and environmentally-friendly co-precipitation method was utilized to prepare a series of Cu–Mn mixed oxides with different Cu/Mn atomic ratios as catalysts for soot combustion. Thereinto, Cu1Mn1 (atomic ratio of Cu : Mn equals to 1 : 1) with a pure spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase exhibits the best activity, showing a much low  $T_f$  value of 360 °C even compared to the reported 400 °C.<sup>11,12</sup> Multiple measurements have been conducted to reveal the reason for the high activity of  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase. A plausible mechanism for soot combustion over Cu1Mn1 is also proposed.

## Experimental

### Catalyst preparation

All the chemicals used in this study were of analytical grade, and were used without further purification. Cu–Mn mixed oxides were prepared by the co-precipitation method as reported before with some modification.<sup>24</sup> The whole procedure was performed at room temperature except the drying and calcination steps. A typical preparation procedure was as follows: firstly, 7.5 mmol of nitrates including  $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$  and  $\text{Mn}(\text{NO}_3)_2$  (50 wt% in aqueous solution) with different Cu/Mn atomic ratios were thoroughly dissolved in 30 mL of deionized water under stirring. Then, another 30 mL of deionized water with 30 mmol of  $\text{NaHCO}_3$  dissolved in it was quickly poured into the nitrate solution and was left to react for 30 min with the pH of the solution reaching a final value of 8–9. The precipitates were centrifuged and rinsed thoroughly with deionized water and absolute ethyl alcohol alternately for several times until the residual Na content in the supernatant was below 0.5 wt% (measured by inductively coupled plasma-atomic emission spectrometry, ICP-AES). After drying at 100 °C, the as-prepared samples were grinded and then calcined under static air at

500 °C for 2 h with a heating rate of 1 °C min<sup>−1</sup>. For ease of reference, the prepared catalysts are designated  $\text{Cu}_x\text{Mn}_y$ , where  $x : y$  stands for the Cu : Mn atomic ratio in the recipe. In addition, single oxide CuO or  $\text{MnO}_2$  for reference was also prepared with the same synthesis procedure in the absence of  $\text{Mn}(\text{NO}_3)_2$  or  $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$ .

### Characterizations

Powder X-ray diffraction (XRD) patterns of the prepared samples were obtained using a Rigaku D/Max 2200 PC diffractometer with Cu K $\alpha$  radiation (40 kV and 40 mA). The nitrogen adsorption and desorption curves were recorded using Micromeritics Tristar 3000 at 77 K, and the specific surface area (SSA) and the pore size distribution were calculated using the Brunauer–Emmett–Teller (BET) and Barrett–Joyner–Halenda (BJH) methods, respectively. Scanning transmission electron microscopic (STEM) and elements mapping imaging were performed using Hitachi S-4800. X-ray photoelectron spectroscopy (XPS) signals were recorded using an ESCALAB250 instrument. The fitting of the Mn element was carried out using Gaussian fitting parameters. The diffuse reflectance infrared Fourier transform (DRIFT) spectra were obtained at different temperatures in the range of RT–400 °C, using a Thermo-Scientific Nicolet FT-IR model iS10 equipped with an *in situ* DRIFTS cell (Harric Scientific Inc.) and a gas flow system. The pre-mixed catalyst/soot (mass ratio = 10 : 1, in total of 3 mg) was diluted with KBr powder (80 mg) and then filled into the DRIFTS cell. The DRIFTS cell was then exposed to certain reactant gas mixtures (350 ppm NO, 10% O<sub>2</sub>, and N<sub>2</sub> as balance, total flow = 200 mL min<sup>−1</sup>), and the spectra were recorded after the temperature was stable for 20 min for each temperature. The temperature-programed reduction with hydrogen (H<sub>2</sub>-TPR) experiments were performed using a Micromeritics Chemisorb 2750 instrument in a 5% H<sub>2</sub>/N<sub>2</sub> flow (25 mL min<sup>−1</sup>) using 50 mg catalyst with a heating rate of 10 °C min<sup>−1</sup>. The uptake amount of H<sub>2</sub> was measured using a thermal conductivity detector (TCD). Na content was analyzed by means of ICP-AES.

### Catalytic activity measurements

Carbon black from Degussa (Printex U, diameters: 10–50 nm) was used as the model soot particles. Following a well-accepted procedure,<sup>23</sup> the model soot particles (10 mg) and catalyst (100 mg) were carefully mixed for 20 min with a spatula to simulate the loose contact mode. Then, the mixture was loaded in a quartz tube (i.d. 6.0 mm), after mixing with 1 g silica pellets to avoid pressure drop and favor heat transfer. A gas mixture of 350 ppm NO, 10% O<sub>2</sub> and balance N<sub>2</sub> was feed with a flow rate of 200 mL min<sup>−1</sup>, leaving the space velocity to be 120 000 mL g<sup>−1</sup> h<sup>−1</sup>. The mixture was then heated at a rate of 5 °C min<sup>−1</sup> in a tube furnace equipped with a thermal couple. To minish the error of the measurement to a least extent, every gas flow was confirmed by a mechanical gas flowmeter and the concentration of NO<sub>x</sub> was verified by a NO<sub>x</sub> analyzer (Thermo Fisher 42i-LS). The analysis of the emissions from the reactor was performed using an online GC-FID analyzer equipped with a methane converter. The catalytic activities (conversion and



selectivity) were calculated as indicated in previous reports in the literature,<sup>10,25</sup> in terms of  $T_i$ ,  $T_m$  and  $T_f$ , which were defined as the temperatures at 10%, 50% and 90% of soot conversion, respectively, as well as the selectivity to  $\text{CO}_2$  ( $S_{\text{CO}_2}$ ), which was defined as the integrated  $\text{CO}_2$  outlet amount divided by integrated  $\text{CO}_x$  (containing CO and  $\text{CO}_2$ ) outlet amount during the whole combustion process. For the repeated activity tests, the spent catalyst, still mixed with silica pellets, was recharged with fresh soot particles (10 mg), followed by a thorough mixing using a spatula to simulate the loose soot–catalyst contact. Following the identical procedure to that described above, the activity tests were repeated 5 times.

## Results and discussion

### Soot combustion catalytic activity

Fig. 1a shows the catalytic activities of different  $\text{Cu}_x\text{Mn}_y$  catalysts and reference CuO and  $\text{MnO}_\delta$  towards soot combustion in  $\text{NO}_x/\text{O}_2/\text{N}_2$  (catalyst–soot in loose contact mode). It is clear that all the catalysts can greatly promote soot combustion, and improve the selectivity to  $\text{CO}_2$  formation from ~60% to over 90% (Table S1†). Especially, Cu1Mn1 exhibits the best catalytic activity with the lowest characteristic temperatures (temperature of maximum soot combustion rate ( $T_m$ ) = 330 °C, and  $T_f$  = 360 °C), which are desirably within the temperature range of diesel exhaust (175–400 °C).<sup>3</sup> Additionally, it is worth noting that both Cu2Mn1 and Cu1Mn2 show lower catalytic activity than CuO, indicating that suitable Cu/Mn ratio (1 : 1 in this case), which could lead to a strong synergetic effect, is crucial to the enhanced catalytic activity. Moreover, the reusability of the optimized Cu1Mn1 is observed to be of excellence (Fig. S1†), with  $T_f$  and  $T_m$  below 380 and 370 °C, respectively, even after 5 runs of repeated catalytic soot combustion tests. It should be noted that the slight loss of catalytic activity in repeated tests

could be mainly attributed to the inevitable catalyst mass loss. Additionally, the selectivity of  $\text{CO}_2$  was kept ~95% in the repeated tests, also demonstrating the stable and excellent catalytic activity. The effect of the residual Na species in Cu1Mn1 on the catalytic activity for soot combustion has also been investigated. As shown in Fig. S2 and S3,† the residual Na species (0.32 wt% by ICP-AES) impose no obvious influences on the catalytic activity of the spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase.

To get a kinetics insight into the catalytic soot combustion over CuO,  $\text{Cu}_x\text{Mn}_y$  and  $\text{MnO}_\delta$ , the corresponding Arrhenius curves (Fig. 1b) were plotted from the  $\text{CO}_x$  concentration–temperature curves shown in Fig. S4† using an integral method.<sup>26</sup> The kinetics parameters, such as apparent activation energy ( $E_a$ ) and frequency factor ( $A$ ) are derived from the Arrhenius plots and summarized in Table 1, according to the Arrhenius equation:  $\ln k = \ln A - E_a/RT$ , where  $k$  is specific reaction rate,  $R$  is molar gas constant,  $T$  is temperature in Kelvin. As can be seen in Table 1, the value of  $E_a$  gradually decreases with increasing Mn content, reaching the highest in CuO (140.0 kJ mol<sup>−1</sup>) and the lowest in  $\text{MnO}_\delta$  (48.1 kJ mol<sup>−1</sup>), while keeping roughly constant in  $\text{Cu}_x\text{Mn}_y$  (100–116 kJ mol<sup>−1</sup>),

Table 1 Apparent activation energy, “ln A” values and lattice constant derived from XRD patterns of different catalysts

Catalyst	CuO	Cu2Mn1	Cu1Mn1	Cu1Mn2	MnO <sub>δ</sub>
$E_a^{[a]}$ (kJ mol <sup>−1</sup> )	140.0	115.8	115.6	100.7	48.1
$\ln A^{[a]}$	27.37	21.97	23.70	18.49	9.16
Lattice constant <sup>[b]</sup> (Å)	$a = 4.687$ $b = 3.433$ $c = 5.134$	8.279	8.283	8.266	9.414

<sup>a</sup> Derived from the  $\ln k - 1/T$  plots in Fig. 1b according to Arrhenius equation:  $\ln k = \ln A - E_a/RT$ . <sup>b</sup> Derived from XRD patterns shown in Fig. 2.

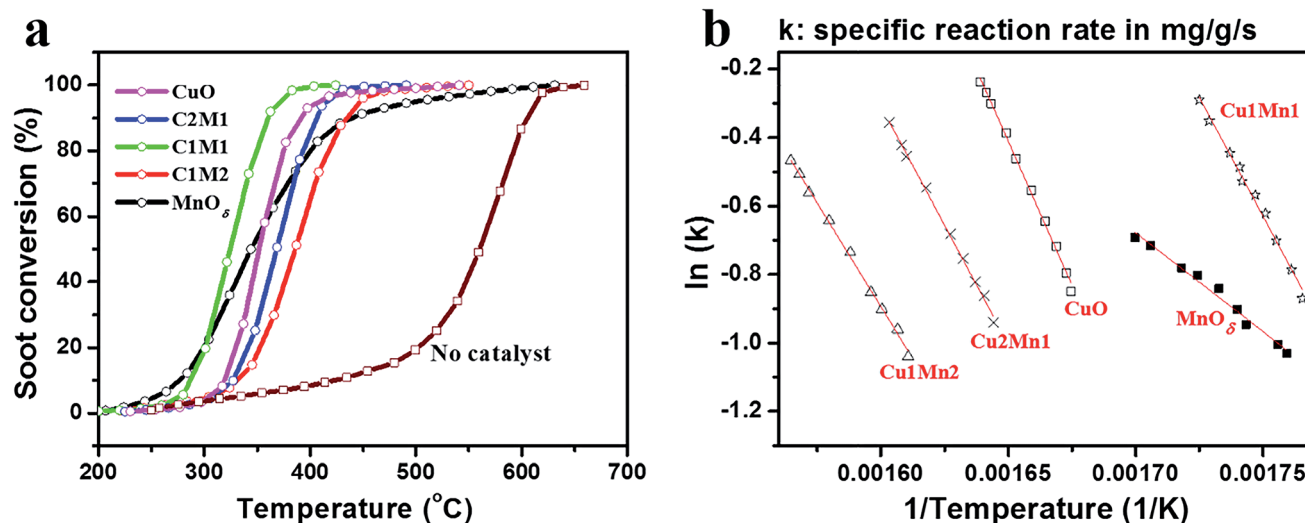


Fig. 1 Soot combustion performance without catalyst, or with different catalysts under loose contact mode (a), and the corresponding Arrhenius plots (b) (reaction conditions: 350 ppm NO and 10%  $\text{O}_2$  in  $\text{N}_2$  with a total flow of 200 mL min<sup>−1</sup>, mass of soot–catalyst–silica is 10–100–1000 mg).



indicating the similar catalysis mechanism for soot combustion over  $\text{Cu}_x\text{Mn}_y$ . Additionally, as shown in Table 1,  $\text{CuO}$  and  $\text{Cu1Mn1}$  show higher ( $\ln A$ ) values among all the catalysts, while  $\text{MnO}_2$  possesses the lowest one. Therefore, according to the Arrhenius equation, it can be inferred that  $\text{Cu1Mn1}$  could show the best catalytic activity, as confirmed in Fig. 1b, where  $\text{Cu1Mn1}$  can achieve high ( $\ln k$ ) value even at the largest  $1/T$  (i.e., the lowest temperature). More detailed characterizations were conducted and analyzed as follows.

### Physical and textural properties

The XRD patterns of different  $\text{Cu}_x\text{Mn}_y$  oxides and reference  $\text{MnO}_2$  and  $\text{CuO}$  are displayed in Fig. 2, and the corresponding lattice constant data are listed in Table 1. Apparently, all the samples show well crystallization. Thereinto,  $\text{CuO}$  presents pure phase of monoclinic  $\text{CuO}$ , while  $\text{MnO}_2$  exhibits mixed  $\text{MnO}_2$ – $\text{Mn}_2\text{O}_3$  phases, suggesting the co-existence of Mn species with different valence states. Interestingly, only  $\text{Cu1Mn1}$  possesses pure spinel phase of  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$ . Whereas,  $\text{Cu2Mn1}$  shows a secondary  $\text{CuO}$  phase besides the predominant spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$ ; and in  $\text{Cu1Mn2}$ , some amorphous or highly dispersed manganese oxides co-exist with the main spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$ . More interestingly, it is worth noting that the crystallinity of  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  spinel phase decreases in the order of  $\text{Cu1Mn1} > \text{Cu2Mn1} > \text{Cu1Mn2}$ , which presents the same tendency with the order of catalytic activity (Fig. 1a). Thus it is reasonable to assume that a well-crystallized  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  spinel phase could be mainly responsible for the improved catalytic activity towards soot combustion over  $\text{Cu}_x\text{Mn}_y$ . Detailed information about the SSA and pore structure for each catalyst can be found in Fig. S5 and Table S2.† Thereinto,  $\text{Cu1Mn1}$  shows the lowest SSA value among  $\text{Cu}_x\text{Mn}_y$ , consistent with its highest crystallinity (Fig. 2). Nevertheless,  $\text{Cu1Mn1}$  exhibits the highest activity towards catalytic soot combustion, demonstrating the high intrinsic activity of the spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase.

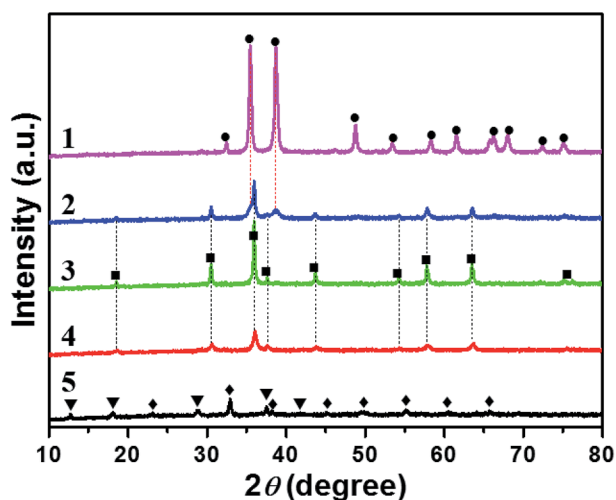


Fig. 2 XRD patterns of different samples, (1)  $\text{CuO}$ , (2)  $\text{Cu2Mn1}$ , (3)  $\text{Cu1Mn1}$ , (4)  $\text{Cu1Mn2}$  and (5)  $\text{MnO}_2$ . ●  $\text{CuO}$  (JCPDS 80-1916), ■  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  (JCPDS 70-0260), ▼  $\text{MnO}_2$  (JCPDS 72-1982), ◆  $\text{Mn}_2\text{O}_3$  (JCPDS 73-1826).

Furthermore, the characterization of morphology and chemical composition of these catalysts was conducted for comparison.

### Morphology

The different morphology and elemental distribution images of  $\text{Cu2Mn1}$ ,  $\text{Cu1Mn1}$  and  $\text{Cu1Mn2}$  are depicted in Fig. 3. It is clear that well-dispersed microspheres and nanoparticles co-exist in  $\text{Cu2Mn1}$ , and the microspheres show uniform distribution of Cu and Mn species while the nanoparticles mainly consist of copper oxide species. Whereas,  $\text{Cu1Mn2}$  presents a unique core-shell structure, with uniformly-distributed Cu and Mn species in the core and excessive Mn species in the shell (Fig. S6,†  $\text{Mn/Cu} > 1.3$ ).

Different from either  $\text{Cu2Mn1}$  or  $\text{Cu1Mn2}$ , only homogeneous microspheres occur in  $\text{Cu1Mn1}$ . Combined with the XRD results in Fig. 2, it can be inferred that the microspheres in  $\text{Cu2Mn1}$  and  $\text{Cu1Mn1}$ , as well as the inner core in  $\text{Cu1Mn2}$  all belong to the spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase. The typical SEM image and corresponding EDS result of  $\text{Cu1Mn1}$  shown in Fig. S7,† confirm that Cu/Mn atomic ratio in  $\text{Cu1Mn1}$  is close to 1 : 1, which is in good consistence with the composition of  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase. In addition,  $\text{Cu1Mn1}$  microspheres present rather rough surface, different from the smooth surface in  $\text{Cu1Mn2}$ . The STEM image with high magnification of  $\text{Cu1Mn1}$  (Fig. S8†) reveals that the microsphere rough surface is derived from the loosely-packed nanoparticles with particle size of around 20–30 nm and the stacked pores within them. Therefore, the following two aspects are believed to mainly contribute to the excellent catalytic activity of  $\text{Cu1Mn1}$ : (1) the pure  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase without extra components (e.g.,  $\text{CuO}$  nanoparticles in  $\text{Cu2Mn1}$  and the Mn-rich shell in  $\text{Cu1Mn2}$ ) benefits the sufficient contact between soot and the active sites on catalyst surface, and (2) the well-dispersion and rough surface of  $\text{Cu1Mn1}$  microspheres both favor the sufficient contact between catalyst and soot particles, and the presence of stacked pores within the microspheres is also helpful for the diffusion of gaseous reactant or product, such as  $\text{O}_2$ ,  $\text{NO}$  and  $\text{NO}_2$ .

### Surface composition measured with XPS

The deconvolutions of the O 1s, Mn 2p and Cu 2p spectra of  $\text{Cu}_x\text{Mn}_y$  oxides and the reference  $\text{MnO}_2$  and/or  $\text{CuO}$  are shown in Fig. 4. The O 1s spectrum can be well fitted into a main peak located at 529.6–529.7 eV that is assigned to the lattice oxygen, and several peaks with higher binding energies corresponding to different kinds of absorbed oxygen species.<sup>27</sup> The Mn 2p<sub>3/2</sub> XPS spectrum is composed of three peaks, i.e., peaks at 640.4–640.6, 641.7–642.1 and 643.8–644.0 eV corresponding to  $\text{Mn}^{2+}$ ,  $\text{Mn}^{3+}$  and  $\text{Mn}^{4+}$ , respectively,<sup>28,29</sup> and a satellite peak at 646.8–648.4 eV belonging to the  $\text{MnO}$  satellite feature.<sup>30</sup> As for the Cu 2p XPS spectrum, it is clearly found that the  $\text{Cu}_x\text{Mn}_y$  mixed oxides show great difference from pure  $\text{CuO}$ . Cu 2p<sub>3/2</sub> spectrum of  $\text{CuO}$  exhibits two peaks, i.e., the main one at 932.7 eV corresponding to  $\text{Cu}^+$  and another one at 934.0 eV due to  $\text{Cu}^{2+}$ ,<sup>31</sup> while the Cu 2p<sub>3/2</sub> spectra of  $\text{Cu}_x\text{Mn}_y$  show peaks at much lower binding energies of 930.7–930.8 eV ( $\text{Cu}^+$  in  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$ ), and 933.4–933.7 eV ( $\text{Cu}^{2+}$  in  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$ ).<sup>32</sup> The remarkable





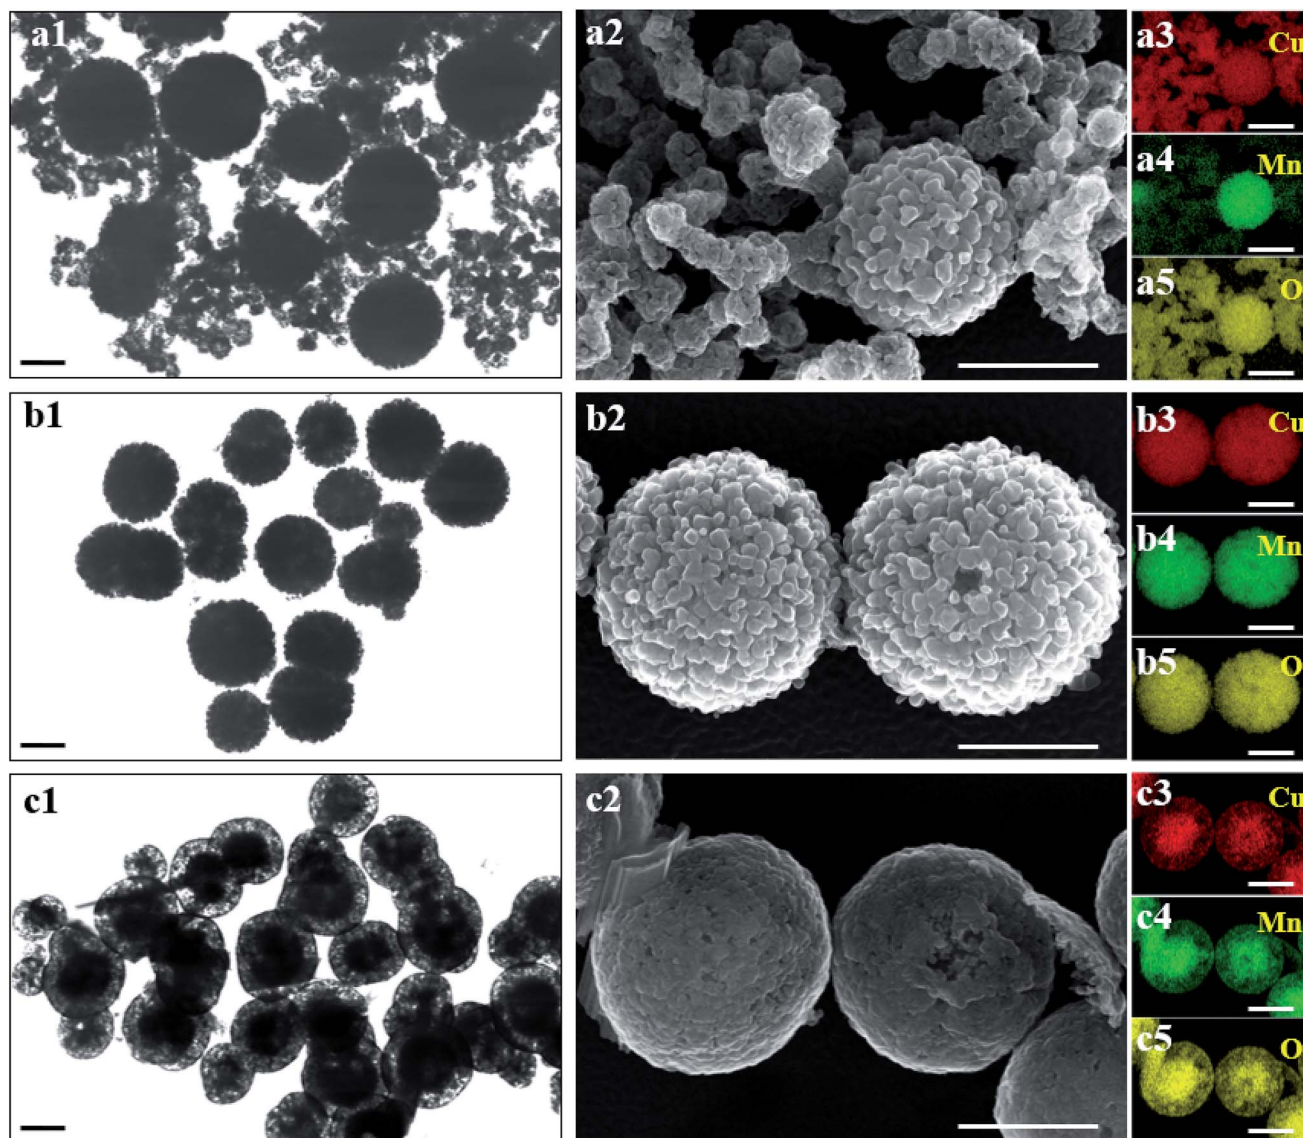


Fig. 3 Typical STEM images (a1, b1, c1), SEM images (a2, b2, c2) and the corresponding elemental mapping (a3–a5, b3–b5, c3–c5) of Cu<sub>2</sub>Mn<sub>1</sub> (a1–a5), Cu<sub>1</sub>Mn<sub>1</sub> (b1–b5) and Cu<sub>1</sub>Mn<sub>2</sub> (c1–c5) samples. Scale bars: 400 nm.

difference in the peak position highlights the great difference in chemical environment between CuO and Cu<sub>1.5</sub>Mn<sub>1.5</sub>O<sub>4</sub>.

Table 2 lists the quantified results of the XPS analysis for Cu<sub>x</sub>Mn<sub>y</sub> oxides, MnO<sub>δ</sub> and CuO. It is clearly observed that it is Mn<sup>3+</sup> instead of Mn<sup>4+</sup> (Cu<sub>1.5</sub>Mn<sub>1.5</sub>O<sub>4</sub> = Cu<sub>1.0</sub><sup>+</sup>Cu<sub>0.5</sub><sup>2+</sup>Mn<sub>1.5</sub><sup>4+</sup>O<sub>4</sub><sup>2-</sup>), that dominates in the Mn 2p spectra for all the Cu<sub>x</sub>Mn<sub>y</sub> catalysts, confirming the existence of the redox equilibrium (Cu<sup>+</sup> + Mn<sup>4+</sup> ↔ Mn<sup>3+</sup> + Cu<sup>2+</sup>) in the Cu<sub>1.5</sub>Mn<sub>1.5</sub>O<sub>4</sub> phase.<sup>21,22</sup> As for Cu species, the Cu<sup>+</sup> proportion on catalyst surface rises with increasing Mn content in Cu<sub>x</sub>Mn<sub>y</sub>, reaching a maximum value in Cu<sub>1</sub>Mn<sub>2</sub> (69.6%), which is, however, still lower than that in reference CuO (78.7%). This extremely high Cu<sup>+</sup> proportion in CuO, which can be verified by the rather weak Cu<sup>2+</sup> satellite peak for CuO in Fig. 4c, corresponds well with its highest ratio of O<sub>ads</sub>/O (shown in Table 3), since the reduction of Cu<sup>2+</sup> in CuO is always accompanied by

the generation of oxygen vacancies (V<sub>O</sub>).<sup>33</sup> The interaction between Cu and Mn species through electron exchange is also verified by H<sub>2</sub>-TPR measurement, as shown in Fig. S9,† where H<sub>2</sub> reduction of Cu<sub>x</sub>Mn<sub>y</sub> occurs at much lower temperatures than that for either CuO or MnO<sub>δ</sub>. It should be mentioned that there is inconsistency between the activity order and reducibility order, as previously reported,<sup>34</sup> which could be attributed to the difference in chemical and structural properties between H<sub>2</sub> and soot, *e.g.*, reactive species at the inner pores surface can be attacked by H<sub>2</sub> molecule, but are unavailable for soot particles. Nevertheless, H<sub>2</sub>-TPR results firmly prove the existence of Cu–Mn synergetic effect in the prepared Cu<sub>x</sub>Mn<sub>y</sub> catalysts.

As reported by previous works, Cu<sup>+</sup>–Mn<sup>2+</sup> cation pair can serve as active site for NO<sub>2</sub> production, since Cu<sup>+</sup> and Mn<sup>2+</sup> can facilitate the adsorption and activation of O<sub>2</sub> and NO, respectively.<sup>35,36</sup> Therefore a parameter “Ω” was introduced (defined in



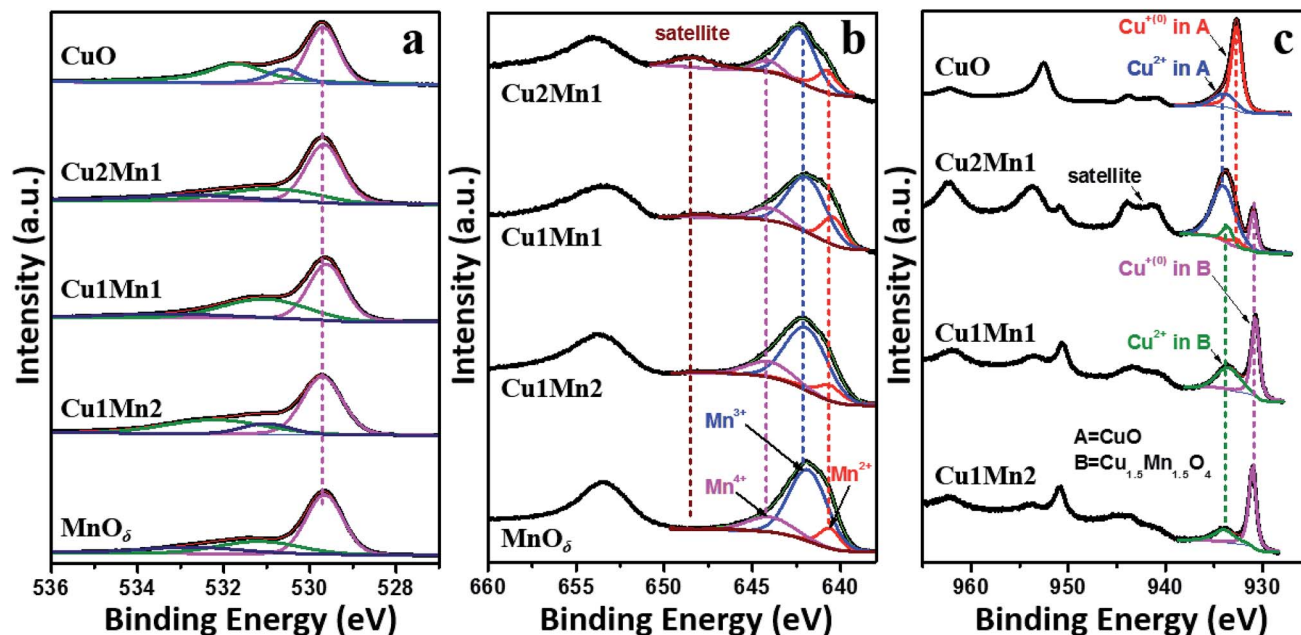


Fig. 4 The XPS spectra of different catalysts, O 1s (a), Mn 2p (b) and Cu 2p (c).

Table 2 XPS surface composition analysis of different catalysts

Catalysts	Mn <sup>x+</sup> /Mn <sup>[a]</sup>			Cu <sup>x+</sup> /Cu <sup>[b]</sup>	
	Mn <sup>2+</sup> (%)	Mn <sup>3+</sup> (%)	Mn <sup>4+</sup> (%)	Cu <sup>+</sup> (%)	Cu <sup>2+</sup> (%)
CuO				78.7	21.3
Cu2Mn1	23.3	65.4	11.2	23.6	76.4
Cu1Mn1	19.7	66.8	13.5	60.0	40.0
Cu1Mn2	14.2	68.0	17.7	69.6	30.4
MnO <sub>δ</sub>	11.5	69.9	18.6		

<sup>a</sup> The whole Mn species with various valence states. <sup>b</sup> The whole Cu species with various valence states.

Table 3 Comparison of  $T_m'$  vs.  $O_{ads}$  proportion, and  $\Delta T_m$  vs.  $\Omega$

Catalysts	$T_m'$ <sup>[a]</sup> (°C)	$O_{ads}/(O_{ads} + O_{latt})$ <sup>[b]</sup>	$\Delta T_m$ <sup>[c]</sup> (°C)	$\Omega$
CuO	379	0.50		
Cu2Mn1	414	0.40	41	1.42
Cu1Mn1	397	0.49	73	2.14
Cu1Mn2	403	0.46	17	1.08
MnO <sub>δ</sub>	413	0.43		

<sup>a</sup>  $T_m'$  is for the catalytic soot combustion in  $O_2/N_2$  (Fig. S10). <sup>b</sup>  $O_{latt}$ : lattice oxygen. <sup>c</sup>  $\Delta T_m = T_m' - T_m$ , where  $T_m$  is for the catalytic soot combustion in  $NO_x/O_2/N_2$  (Fig. 1a).

eqn (2)) to quantify the concentration of  $Cu^+-Mn^{\lambda+}$  cation pair in different  $Cu_xMn_y$  catalysts.

$$\Omega = \{ (Cu^+/Cu) \cdot [Cu/(Cu + Mn)] \} / \{ (Mn^{2+}/Mn) \cdot [Mn/(Cu + Mn)] \} \quad (2)$$

where, Cu (or Mn) stands for all the Cu (or Mn) species with different valence states, and all the atomic ratios are obtained

by XPS measurement. The  $\Omega$  values as well as the  $O_{ads}$  proportions for different catalysts are summarized in Table 3.


Catalytic activity measurement in the absence of  $NO_x$  ( $O_2/N_2$ ) was also conducted in an attempt to find the key factors determining the catalysis performance. The catalytic behavior in  $O_2/N_2$  (represented by  $T_m'$ ) was shown in Table 3. It's clearly observed that the higher ratio of  $O_{ads}/(O_{ads} + O_{latt})$ , the lower value of  $T_m'$  (the better catalytic activity), which is in good coincidence with the widely accepted "Active Oxygen Mechanism",<sup>37</sup> wherein soot is directly oxidized by the reactive oxygen species on catalyst surface. Additionally, it is worth noting that CuO with a slightly higher  $O_{ads}$  proportion than Cu1Mn1, possesses much better catalytic activity in  $O_2/N_2$ , indicating that the highest  $Cu^+$  proportion in CuO could make extra contribution to its superb activity.

Additionally, a new parameter " $\Delta T_m$ " was introduced to quantify the enhancement efficiency of  $NO_x$  for catalytic activity of different  $Cu_xMn_y$ , as shown in Table 3. It is interesting to find that Cu1Mn1 with the highest  $\Omega$  value (2.14) shows the greatest  $NO_x$  enhancement efficiency (corresponding to the largest  $\Delta T_m$  value of 73 °C), suggesting that in addition to "Active Oxygen Mechanism", the  $Cu^+-Mn^{\lambda+}$  pairs as active sites could also promote the catalytic soot combustion by improving  $NO_2$  production. Therefore, it is believed that the catalytic soot combustion in  $NO_x/O_2/N_2$  over Cu1Mn1 follows both the "Active Oxygen Mechanism" and the "NO-aided Oxidation Mechanism".<sup>37</sup>

### Mechanism analysis


Based on the above discussion, combined "Active Oxygen Mechanism" and "NO-aided Oxidation Mechanism" for catalytic soot combustion over Cu1Mn1 was proposed, as shown in Scheme 1. Therein, the "Active Oxygen Mechanism" shown in






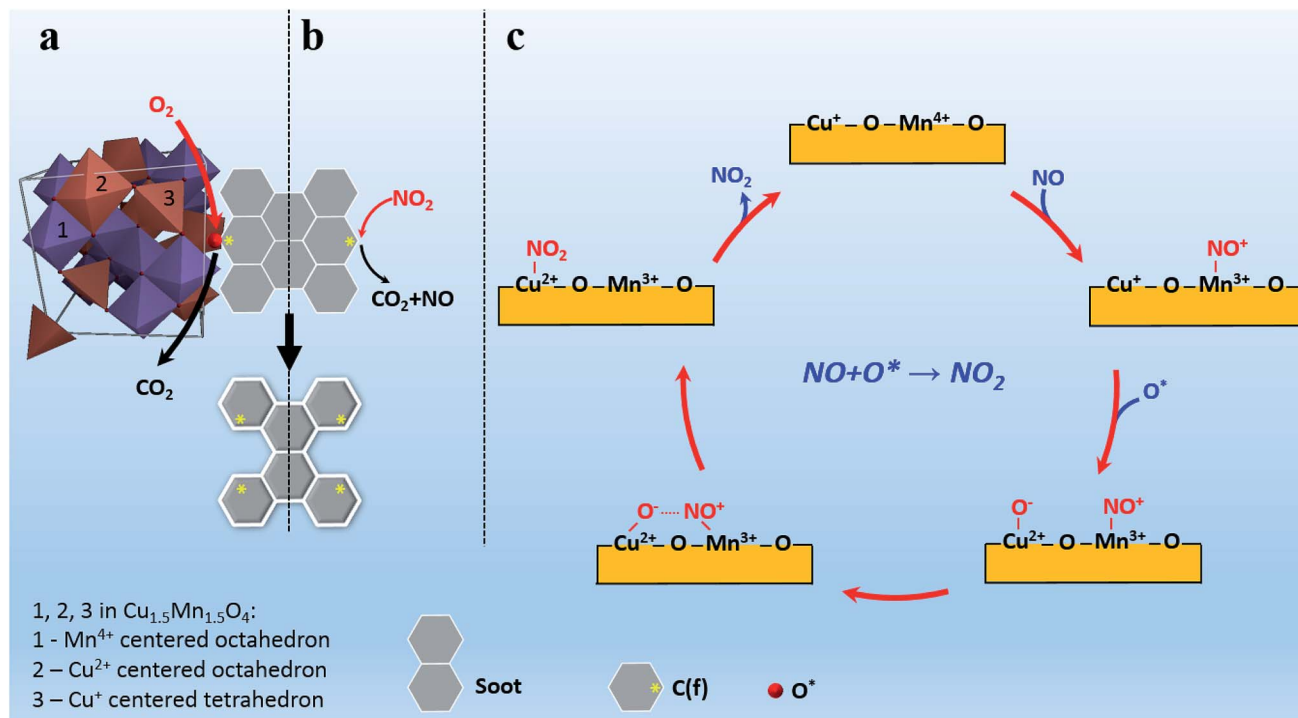


Scheme 1 Schematic illustrations of the possible combined catalytic mechanism, (a) "Active Oxygen Mechanism", (b) "NO-aided Oxidation Mechanism", (c) formation of  $\text{NO}_2$  in the "NO-aided Oxidation Mechanism".

Scheme 1a indicates that the active oxygen species ( $\text{O}^*$ ) can attack the nearby active sites on carbon surface [C(f)], producing carbon oxides (mostly  $\text{CO}_2$ ) and more C(f) (eqn (3)).<sup>38</sup> Afterwards, the spent oxygen species can be supplemented by gaseous  $\text{O}_2$ .<sup>37</sup>



Scheme 1b shows the schematic illustration of "NO-aided oxidation mechanism". Similar to  $\text{O}^*$  in the "Active Oxygen Mechanism",  $\text{NO}_2$  can also directly oxidize C(f) into  $\text{CO}_2$ , and regenerate more C(f) (eqn (4)).<sup>39</sup> The process of  $\text{NO}_2$  production over  $\text{Cu}^+-\text{Mn}^{\lambda+}$  cation pairs (herein,  $\text{Cu}^+-\text{Mn}^{4+}$  is taken as an example) is depicted in Scheme 1c.



$\text{Cu}^+$  cations in  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  can adsorb, then activate gaseous  $\text{O}_2$  to generate active oxygen (eqn (5)).<sup>35</sup> Similarly,  $\text{Mn}^{\lambda+}$  cations can also adsorb as well as activate NO in the feed gas, resulting in reactive nitrogen oxide ( $\text{NO}^+$ ) species (eqn (6)).<sup>36</sup> Then, the produced active species can easily react with each

other to form  $\text{NO}_2$ , as shown in eqn (7).<sup>36</sup> The obtained  $\text{NO}_2$ , as a stronger oxidant than  $\text{O}_2$ ,<sup>40</sup> can effectively accelerate soot combustion (Fig. S11†). Besides, it is worth noting that the  $\text{NO}_2$  molecules are inclined to adsorb on metal ions, e.g.,  $\text{Cu}^{2+}$ , producing  $\text{Cu}^{2+} \cdot \text{NO}_2$  species.<sup>41</sup>

The presence of such  $\text{Cu}^{2+} \cdot \text{NO}_2$  species could keep  $\text{NO}_2$  from effusion into the gas flow at low temperatures, and ensure the steady release of  $\text{NO}_2$  when heated (eqn (8)), thus realizing the full use of  $\text{NO}_2$ . This can well explain the finding that  $\text{MnO}_x$ , though with the higher  $\text{NO}_2$  producing activity than  $\text{CuMn1}$  (Fig. S12†), shows lower enhancement efficiency of  $\text{NO}_x$  for catalytic soot combustion, especially in high temperatures (Fig. S13†). After  $\text{NO}_2$  releasing, the active sites can be regenerated through reaction equilibrium  $\text{Mn}^{3+} + \text{Cu}^{2+} \leftrightarrow \text{Cu}^+ + \text{Mn}^{4+}$ , thus completing the catalysis circle.

To sum it up, the presence of enormous  $\text{O}_{\text{ads}}$  and  $\text{Cu}^+-\text{Mn}^{\lambda+}$  cation pairs on  $\text{CuMn1}$  surface mainly contributes to the extremely high intrinsic catalytic activity of the spinel  $\text{Cu}_{1.5}\text{Mn}_{1.5}\text{O}_4$  phase, and the interaction between  $\text{NO}_2$  and  $\text{Cu}^{2+}$  also ensures the sufficient utilization of  $\text{NO}_2$ .

#### In Situ DRIFT studies of soot combustion over CuMn1

To verify the mechanism shown in Scheme 1, DRIFT measurement was performed to investigate the existence and evolution of different types of absorbed species over CuMn1 during catalytic soot oxidation in  $\text{NO}_x/\text{O}_2/\text{N}_2$ , as shown in Fig. 5. It is clearly found that the intensity of the  $\text{NO}_2^-$  peak ca.  $1250 \text{ cm}^{-1}$  decreases with increasing temperatures (RT–400 °C),<sup>42</sup> and  $\text{NO}_3^-$  peak ca.  $1404 \text{ cm}^{-1}$  can be obviously observed at 400 °C.<sup>43</sup> The



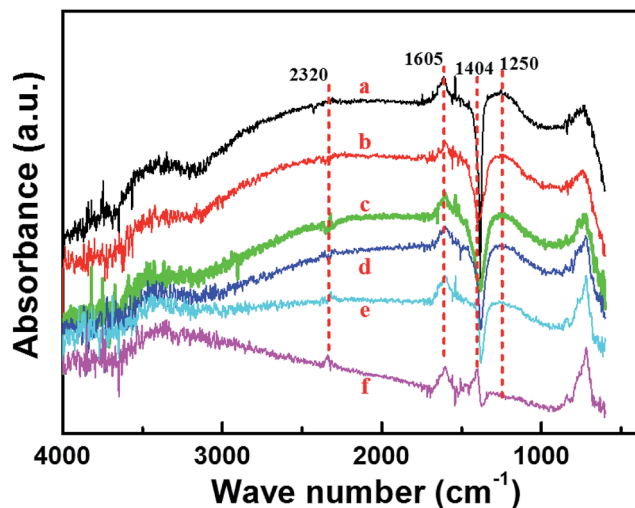


Fig. 5 *In situ* DRIFT spectra during the catalytic soot combustion on Cu<sub>1</sub>Mn<sub>1</sub> ((a) RT, (b) 100 °C, (c) 200 °C, (d) 300 °C, (e) 350 °C, (f) 400 °C). Feed gas: N<sub>2</sub> (balance) + O<sub>2</sub> (10%) + NO (350 ppm).

evolution of the NO<sub>2</sub><sup>-</sup> peak and the appearance of the NO<sub>3</sub><sup>-</sup> peak both indicate the gradual oxidation of NO<sub>x</sub> species on the catalyst surface with increasing temperature. In addition, the presence of both NO<sup>+</sup> (~2320 cm<sup>-1</sup>)<sup>44</sup> and the Cu<sup>2+</sup>·NO<sub>2</sub> intermediates (~1605 cm<sup>-1</sup>)<sup>42</sup> is also confirmed by the spectra.

## Conclusions

A facile co-precipitation method was utilized to prepare a series of Cu<sub>x</sub>Mn<sub>y</sub> oxides to catalyze the combustion of diesel soot in NO<sub>x</sub>/O<sub>2</sub>/N<sub>2</sub>. Among, Cu<sub>1</sub>Mn<sub>1</sub> with a pure phase of spinel-type Cu<sub>1.5</sub>Mn<sub>1.5</sub>O<sub>4</sub>, shows the optimized catalytic activity (*T<sub>f</sub>* = 360 °C, under loose contact mode), owing to both its beneficial morphological features and high intrinsic activity. The well-dispersed rough microspheres in Cu<sub>1</sub>Mn<sub>1</sub> could facilitate soot combustion by improving the contact between soot and the active sites on catalyst surface. Besides, the presence of stacked pores among the loosely-packed nanoparticles within the microspheres is also helpful for the diffusion of gaseous reactant or product, such as O<sub>2</sub>, NO and NO<sub>2</sub>. Apart from these beneficial morphological features, the pure spinel Cu<sub>1.5</sub>Mn<sub>1.5</sub>O<sub>4</sub> in Cu<sub>1</sub>Mn<sub>1</sub>, as highly active phase, could provide abundant O<sub>ads</sub> and Cu<sup>+</sup>–Mn<sup>3+</sup> cation pairs, as well as Cu<sup>2+</sup>–NO<sub>2</sub> interaction. The reactive O<sub>ads</sub> could directly oxidize soot following the “Active Oxygen Mechanism”. And the Cu<sup>+</sup>–Mn<sup>3+</sup> cation pairs could accelerate production of NO<sub>2</sub>, which, by virtue of Cu<sup>2+</sup>–NO<sub>2</sub> interaction, will effectively enhance soot combustion following the “NO-aided Oxidation Mechanism”. This kind of Cu<sub>x</sub>Mn<sub>y</sub> mixed oxides prepared by this low-cost and easily-scalable method may find its potential application in the catalytic removal of soot in the diesel exhaust.

## Acknowledgements

This research was sponsored by National Key Basic Research Program of China (2013CB933202), China National Funds for

Distinguished Young Scientists (51225202) and National Natural Science Foundation of China (51502330).

## Notes and references

- 1 B. A. Van Setten, M. Makkee and J. A. Moulijn, *Catal. Rev.*, 2001, **43**, 489–564.
- 2 H. Horvath, *Atmos. Environ.*, 1993, **27**, 293–317.
- 3 X. Yu, Z. Zhao, Y. Wei, J. Liu, J. Li, A. Duan and G. Jiang, *Chin. J. Catal.*, 2015, **36**, 1957–1967.
- 4 E. Obeid, L. Lizarraga, M. Tsampas, A. Cordier, A. Boréave, M. Steil, G. Blanchard, K. Pajot and P. Vernoux, *J. Catal.*, 2014, **309**, 87–96.
- 5 J. O. Uchisawa, A. Obuchi, Z. Zhao and S. Kushiya, *Appl. Catal., B*, 1998, **18**, L183–L187.
- 6 X. Wu, S. Liu, F. Lin and D. Weng, *J. Hazard. Mater.*, 2010, **181**, 722–728.
- 7 J. Xu, J. Liu, Z. Zhao, C. Xu, J. Zheng, A. Duan and G. Jiang, *J. Catal.*, 2011, **282**, 1–12.
- 8 D. Fino, N. Russo, G. Saracco and V. Specchia, *J. Catal.*, 2006, **242**, 38–47.
- 9 L. Castoldi, R. Matarrese, L. Lietti and P. Forzatti, *Appl. Catal., B*, 2009, **90**, 278–285.
- 10 J. Liu, Z. Zhao, J. Wang, C. Xu, A. Duan, G. Jiang and Q. Yang, *Appl. Catal., B*, 2008, **84**, 185–195.
- 11 Y. Wei, J. Liu, Z. Zhao, A. Duan, G. Jiang, C. Xu, J. Gao, H. He and X. Wang, *Energy Environ. Sci.*, 2011, **4**, 2959–2970.
- 12 L. Nascimento, J. Lima, P. de Sousa Filho and O. Serra, *Chem. Eng. J.*, 2016, **290**, 454–464.
- 13 Y. Nagahara, S. Sugawara and K. Shinohara, *J. Power Sources*, 2008, **182**, 422–428.
- 14 I. Heo, J. W. Choung, P. S. Kim, I.-S. Nam, Y. I. Song, C. B. In and G. K. Yeo, *Appl. Catal., B*, 2009, **92**, 114–125.
- 15 S. Behar, N.-A. Gomez-Mendoza, M.-A. Gomez-Garcia, D. Swierczynski, F. Quignard and N. Tanchoux, *Appl. Catal., A*, 2015, **504**, 203–210.
- 16 J. Papavasiliou, G. Avgouropoulos and T. Ioannides, *J. Catal.*, 2007, **251**, 7–20.
- 17 Y. Tanaka, T. Utaka, R. Kikuchi, T. Takeguchi, K. Sasaki and K. Eguchi, *J. Catal.*, 2003, **215**, 271–278.
- 18 I. Spassova, M. Khristova, D. Panayotov and D. Mehandjiev, *J. Catal.*, 1999, **185**, 43–57.
- 19 A. S. Reddy, C. S. Gopinath and S. Chilukuri, *J. Catal.*, 2006, **243**, 278–291.
- 20 P. Decyk, A. B. Więckowski, L. Najder-Kozdrowska, I. Bilkova and M. Ziolk, *Copper and manganese mixed oxides in zeolites: study of EMR spectra*, ed. C. Rudowicz, Z. Sojka, J. Jezierska and P. Pietrzyk, Polish EMR Group, Krakow, 2014.
- 21 R. Vandenbergh, E. Legrand, D. Scheerlinck and V. Brabers, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.*, 1976, **32**, 2796–2798.
- 22 R. Bayon, G. S. Vicente, C. Maffiotte and A. Morales, *Sol. Energy Mater. Sol. Cells*, 2008, **92**, 1211–1216.
- 23 X. Zhou, H. Chen, G. Zhang, J. Wang, Z. Xie, Z. Hua, L. Zhang and J. Shi, *J. Mater. Chem. A*, 2015, **3**, 9745–9753.
- 24 L. Cai, Z. Hu, P. Branton and W. Li, *Chin. J. Catal.*, 2014, **35**, 159–167.





- 25 A. L. Kustov and M. Makkee, *Appl. Catal., B*, 2009, **88**, 263–271.
- 26 B. Dernaika and D. Uner, *Appl. Catal., B*, 2003, **40**, 219–229.
- 27 S. Xie, Y. Liu, J. Deng, X. Zhao, J. Yang, K. Zhang, Z. Han and H. Dai, *J. Catal.*, 2016, **342**, 17–26.
- 28 U. Ilyas, R. Rawat, G. Roshan, T. Tan, P. Lee, S. Springham, S. Zhang, L. Fengji, R. Chen and H. Sun, *Appl. Surf. Sci.*, 2011, **258**, 890–897.
- 29 M. Kang, E. D. Park, J. M. Kim and J. E. Yie, *Appl. Catal., A*, 2007, **327**, 261–269.
- 30 R. Sun, L. Wang, H. Yu, A. Zain ul, Y. Chen, H. Khalid, N. M. Abbasi, M. Akram, S. Z. Vatsadze and D. A. Lemenovskii, *J. Inorg. Organomet. Polym.*, 2016, **26**, 545–554.
- 31 P. E. Laibinis and G. M. Whitesides, *J. Am. Chem. Soc.*, 1992, **114**, 9022–9028.
- 32 Y. Tanaka, T. Takeguchi, R. Kikuchi and K. Eguchi, *Appl. Catal., A*, 2005, **279**, 59–66.
- 33 Y. Maimaiti, M. Nolan and S. D. Elliott, *Phys. Chem. Chem. Phys.*, 2014, **16**, 3036–3046.
- 34 Z. Li, M. Meng, F. Dai, T. Hu, Y. Xie and J. Zhang, *Fuel*, 2012, **93**, 606–610.
- 35 J. Sarkany, *J. Mol. Struct.*, 1997, **410**, 95–98.
- 36 J. Wang, J. Zhu, X. Zhou, Y. Du, W. Huang, J. Liu, W. Zhang, J. Shi and H. Chen, *J. Mater. Chem. A*, 2015, **3**, 7631–7638.
- 37 A. Bueno-López, *Appl. Catal., B*, 2014, **146**, 1–11.
- 38 W. Shangguan, Y. Teraoka and S. Kagawa, *Appl. Catal., B*, 1997, **12**, 237–247.
- 39 M. Jeguirim, V. Tschamber, K. Villani, J. F. Brilhac and J. A. Martens, *Chem. Eng. Technol.*, 2009, **32**, 830–834.
- 40 A. Setiabudi, M. Makkee and J. A. Moulijn, *Appl. Catal., B*, 2004, **50**, 185–194.
- 41 Y. Li, J. Liang, Z. Tao and J. Chen, *Mater. Res. Bull.*, 2008, **43**, 2380–2385.
- 42 R. Izquierdo, L. J. Rodriguez, R. Anez and A. Sierraalta, *J. Mol. Catal. A: Chem.*, 2011, **348**, 55–62.
- 43 U. Bentrup, A. Brückner, M. Richter and R. Fricke, *Appl. Catal., B*, 2001, **32**, 229–241.
- 44 K. I. Hadjiivanov, *Catal. Rev.*, 2000, **42**, 71–144.

