

Dalton Transactions

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: M. A. Faraonov, D. V. Konarev, A. M. Fatalov, S. S. Khasanov, S. Troyanov and R. N. Lyubovskaya, *Dalton Trans.*, 2017, DOI: 10.1039/C6DT04896J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

Radical anion and dianion salts of titanyl macrocycles with acceptor substituents or extended π -system†

Maxim A. Faraonov,^a Dmitri V. Konarev,^{*a} Alexey M. Fatalov,^{a,b} Salavat S. Khasanov,^c Sergey I. Troyanov,^b Rimma N. Lyubovskaya^a

Crystalline anionic salts of titanyl macrocycles with acceptor substituents or extended π -system have been obtained for the first time: $(\text{PPN}^+)_2\{\text{O}=\text{Ti}^{\text{IV}}(\text{PcCl}_8^{4-})\}^{2-}$ (**1**), $(\text{PPN}^+)\{\text{O}=\text{Ti}^{\text{IV}}(\text{Nc}^{3-})\}^+ \cdot 2\text{C}_6\text{H}_4\text{Cl}_2$ (**2**) and $(\text{PPN}^+)_2\{\text{O}=\text{Ti}^{\text{IV}}(\text{AceTPrzPz}^{4-})\}^{2-} \cdot 1.3\text{C}_6\text{H}_4\text{Cl}_2 \cdot 0.8\text{C}_6\text{H}_5\text{CN}$ (**3**) where PPN^+ is bis(triphenylphosphoranylidene)ammonium cation, PcCl_8 – 2,3,9,10,16,17,23,24-octachlorophthalocyanine; Nc – 2,3-naphthalocynine, AceTPrzPz – tetra(acenaphthenopyrazino)porphyrizine. Salts **1–3** were obtained at the reduction of parent titanyl macrocycles by fluorenone ketyl in the presence of an excess of PPNCl in *o*-dichlorobenzene with following precipitation of crystals by *n*-hexane. Reduction of macrocycles in **1–3** is accompanied by the appearance of intense NIR bands in the solid spectra at 963–1159 nm. It has been found that extended π -system with linear annulation in $\{\text{O}=\text{Ti}^{\text{IV}}(\text{Nc}^{3-})\}^+$ provides the shift of the NIR band to smaller energies (1159 nm) in comparison with those in the spectra of $\{\text{O}=\text{Ti}^{\text{IV}}(\text{Pc}^{3-})\}^+$ (995–998 nm). Reduction of macrocycles leads also to the alternation of C–N_{imine} bonds due to partial disruption of their aromaticity. The disruption is higher for the dianions in **1** and **3** in comparison with the radical anions in **2**. One-dimensional π – π stacking chains and layers are formed in **1** and **3** with diamagnetic $\{\text{O}=\text{Ti}^{\text{IV}}(\text{PcCl}_8^{4-})\}^{2-}$ and $\{\text{O}=\text{Ti}^{\text{IV}}(\text{AceTPrzPz}^{4-})\}^{2-}$ dianions, respectively. Salt **2** contains nearly isolated $\{\{\text{O}=\text{Ti}^{\text{IV}}(\text{Nc}^{3-})\}^+\}_2$ dimers with strong π – π interaction between paramagnetic radical anion macrocycles. As a result, transition from triplet to singlet state with antiparallel ordering of spins within the dimers is observed in **2** below 200 K.

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Introduction

Metal phthalocyanine compounds can possess promising optical, conducting and magnetic properties. Some phthalocyanine derivatives can be used as sensors and materials for optical, electronic and photoelectronic devices.^{1,2} Conducting compounds can be obtained by oxidation of phthalocyanines or axially substituted phthalocyanine anions $\{\text{M}^{\text{III}}\text{L}_2(\text{Pc}^{2-})\}^-$ ($\text{M} = \text{Co}, \text{Fe}; \text{L} = \text{CN}, \text{Cl}, \text{Br}$) to produce crystalline salts with quasi-one-dimensional metallic behavior down to liquid helium temperatures. These salts have π – π stacking columnar arrangement of the macrocycles.^{3,4} Since some metal phthalocyanines contain paramagnetic metals they also used as an active components in the design of magnetic compounds. For example, oxidation of substituted manganese(II) naphthalocyanine by tetracyanoethylene or reduction of iron(II) phthalocyanine by decamethylchromocene yield compounds with the alternation of the ions and ferrimagnetic ordering of spins.^{5,6}

Several radical anion and dianion salts of metal phthalocyanines were also synthesized as single crystals.^{7–21} Crystalline anionic salts

were obtained at the reduction of $\text{Mg}^{\text{II}}, \text{Nb}^{\text{IV}}, \text{Al}^{\text{III}}, \text{Ge}^{\text{IV}}$ and Zr^{IV} phthalocyanines by Na/Hg, potassium graphite (KC_8) or $\text{LiCp}^{\cdot-}$.^{7–11} Salts with the reduced cobalt(II) and iron(II) phthalocyanines^{12–16}, iron(II) hexadecachlorophthalocyanine^{17,18}, large series of radical anion $\{\text{M}(\text{Pc}^{3-})\}^{\cdot-}$ salts, $\text{M} = \text{Cu}^{\text{II}}, \text{Ni}^{\text{II}}, \text{H}_2, \text{Sn}^{\text{II}}, \text{Pb}^{\text{II}}, \text{O}=\text{Ti}^{\text{IV}}, \text{O}=\text{V}^{\text{IV}}, \text{Sn}^{\text{IV}}\text{Cl}_2$ and $\text{In}^{\text{III}}\text{Br}$ were also obtained and structurally characterized.^{19–22} Nevertheless, till now no anionic salts of such type were obtained with other macrocycles excepting phthalocyanines. These macrocycles can contain acceptor substituents to stabilize their radical anions in the air or extended π -system allowing the synthesis of structures with stronger π – π interactions. Reduction of metal macrocycles can also be used to obtain them in a crystalline form since in spite of large size of the macrocycles they are well soluble in organic solvents in radical anion and dianion states.

Titanyl phthalocyanine is a well-known organic photoconductor which shows very good photoconductivity, excellent photostability, wide absorption in the visible region with high absorbance.^{2,23–25} Up to now several substituted titanyl and vanadyl phthalocyanines were obtained.^{26–28} However, molecular structure was determined for unsubstituted titanyl and vanadyl phthalocyanine only using Rietveld method on powdered samples^{29,30} or crystal³¹, respectively.

In this work we chose titanyl macrocycles to introduce acceptor substituents or extended π -system. We dissolve them in *o*-dichlorobenzene by their reduction and crystallize radical anion and dianion salts of titanyl octachlorophthalocyanine in

^a Institute of Problems of Chemical Physics RAS, Chernogolovka, Moscow region, 142432 Russia; E-mail: konarev3@yandex.ru

^b Moscow State University, Leninskie Gory, 119991 Moscow, Russia.


^c Institute of Solid State Physics RAS, Chernogolovka, Moscow region, 142432 Russia.

† Electronic supplementary information (ESI) available: The IR spectra of the starting compounds and salts **1–3**. CCDC 1518488, 1518412 and 1518411. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/x0xx00000x

ARTICLE

Journal Name

$(PPN^+)_2\{O=Ti^{IV}(PcCl_8^{4-})\}^{2-}$ (**1**), titanyl naphthalocyanine in $(PPN^+)_2\{O=Ti^{IV}(Nc^{3-})\}^{2-} \cdot 2C_6H_4Cl_2$ (**2**) and tetra(acenaphthenopyrazino)porphyrane in $(PPN^+)_2\{O=Ti^{IV}(AcTPrzPz^{4-})\}^{2-} \cdot 1.3C_6H_4Cl_2 \cdot 0.8C_6H_5CN$ (**3**) (Scheme 1). Preparation of single crystals of these salts allows to determine the molecular structures of titanyl macrocycles including that of AcTPrzPz (Scheme 1) which is one of the largest macrocycle among tetrapyrrolineporphyrans.³² We provide information on the reduction effect on molecular structures, optical and magnetic properties of titanyl macrocycles.

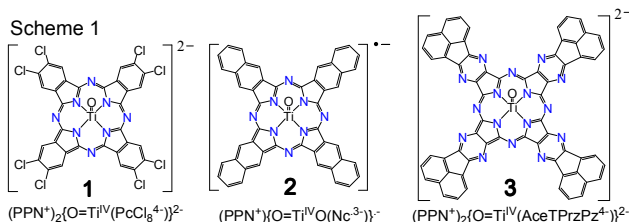

Results and discussion

Synthesis

Titanium dichloride macrocycles were synthesized by tetramerization of corresponding dicarbonitriles in the presence of $TiCl_4$ or $TiCl_4 \cdot 2THF$ in 1-chloronaphthalene in 68–75% yield. Addition of 2-methylnaphthalene prevents the formation of products with chlorinated periphery of the macrocycle. Substitution of chlorine atoms at titanium by oxygen with the formation of titanyl macrocycles was made by boiling of titanium dichloride macrocycles in wet pyridine (5% of H_2O).³³ Scheme 2 of the reactions is shown below.

Obtained titanyl macrocycles are reduced by sodium fluorenone ketyl in the presence of an excess of PPNCl. That leads to the dissolution of all titanyl macrocycles in the form of anions though, for example, neutral $O=Ti^{IV}(AcTPrzPz^{4-})$ is completely insoluble in *o*-dichlorobenzene. The reduction of $Ti^{IV}Cl_2(Nc^{2-})$ by sodium fluorenone ketyl is accompanied by the substitution of chloride anions by oxygen at titanium(IV) atoms. Oxygen originates from fluorenone ketyl, and salt **2** with the $\{O=Ti^{IV}(Nc^{3-})\}^{2-}$ radical anions is formed.

According to redox potentials,^{34–36} naphthalocyanine macrocycle shows weaker acceptor properties than tetrapyrrolineporphyrane and phthalocyanine macrocycles with electron-withdrawing chloro- and pyrazino-substituents. As a result, the reduction of $Ti^{IV}Cl_2Nc$ produces radical anion salt **2**, whereas the reduction of $O=Ti^{IV}(PcCl_8)$ and $O=Ti^{IV}(AcTPrzPz)$ in the same reaction conditions leads to the formation of dianion salts **1** and **3**.


Spectra of salts in the IR and UV-visible-NIR ranges

According to the composition titanyl naphthalocyanine should have -1 charge since the titanyl macrocycle: cation ratio of 1:1 in salt **2**, whereas the titanyl macrocycle: cation ratio of 1:2 in salts **1** and **3** shows the formation of titanyl macrocycle dianions (**2**–).

IR spectra of parent compounds and their salts are shown in Figures S1–S3 and the observed absorption bands are listed in

Table S1. Titanyl macrocycles show absorption bands attributed to the $Ti=O$ stretching mode. The absorption band of this mode is manifested at 946 cm^{-1} in spectra of $O=Ti^{IV}(PcCl_8^{2-})$ and salt **1**. The $Ti=O$ stretching mode is split into three bands manifested at 927, 947 and 974 cm^{-1} in the spectrum of $O=Ti^{IV}(AcTPrzPz^{2-})$. These bands are shifted to lower wavenumbers at 917, 927 and 941 cm^{-1} in the spectrum **3** indicating the elongation of the $Ti=O$ bonds in this salt. Salt **2** was obtained at the reduction of $Ti^{IV}Cl_2(Nc^{2-})$ by sodium fluorenone ketyl with the formation of $\{O=Ti^{IV}(Nc^{3-})\}^{2-}$ and the appearance of new $Ti=O$ bond. That is accompanied by the manifestation of new band at 974 cm^{-1} . Earlier it was shown that the reduction of unsubstituted $O=Ti^{IV}(Pc^{2-})$ in $(Bu_4N^+)\{O=Ti^{IV}(Pc^{3-})\}^{2-}$ and $(Et_4N^+)\{O=Ti^{IV}(Pc^{3-})\}^{2-} \cdot C_6H_4Cl_2$ is accompanied by the elongation of $Ti=O$ bonds since corresponding absorption bands are shifted from 962 to $923\text{--}928\text{ cm}^{-1}$.¹³

Spectra of starting titanyl macrocycles and salts **1–3** in KBr pellets in the UV-visible-NIR range are shown in Fig. 1. Unsubstituted $O=Ti^{IV}(Pc^{2-})$ shows the Soret band at 347 nm and the split Q-band at 654 and 708 nm.²⁰ The Soret and Q-bands have close position in the spectra of $O=Ti^{IV}(PcCl_8^{2-})$ and $O=Ti^{IV}(AcTPrzPz^{2-})$ manifesting at 353, 660, 706 nm and 331, 652, 710 nm, respectively. Unsubstituted $Ti^{IV}Cl_2(Nc^{2-})$ shows absorption bands at 352, 665 and 721 nm. Linear annulation in the naphthalocyanine macrocycle of $Ti^{IV}Cl_2(Nc^{2-})$ results in a blue shift of the Soret band up to 340 nm and strong red shift of the Q-band up to 753 and 834 nm (Fig. 1).

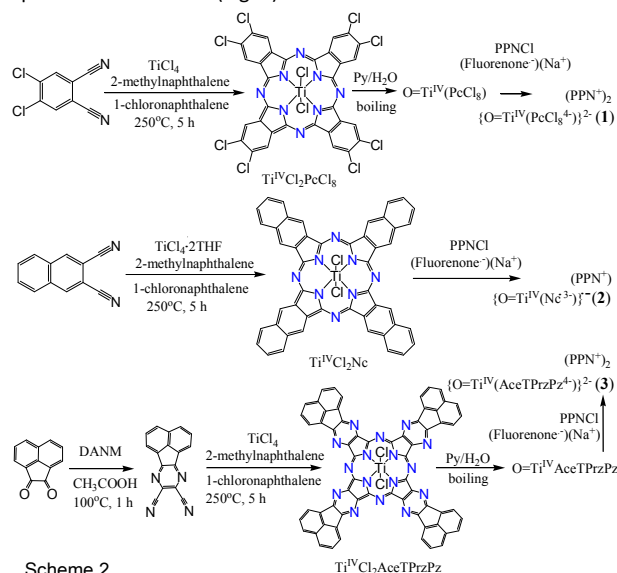

Scheme 2

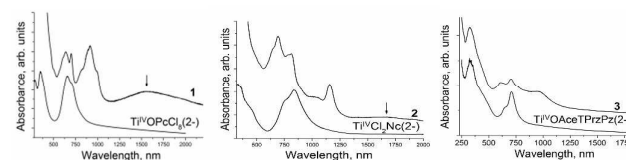


Fig. 1 UV-visible-NIR spectra of starting titanyl macrocycles and salts **1–3** in KBr pellets prepared in anaerobic conditions. Charge transfer bands (CTB) are shown by arrows.

Table 1. Data of UV-visible-NIR spectra of starting titanyl macrocycles and salts **1-3**.

Compound	Position of absorption band of phthalocyanines, nm		
	Soret band, nm	Q-band, nm	Bands in NIR, nm
$\text{O}=\text{Ti}^{\text{IV}}(\text{Pc}^{2-})^{20}$	347	654, 708	-
$(\text{TBA}^+)(\text{O}=\text{Ti}^{\text{IV}}(\text{Pc}^{3-}))^{+20}$	343	597, 630, 701	844 (weak), 995
$(\text{TEA}^+)(\text{O}=\text{Ti}^{\text{IV}}(\text{Pc}^{3-}))^{+}\cdot\text{C}_6\text{H}_4\text{Cl}_2^{20}$	340	600, 630, 698	911 (weak), 998 1475 (CT band)
$\text{O}=\text{Ti}^{\text{IV}}(\text{PcCl}_8^{2-})$	353	660 (max), 706	-
$(\text{PPN}^+)_2(\text{O}=\text{Ti}^{\text{IV}}(\text{PcCl}_8^{4-}))^{2-}(1)$	340	637 (max), 703	818, 916, 999 1550 (CT band)
$\text{Ti}^{\text{IV}}\text{Cl}_2(\text{Pc}^{2-})$	352	665(sh), 721 (max)	-
$\text{Ti}^{\text{IV}}\text{Cl}_2(\text{Nc}^{2-})$	340	753, 834 (max)	-
$(\text{PPN}^+)(\text{O}=\text{Ti}^{\text{IV}}(\text{Nc}^{3-}))^{+}\cdot(\text{Solvent})(2)$	340	697 (max), 814	1040 (weak), 1159, 1672 (CT band)
$\text{O}=\text{Ti}^{\text{IV}}(\text{AcTPrzPz}^{2-})$	331	652 (weak), 710 (max)	-
$(\text{PPN}^+)_2(\text{O}=\text{Ti}^{\text{IV}}(\text{AcTPrzPz}^{4-}))^{2-}(\text{Solvent})(3)$	325	607, 706 (max)	963

sh – shoulder; max – maximum

Spectra of **1-3** (Table 1) allow one to study how the reduction affects optical properties of titanyl macrocycles. Analysis of these spectra shows that Soret bands are blue shifted at the reduction of the macrocycle in **1** and **3** whereas maxima of the Q-bands are strongly blue shifted in the spectra of **1** and **2**, but remain nearly unshifted in the spectrum of **3** (Table 1, Fig. 1). The most pronounced changes at the formation of radical anions and dianions of titanyl macrocycles are the appearance of new intense NIR bands. The presence of these bands unambiguously allows one to determine the formation of reduced macrocycle anions. The blue shift of the Soret and Q bands and the appearance of NIR bands are characteristic of the radical anion salts of $\{\text{O}=\text{Ti}^{\text{IV}}(\text{Pc}^{3-})\}^{+}$ and other metal phthalocyanines.^{20, 21} It should be noted that the NIR band in the spectrum of **2** (1159 nm) is strongly red shifted in comparison with the spectra of the $\{\text{O}=\text{Ti}^{\text{IV}}(\text{Pc}^{3-})\}^{+}$ salts (995-998 nm)²⁰. At the same time these bands are observed almost at the same position in the spectra of **1** and **3** (999 and 963 nm, respectively). Thus, linear annulation in naphthalocyanine essentially stronger decreases the energy of the Q band and the NIR band of the radical anion even in comparison with those for tetra(acenaphthenopyrazino)porphyrane which has essentially larger π -system but no linear annulation. Spectra of **1** and **2** also show broad low-energy bands at 1550 and 1672 nm (Fig. 1), respectively, which can be attributed to charge transfer between macrocycles as it will be discussed in the next section. This band is not observed in the spectrum of **3** (Fig. 1), probably due to ineffective overlapping between the $\{\text{O}=\text{Ti}^{\text{IV}}(\text{AcTPrzPz}^{4-})\}^{2-}$ dianions.

Molecular and crystal structures of salts 1-3.

Geometric parameters of macrocycles in **1-3** are presented in Table 2. The average lengths of the Ti-N(Pc) bonds in **1-3** are 2.068(2)-2.097(6) Å. That is slightly longer than those in $\{\text{O}=\text{Ti}^{\text{IV}}(\text{Pc}^{3-})\}^{+}$ (2.055(1)-2.062(1) Å).²⁰ The elongation of the Ti-N(Pc) bonds results in a stronger displacement of the Ti atoms from the 24-atom Pc plane which is maximal for the $\{\text{O}=\text{Ti}^{\text{IV}}(\text{AcTPrzPz}^{4-})\}^{2-}$ dianions in **3**. The length of the O=Ti bond also varies from 1.615(6) to 1.645(5) Å, and the shortest bonds are observed for the macrocycles with extended π -system in **2** and **3**.

The reduction of the Pc macrocycle is accompanied by transition from aromatic 18 electron π -system to antiaromatic 19 and 20 electron π -system for radical trianion and tetraanion macrocycles, respectively. As a result, partial disruption of aromaticity of the macrocycles is observed in the reduced state leading to the alternation of the C-N_{imine} bonds.^{7-11,20,21} Such alternation is also observed for the reduced macrocycles in **1-3** (Table 2), but the difference between the shorter and longer C-N_{imine} bonds in **1** and **3** with tetraanion macroheterocycles is nearly two times larger than those for the radical trianion Pc^{3-20} and Nc^{3-} macrocycles (Table 2). Thus, disruption of aromaticity is more pronounced for the dianion titanyl macrocycles. Alternation of bonds is realized in such a way that shorter and longer C-N_{imine} bonds belong to two oppositely located isoindole units in **1-3** as is also observed in the radical anions of other metal phthalocyanines.^{20, 21}

Half of $\{\text{O}=\text{Ti}^{\text{IV}}(\text{PcCl}_8^{4-})\}^{2-}$ dianion and one PPN^+ cation are independent in **1**. These dianions form layers in the *ab* plane (Fig. 2a), which are separated by the PPN^+ cations (Fig. 2b). More closely packed chains can be outlined along the *a* axis within the phthalocyanine layers (Fig. 2a). Each phthalocyanine macrocycle has four short van der Waals (vdW) C...C and Cl...Cl contacts of about 3.5 Å length with the neighboring dianions in these chains. The interplanar distance in the chains is uniform and is rather short (3.38 Å). Most probably namely close packing of the PcCl_8 macrocycles in **1** provides the appearance of intense charge transfer band in the NIR spectrum (see above). Any vdW contacts between phthalocyanines from the neighboring chains within the layer are absent. The macrocycle is almost flat in **1** with only slight deviations of atoms from the 24-atom Pc plane (less than 0.065 Å).

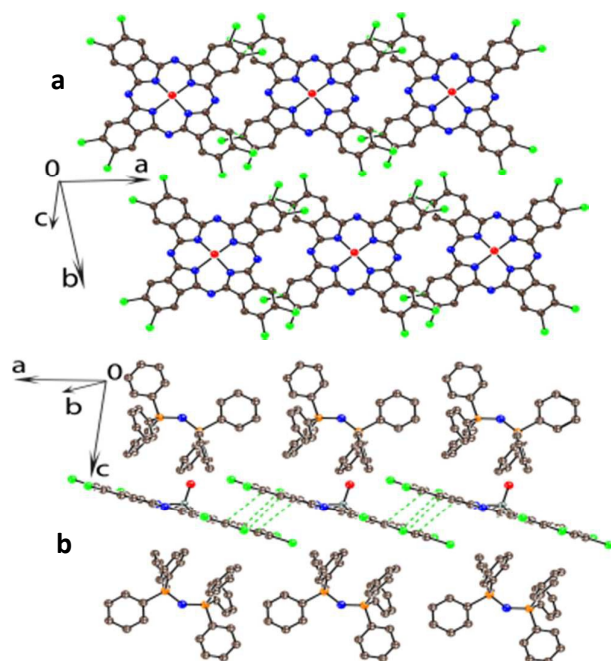
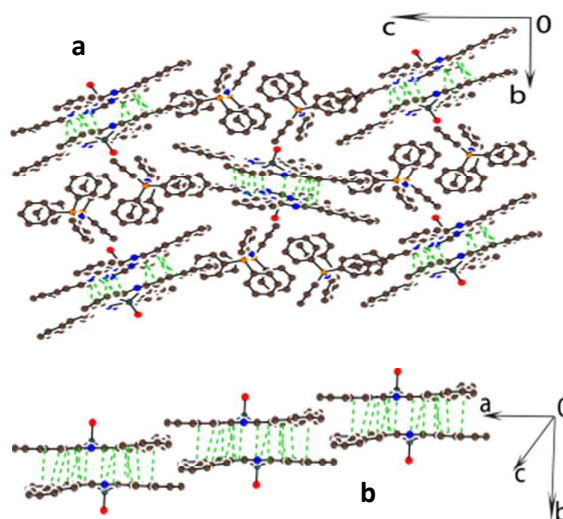
One $\{\text{O}=\text{Ti}^{\text{IV}}(\text{Nc}^{3-})\}^{+}$ radical anion, one PPN^+ cation and two solvent $\text{C}_6\text{H}_4\text{Cl}_2$ molecules are independent in **2**. There are naphthalocyanine chains along *a* axis (Fig. 3) which are isolated by the PPN^+ cations. The $\{\text{O}=\text{Ti}^{\text{IV}}(\text{Nc}^{3-})\}^{+}$ radical anions form dimers in these chains with multiple C,N...C,N vdW contacts, but macrocycles in these dimers are only slightly shifted relative to each other. As a result, there are no short vdW contacts between the neighboring dimers within the chains. The naphthalocyanine macrocycle has two

Table 2. Geometric parameters of titanyl macrocycles in neutral, radical anion and dianion state.

Compound	Average length of bonds and contacts, Å			Displacement of atoms from the 24-atom Pc plane, Å	
	M-N _{pyrrole}	C-N _{pyrrole}	C-N _{imine} short/long, difference	Metal	N _{pyrrole}
O=Ti ^{IV} (Pc ²⁻) (P 2 ₁ /c) O=Ti (1.628(3) Å) ²⁴ O=Ti ^{IV} (Pc ²⁻) (C c) O=Ti (1.643(3) Å) ²⁵ (both made by Rietveld analysis)	2.067(6)	1.374(6)	1.330(6)	0.778	0.091-0.184
(Bu ₄ N ⁺){O=Ti ^{IV} (Pc ³⁻)} ²⁻ O=Ti (1.640(1) Å) ²⁰	2.062(1)	1.386(2)	1.325(2)/1.350(2), 0.025	0.711	0.084-0.135
(Et ₄ N ⁺){O=Ti ^{IV} (Pc ³⁻)} ²⁻ ·C ₆ H ₄ Cl ₂ (O=Ti (1.657(1) Å)) ²⁰	2.055(1)	1.388(2)	1.312(2)/1.351(2), 0.039	0.595	0.004-0.031
(PPN ⁺) ₂ {O=Ti ^{IV} (PcCl ₈ ⁴⁻) ²⁻ } (1), O=Ti (1.645(5) Å)	2.072(3)	1.390(4)	1.304(4)/1.375(4), 0.071	0.602	0.015-0.019
(PPN ⁺){O=Ti ^{IV} (Nc ³⁻)} ²⁻ (Solvent) (2) O=Ti (1.638(2) Å)	2.068(2)	1.397(3)	1.315(3)/1.353(3), 0.038	0.556	0.007-0.088
(PPN ⁺) ₂ {O=Ti ^{IV} (AceTPrzPz ⁴⁻) ²⁻ } (Solvent) (3) (O=Ti (1.615(6) Å))	2.097(6)	1.402(9)	1.314(9)/1.374(9), 0.060	0.741	0.067-0.166

adjacent naphthalene groups located strictly above the 24-atom plane, whereas two other groups are located almost in the plane. The interplanar distance of 3.169 Å is very short in the dimer indicating effective π - π interaction between the macrocycles in **2** explaining the appearance of a charge transfer (CT) band in the NIR spectrum. The interplanar distance in **2** is close to that in previously studied (Et₄N⁺){O=Ti^{IV}(Pc³⁻)}²⁻·C₆H₄Cl₂ salt (3.129 Å) which also shows an intense CT band in the NIR range.²⁰

As a result of strong disorder of solvent molecules, the structure of **3** was refined with relatively high *R*-factor value (0.1158).

**Fig.2** Crystal structure of (PPN⁺)₂{O=Ti^{IV}(PcCl₈⁴⁻)²⁻} (1). Views perpendicular (a) and parallel (b) to the phthalocyanine layers. Shortened vdW C...C, Cl...C, Cl contacts are shown by green dashed lines.**Fig. 3** Crystal structure of (PPN⁺){O=Ti^{IV}(Nc³⁻)}²⁻·2C₆H₄Cl₂ (**2**). View along *a* axis and the naphthalocyanine chains (a) and view on these chains (b). Shortened vdW C...N...C, N...C, N contacts are shown by green dashed lines. Solvent molecules are not shown for clarity.

Nevertheless, the structure of the {O=Ti^{IV}(AceTPrzPz⁴⁻)²⁻} dianion and the PPN⁺ cations were determined quite reliably. Dianions form the [{O=Ti^{IV}(AceTPrzPz⁴⁻)²⁻]₂ dimers with strong shift of the macrocycles but effective π - π stacking between one of four acenaphthenopyrazino groups of the {O=Ti^{IV}(AceTPrzPz⁴⁻)²⁻} dianions (Figs. 4a, b).

The interplanar distance between them is 3.38 Å and the shortest C...N...C, N vdW contacts are in the 3.19-3.36 Å range. The dihedral angle between the planes of the acenaphthenopyrazino-groups of neighboring dianions in the dimer is only 0.22° showing their parallel arrangement. Strong shift of the macroheterocycles relative to each other in the dimers leads to the formation of chains arranged along the [1-1-0] direction (Figs. 4c, d). There are 4 C...C

vdW contacts between the neighboring dimers in these chains of 3.47–3.56 Å length. These contacts are of π -type since the acenaphthene planes of two dianions involved in this interaction are nearly parallel (the dihedral angle between them is 8.12°) and the interplanar distance is only 3.42 Å. There are also several side-by-side vdW C...C contacts of 3.31 Å length between the $\{[O=Ti^{IV}(AcTPzPz^{4-})]_2\}^{2-}$ dimers from the neighboring chains (Fig. 4c, green dashed lines). The macrocycle in **3** has concave conformation and deviates strongly from planarity in contrast to the geometry of the macrocycles in **1** and **2**.

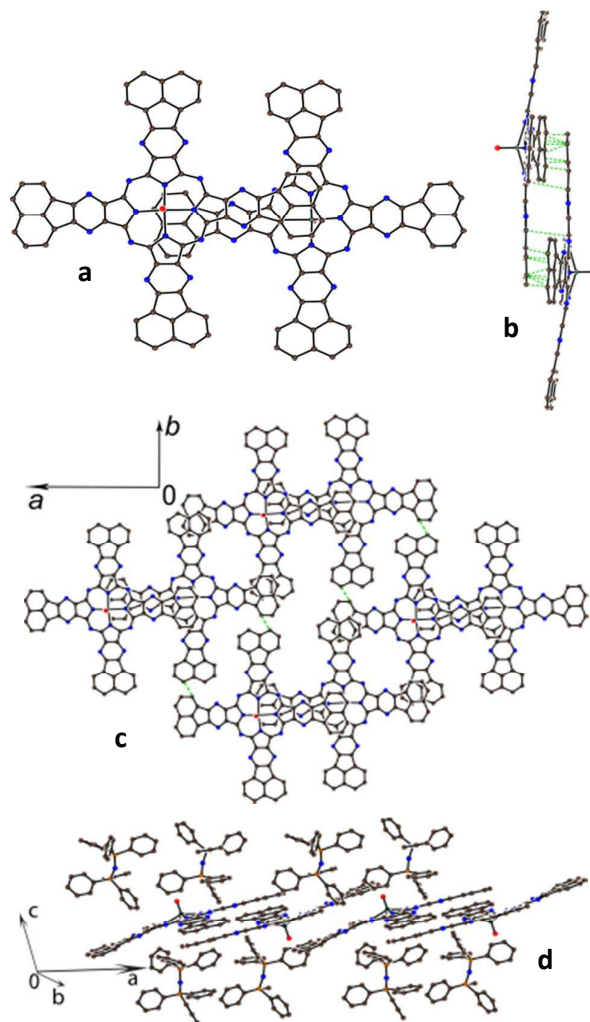


Fig. 4 Crystal structure of $(PPN^+)_2[O=Ti^{IV}(AcTPzPz^{4-})]_2 \cdot 1.2C_6H_4Cl_2 \cdot 0.8C_6H_4Cl_2$ (**3**): view on (a) and along (b) the $\{[O=Ti^{IV}(AcTPzPz^{4-})]_2\}^{2-}$ dimer, view on (c) and along (d) the layers from the dimers. Shortened vdW C...C contacts are shown by green dashed lines. Solvent molecules are not shown for clarity.

EPR studies of the salts

EPR spectra of salts **1** and **3** at 300 K contain weak asymmetric signals which can be approximated by three lines with $g = 1.9975$ – 2.0042 and the linewidth (ΔH) = 0.45–0.92 mT, which are characteristic of radical anions of phthalocyanine species. Intensity of these signals is very low (less than 1% of spins from total amount

of titanyl macrocycle). Therefore, the signals can be most probably attributed to paramagnetic impurities. Thus, the $\{O=Ti^{IV}(PcCl_8^{4-})\}^{2-}$ and $\{O=Ti^{IV}(AcTPzPz^{4-})\}^{2-}$ dianions are diamagnetic.

Salt **2** shows an asymmetric EPR signal which can be simulated well by two narrow lines ($g_1 = 2.0034$ и $\Delta H = 0.50$ mT, $g_2 = 2.0014$ и $\Delta H = 0.88$ mT) and one broad line with $g_3 = 2.0018$ and $\Delta H = 4.67$ mT at 300 K (Fig. 5).

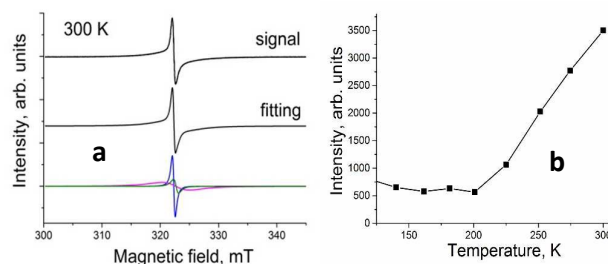


Fig. 5 EPR spectrum of **2** at 300 K (a). Temperature dependence of main component of EPR signal of salt **2** (b).

Narrow lines can be attributed to paramagnetic impurities due to that their intensities are less than 3% from that of the broad signal. The broad line decreases seven times in intensity upon cooling the sample from 300 down to 200 K (Fig. 5b). Below 200 K all three lines are of low intensity and show paramagnetic temperature dependence down to 4 K. Thus, salt **2** is diamagnetic below 200 K. Crystal structure of **2** shows that the $\{O=Ti^{IV}(Nc^{3-})\}^{•-}$ radical anions form closely packed π -stacking $\{[O=Ti^{IV}(Nc^{3-})]_2\}^{•-}$ dimers that can provide strong coupling between them. As a result, diamagnetic singlet state with an antiparallel arrangement of spins in the dimers is formed below 200 K. Triplet state of the dimers with a parallel arrangement of spins is populated above 200 K. The observed singlet-triplet transition in **2** is similar to that observed in $(Et_4N^+)[O=Ti^{IV}(Pc^{3-})]^{•-} \cdot C_6H_4Cl_2$ which also contains π -stacking $\{[O=Ti^{IV}(Pc^{3-})]_2\}^{•-}$ dimers. However, temperature of the transition to singlet state in **2** (200 K) is higher than that in $(Et_4N^+)[O=Ti^{IV}(Pc^{3-})]^{•-} \cdot C_6H_4Cl_2$ (150 K).²⁰ That can be explained by stronger π - π interactions in **2**, probably due to the larger π -system of the naphthalocyanine macrocycle.

Conclusions

A series of the radical anion and dianion salts based on titanyl macrocycles with acceptor substituents or an extended π -system were obtained as single crystals for the first time. The reduction of titanyl macrocycles in the presence of bulky PPN^+ cations allows their dissolution due to the formation of the radical anions or dianions, whereas they are very weakly soluble in organic solvents in the neutral state. Thus, titanyl macrocycles can be crystallized and their molecular structures are determined from X-ray diffraction on single crystals. Extension of a π -system by linear annulation in naphthalocyanine leads to strong red shift of the Q-band and NIR bands of the radical anions, whereas tetra(acenaphthenopyrazino)porphyrane with extended π -system show Q-bands and a NIR band of the anions nearly at the same

ARTICLE

Journal Name

position as in the spectra of the salts with unsubstituted titanyl phthalocyanine radical anions, $\{O=Ti^{IV}(Pc^{\bullet-})\}^{\bullet-}$. Partial disruption of aromaticity is observed at the reduction of the macrocycles. This effect is more pronounced for the dianions than for the radical anions. Increased size of the macrocycle leads to the formation of π -stacked structures. In case of **2** that provides effective magnetic coupling between the spins within the $\{O=Ti^{IV}(Nc^{\bullet-})\}^{\bullet-}_2$ dimers and the transition of the dimers to the singlet ground state even below 200 K (at temperature higher than that in the $\{O=Ti^{IV}(Pc^{\bullet-})\}^{\bullet-}_2$ dimers). Macrocycles in **1** and **3** are packed in the π -stacked chains. However, diamagnetic nature of the dianions does not allow one to expect the realization of conductivity or magnetic interactions in these chains. We suppose that the radical anions of these titanyl macrocycles can provide more promising magnetic properties. Preparation of these salts is now in progress.

Experimental

Materials

4,5-Dichlorophthalonitrile (Aldrich, 99%), 2,3-dicyanonaphthalene (TCI, 99%), acenaphthenequinone (Acros, 95%), and diaminomaleonitrile (Acros, 98%) were used as received. $TiCl_4$ (Aldrich, 99%) and $TiCl_4 \cdot 2THF$ (Aldrich, 97%) were used as received. Bis(triphenylphosphoranylidene)ammonium chloride (PPNCl) was purchased from Aldrich (98%). 1-chloronaphthalene (Aldrich, technical grade) was used as received. Sodium fluorenone ketyl was obtained as described.³⁷ Solvents were purified in argon atmosphere. *o*-Dichlorobenzene ($C_6H_4Cl_2$) was distilled over CaH_2 under reduced pressure; hexane was distilled over Na/benzophenone, and benzonitrile (C_6H_5CN) was distilled over Na under reduced pressure. The solvents were degassed and stored in a glove box. The crystals of **1** – **3** were stored in a glove box. KBr pellets for IR- and UV-visible-NIR measurements were also prepared in the glove box. EPR measurements were performed on polycrystalline samples of **1-3** sealed in 2 mm quartz tubes under 10^{-5} Torr.

Synthesis of titanyl macrocycles

Titanyl macrocycles (Scheme 2) were synthesized as described in ref.³³

Titanyl 2,3,9,10,16,17,23,24-octachlorophthalocyanine, $O=Ti^{IV}(PcCl_8^{2-})$.

4,5-Dichlorophthalonitrile (1 g, 5.076 mmol), 2-methylnaphthalene (180 mg, 1.269 mmol) and $TiCl_4$ (0.14 ml, 1.269 mmol) in 10 ml of 1-chloronaphthalene were heated up to 250 °C upon stirring for 5 hours in argon atmosphere. Then the reaction mixture was cooled down to 50 °C, precipitate was filtered under reduced pressure and washed with toluene and methanol. $Ti^{IV}Cl_2(PcCl_8^{2-})$ was converted to $O=Ti^{IV}(PcCl_8^{2-})$ by boiling in wet pyridine (5% of H_2O) for two hours. $O=Ti^{IV}(PcCl_8^{2-})$ was filtered, washed with water and dried at 100 °C in vacuum for 2 hours to yield 800 mg of blue powder (68%). Anal. found: C, 44.86, N 13.01, H 1.12, Cl 33.21 %. Calcd. for $C_{32}H_8N_8Cl_8OTi$: C, 45.08, N 13.15, H 0.94, Cl 33.34 %. IR (KBr), ν , cm^{-1} : 3087m, 2922m, 2849w, 2353w, 1603m, 1471m, 1413s, 1375m, 1320m, 1069s, 980w, 945m, 890m, 829m, 775m, 705m, 659m, 463w, 431w. UV-VIS, KBr pellet λ_{max} , nm: 353, 660, 706.

Titanium (IV) 2,3-naphthalocyanine dichloride, $Ti^{IV}Cl_2(Nc^{2-})$.

2,3-Dicyanonaphthalene (1 g, 5.612 mmol), 2-methylnaphthalene (200 mg, 1.403 mmol) and $TiCl_4 \cdot 2THF$ (468 mg, 1.403 mmol) in 10 ml of 1-chloronaphthalene were heated up to 250 °C upon stirring for 5 hours in argon atmosphere. Then the reaction mixture was cooled down to 50 °C and precipitate was filtered under reduced pressure and washed with toluene and methanol. $Ti^{IV}Cl_2Nc$ was dried at 100 °C in vacuum for 2 hours to yield 850 mg of dark green powder (73%). Anal. found: C, 69.01, N 13.30, H 3.06, Cl 8.44 %. Calcd. for $C_{48}H_{24}N_8Cl_2Ti$: C, 69.26, N 13.47, H 2.89, Cl 8.54 %. IR (KBr), ν , cm^{-1} : 1747w, 1639m, 1468w, 1358m, 1338m, 1318m, 1153w, 1125m, 1062s, 1011m, 1077s, 968m, 886m, 863m, 798w, 752s, 733w, 716m, 690w, 656w, 514w, 488w, 469m. UV-VIS, KBr pellet λ_{max} , nm: 340, 753, 834.

Acenaphtho[1,2-b]pyrazine-8,9-dicarbonitrile.

A mixture of acenaphthenequinone (2 g, 11 mmol) and equimolar quantity of diaminomaleonitrile (1.187 g, 11 mmol) in 30 ml acetic acid was heated at 100 °C upon stirring for 1 hours. The residue was filtered off, washed with water and acetone (3 ml) and dried at 100 °C in vacuum for 2 hours to yield 2.15 g of dark orange powder (77%).

Titanyl tetra(acenaphthenopyrazino)porphyrzine, $O=Ti^{IV}(AceTPrzPz^{2-})$.

Acenaphtho[1,2-b]pyrazine-8,9-dicarbonitrile (1 g, 3.933 mmol), 2-methylnaphthalene (140 mg, 0.983 mmol) and $TiCl_4$ (0.11 mL, 0.983 mmol) in 10 ml of 1-chloronaphthalene were heated up to 250 °C upon stirring for 5 hours in argon atmosphere. Then the reaction mixture was cooled down to 50 °C, precipitate was filtered under reduced pressure and washed with toluene and methanol. $Ti^{IV}Cl_2(AceTPrzPz^{2-})$ was converted to $O=Ti^{IV}(AceTPrzPz^{2-})$ by boiling in wet pyridine (5% of H_2O) for two hours. $O=Ti^{IV}(AceTPrzPz^{2-})$ was filtered, washed with water and dried at 100 °C in vacuum for 2 hours to yield 800 mg of black powder (75%). Anal. found: C 70.88, N 20.59, H 2.49 %. Calcd. for $C_{64}H_{24}N_{16}OTi$: C 71.04, N 20.72, H 2.22 %. IR (KBr), ν , cm^{-1} : 2921m, 2851m, 1615s, 1514m, 1458m, 1431s, 1369w, 1333s, 1262m, 1229s, 1179m, 1134s, 1099m, 1033s, 974w, 947m, 927m, 828m, 772s, 716m, 675m, 660m, 630m, 559w, 464s, 449m. UV-VIS, KBr pellet λ_{max} , nm: 331, 652, 710.

Syntheses of crystalline salts 1-3

Crystals of **1-3** were obtained by diffusion technique. The reaction solutions of salts **1-3** were filtered in a 50 mL glass tube of 1.8 cm diameter with a ground glass plug, and 30 mL of hexane was layered over the solution. Slow mixing of two solvents during 1.5 months provided precipitation of crystals on the walls of the tube. The solvent was decanted from the crystals and they were washed with hexane.

Salts $(PPN)_2\{O=Ti^{IV}PcCl_8\}$ (**1**) and $(PPN)\{O=Ti^{IV}Nc\} \cdot 2C_6H_4Cl_2$ (**2**) were obtained by reduction of 34.6 mg of $Ti^{IV}OPcCl_8$ (0.042 mmol) or 35.5 mg of $Ti^{IV}Cl_2Nc$ (0.042 mmol) by sodium fluorenone ketyl (55 mg, 0.27 mmol) in the presence of PPNCl (75 mg, 0.131 mmol) in 16 ml of *o*-dichlorobenzene for two hours at 100 °C till complete dissolution of starting compounds and the formation of dark green and deep-blue-green solutions, respectively. The final solutions were filtered into a tube for diffusion. Black blocks of **1** and dark violet elongated prisms of **2** were obtained in 25 and 45% yield, respectively.

Salt $(\text{PPN})_2\{\text{O}=\text{Ti}^{\text{IV}}\text{AceTPrzPz}\}\cdot 1.3\text{C}_6\text{H}_4\text{Cl}_2\cdot 0.8\text{C}_6\text{H}_5\text{CN}$ (**3**) was obtained by the reduction of 36 mg of $\text{O}=\text{Ti}^{\text{IV}}\text{AceTPrzPz}$ (0.033 mmol) by sodium fluorenone ketyl (55 mg, 0.27 mmol) in the presence of PPNCl (75 mg, 0.131 mmol) in 18 ml of *o*-dichlorobenzene/benzonitrile mixture (15:3) for two hours at 100°C till complete dissolution of phthalocyanine and the formation of dark green solution. The final solution was filtered into a tube for diffusion. Black prisms were obtained in 15 % yield.

The composition of **1-3** (Table 3) was determined from X-ray diffraction on single crystals. The analysis of the obtained crystals under microscope in a glove box as well as testing of several single crystals from each synthesis by X-ray diffraction showed that only one crystalline phase is formed. Elemental analysis cannot be used to determine the composition of the obtained crystals due to their high air sensitivity and an addition of oxygen during the procedure of elemental analysis.

General

UV-visible-NIR spectra were measured in KBr pellets on a Perkin Elmer Lambda 1050 spectrometer in the 250-2500 nm range. FT-IR spectra were obtained in KBr pellets with a Perkin-Elmer Spectrum 400 spectrometer (400-7800 cm^{-1}). EPR spectra were recorded on polycrystalline samples of **1-3** from 4 up to 295 K and back from 295 to 150 K for **2** with a JEOL JES-TE 200 X-band ESR spectrometer equipped with a JEOL ES-CT470 cryostat.

Crystal structure determination

Crystallographic data for **1-3** are listed in Table 3. Synchrotron X-ray data for **1** were collected at 100 K on the BL14.3 at the BESSY storage ring (Berlin, Germany) using a MAR225 detector, $\lambda = 0.8950 \text{ \AA}$.

The data for **2** and **3** were collected on an Oxford diffraction "Gemini-R" CCD diffractometer with graphite monochromated MoK_α radiation at low temperature using an Oxford Instrument Cryojet cooler. Experimental data were processed using CrysAlisPro software, Oxford Diffraction Ltd, raw data reduction to F^2 was carried out using Bruker SAINT.³⁸ The structures were solved by direct method and refined by the full-matrix least-squares method against F^2 using SHELX-2013 and 2014.³⁹ Non-hydrogen atoms were refined in the anisotropic approximation. Positions of hydrogen atoms were calculated geometrically.

The Ti1 and O1 atoms in structure **1** are disordered around an inversion center. Structure of **2** contains one strongly disordered $\text{C}_6\text{H}_4\text{Cl}_2$ molecule with the 0.355(3)/0.275(3)/0.231(3)/0.139(3) occupancies. In structure of **3** there are completely ordered $\{\text{O}=\text{Ti}^{\text{IV}}(\text{AceTPrzPz}^{4-})\}^{2-}$ dianion and one and two halves of independent PPN^+ cations. One and half independent PPN^+ cations contain one statistically disordered phenyl group. Two positions of solvent molecules contain strongly disordered $\text{C}_6\text{H}_4\text{Cl}_2$ and $\text{C}_6\text{H}_5\text{CN}$ molecules. Due to strong disorder of some solvent molecules in **2** and **3** and phenyl substituents of PPN^+ in **3**, a multiple restraints were used for the crystal structure refinement of these salts. To keep solvent and phenyl geometry close to ideal one in the disordered groups, the bond length restraints were applied along with the next-neighbor distances using the SADI SHELXL instruction. To keep the anisotropic thermal parameters of the disordered

groups within reasonable limits the displacement components were restrained using the SIMU and DELU SHELXL instructions.

Table 3. X-ray diffraction data for salts **1-3**.

Compound	1	2	3
Emp. formula	$\text{C}_{104}\text{H}_{68}\text{Cl}_8\text{N}_{10}\text{OP}_4\text{Ti}$	$\text{C}_{96}\text{H}_{62}\text{Cl}_4\text{N}_9\text{OP}_2\text{Ti}$	$\text{C}_{149.4}\text{H}_{93.2}\text{Cl}_{2.6}\text{N}_{18.8}\text{OP}_4\text{Ti}$
M_r [$\text{g}\cdot\text{mol}^{-1}$]	1929.06	1609.18	2431.57
Color and shape	Black block	Dark-violet prism	Black prism
Crystal system	triclinic	monoclinic	monoclinic
Space group	$P\bar{1}$	$P2_1/c$	$C2/c$
a , \AA	11.3971(7)	15.1213(3)	36.695(2)
b , \AA	14.8799(8)	18.0169(3)	25.1999(8)
c , \AA	15.0231(9)	29.1976(6)	27.4198(11)
α , $^\circ$	63.130(6)	90	90
β , $^\circ$	77.450(8)	98.402(2)	101.073(5)
γ , $^\circ$	78.459(8)	90	90
V , \AA^3	2203.1(3)	7869.2(3)	24883.5(19)
Z	1	4	8
ρ_{calc} [g/cm^3]	1.454	1.358	1.298
μ [mm^{-1}]	0.888	0.343	0.239
$F(000)$	988	3316	10043
T [K]	100(2)	150(2)	100(2)
Max. 2θ , $^\circ$	73.500	58.748	50.000
Reflns measured	32780	100772	68100
Unique reflns	8464	20327	20895
Parameters	586	1035	1529
Restraints	0	1238	797
Reflns [$F_o > 2(F_\sigma)$]	7252	15449	11354
R_1 [$F_o > 2\sigma(F_o)$]	0.0613	0.0818	0.1158
WR_2 (all data) ^a	0.1468	0.1824	0.3277
G.O.F	0.998	1.105	1.063
CCDC number	1518488	1518412	1518411

Acknowledgements

The reported study was funded by RFBR according to the research project No. 16-33-00588 mol_a.

Notes and references


- C. G. Claessens, W. J. Blau, M. Cook, M. Hanack, R. J. M. Nolte, T. Torres and D. Wöhrle, *Monat. Chem.* 2001, **132**, 3.
- D. Wöhrle, G. Schnurpfeil, S. G. Makarov, A. Kazarin and O.N. Suvorova, *Macrocyclics* 2012, **5**, 191.
- D. C. Y. Ethelbherth, M. Matsuda, H. Tajima, A. Kikuchi, T. Taketsugu, N. Hanasaki, T. Naito and T. Inabe, *J. Mater. Chem.*, 2009, **19**, 718.
- T. Inabe and H. Tajima, *Chem. Rev.*, 2004, **104**, 5503.
- D. K. Rittenberg, L. Baars-Hibbe, A. B. Böhm and J. S. Miller, *J. Mater. Chem.* 2000, **10**, 241.
- D. V. Konarev, L. V. Zorina, S. S. Khasanov, E. U. Hakimova, R. N. Lyubovskaya, *New J. Chem.* 2012, **36**, 48.
- E. W. Y Wong and D. B. Leznoff, *J. Porph. Phth.* 2012, **16**, 154.

ARTICLE

Journal Name

8. J. A. Cissell, T. P. Vaid, A. G. DiPasquale and A. L. Rheingold, *Inorg. Chem.* 2007, **46**, 7713.
9. J. A. Cissell, T. P. Vaid and A. L. Rheingold, *Inorg. Chem.* 2006, **45**, 2367.
10. E. W. Y. Wong, C. J. Walsby, T. Storr and D. B. Leznoff, *Inorg. Chem.*, 2010, **49**, 3343.
11. W. Zhou, R. H. Platel, T. T. Tasso, T. Furuyama, N. Kobayashi and D. B. Leznoff, *Dalton Trans.* 2015, **44**, 13955.
12. M. Tahiri, P. Doppelt, J. Fischer and R. Weiss, *Inorg. Chim. Acta* 1987, **127**, L1.
13. D. V. Konarev, A. V. Kuzmin, S. V. Simonov, S. S. Khasanov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Dalton Trans.* 2012, **41**, 13841.
14. H. Hückstädt and H. Homborg, *Z. Anorg. Allg. Chem.* 1998, **624**, 715.
15. D. V. Konarev, S. S. Khasanov, M. Ishikawa, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Inorg. Chem.* 2013, **52**, 3851.
16. D. V. Konarev, A. V. Kuzmin, S. S. Khasanov and R. N. Lyubovskaya, *Dalton Trans.* 2013, **42**, 9870.
17. D. V. Konarev, L. V. Zorina, M. Ishikawa, S. S. Khasanov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Cryst. Growth Des.* 2013, **13**, 4930.
18. D. V. Konarev, A. V. Kuzmin, M. Ishikawa, Y. Nakano, M. A. Faraonov, S. S. Khasanov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Eur. J. Inorg. Chem.*, 2014, 3863.
19. D. V. Konarev, L. V. Zorina, S. S. Khasanov, A. L. Litvinov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Dalton Trans.* 2013, **42**, 6810.
20. D. V. Konarev, A. V. Kuzmin, M. A. Faraonov, M. Ishikawa, S. S. Khasanov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *Chem. Eur. J.* 2015, **21**, 1014.
21. D. V. Konarev, S. I. Troyanov, M. Ishikawa, M. A. Faraonov, A. Otsuka, H. Yamochi, G. Saito and R. N. Lyubovskaya, *J. Porph. Phth.* 2014, **18**, 1157.
22. D. V. Konarev, A. V. Kuzmin, S. S. Khasanov, A. Otsuka, H. Yamochi, G. Saito, R. N. Lyubovskaya, *Dalton Trans.* 2014, **43**, 13061.
23. M. Tanaka. In: High Performance Pigments, Eds. E.B. Faulkner, R.J. Schwartz, Wiley-VCH: Weinheim, 2009, P. 275.
24. K.-Y. Law, *Chem. Rev.* 1993, **93**, 449.
25. Y. Wang and D. Liang, *Adv. Mater.* 2010, **22**, 1521.
26. H.-J. Kang, E.-H. Kang, S.-W. Park, J.-W. Lee and J.-K. Lee. *Macromolecular Symposia*, 2006, **235**, 195.
27. M. Mayukh, C. M. Sema, J. M. Roberts and D. V. McGrath, *J. Org. Chem.*, 2010, **21**, 7893.
28. (a) E. A. Lukyanets, V. N. Nemykin, *J. Porph. Phth.*, 2010, **14**, 1; (b) V. N. Nemykin, E. A. Lukyanets, *ARKIVOC*, 2010, Part 1, 136; (c) E. A. Lukyanets, V. N. Nemykin, in Handbook of porphyrin science with applications to chemistry, physics, materials science, engineering, biology and medicine: synthetic methodology, Series Handbook of Porphyrin Science, 2010, V. 3, P. 1-323.
29. K. Oka, O. Okada and K. Nukada, *Jpn. J. Appl. Phys.* 1992, **31**, 2181.
30. O. Okada, K. Oka and M. Iijima, *Jpn. J. Appl. Phys.* 1993, **32**, 3556.
31. A. J. Ramadan, L. A. Rochford, D. S. Keeble, P. Sullivan, M. P. Ryan, T. S. Jones and S. Heutz, *J. Mater. Chem. C*, 2015, **3**, 461.
32. M. P. Donzello, C. Ercolani, V. Novakova, P. Zimcik and P. A. Stuzhin, *Coord. Chem. Rev.* 2016, **309**, 107.
33. L. A. Tomachynsk, V. Ya. Chernii and S. V. Volkov, *Russ. J. Inorg. Chem.* 2002, **47**, 208.
34. A. B. P. Lever, E. R. Milaeva and G. Speier. In Phthalocyanines: Properties and Applications. Eds. C. C. Leznoff, A. B. P. Lever, VCH Publishers, Inc.: New York, 1993, **3**, P. 1.
35. K. Takahashi, Y. Aoki, T. Sugitani, F. Moriyama, Y. Tomita, M. Handa, K. Kasuga and K. Sogabe, *Inorg. Chim. Acta*, 1992, **201**, 247.
36. B. L. Wheeler, G. Nagasubramanian, A. J. Bard, L. A. Schechtman, D.R. Dininny and M. E. Kenney, *J. Am. Chem. Soc.* 1984, **106**, 7405.
37. D. V. Konarev, S. S. Khasanov, E. I. Yudanov and R. N. Lyubovskaya, *Eur. J. Inorg. Chem.* 2011, 816.
38. Bruker AXS Inc., Madison, Wisconsin, USA.
39. G. M. Sheldrick, *Acta Crystallogr. Sect. A*, 2008, **64**, 112.

Graphical abstract

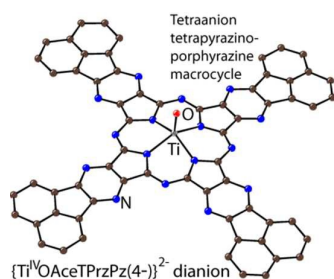

Crystalline anionic salts of titanyl macrocycles with acceptor substituents or extended π -system have been obtained: $(PPN^+)_2\{O=Ti^{IV}(PcCl_8^{4-})\}^{2-}$ (**1**), $(PPN^+)\{O=Ti^{IV}(Nc^{3-})\}^{*-}$ ·solv (**2**) and $(PPN^+)_2\{O=Ti^{IV}(AcTPrzPz^{4-})\}^{2-}$ ·solv (see figure, **3**). Diamagnetic $\{O=Ti^{IV}(PcCl_8^{4-})\}^{2-}$ and $\{O=Ti^{IV}(AcTPrzPz^{4-})\}^{2-}$ dianions form chains and layers. Transition from triplet to singlet state is observed in **2** below 200 K due to the antiparallel arrangement of spins in the $[\{O=Ti^{IV}(Nc^{3-})\}^{*-}]_2$ dimers.