

Green Chemistry

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: N. Baig, S. Verma, M. N. Nadagouda and R. S. Varma, *Green Chem.*, 2015, DOI: 10.1039/C5GC02799C.



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

Photoactive bimetallic framework for direct aminoformylation of nitroarenes

R. B. Nasir Baig^{a†}, Sanny Verma^{a†}, Mallikarjuna N. Nadagouda^b and Rajender S. Varma^{a*}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

A bimetallic catalyst, AgPd@g-C₃N₄, synthesized by reducing silver and palladium salts over the graphitic carbon nitride (g-C₃N₄), performs concerted reductive formylation of aromatic nitro compounds under photo-chemical conditions using formic acid which serves the dual role as hydrogen source and formylating agent.

Introduction:

The synthesis of amines and their conversion to *N*-formyl derivatives is an important reaction in organic synthesis due to its extensive application in natural product synthesis and drug discovery.¹ Conventionally, amino-formyl derivatives have been synthesized from nitro compounds in two separate steps involving nitro reduction followed by *N*-formylation.² Most of the earlier developed processes in the reduction of nitro group use stoichiometric amount of reagents. The heightened awareness surrounding climate change and the growing importance of pollution prevention have resulted in the dramatic shift to use catalytic reagents instead. In general, the catalytic variant developed for the reduction of nitro compounds often requires high hydrogen pressure and elevated temperature;³ safety being a worrisome concern for high pressure hydrogenation on industrial scale. Alternative protocols have been advanced by employing *in-situ* generated hydrogen along with a precious metal catalyst. Most of these procedures require vigorous stirring in aqueous media under a carbon monoxide atmosphere;⁴ a hazardous and toxic contaminant. Formic acid, available from biomass resources, has been introduced as a safer alternative for the transfer hydrogenation of nitro compounds to generate aryl amines.⁵ The formylation of amine has to be carried out subsequently in a separate step. Rutile-supported gold catalyst has achieved

However, this reaction is temperature dependent. At elevated temperatures, it leads to the formation of *N*, *N*-demethylation whereas slight variation towards lower side (~ 60 °C) doesn't allow the formylation of reduced products.⁷ In addition, it requires an inert atmosphere along with the use of organic solvents. Magnetically retrievable palladium catalyst has also been used for the conversion of nitro-arenes to the corresponding *N*-formyl derivatives; complexity of the catalyst preparation and its higher loading are the main limitations of this method.⁸ Iron metal in combination with corresponding carboxylic acid has been introduced but the lower product yields and heating over extended period of time renders this an unproductive and tedious method.⁹ This prompted us to develop a simple and sustainable catalyst which can accomplish this transformation in aqueous media under ambient conditions. In continuation of our ongoing efforts to develop sustainable methods¹⁰ that aim for reduction in chemical waste generation,¹¹ we have designed a bimetallic

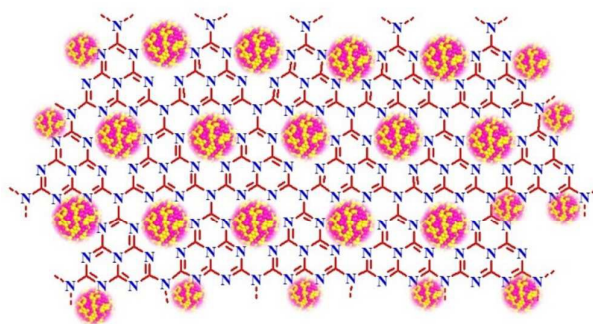


Figure 1 Structure of AgPd@g-C₃N₄

AgPd@g-C₃N₄ photoactive heterogeneous catalyst system for the direct transformation of aromatic nitro compounds to *N*-formylamines.

Synthesis and characterization

^a Sustainable Technology Division, National Risk Management Research Laboratory, U. S. Environmental Protection Agency, MS 443, Cincinnati, Ohio 45268, USA. Fax: 513- 569-7677; Tel: 513-487-2701. E-mail: varma.rajender@epa.gov

^b WQMB, WSWRD, National Risk Management Research Laboratory, U. S. Environmental Protection Agency, MS 443, Cincinnati, Ohio 45268, USA

[†] Equal contribution

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See

such direct conversion of nitro compounds to *N*-formylamines.⁶

ARTICLE

Journal Name

Graphitic carbon nitride ($g\text{-C}_3\text{N}_4$) was synthesized by heating urea in a furnace at 500°C and the ensuing pale yellow solid was dispersed in water by sonicating over a period of 15 mins.¹² The silver and palladium salts (AgNO_3 and $\text{Pd}(\text{NO}_3)_2$) were sequentially added and the reaction mixture was stirred for 12 hours. The reaction temperature was raised to 50°C and the silver and palladium salts were reduced to $\text{Ag}(0)$ and $\text{Pd}(0)$ nanoparticles using excess of sodium borohydride (NaBH_4). The reaction temperature was cooled to ambient temperature, centrifuged and the solid was washed with methanol and vacuum dried at 50°C . The $\text{AgPd@g-C}_3\text{N}_4$ catalyst (Figure 1) was isolated as a fine solid powder.

The catalyst was characterized using transmission electron microscopy, scanning electron microscope, X-ray

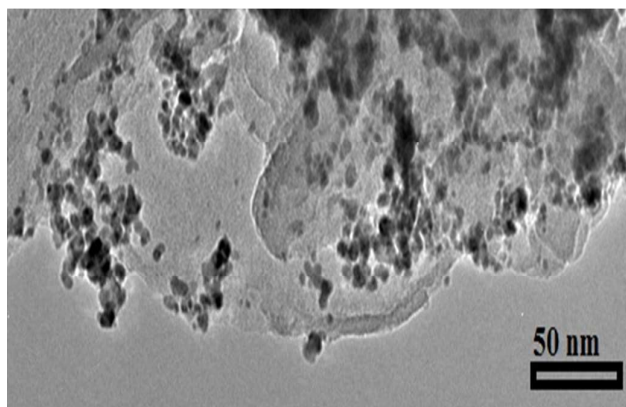


Figure 2 TEM image of $\text{AgPd@g-C}_3\text{N}_4$ catalyst

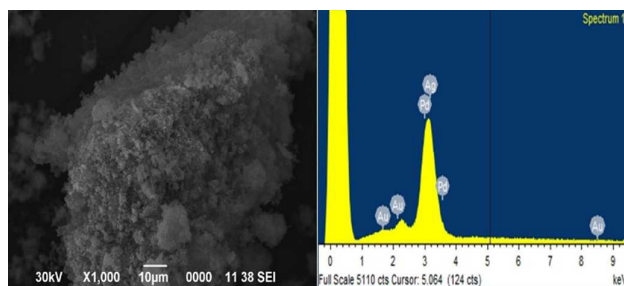


Figure 3 SEM and EDX data of $\text{AgPd@g-C}_3\text{N}_4$ catalyst

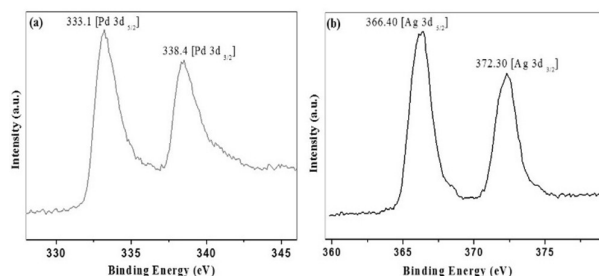


Figure 4 XPS spectra of $\text{AgPd@g-C}_3\text{N}_4$; a) Pd 3d XPS spectra; b) Ag 3d XPS spectra

photoelectron spectroscopy, X-ray diffraction and Inductive coupled plasma atomic emission spectroscopy (ICP-AES).

TEM spectra of the catalyst endorse the formation of single phase silver and palladium nanoparticles with spherical morphology (Figure 2). The SEM image of $\text{AgPd@g-C}_3\text{N}_4$ and its EDX confirm the immobilization of silver (Ag) and palladium (Pd) nanoparticles over the surface of $g\text{-C}_3\text{N}_4$ (Figure 3). The concentration of Ag (4.67%) and Pd (4.55%) were found using ICP-AES analysis. The XPS (Figure 4) analysis of $\text{AgPd@g-C}_3\text{N}_4$ corroborated the formation of palladium and silver nanoparticles on the surface of graphitic carbon nitride (Figure

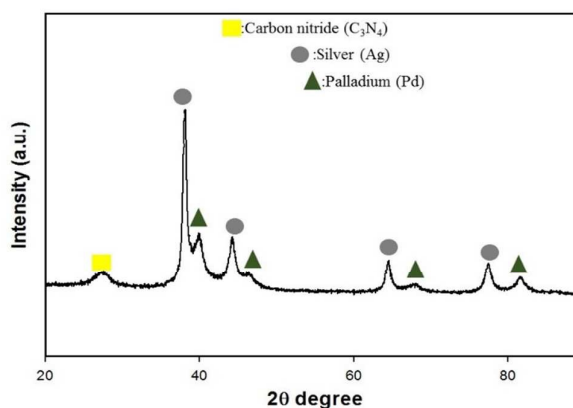


Figure 5 XRD spectra of $\text{AgPd@g-C}_3\text{N}_4$ catalyst

3) which was further supported by XRD (Figure 5).

Result and discussion


The most important step in the development of the active catalyst was the design and synthesis of catalytic system for the direct conversion of nitro compounds to *N*-formylamine derivatives, preferably using visible light to derive this reaction. In view of the known prowess of graphitic carbon nitride ($g\text{-C}_3\text{N}_4$) as a photo active support,¹³ we pursued this approach using formic acid as the reducing as well as a formylating agent in presence of bimetallic catalyst.

First, Pd (10 mol %) was immobilized on $g\text{-C}_3\text{N}_4$ and tested for the aqueous reductive formylation of the nitro group using formic acid as an hydrogen source; the formation of 47% of desired product after 12 hours of exposure to visible light (Table, entry 1) was encouraging. Increasing palladium load (Table 1, entry 2) did not improve catalytic activity whereas low-loading decreased the yield to 30% (Table 1, entry 3). These results suggested that the $\text{Pd@g-C}_3\text{N}_4$ was not sufficiently active to accomplish this transformation. We sought to enhance its activity by adding a catalytic promoter, preferably an abundant material such as copper. Consequently, copper-palladium $\text{CuPd@g-C}_3\text{N}_4$ catalysts were synthesized and used which afforded higher yields (65%) of the desired product (Table 1, entry 4). Various amounts of copper and palladium loadings were next examined (Table 1, entries 5-6). The $\text{CuPd@g-C}_3\text{N}_4$ catalyst with 10% Cu and 5% Pd (Table 1, entry 5) gave the desired product in 55% yield, whereas $\text{CuPd@g-C}_3\text{N}_4$ catalyst with 5% Cu and 10% Pd gave 69% of

product. A recent report on the use of Ag-Pd system on an ultrathin support,¹⁴ encouraged us to explore the use of silver as co-catalyst partner, and therefore we synthesized AgPd@g-C₃N₄ framework. The reaction of nitrobenzene with formic acid in the presence of bimetallic AgPd@g-C₃N₄ gave a quantitative yield of *N*-formyl aniline (Table 1, entry 7, 2 h). The variation in Ag and Pd concentration in the catalyst played a crucial role in the reductive formylation of the nitro group. The catalyst with 10% Ag and 5% Pd loading required 5 h for the completion of reaction (Table 1, entry 8). On the other hand, the catalyst system comprising 5% Ag and 10% Pd gave a quantitative yield of the desired product within 2 h (Table 1, entry 9). Further reduction in silver concentration led to an increase in reaction time and decrease in the product yield (Table 1, entry 10). The reaction with silver alone, Ag@g-C₃N₄, did not show any evidence of reductive formylation product even after 24 hours (Table 1, entry 11).

After establishing the ideal reaction conditions for the catalyst, it was imperative to evaluate the performance of AgPd@g-C₃N₄ with a wide variety of substrates. Accordingly, an array of nitro derivatives were subjected to reductive formylation reaction (Table 2, entries 1-9); all the substrates bearing electron donating (Table 2, entries 2-3) and electron withdrawing substituents (Table 2, entries 4-9) were converted to the corresponding amino formyl derivatives. It was difficult to corroborate the reactivity pattern in line with the nature of the substituents and electronic behavior as most of the reactions were completed within 2 hours.

Table 1 Screening of catalysts for *N*-formylation

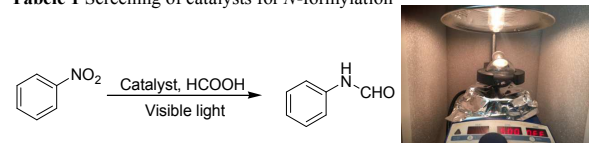

Entry	Catalyst	Time	Yield ^{a, b}
1	Pd@g-C ₃ N ₄ (10% Pd)	12 h	48 %
2	Pd@g-C ₃ N ₄ (20% Pd)	12 h	49%
3	Pd@g-C ₃ N ₄ (5% Pd)	12 h	31%
4	CuPd@g-C ₃ N ₄ (10%Cu : 10% Pd)	12 h	65 %
5	CuPd@g-C ₃ N ₄ (10%Cu : 5% Pd)	12 h	55 %
6	CuPd@g-C ₃ N ₄ (5%Cu : 10% Pd)	12 h	69 %
7	AgPd@g-C ₃ N ₄ (10%Ag : 10% Pd)	2 h	99 %
8	AgPd@g-C ₃ N ₄ (10%Ag : 5% Pd)	5 h	88 %
9	AgPd@g-C ₃ N ₄ (5%Ag : 10% Pd)	2 h	99 %
10	AgPd@g-C ₃ N ₄ (2%Ag : 10% Pd)	5 h	85 %
11	Ag@g-C ₃ N ₄ (10% Ag)	24 h	-

a) Reaction conditions: 1 mmol of nitrobenzene; Formic acid (2 mmol); Water (1.0 mL); Catalyst (25 mg); 40 watt domestic bulb; b) Isolated yield

recyclability of the catalyst in terms of practical and sustainable use were established using recycling experiments for the reductive formylation of nitrobenzene. After the completion of the first reaction, AgPd@g-C₃N₄ was recovered

and reused for the reductive formylation of fresh batch of nitrobenzene. AgPd@g-C₃N₄ was found to be stable and could be reused several times without losing its activity (ESI, S2); even after 6th cycle, the nitrobenzene was efficiently converted into *N*-formyl aniline. The reactivity and stability of the catalyst could be attributed to the graphitic carbon nitride (g-C₃N₄) which holds Ag and Pd nanoparticles tightly. The metal leaching in the AgPd@g-C₃N₄ catalyst was studied using ICP-AES analysis of the reaction solvent and the recycled catalyst before and after the reaction. The absence of metals in the mother liquor and the percentage of Ag (4.65%) and Pd (4.54%) in recycled catalyst confirmed that g-C₃N₄ holds the metals tightly. The trifling metal leaching may be attributed to high porosity and polarity of the g-C₃N₄ support which holds these metals *via* non-covalent interactions.

Table 2 *N*-formylation of nitroarenes catalyzed by AgPd@g-C₃N₄^a

Entry	Reactant	Product	Time	Yield ^b
1			2h	99 %
2			2h	98 %
3			2h	96 %
4			2h	97 %
5			2h	97 %
6			2h	97 %
7			2h	96%
8			2h	97 %
9			2h	96 %
10			3h	76 %
11		-	12h	-

Conclusions

The silver^{Pd} and palladium were

a) Reaction conditions: Nitroarenes (1 mmol); Formic acid (2 mmol); Water (1.0 mL); Catalyst (25 mg); 40 watt domestic bulb; b) Isolated yield immobilized by reducing their salt forms over g-C₃N₄ (graphitic carbon nitride) surface. The synthesized AgPd@g-C₃N₄ catalyst was used for the direct amino formylation of aromatic nitro

ARTICLE

Journal Name

group under photo chemical condition using visible light as a source of energy and formic acid as a reducing as well as formylating agent. The bimetallic catalyst is highly effective in decomposing formic acid into hydrogen and using it as a formylating agent in a concerted process.

Acknowledgements

RBNB and SV were supported by the Postgraduate Research Program at the National Risk Management Research Laboratory administered by the Oak Ridge Institute for Science and Education through an interagency agreement between the U.S. Department of Energy and the U.S. Environmental Protection Agency.

Disclaimer

The U.S. Environmental Protection Agency, through its Office of Research and Development, funded and managed the research described herein. It has been subjected to the Agency's administrative review and has been approved for external publication. Any opinions expressed in this paper are those of the author(s) and do not necessarily reflect the views of the Agency, therefore, no official endorsement should be inferred. Any mention of trade names or commercial products does not constitute endorsement or recommendation for use.

Notes and references

1. a) S. Kotachi, Y. Tsuji, T. Kondo and Y. J. Watanabe, *Chem. Soc., Chem. Commun.*, 1990, 549-550; b) G. W. Kabalka and R. S. Varma, in: *Comprehensive Organic Synthesis*, 1st edn., Vol. 8, (Eds.: B. M. Trost, I. Fleming), Oxford, Pergamon, 1992, 363-388; c) G. R. Petit, M. V. Kalnins, T. M. H. Liu, E. G. Thomas and K. J. Parent, *Org. Chem.*, 1961, **26**, 2563-2566; d) A. Jackson and O. Meth-Cohn, *J. Chem. Soc., Chem. Commun.*, 1995, 1319-1319.
2. a) A. S. Guram and S. L. Buchwald, *Angew. Chem., Int. Ed. Engl.*, 1995, **34**, 1348-1350; b) M. K. Basu, F. F. Becker and B. K. Banik, *Tetrahedron Lett.*, 2000, **41**, 5603-5722; c) P. Strazzolini, A. G. Giumanini and S. Cauci, *Tetrahedron*, 1990, **46**, 1081-1118.
3. G. S. Vanier, *Synlett*, 2007, 131-135.
4. L. He, L. C. Wang, H. Sun, J. Ni, Y. Cao, H. Y. He and K. N. Fan, *Angew. Chem. Int. Ed.*, 2009, **48**, 9538-9541.
5. X. H. Li, Y. Y. Cai, L. H. Gong, W. Fu, K. X. Wang, H. L. Bao, X. Wei and J. S. Chen, *Chem. Eur. J.*, 2014, **20**, 16732-16737.
6. X. B. Lou, L. He, Y. Qian, Y. M. Liu, Y. Cao and K. N. Fana, *Adv. Synth. Catal.*, 2011, **353**, 281-286.
7. B. Karimi, F. Mansouri and H. Vali, *ChemPlusChem*, 2015, **80**, 1750-1759.
8. L. Yu, Q. Zhang, S. S. Li, J. Huang, Y. M. Liu, H. Y. He and Y. Cao, *ChemSusChem*, 2015, **8**, 3029-3035.
9. K. Y. Lee, J. M. Kim and J. N. Kim, *Bulletin of Korean Society*, 2002, **23**, 1355-1498.
10. a) R. S. Varma, *Green Chem.*, 2014, **16**, 2027-2041; b) R. B. Nasir Baig and R. S. Varma, *ACS Sustainable Chemistry & Engineering*, 2014, **2**, 2155-2158; c) S. Verma, H. P. Mungse, N. Kumar, S. Choudhary, S. L. Jain, B. Sain and O. P. Khatri, *Chem. Commun.*, 2011, 47, 12673-12675; d) S. Verma, J. L. Bras, S. L. Jain and J. Muzart, *Dalton Trans.*, 2013, **42**, 14454-14459.
11. a) R. B. Nasir Baig, M. N. Nadagouda and R. S. Varma, *Green Chem.*, 2014, **16**, 4333-4338; b) S. Verma, R. Singh, D. Tripathi, P. Gupta, G. M. Bahuguna and S. L. Jain, *RSC Adv.*, 2013, **3**, 4184-4188.
12. a) J. Zhu, P. Xiao, H. Li and S. A. C. Carabineiro, *ACS Appl. Mater. Interfaces*, 2014, **6**, 16449-16465; b) S. Verma, R. B. Nasir Baig, C. Han, M. N. Nadagouda and R. S. Varma, *Green Chem.*, 2015, DOI:10.1039/C5GC02025E; c) S. Verma, R. B. Nasir Baig, C. Han, M. N. Nadagouda and R. S. Varma, *Chem. Commun.*, 2015, **51**, 15554-15557.
13. Z. Zhao, Y. Sun and F. Dong, *Nanoscale*, 2015, **7**, 15-37.
14. C. Hu, X. Mu, J. Fan, H. Ma, X. Zhao, G. Chen, Z. Zhou and N. Zheng, *ChemNanoMat.*, 2015, DOI: 10.1002/cnma.201500162.

Photoactive bimetallic framework for direct aminoformylation of nitroarenes

A bimetallic catalyst $\text{AgPd}@g\text{-C}_3\text{N}_4$ on graphitic carbon nitride enables concerted reductive formylation of aromatic nitro compounds under photo-chemical conditions; formic acid serves the dual role as hydrogen source and formylating agent.

