

PCCP

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: R. Fuentes Pineda, J. Troughton, M. Planells, I. Sanchez Molina, F. Muhith, G. S. Nichol, S. A. Haque, T. M. Watson and N. Robertson, *Phys. Chem. Chem. Phys.*, 2017, DOI: 10.1039/C7CP07682G.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

Effect of alkyl chain length on the properties of triphenylamine-based hole transport materials and their performance in perovskite solar cells†.

Rosinda Fuentes Pineda^a, Joel Troughton^b, Miquel Planells^a, Irene Sanchez-Molina Santos^c, Farmin Muhith^a, Gary S. Nichol^a, Saif Haque^c, Trystan Watson^{b*} and Neil Robertson^{a*}.

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

A new series of diacetylide-triphenylamine (DATPA) derivatives with five different alkyl chains in the para position, MeO, EtO, ^tPrO, ⁱPrO and BuO, was synthesised, fully characterised and their function as hole-transport materials in perovskite solar cells (PSC) studied. Their thermal, optical and electrochemical properties were investigated along with their molecular packing and charge transport properties to analyse the influence of different alkyl chains in the solar cells parameters. The shorter alkyl chain facilitates more compact packing structures which enhanced the hole mobilities and reduced recombination. This work suggests that the molecule with the methoxy substituent (MeO) exhibits the best semiconductive properties with a power conversion efficiency of up to 5.63%, an open circuit voltage (V_{oc}) of 0.83 V, a photocurrent density (J_{sc}) of 10.84 mA cm⁻² and a fill factor of 62.3% in perovskite solar cells. Upon replacing the methoxy group by longer alkyl chain substituents without changing the energy levels, there is a decrease in the charge mobility as well as PCE (e.g. 3.29% for BuO-DATPA). The alkyl chain length of semiconductive molecules plays an important role for achieving high performance perovskite solar cells.

1 Introduction

^a EaStCHEM School of Chemistry, The University of Edinburgh, King's Buildings, West Mains Road, Edinburgh, EH9 3FJ, United Kingdom. Email: neil.robertson@ed.ac.uk

^b SPECIFIC, Swansea University, Bay Campus, Fabian Way, Swansea, SA1 8EN, United Kingdom. Email: T.M.Watson@swansea.ac.uk

^c Department of Chemistry, Imperial College London, London SW7 2AZ, United Kingdom Email: s.a.haque@imperial.ac.uk

† Electronic Supplementary Information (ESI) available: Experimental details of the synthesis of the DATPA derivatives, additional electrochemical measurements, DSC curves, X-Ray structures, extended crystallographic table, powder diffraction data, calculated HOMO and LUMO energy levels of all DATPA derivatives, Transfer Characteristic curves for the mobility calculations, transient absorption spectroscopy curves and additional solar cell parameters. ¹H and ¹³C for all the synthesised compounds... See DOI: 10.1039/x0xx00000x



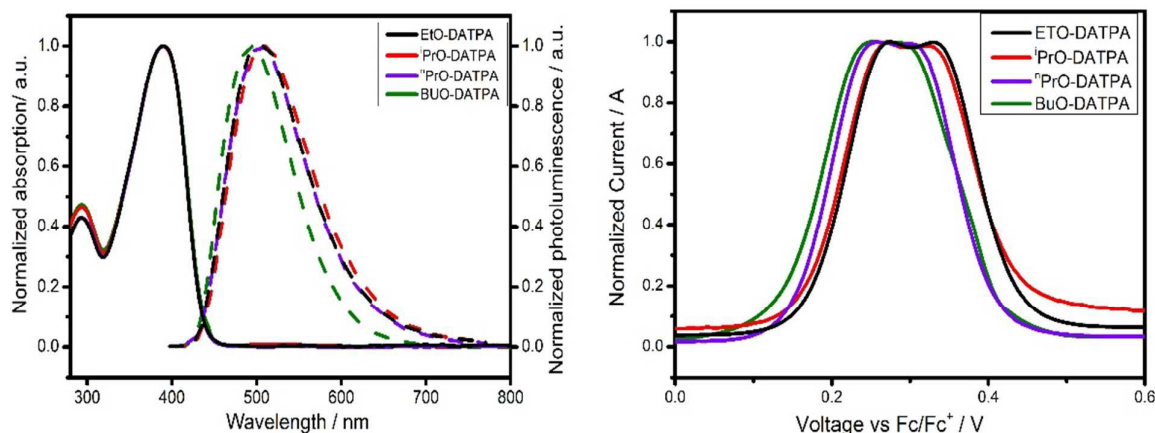


Figure 2. Left: Normalized UV-Vis absorption (solid line) and emission (dashed line) of each DATPA derivative. EtO-DATPA (black line), ⁱPrO-DATPA (red line), ⁿPrO-DATPA (purple line) and BuO-DATPA (green line). Right: Square-wave voltammetry of EtO-DATPA (black line), ⁱPrO-DATPA (red line), ⁿPrO-DATPA (purple line) BuO-DATPA (green line).

In recent years, organic-inorganic halide perovskites have generated tremendous interest from the academic community, showing rapid improvements in their performance as absorbers in photovoltaic solar cells. Starting from 3.8% in 2009 by Miyasaka¹ to a current certified record efficiency of 22.1%^{2,3}, perovskite-based solar cells have surpassed values of the commercialised polycrystalline silicon solar cells and are currently competitive with the established thin-film technologies. This rapid development is mainly the product of the remarkable properties of the perovskite absorber materials, e.g. MAPbX₃ (MA= methylammonium; X = I, or mixed I/Br, I/Cl), such as high panchromatic absorption, large carrier diffusion length, low non-radiative recombination and easy processability, leading to great potential for low cost and large scale technologies⁴⁻⁶. Different configurations for photovoltaic devices have been proposed including mesoscopic structure, planar layers and HTM-free devices. Nevertheless, the most-common standard architectures for these devices comprise six main constituents: 1) a conductive glass substrate FTO (fluorine tin oxide), 2) a compact TiO₂ blocking layer, 3) mesoporous TiO₂ (mp-TiO₂), 4) a perovskite layer, 5) a hole transport layer and 6) gold as counter electrode. One of the main components in these devices is the hole-transporting semiconductor either in the form of a π -conjugated polymer^{7,8}, an inorganic salt⁹⁻¹¹ or small organic molecule. Although many different materials have been explored, most attention has focused on small molecules due to their simplicity, ease of purification and batch-to-batch consistency. Spiro-OMeTAD¹² is the most common hole transport material (HTM) in perovskite solar cells showing high conversion efficiencies. Yet, Spiro-OMeTAD is expensive due to its lengthy synthetic procedure and problematic purification. To address these limitations, researchers have explored alternative HTMs structures with different motifs such as carbazole^{13,14}, triarylamine derivatives¹⁵⁻¹⁷, spiro-based derivatives¹⁸⁻²⁰, triazatruxenes^{21,22}, azulenes²³, and other related examples^{24,25}, leading to efficiencies comparable with

Spiro-OMeTAD and progress on the preparation methods and cost. However, to date Spiro-OMeTAD remains the preferred choice.

Triarylamines (TAA)²⁶ are widely used as a result of the easy oxidation of the nitrogen centre and their capacity to transport positive charges via radical cations. In previous work reported by our group, a series of triphenylamine-based HTMs having two diacetylide-triphenylamine (DATPA)²⁷ moieties and varying redox potentials was prepared by a simple synthetic route which allows easy tuning of electrochemical and other properties through varying the substituent R groups. These materials were studied as HTMs in PSCs and showed promising properties in comparison with Spiro-OMeTAD. The chemical structure of the HTMs can significantly affect the hole transfer kinetics between the HTM and the perovskite and the HTM and the metal contact which affect the performance of the solar cell^{28,29}. The length of alkyl chain for instance, can influence the solubility, molecular ordering and charge transport of the HTMs thus affecting the performance of the solar cell^{30,31}.

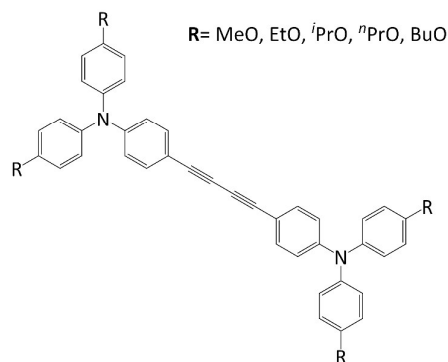


Figure 1. Chemical structure of HTMs used in this study. Each molecule is comprised of two bridged Ph₃N moieties.



Table 1 Summary of the optical and electrochemical properties

HTM	λ_{max} (nm)	ϵ ($\text{cm}^{-1} \text{M}^{-1}$)	λ_{em} (nm) ^a	E_{gap} (V) ^b	E_{ox} (V) ^c	E_{HOMO} (eV) ^d
EtO-DATPA	389	60300	504	2.85	+0.28	-5.38
ⁿ PrO-DATPA	389	69200	504	2.85	+0.26	-5.36
ⁱ PrO-DATPA	389	64280	508	2.84	+0.28	-5.38
BuO-DATPA	389	65990	495	2.85	+0.26	-5.36
Spiro-OMETAD	385	-	424	3.05	+0.03	-5.13

^aExcitation at λ_{max} . ^b E_{gap} is the optical gap determined from the intersection of absorption and emission spectra. ^cFrom SWV and CV measurements and referenced to ferrocene. ^d E_{HOMO} (eV) = -5.1 - (E_{ox})⁴².


Although the large majority of triarylamine HTMs include methoxy groups to tune the redox potential, little research has been done to study the effect of the alkyl chain on the properties of the HTM. In previous studies Hagfeldt³⁰ and co-workers demonstrated the importance of the substituents by tuning the position and length of the alkyl chain in four triphenylamine-based organic HTMs. In a different study, Nazeeruddin³² and co-workers studied the influence of alkyl chain length on the power conversion efficiency of a series of hole transport material. Such reports are rare however, and there are still limited comprehensive studies of the effect of alkyl chain length on material and device properties. In the case of organic photovoltaics, studies have shown both increases and decreases in power-conversion efficiency through increasing the length of alkyl chains^{31,33–35}, therefore

greater systematic understanding of this effect for HTMs in PSCs is important. Accordingly, we report a series of new diacetylide-triphenylamine substituents HTM coded as EtO-DATPA, ⁱPrO-DATPA, ⁿPrO-DATPA and BuO-DATPA with similar optical and electrochemical properties to the MeO-DATPA studied before²⁷. We have systematically investigated the effect of varying the alkyl chain in structurally-similar HTMs on material properties and solar cell performance parameters.

2 Results and Discussion

2.1 Synthesis

The synthetic route (Scheme 1) reported for MeO-DATPA in our previous work²⁷ was revised and optimised to improve

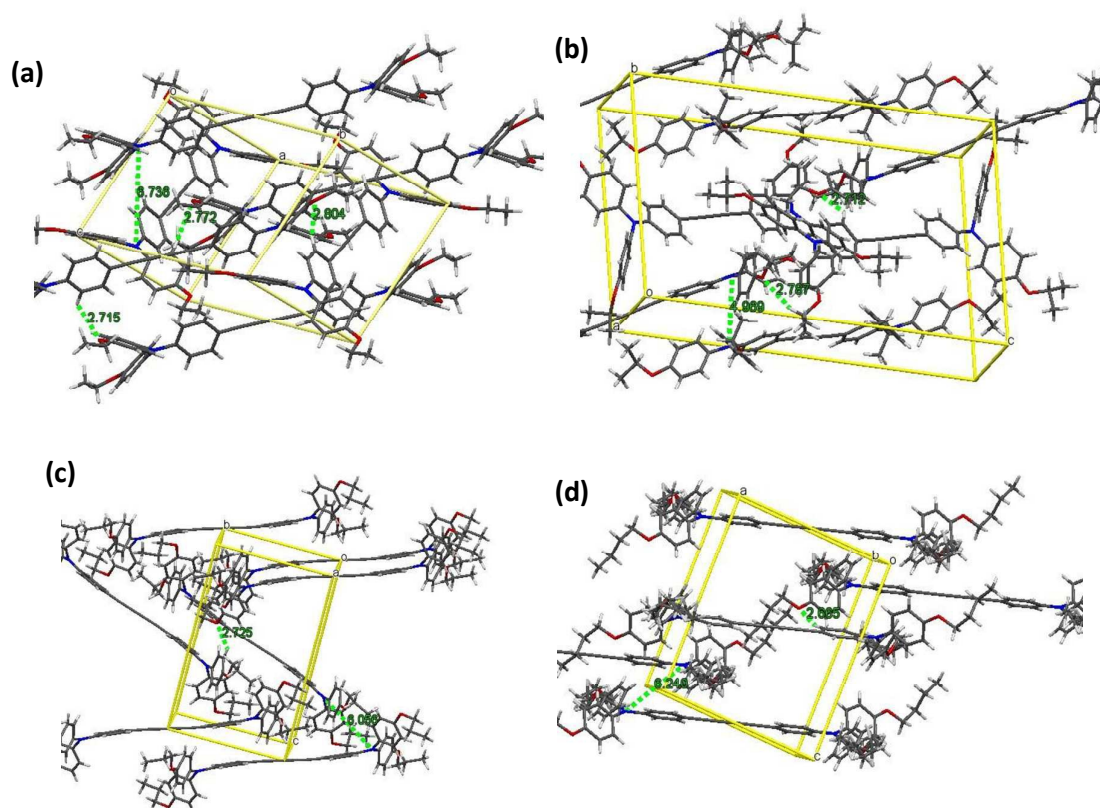**Figure 3.** Crystal packing of all DATPA derivatives: (a) EtO-DATPA, (b) ⁱPrO-DATPA, (c) ⁿPrO-DATPA and (d) BuO-DATPA

chromophore, N_2 , 120 °C, $\text{C}_{10}\text{H}_{16}\text{O}_4$, CuI, piperidine, $(\text{CH}_3)_2\text{PdCl}_2$, CH_3I , CH_3I , N_2 , 50 °C, $\text{C}_{10}\text{H}_{16}\text{O}_4$, CuI, N_2 , $\text{C}_{10}\text{H}_{16}\text{O}_4$, molecular sieves, CuI, air



yields and reduce reactions times. Detailed experimental procedures are described in the Supporting Information. Apart from EtO-DATPA, the method of synthesis involved five stages. The first step is a simple $\text{S}_{\text{N}}2$ reaction, however for EtO-DATPA 1-Ethoxy-4-iodobenzene is commercially available, and this step was omitted. The triarylamine moieties were formed with a Copper Catalysed Ullmann³⁶ coupling reaction, and subsequently the acetylene was attached with a silyl protecting group via Sonogashira cross-coupling³⁷. The silyl group was removed using TBAF (tetrabutylammonium fluoride), leaving the compound with a terminal alkyne. The final product was obtained by a Copper-mediated Oxidative Homocoupling³⁸ reaction at room temperature. The analytical and spectroscopic data for all HTMs are consistent with the formulated structures.

2.2 Optical and electrochemical properties

The UV-Vis absorption spectra of the DATPA derivatives (EtO, ⁿPrO, ⁱPrO, BuO) measured in dichloromethane (DCM), are shown in Figure 2 (left, solid line). All compounds exhibit an absorption peak at 389 nm independent of the substituent. Molar extinction coefficients were calculated for each compound using the Lambert-Beer law and results are displayed in Table 1. Additionally, photoluminescence (PL) spectra were recorded (dashed line, Figure 2 left). The results show similar PL spectra for all DATPA derivatives with a maximum emission at 493 nm.

Optical gaps were determined from the intersection of the excitation and the emission spectra. Cyclic voltammograms (CV) of the DATPA series are displayed in Figure S5 (Supporting information). The redox peaks of all HTMs are chemically and electrochemically reversible, indicating excellent stability and rapid electron transfer. These materials present two oxidation peaks corresponding to one electron oxidation for each triarylamine unit. However, in cyclic voltammetry, the two oxidation processes are strongly overlapped because of their similar potentials. To distinguish both processes, square-wave voltammetry (SWV) was carried out (Figure 2, right). The similarity of the two redox potentials suggests a low interaction between the two triarylamine units. The HOMO energy level is of most importance for hole transfer from the perovskite and HTM and from molecule to molecule. The HOMO energy levels were calculated from the CV data using the following equation $E_{\text{HOMO}} = -5.1 - (E_{\text{ox}})$, where E_{ox} is the oxidation potential of the HTM with reference to ferrocene. The extracted values are listed in Table 1. Overall these results indicate that the hole transfer from $\text{CH}_3\text{NH}_3\text{PbI}_3$ to the HTM is energetically favourable. Spiro-OMeTAD has a HOMO of -5.13 eV, which it is at higher energy than the materials reported here.

Density Functional Theory (DFT) calculations were performed to predict the electronic properties of all HTMs using Gaussian 09 with B3LYP 6-31G(d) level of theory. Figure S1 (Supporting Information) shows the position of the HOMO–LUMO energy levels and their electron density on the molecules of all DATPA

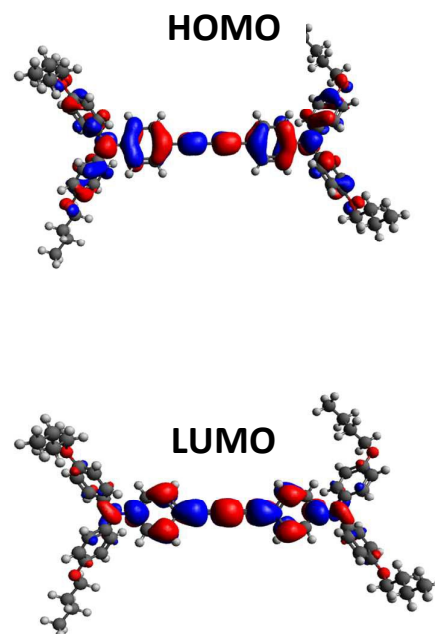


Figure 4. Molecular orbital distribution for BuO-DATPA at B3LYP/6-31G(d) level of theory.

derivatives. The calculated trend of HOMO and LUMO matches the experimental data, and no significant difference was found among the DATPA series. The HOMO (Figure 4) is delocalized over the π orbitals of the triphenylamine unit and the diacetylene bridge. The alkyl groups do not contribute to the HOMO energy level; therefore any change beyond the oxygen does not affect the optoelectronic properties, which coincides with the electrochemistry results. The LUMO electron density is localised on the diacetylene bridge and is also not significantly influenced by the substituents of the triphenylamine unit. A summary of the optical and electrochemical properties of all DATPA derivative is presented in Table 1. As expected, different alkyl substituents do not significantly modify the optical and electrochemical properties of the hole transport materials. This confirms that this series is appropriate to compare the structural, morphological and interface effects of differing alkyl chains without any

Table 2 Charge transport and thermal properties

HTM	Hole Mobility μ_{FE} (cm^2/Vs) ^a	T_g ($^{\circ}\text{C}$) ^b	T_m ($^{\circ}\text{C}$) ^b
MeO-DATPA	1.90×10^{-4}	76.9	197.3
EtO-DATPA	1.45×10^{-4}	69.5	149.4
ⁱ PrO-DATPA	x	70.7	160.8
ⁿ PrO-DATPA	1.11×10^{-4}	x	148.0
BuO-DATPA	8.81×10^{-5}	x	118.9

^aEstimated from OFET measurements. ^bDetermined from differential scanning calorimetry (DSC).



complicating changes to the optoelectronic properties.

2.3 XRD analysis

Single crystals of the new molecules were grown by the slow solvent evaporation method to determine the crystal packing (Figure 3) by X-ray diffraction (XRD). The compounds were found to crystallize in the monoclinic space group $P2_1/n$ (EtO-DATPA, $^n\text{PrO-DATPA}$), monoclinic space group $P2_1/c$ (BuO-DATPA) with half of the formula unit present in the asymmetric unit and the other half consisting of symmetry equivalent atoms; $^i\text{PrO-DATPA}$ crystallizes in the triclinic space group $P-1$ showing two independent molecules in the asymmetric unit (Figure S3, Supporting Information). In every case the molecule crystallises without the presence of any solvent within the unit cell. The EtO-DATPA molecules are packed in a layer-by-layer configuration with molecules arranged in a herringbone motif characterised by edge-to-face contacts. The intersection angle between two adjacent fragments is measured to be 72.18° . The distance between parallel fragments is too large to induce co-facial $\pi \cdots \pi$ interactions. The molecules interact mainly via $\text{C-H} \cdots \pi$ (3.154 Å) and $\text{C-H} \cdots \text{HC}$ formed by the CH groups of phenyls ($\text{dCH} \cdots \text{HC} = 2.554$ Å, 2.634 Å). The EtO-DATPA molecules also form intermolecular H-bonding interactions in the crystal lattice formed by the oxygen and the hydrogen atom of the aromatic rings ($\text{dC-H} \cdots \text{O-R} = 2.715$ Å, 2.804 Å, 2.916 Å). The crystal structure of $^n\text{PrO-DATPA}$ also exhibits a layer-by-layer herringbone pattern. The T-shaped edge-to-face and the parallel-displaced stacking arrangement predominate. Although similar, the structure of $^n\text{PrO-DATPA}$ is stabilised via $\pi \cdots \pi$ interactions. The distance between two parallel fragments and the intersection angle of adjacent molecules were measured to be 3.44 Å and 46.63° respectively. The $^n\text{PrO-DATPA}$ molecules also interact via $\text{C-H} \cdots \pi$ (3.086 Å) and $\text{C-H} \cdots \text{O-R}$ (shortest distance found 2.725 Å). A more complex packing is observed for $^i\text{PrO-DATPA}$. The X-ray crystal structure reveals three crystallographically unique molecules in the asymmetric unit. Two lie on crystallographic inversion centres while the third lies entirely in general positions. Each unit is surrounded by six molecules arranged in an alternating layered pattern with an intersection angle of 77.59° . The interactions arising in the structure of $^i\text{PrO-DATPA}$ are mainly $\text{C-H} \cdots \pi$ (3.034 Å, 2.813 Å, and 2.875 Å) and $\text{C-H} \cdots \text{O-R}$ (shortest distance found 2.712 Å). Furthermore, $\text{C-H} \cdots \text{O-R}$ contact is also observed between the CH group of the alkyl chain and the oxygen atom (2.788 Å). The aromatic cores of the $^i\text{PrO-DATPA}$ are aligned with a very strong slipped π -stacking configuration such that no $\pi \cdots \pi$ interactions are observed. In the case of BuO-DATPA, the molecules are arranged in a zig-zag largely slipped stack packing. Similar to $^i\text{PrO-DATPA}$, the aromatic cores have a very strong slipped π -stacking with an average distance of 4.820 Å which it is too large to induce π -orbital overlap in the crystalline structure. The bulkiness of the alkyl chain in the para position largely impacts the overlapping of

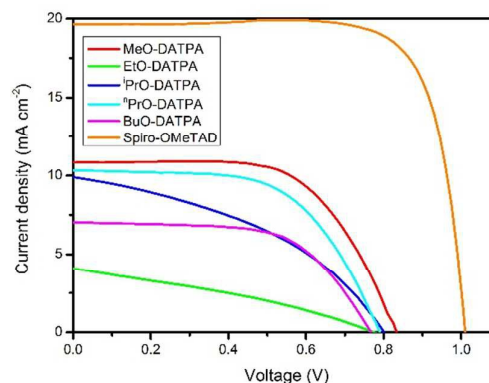


Figure 5. J-V curves (light and dark) of the champion PSCs with the DATPA series and Spiro-MeOTAD HTMs.

the aromatic moieties resulting in the absence of face to face stacking. The crystal lattice shows $\text{C-H} \cdots \text{O-R}$ (2.665 Å), $\text{C-H} \cdots \text{HC}$ (2.270 Å, 2.304 Å) formed between one hydrogen atom of the alkyl chain and CH group of an aromatic ring. The molecules also interact via $\text{C-H} \cdots \pi$ (2.720 Å) formed between an aromatic centroid and the alkyl chain. The crystal packing of MeO-DATPA was reported and discussed in more detail in our previous work²⁷, showing a herringbone pattern, with one molecule in the asymmetric unit and a regular stacking distance between the molecules. Overall, it was observed that as the alkyl chain increases, the number of van der Waals interactions between alkyl chains also increases while the H-bonding contacts decrease. Among all of the examples, MeO-DATPA and EtO-DATPA showed the strongest and highest number of intermolecular interactions (H-bonding) while fewer H-bonds were found in the crystal lattice of BuO-DATPA but stronger van der Waals interactions within the alkyl chains. Longer alkyl chains result in the poorer stacking of the molecule and therefore weaker intermolecular interactions. Furthermore, it is known that closer molecular arrangements can facilitate charge transport in thin film devices³⁹. The X-ray powder diffraction patterns were experimentally obtained and compared with those calculated from their single-crystal data (Figure S6-7, Supporting Information). The powder pattern of all DATPA derivatives showed some crystallinity, and were in agreement with the same phase as the calculated pattern from single-crystal data. A summary of the crystallographic data is depicted in the supporting information Table S4.

2.4 Thermal properties

Thermal properties of the HTMs were evaluated by Differential Scanning Calorimetry (DSC), and the results are presented in the Supporting information (Figure S9-10). The DSC results showed a glass transition temperature (T_g) of 69.5°C and 70.7°C for EtO-DATPA and $^i\text{PrO-DATPA}$. $^n\text{PrO-DATPA}$ and BuO-DATPA however do not present T_g . On the other hand, lower melting points were observed for longer alkyl chains. These observations can be explained by the difference in the crystal packing, and their intermolecular interaction observed in the



XRD analysis. Longer alkyl chains presented poorer stacking as the molecules are more disordered which results in weaker interactions. This explains why the BuO group showed the lowest melting point. The MeO and EtO groups have the highest melting points and the strongest intermolecular interactions. We can also observe that branched ⁱPrO has a higher melting point than the straight-chain ⁿPrO, although ⁿPrO-DATPA (2080 Å³/molecule) has a more compact structure than ⁱPrO-DATPA (2213 Å³/molecule). The ⁱPrO chain typically has a smaller surface area which leads to weaker Van der Waals interactions. However as we can observe in the crystal packing, ⁱPrO shows shorter C-H...O-R interactions, which likely explains the higher melting point in comparison to ⁿPrO.

2.5 Charge Transport Characteristics

Charge mobility is an important parameter to evaluate the properties of hole-transport materials in photovoltaic devices. To investigate the hole mobilities, OFETs (Organic Field-Effect Transistors)⁴⁰ were fabricated for four of the compounds reported here (MeO-DATPA, EtO-DATPA, ⁿPrO-DATPA and BuO-DATPA) and the mobilities were extracted from the saturation regime of the transfer characteristic curves (Figure S8, Supporting Information). Details of the device fabrication and measurement are found in the Experimental section. It was not possible to fabricate a high-quality thin film for ⁱPrO-DATPA. In general, the molecules with the shorter alkyl chains presented higher mobilities which can be attributed to stronger intermolecular interactions in the XRD analysis. A summary of the estimated hole mobilities is presented in Table 2.

2.6 Transient absorption spectroscopy

To further probe the performance in PSCs, the charge transfer dynamics occurring in an mp-TiO₂/CH₃NH₃PbI₃/HTM arrangement for all DATPA derivatives were obtained by ultrafast absorption spectroscopy (TAS). Samples were prepared by spin-coating of the perovskite onto a mesoporous TiO₂ layer and with the HTM on top. Details of the sample preparation and measurements are described in the experimental section. The corresponding steady-state absorption spectra are shown in Figure S11b, where all samples show the dominant spectral features of the perovskite layer CH₃NH₃PbI₃, with the onset at 800 nm and the bands corresponding to the oxidised HTMs (at 1600 nm). Figure S11a shows the TAS time profiles following 510 nm excitation probed at 1600 nm. All signals have a negative feature that arises from some charge separation already happening in the ground state, and the intensity of these bleaches correlates with the intensity of the band of the oxidised HTMs observed in the steady-state absorption spectra. The analysis of the normalised TAS time profiles also displays a hint of the lifetimes of the charge-separated states. From the results, MeO-DATPA presents the most long-lived signal indicating a greater charge-pair separation. Among the other DATPA derivatives, no significant differences of the lifetimes of the charge separation states could be resolved, albeit all were shorter than for MeO-DATPA.

2.7 Solar cell studies

To investigate the effect of the alkyl chain of these HTMs in perovskite solar cells, we prepared a set of PSCs in the configuration FTO/bl-TiO₂/mp-TiO₂/CH₃NH₃PbI₃/HTM/Au. All

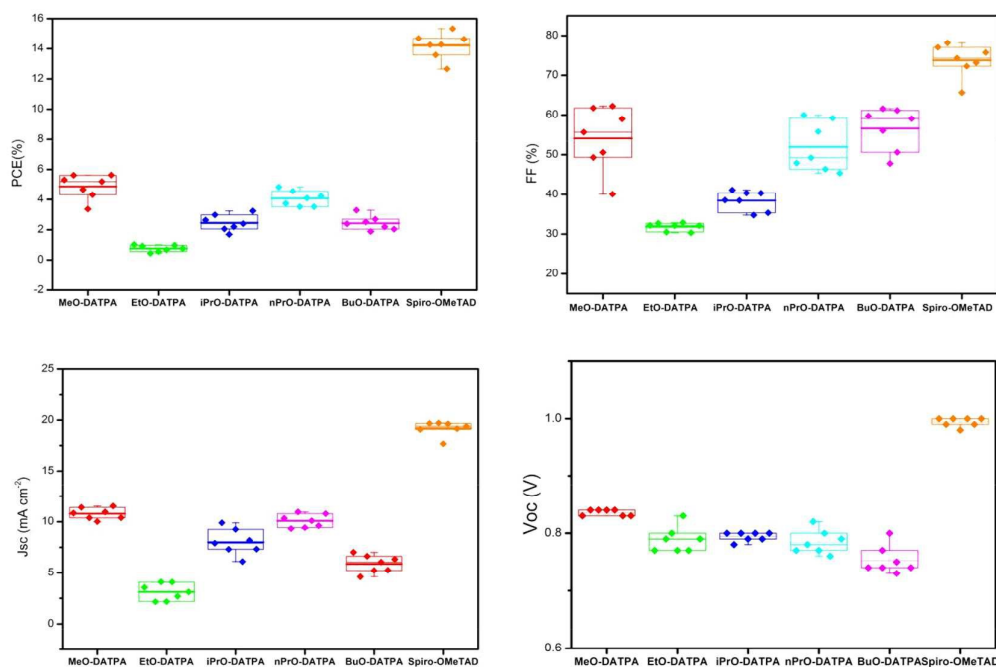


Figure 6. Solar cells parameters over 7 repeats for each HTM



Table 3 Summary of device performance for champion cells

HTM	PCE (%)	J_{sc} (mA cm ⁻²)	V_{oc} (V)	FF (%)
MeO-DATPA	5.63	10.84	0.83	62.25
EtO-DATPA	1.02	4.10	0.77	32.19
ⁿ PrO-DATPA	4.83	10.33	0.79	59.22
ⁱ PrO-DATPA	3.24	9.89	0.80	41.11
BuO-DATPA	3.29	7.02	0.77	61.19
Spiro-OMeTAD	15.34	19.67	1.00	78.13

DATPA HTMs were doped using two times the concentration of additives typically used for Spiro-OMeTAD¹² which include bis(trifluoromethylsulfonyl)imide lithium salt (Li-TFSI), 4-tert-butylpyridine (tBP) and tris(2-(1H-pyrazol-1-yl)-4-tert-butylpyridine)-cobalt(III)tris(bis(trifluoromethylsulfonyl)imide) (FK209). Full details of the solar cell fabrication are given in the experimental section. Current-voltage scans were recorded using an AAA-rated solar simulator calibrated against a KG5 global (AM 1.5 G) solar irradiation. All devices were fabricated in a single continuous study over 7 repeat cells for each HTM to facilitate comparison. Figure 6 shows the box plots with the mean and standard deviation of the solar cell parameters and a summary of the data can be found in Table S12 (Supporting information). The J-V graphs of the champion cells are shown in Figure 5 and the results are summarised in Table 3. Despite the identical backbone structures and HOMO energy levels, the difference in the alkyl chain length had an effect on the photovoltaic device performances. Among the DATPA series, MeO-DATPA shows the highest performance with a PCE of 5.63%. Upon increasing the length of alkyl chain the performance of the devices decreases to 4.83% for nPrO-DATPA, 3.24% for iPrO-DATPA and 2.54% for BuO-DATPA. Also noticeable is the decrease in the short circuit current values (J_{sc}) from 10.84 mA cm⁻² for MeO-DATPA to 7.02 mA cm⁻² for BuO-DATPA. These trends are in broad agreement with mobility and structural packing trends, with the exception of EtO-DATPA which gives unexpectedly poor cells. Since the HTMs in the device are doped, it is perhaps unsurprising to see some deviation from the expected trend since the morphology of the doped materials will also play a role in the final properties. The methoxy substituent presents the best semiconductive properties in comparison with the longer alkyl chains. The variance in PCE values can be attributed to the differences in the photocurrent density and fill factor which may have resulted from the higher hole mobility, greater charge-pair separation and optimal morphology. This is sustained by the results from the hole mobility data, transient absorption spectroscopy studies and XRD analyses discussed previously.

3 Conclusions

In summary, we have presented the synthesis and characterisation of a new series of diacetylide-triphenylamine (DATPA) derivatives to study their function in PSCs. These molecules have the same backbone structures but different alkyl chain length in the para position, i.e., ethoxy (EtO), propoxy (ⁿPrO), isopropoxy (ⁱPrO) and butoxy (BuO). Although the length of the aliphatic side chain does not influence the optoelectronic properties of the molecules such as the HOMO levels, it strongly affects the charge transport properties and transfer dynamics of the molecules as well as the morphology and photovoltaic performance in PSCs. The molecules with shorter alkyl chains have a more ordered and compact structure which facilitates charge transport in the thin films. These results are in agreement with the previous work found by Hagfeldt⁴¹ and Nazeeruddin. The methoxy substituent shows the best semiconductive properties and PCE of 5.63% compared with the longer side chain. This is due to the molecular packing and faster charge transport. This work provides insight on the importance of the alkyl chain length in the design of organic semiconductors.

4 Experimental details.

4.1 Chemical characterization

¹H and ¹³C NMR spectra were recorded on a Bruker Advance 500 spectrometer (500 MHz). The deuterated solvents are indicated in the synthesis description. Chemical shifts, δ , are given in ppm, using the solvent residual as an internal standard. MS were recorded on Micro-ToF using electrospray ionisation (ESI) technique. Elemental analyses were carried out by Stephen Boyer at London Metropolitan University.

4.2 Optical characterization

Solution UV-Visible absorption spectra were recorded using a Jasco V-670 UV/Vis/NIR spectrometer controlled with SpectraManager software. Photoluminescence (PL) spectra were recorded with a Fluoromax-3 fluorimeter controlled by ISAMain software. All samples were measured in a 1 cm cell at room temperature in dichloromethane as solvent. Concentrations of 2.5×10^{-5} M and 1×10^{-6} M were used for UV/Vis and PL respectively.

Crystallographic details

Powder diffraction was performed on a Bruker Discover D8 with CuK α 1/2 source and a scintillation detector 4860. Single yellow block-shaped crystals of EtO-DATPA were recrystallised from benzene by slow evaporation. Single orange block-shaped crystals of ⁱPrO-DATPA were recrystallised from benzene by slow evaporation. Single yellow plate-shaped crystals of ⁿPrO-DATPA were recrystallised from a mixture of DCM and hexane by slow evaporation. Single orange block-shaped crystals of BuO-DATPA were recrystallized from benzene by slow evaporation. A suitable crystal of EtO-DATPA (0.24×0.16×0.14), ⁱPrO-DATPA



ARTICLE

Journal Name

(0.51×0.23×0.10), ⁿPrO-DATPA (0.55×0.29×0.09) and BuO-DATPA (0.25×0.24×0.14) were selected and mounted on a MITIGEN holder in Paratone oil on a Rigaku Oxford Diffraction SuperNova diffractometer. The crystal was kept at T = 120.0 K during data collection. Using Olex2 (Dolomanov et al., 2009), the structure was solved with the ShelXS (Sheldrick, 2008) structure solution program, using the Direct Methods solution method. The model was refined with version of ShelXL (Sheldrick, 2008) using Least Squares minimisation. A summary of the data collection and structure refinement is reported in Table S4.

4.3 Thermal characterization

Differential scanning calorimetry (DSC) was performed on NETZSCH STA 449F1 at a scan rate of 5 K min⁻¹ under a nitrogen atmosphere in DSC/TG aluminium pan. The measurement range was 25 °C to 250 °C.

4.4 Electrochemical characterization

All cyclic voltammetry measurements were carried out in freshly distilled CH₂Cl₂ using 0.3 M [TBA][BF₄] electrolyte in a three-electrode system with each solution being purged with N₂ prior to measurement. The working electrode was a Pt disk, the reference electrode was Ag/AgCl, and the counter electrode was a Pt rod. All measurements were made at room temperature using a μTOLAB Type III potentiostat, driven by the electrochemical software GPES. Cyclic voltammetry (CV) measurements used scan rates of 100 mV/s: square wave voltammetry (SWV) was carried out at a step potential of 4 mV, square wave amplitude of 25 mV, and a square wave frequency of 10 Hz, giving a scan rate of 40 mV/s. Ferrocene was used as the internal standard in each measurement.

4.5 Computational details

All calculations were carried out using the Gaussian 09 program with Lee Yang–Parr correlation functional (B3LYP) level of theory. All atoms were described by the 6-31G(d) basis set. All structures were input and processed through the Avogadro software package.

4.6 Organic Field-Effect Transistors

The Ossila low-density Pre-fabricated substrates (channel length 0.1 mm width 0.03 mm) with a bottom gate/bottom contact were used to fabricate OFET devices. The substrates were treated with HMDS (Hexamethyldisilazane) to optimise the silicon surface property. A solution of the HTM (5 mg/mL) in dichlorobenzene was stirred at room temperature. The Ossila substrate was covered with the solution by drop-casting. The electric characteristics of the fabricated OFETs were measured using a Keithley 2612A System SourceMeter. Mobilities were calculated using the following equation

$$\mu_{FE} = \left(\frac{\sqrt{\partial I_{DS}}}{\partial V_G} \right)^2 \cdot \left(\frac{2L}{WC_i} \right)$$

Where Z is the channel width, L the channel length, C_i the capacitance, V_G the gate voltage and I_{DS} is the drain current and $\sqrt{\partial I_{DS}}/\partial V_G$, the slope of the Transfer Characteristic Curves in the saturation regime⁴⁰.

4.7 Transient Absorption Spectroscopy

Sample preparation

A solution of mesoporous TiO₂ in terpineol (Dyesol 30 nm TiO₂, weight ratio 1:2) was spin coated on a 10 mm by 10 mm glass square, with an acceleration of 12,000 rpm for 30 s. The pieces of glass were cleaned with isopropanol (IPA) in a sonicator for 5 minutes before spin coating. After spin coating, the substrates were placed into a 450 °C oven for 1 hour and cooled down to room temperature before deposition of the perovskite layer. For the deposition of the perovskite layer 1M solution of PbI₂ and MeNH₃I in DMSO was prepared. This solution was spin-coated onto the glass slides covered with the mesoporous oxide via a 3-step spin coating process: (i) 1000 rpm, 10s, 2000 acc; (ii) 5000 rpm, 20s, 2000 acc; (iii) 6000 rpm, 20s, 2000acc. Toluene (300 μL) was dropped on the substrates by the end of the second step. The films were then annealed at 50°C for 20 min and at 100°C for 25-30 min and cooled down to room temperature. A 20 mg/mL solution in chlorobenzene of the corresponding HTM was spin-coated onto the perovskite layer at 200 rpm for 30 s, with an acceleration of 2000.

Measurements

UV-Vis was performed on a PerkinElmer UV/VIS Spectrometer Lambda 25. Photoluminescence spectra were recorded on a Horiba Yobin-Ybon Fluorolog-3 spectrofluorometer, using an excitation wavelength of 450 nm and slit widths of 10 nm. For pump-probe micro to millisecond transient absorption spectroscopy, films were excited by a dye laser (Photon Technology International GL-301, sub-nanosecond pulse width) pumped by a pulsed nitrogen laser (Photon Technology International GL-3300). A quartz halogen lamp (Bentham IL1) was passed through a monochromator and used to probe changes in the absorption characteristics of the film as a function of time after the laser excitation. The probe light was detected using home-built silicon (≤ 1000 nm) or InxGa1-xAs (> 1000 nm) photodiodes and an oscilloscope. Unless otherwise stated, films were kept under flowing N₂ during the measurements. All micro to millisecond transient absorption spectroscopy measurements were conducted employing 450 nm laser pulses (25 μJ/cm²).

4.8 Perovskite Solar Cells and Characterisation

Etched FTO glass substrates (NSG Pilkington, TEC7) were cleaned sequentially in detergent, deionised water, acetone



and ethanol before undergoing 10 minutes of O_2 plasma treatment. A compact TiO_2 layer was deposited on the glass substrates through spray pyrolysis of a 0.2M solution of titanium diisopropoxide bis(acetylacetonate) in isopropanol at 450 °C. Upon cooling, a mesoporous layer of TiO_2 nanoparticles was spin-coated from a 2:7wt suspension of Dyesol 30NR-D paste in ethanol (4,500rpm for 30 seconds), followed by sintering at 550°C for 30 minutes. A $CH_3NH_3PbI_3$ perovskite precursor solution was prepared by dissolving 576mg PbI_2 , and 199 mg CH_3NH_3I in a 4:1 vol solution of DMF:DMSO. 100 μ l of the perovskite precursor solution was deposited onto the TiO_2 films and spin-coated at 4,000rpm for 30 seconds, with 200 μ l of ethyl acetate dripped onto the spinning substrate 10 seconds prior to the end of the spin-coating process. Perovskite films were annealed at 100°C for 10 minutes. In the case of the Spiro-OMeTAD HTM, a 85mg/ml solution of Spiro-OMeTAD in chlorobenzene was prepared with dopants including bis(trifluoromethylsulfonyl)imide lithium salt (Li-TFSI) (20ul/ml of a 520mg/ml solution in acetonitrile), 4-tert-butylpyridine (tBP, 30ul/ml) and tris(2-(1H-pyrazol-1-yl)-4-tert-butylpyridine)-cobalt(III) tris(bis(trifluoromethylsulfonyl)imide) (FK209, 10 ul/ml of a 300 mg/ml solution in acetonitrile). For other HTMs, the same weight of material was dissolved in chlorobenzene with 2 times the volume of additives included. The higher dopant concentration used for the DATPA HTMs was found to be beneficial due to the deeper HOMO level of these compared with Spiro-OMeTAD. The HTM solution was spin-coated onto perovskite films at 4,000rpm for 30 seconds before 80nm thick Au contacts were thermally evaporated onto devices.

Current-voltage measurements were performed using a AAA-rated solar simulator (Oriel Sol3A) calibrated against a KG5-filtered reference diode (Oriel 91150-KG5). Solar cells were masked to 0.1 cm^2 and scanned both from forward to reverse bias and vice versa at 100 mV/s.

Conflicts of Interest

There are no conflicts of interest to declare.

Acknowledgements

RFP thanks CONACYT, Mexico for a PhD studentship. We thank EPSRC EP/H040218/1; EP/M023532/1 for financial support.

Notes and references

- A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, 131, 6050–6051.
- Y. Zhou and K. Zhu, *ACS Energy Lett.*, 2016, 1, 64–67.
- NREL, efficiency-chart.png (4348x2415), <https://www.nrel.gov/pv/assets/images/efficiency-chart.png>, (accessed 21 July 2017).
- P. Gao, M. Grätzel, M. K. Nazeeruddin, K. Zheng, A. Yartsev, T. Pascher, T. Harlang, P. Chabera, T. Pullerits, A. Stepanov, J. P. Wolf, V. Sundstrom, R. Mosca, D. G. Schlom, J. W. Ager and R. Ramesh, *Energy Environ. Sci.*, 2014, 7, 2448–2463.
- S. D. Stranks and H. J. Snaith, *Nat. Nanotechnol.*, 2015, 10, 391–402.
- H. Oga, A. Saeki, Y. Ogomi, S. Hayase and S. Seki, *J. Am. Chem. Soc.*, 2014, 136, 13818–13825.
- M. Stringer, J. E. Bishop, J. A. Smith, D. K. Mohamad, A. Parnell, V. Kumar, C. Rodenburg and D. G. Lidzey, *J. Mater. Chem. A*, 2017, 30, 1410.
- N. Yaghoobi Nia, F. Matteocci, L. Cina and A. Di Carlo, *ChemSusChem*, 2017, 1–10.
- W. Sun, S. Ye, H. Rao, Y. Li, Z. Liu, L. Xiao, Z. Chen, Z. Bian and C. Huang, *Nanoscale*, 2016, 8, 15954–15960.
- C. Zuo and L. Ding, *Small*, 2015, 11, 5528–5532.
- S. Ito, in *Organic-Inorganic Halide Perovskite Photovoltaics*, Springer International Publishing, Cham, 2016, pp. 343–366.
- U. Bach, D. Lupo, P. Comte, J. E. Moser, F. Weissörtel, J. Salbeck, H. Spreitzer and M. Grätzel, *Nature*, 1998, 395, 583–585.
- H. Wang, A. D. Sheikh, Q. Feng, F. Li, Y. Chen, W. Yu, E. Alarousu, C. Ma, M. A. Haque, D. Shi, Z. S. Wang, O. F. Mohammed, O. M. Bakr and T. Wu, *ACS Photonics*, 2015, 2, 849–855.
- M. Daskeviciene, S. Paek, Z. Wang, T. Malinauskas, G. Jokubauskaite, K. Rakstys, K. T. Cho, A. Magomedov, V. Jankauskas, S. Ahmad, H. J. Snaith, V. Getautis and M. K. Nazeeruddin, *Nano Energy*, 2017, 32, 551–557.
- S. Lv, Y. Song, J. Xiao, L. Zhu, J. Shi, H. Wei, Y. Xu, J. Dong, X. Xu, S. Wang, Y. Xiao, Y. Luo, D. Li, X. Li and Q. Meng, *Electrochim. Acta*, 2015, 182, 733–741.
- P. Agarwala, D. Kabra, F. Giordano, J.-P. Correa-Baena, M. Saliba, P. Gao, T. Matsui, J. Ko, S. M. Zakeeruddin, K. H. Dahmen, M. K. Nazeeruddin, K.-L. Liau, H.-C. Chung, C.-Y. Liu, S.-S. Sun and T. J. Chow, *J. Mater. Chem. A*, 2017, 5, 1348–1373.
- H. Choi, S. Park, S. Paek, P. Ekanayake, M. K. Nazeeruddin and J. Ko, *J. Mater. Chem. A*, 2014, 2, 19136–19140.
- P. Ganesan, K. Fu, P. Gao, I. Raabe, K. Schenk, R. Scopelliti, J. Luo, L. H. Wong, M. Grätzel and M. K. Nazeeruddin, *Energy Environ. Sci.*, 2015, 8, 1986–1991.
- M.-H. Li, C.-W. Hsu, P.-S. Shen, H.-M. Cheng, Y. Chi, P. Chen and T.-F. Guo, *Chem. Commun. (Camb.)*, 2015, 51, 15518–21.
- M. Maciejczyk, A. Ivaturi and N. Robertson, *J. Mater. Chem. A*, 2016, 4, 1–22.
- K. Rakstys, A. Abate, M. I. Dar, P. Gao, V. Jankauskas, G. Jacopin, E. Kamarauskas, S. Kazim, S. Ahmad, M. Grätzel and M. K. Nazeeruddin, *J. Am. Chem. Soc.*, 2015, 137, 16172–8.
- F. J. Ramos, K. Rakstys, S. Kazim, M. Grätzel, M. K. Nazeeruddin and S. Ahmad, *RSC Adv.*, 2015, 5, 53426–53432.
- H. Nishimura, N. Ishida, A. Shimazaki, A. Wakamiya, A. Saeki, L. T. Scott and Y. Murata, *J. Am. Chem. Soc.*, 2015, 137, jacs.5b11008.
- P. Dhingra, P. Singh, P. J. S. Rana, A. Garg and P. Kar, *Energy Technol.*, 2016, 4, 891–938.
- L. Calió, S. Kazim, M. Grätzel and S. Ahmad, *Angew. Chemie Int. Ed.*, 2016, 55, 14522–14545.
- M. Thelakkat, *Macromol. Mater. Eng.*, 2002, 287, 442.
- M. Planells, A. Abate, D. J. Hollman, S. D. Stranks, V. Bharti, J. Gaur, D. Mohanty, S. Chand, H. J. Snaith and N. Robertson, *J. Mater. Chem. A*, 2013, 1, 6949.
- D. Bi, L. Yang, G. Boschloo, A. Hagfeldt and E. M. J. Johansson, *J. Phys. Chem. Lett.*, 2013, 4, 1532–1536.



ARTICLE

Journal Name

- 29 S. Ameen, M. A. Rub, S. A. Kosa, K. A. Alamry, M. S. Akhtar, H.-S. Shin, H.-K. Seo, A. M. Asiri and M. K. Nazeeruddin, *ChemSusChem*, 2016, 9, 10–27.
- 30 J. Zhang, B. Xu, M. B. Johansson, M. Hadadian, J. P. Correa Baena, P. Liu, Y. Hua, N. Vlachopoulos, E. M. J. Johansson, G. Boschloo, L. Sun and A. Hagfeldt, *Adv. Energy Mater.*, 2016, 6, 1502536.
- 31 C. E. Song, Y. J. Kim, S. R. Suranagi, G. P. Kini, S. Park, S. K. Lee, W. S. Shin, S.-J. Moon, I.-N. Kang, C. E. Park and J.-C. Lee, *ACS Appl. Mater. Interfaces*, 2016, 8, 12940–12950.
- 32 I. Zimmermann, J. Urieta-Mora, P. Gratia, J. Aragó, G. Grancini, A. Molina-Ontoria, E. Ortí, N. Martín and M. K. Nazeeruddin, *Adv. Energy Mater.*, 2017, 7, 1601674.
- 33 J. Y. Back, T. K. An, Y. R. Cheon, H. Cha, J. Jang, Y. Kim, Y. Baek, D. S. Chung, S.-K. Kwon, C. E. Park and Y.-H. Kim, *ACS Appl. Mater. Interfaces*, 2015, 7, 351–358.
- 34 D. Deng, Y. Zhang, L. Yuan, C. He, K. Lu and Z. Wei, *Adv. Energy Mater.*, 2014, 4, 1400538.
- 35 B. P. Cherniawski, S. A. Lopez, E. K. Burnett, I. Yavuz, L. Zhang, S. R. Parkin, K. N. Houk, A. L. Briseno, M. Muccini, S. Toffanin, A. Weiß, C. Urich, M. Pfeiffer and P. Bäuerle, *J. Mater. Chem. C*, 2017, 5, 582–588.
- 36 C. Sambigi, S. P. Marsden, A. J. Blacker and P. C. McGowan, *Chem. Soc. Rev.*, 2014, 43, 3525–50.
- 37 R. Chinchilla and C. Nájera, *Chem. Rev.*, 2007, 107, 874–922.
- 38 M. H. Vilhelmsen, J. Jensen, C. G. Tortzen and M. B. Nielsen, *European J. Org. Chem.*, 2013, 2013, 701–711.
- 39 J. E. Anthony, *Chem. Rev.*, 2006, 106, 5028–5048.
- 40 C. R. Newman, C. D. Frisbie, D. a. Da Silva Filho, J. L. Brédas, P. C. Ewbank and K. R. Mann, *Chem. Mater.*, 2004, 16, 4436–4451.
- 41 D. Bi, W. Tress, M. I. Dar, P. Gao, J. Luo, C. Renevier, K. Schenk, A. Abate, F. Giordano, J.-P. Correa Baena, J.-D. Decoppet, S. M. Zakeeruddin, M. K. Nazeeruddin, M. Grätzel and A. Hagfeldt, *Sci. Adv.*
- C. M. Cardona, W. Li, A. E. Kaifer, D. Stockdale and G. C. Bazan, *Adv. Mater.*, 2011, 23, 2367–2371.

