

ChemComm

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: D. Le, F. Wagner, M. Takamiya, I. Hsiao, G. Gil Alvaradejo, U. Strähle, C. Weiss and G. Delaittre, *Chem. Commun.*, 2019, DOI: 10.1039/C9CC00407F.





This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Poly(2-ethyl-2-oxazoline) chain transfer agents are employed in photoinitiated RAFTPISA, providing access to biocompatible core-shell polymeric nanostructures with various morphologies.

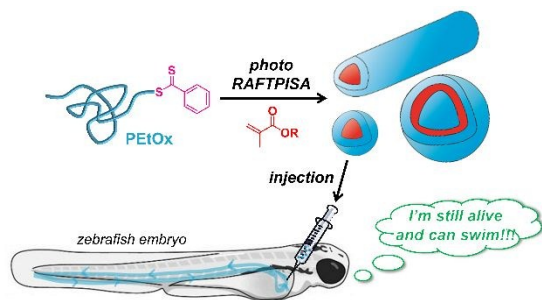

COMMUNICATION

Straightforward access to biocompatible poly(2-oxazoline)-coated nanomaterials by polymerization-induced self-assembly

Dao Le,^{†ab} Friederike Wagner,^{†ab} Masanari Takamiya,^a I-Lun Hsiao,^{ac} Gabriela Gil Alvaradejo,^{ab} Uwe Strähle,^a Carsten Weiss,^a Guillaume Delaittre^{ab*}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

We report the synthesis of poly(2-ethyl-2-oxazoline)-based (PEtOx) nanoobjects by polymerization-induced self-assembly (PISA). First, well-defined PEtOx macromolecular chain transfer agents were synthesized by cationic ring-opening polymerization and click chemistry. The photoinitiated PISA of 2-hydroxypropyl methacrylate mediated by these PEtOx produced nanoobjects spanning the full range of core-shell morphologies. The nanoparticles exhibited high biocompatibility and stealth property *in vitro* or *in vivo*, as well as thermoresponsive behavior.

Poly(2-alkyl/aryl-2-oxazoline)s (PAOx), synthesized by ring-opening cationic polymerization (CROP), are valuable polymers for the biomedical field thanks to their biocompatibility, stealth behavior, and their chemical and physical versatility.^{1–4} Coinciding with the recently renewed interest in PAOx, the first poly(2-ethyl-2-oxazoline) (PEtOx) conjugate already entered Phase II clinical trials for treatment of Parkinson's disease.⁵ Several studies focused on the synthesis of functional PAOx to achieve functional hydrogels,^{6–8} surface coatings,⁹ and polymer-peptide/protein/drug conjugates.^{10,11} Besides, the interest in PAOx-based complex structures is also raising.¹² PEtOx brush-arm star and comb-shaped polymers incorporating nitroxide radicals and perfluorinated segments, respectively, are being reported for magnetic resonance imaging.^{13,14} Patterned PEtOx bottle-brush copolymer brushes on diamond were reported for biosensor design.¹⁵ Notably, PAOx-based core-shell nanoparticles (NPs) are promising nanocarriers for biomedicine.¹⁶ Until now, these have been exclusively prepared by classic self-assembly of pre-synthesized amphiphilic block copolymer (ABCP).

Polymerization-induced self-assembly (PISA), developed in the last decade, has become an important approach for the fabrication of ABCP NPs with elaborate and precise macromolecular architecture, colloidal morphology, and functionality.^{17–23} In a nutshell, PISA is based on two events: (i) chain extension of a solvophilic macromolecular precursor with a monomer forming a solvophobic block and (ii) synchronous self-assembly of the so-formed amphiphilic block copolymer leading to core-shell NPs. As opposed to the classic nanoprecipitation–solvent exchange/evaporation method, PISA can be performed at high polymer concentration (up to 50 vs. 1–2 wt%) and gives *in situ* access to morphologies as diverse as plain spheres, rods/fibers, and hollow vesicles. Reversible-deactivation radical polymerization, mostly reversible addition-fragmentation transfer (RAFT) polymerization, is the major underlying polymerization mechanism for PISA, occurring under either dispersion or emulsion polymerization conditions with styrene, (meth)acrylate, or (meth)acrylamide monomers. Other polymerization mechanisms are slowly making an appearance in the PISA realm, such as ring-opening metathesis polymerization,^{24–27} in order to expand the chemistry and functionality of NPs.²⁸ However, because of the interest in greener solvent and of the general requirement for polar solvents to produce biocompatible nanoparticles (*i.e.*, alcohols and water), employment of ionic polymerization is still limited.²⁹ Therefore, many interesting biocompatible polymers such as PAOx have not yet been included in PISA nanoobjects.

In this study, we describe the first combination of CROP and RAFT/PISA to obtain PAOx-based nanoobjects spanning a wide range of morphologies. First, dithiobenzoate-functionalized PAOx were prepared by CROP of a 2-oxazoline monomer in aprotic solvent, followed by capping to introduce the chain transfer agent (CTA) moiety necessary for RAFT polymerization. The functional PAOx were then used as macromolecular CTA (macroCTA) in photoinitiated aqueous RAFT/PISA (photoRAFT/PISA). The influence of several parameters on the morphologies was investigated, *i.e.*, mode of synthesis of the

^aInstitute of Toxicology and Genetics (ITG), Karlsruhe Institute of Technology (KIT), Hermann-von-Helmholtz-Platz 1, 76344 Eggenstein-Leopoldshafen, Germany.
E-mail: guillaume.delaittre@kit.edu


^bInstitute for Chemical Technology and Polymer Chemistry (ITCP), Karlsruhe Institute of Technology (KIT), Engesserstr. 18, 76128 Karlsruhe, Germany.

^cSchool of Food Safety, College of Nutrition, Taipei Medical University, No.250, Wuxing St., Taipei 11031, Taiwan.

[†]These authors contributed equally.

Electronic Supplementary Information (ESI) available: Materials, characterization methods, experimental procedures, additional data, in-depth discussion of biological data (PDF). See DOI: 10.1039/x0xx00000x



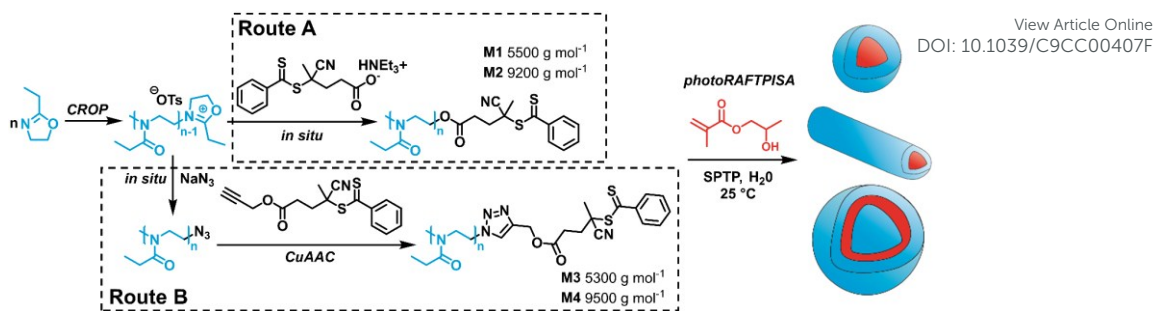

Scheme 1. Synthetic routes towards PETox-stabilized NPs by merging CROP and photoRAFTPISA. SPTP = Sodium phenyl-2,4,6-trimethylbenzoylphosphinate.

macroCTAs, chain length ratio between the solvophilic and solvophobic blocks, and concentration. Besides, we demonstrate that the obtained NPs are biocompatible *in vitro* and *in vivo*, and hence are suitable for potential bioapplications.

In particular, PETox was used in this study for its great hydrophilicity and its potential as alternative to the established polyethylene glycol (PEG).³⁰ PETox was synthesized by CROP using methyl tosylate as initiator. As shown in Scheme 1, the CTA end group could be incorporated either by direct capping with a deprotonated carboxylic acid-functionalized CTA (Route A)^{31,32} or by a two-step sequence consisting of a nucleophilic substitution with sodium azide and a subsequent copper-catalyzed azide-alkyne cycloaddition (CuAAC) (Route B). Both routes showed similar kinetic features and fulfilled elementary criteria for a controlled/living polymerization, *i.e.*, linear increase of pseudo-first order plot, linear increase of number-average molar mass with conversion, and clear shift of size-exclusion chromatography (SEC) traces (Figure S2). However, the nature of the capping reaction impacted the dispersity of the PETox (\mathcal{D}): \mathcal{D} values were systematically slightly higher when capping with the carboxyl CTA, as compared with NaN_3 , concomitant with the presence of a significant shoulder at higher molar masses on the SEC traces (Figure S2C). In Route B, reaction conditions to introduce the CTA moiety by CuAAC (time, solvent) also influenced the shape of the molar mass distribution (MMD), and \mathcal{D} (Figure S7). Performing CuAAC for 4 hours in dichloromethane (DCM) led to the smallest broadening of the MMD. This shouldering phenomenon may be – at least to some extent – due to partial decomposition of the CTA moiety to a thiol, which can be readily oxidized to disulfides and produce high molar mass coupled species (Figure S5, B and C).³³ Indeed, CuAAC of PETox- N_3 with propargyl alcohol in similar conditions led to a significant reduction of MMD broadening (Figure S8). Overall, Route B required one more step but provided well-defined polymers with $\mathcal{D} \leq 1.2$ (Figure S9). For each route, two batches of PETox-CTAs were synthesized for PISA experiments, with M_n of approx. 5500 and 9500 g mol^{-1} . The characteristics of these polymers are listed in Table S1. ^1H NMR and SEC coupled to electrospray ionization mass spectrometry (SEC-ESI-MS) data ascertained high RAFT functionality in all polymers (Figures S3, S4, S10, S11, and S12). Chain extension experiments with benzyl methacrylate in solution confirmed the previous trends: While macroCTAs from Route A underwent only partial chain extension (Figure S13), Route B led to clean block copolymers (Figures S14 and S15).

Nevertheless, as a living character is not mandatory to obtain nanoparticles by PISA,³⁴ we further employed all four macroCTAs.

2-Hydroxypropyl methacrylate (HPMA) was used as core-forming monomer in water. Since PETox exhibits a lower critical solution temperature in water at approx. 60 °C,³⁵ photopolymerization at 25 °C was applied to maintain good solubility and ability for steric stabilization. Firstly, PISA experiments with the short PETox-CTA **M1** were performed with varying targeted degrees of polymerization of HPMA (DP_{HPMA}) and total solids content (Table S3). All PISA experiments were conducted for 3 h and led to full HPMA conversion, as verified by ^1H NMR spectroscopy (Figure S16). As observed by TEM, only pure spherical NPs were obtained in the $DP_{\text{HPMA}} = 30\text{--}100$ range at 5 wt% solids (Figure S18, left). At 10 wt%, a mixture of spheres and nanofibers was obtained for $DP_{\text{HPMA}} = 50$ (Figure S18, right). Higher DP_{HPMA} or solids concentration led to precipitation. Similar results were achieved for the CuAAC-based PETox-CTA **M3** with mainly plain spherical morphology but also large, possibly multicompartmented particles (Table S5 and Figure S22). While both short PETox-CTAs seemed to provide insufficient stabilization and led to aggregation at high DP_{HPMA} and high concentration, PISA with longer analogs allowed the formation of nanoobjects spanning the full range of morphology. Pure spheres, worm-like nanofibers, vesicles as well as morphology mixture were obtained with **M2** (Table S4 and Figure S20). Higher-order morphologies evolved with increasing DP_{HPMA} and solids contents. However, a significant raise in dispersity was also observed, which is most probably due to non-reinitiating PETox-CTA rather than to a loss of control. Indeed, SEC traces of PISA samples showed important amounts of low-molecular-mass species consistent with non-functionalized PETox and unreacted POx-CTA (Figure S19). By using the better-defined PETox-CTA **M4**, strongly improved MMDs were obtained with a total consumption of POx-CTA (Figure S23). Concomitantly, PISA NPs displayed well-defined morphologies, as well as further more intricate shapes such as donut- and jellyfish-like (Figure 1). At low solids content (5 wt%) and with DP_{HPMA} up to 200, only spheres or donuts were observed, as for higher solids content with $DP_{\text{HPMA}} \leq 100$. However, a range of nanoobjects from spheres to vesicles was achieved when targeting higher DP_{HPMA} . Particularly, conditions for the preparation of pure phases were established, even for jellyfish-like objects, an intermediate stage of the nanofiber-to-vesicle morphological transformation.



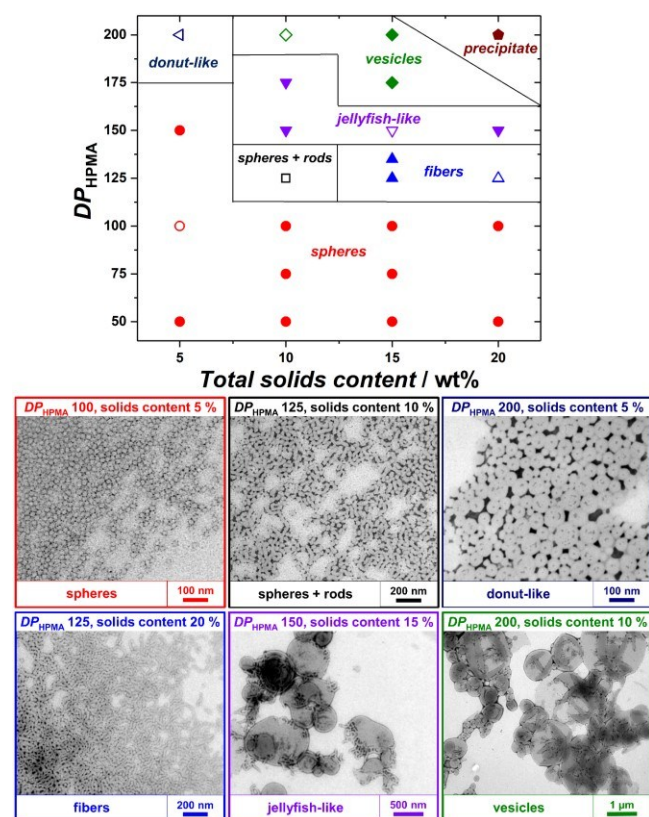


Figure 1. (Top) Phase diagram for RAFT-PISA of HPMA using PETox-CTA **M4** as macroRAFT agent and (bottom) TEM images of representative samples (empty symbols from above). Larger TEM images are provided as Figure S25.

PISA with higher-molar-mass PETox-CTAs therefore gave better results in terms of colloidal stability and morphology control. There is however no clear influence of the degree of livingness of the macromolecular CTAs on the morphological control.

In analogy to systems reported by Armes and co-workers,³⁶ phase transition of the final dispersions could be triggered by changing temperature. At high concentration, the vesicle-to-nanofiber-to-sphere transitions were reversible, irrespective of the initial state, e.g., nanofibers and vesicles for **M4-b-PHPMA**₁₂₅ and **M4-b-PHPMA**₁₇₅ at 25 °C, respectively (Figure 2A). Such order-order transitions in a narrow temperature range are due to not only the weakly hydrophobic nature of the core-forming PHPMA block³⁷ but also the temperature-dependent solubility of PETox. However, at low concentration, e.g., 0.1 wt%, the transitions became irreversible (Figure 2B) because the fusion of spheres or fibers is less likely under these conditions. For instance, vesicles of **M4-b-PHPMA**₁₂₅ obtained by heating a concentrated solution at 40 °C and carefully diluted at the same temperature irreversibly led to nanofibers, then spheres by gradual cooling.

Since PETox is considered as an attractive alternative to PEG for *in vivo* applications, we sought to preliminarily assess the biocompatibility and blood circulation behavior of the present PETox-coated NPs. For imaging purposes, fluorescent NPs were thus produced by simply adding a small amount of fluorescein methacrylate (FMA) or rhodamine 4-vinylbenzyl ester (RVB) comonomer to a PISA recipe (Scheme S2). Spherical NPs with intensity-average hydrodynamic diameters of 40 and 60 nm

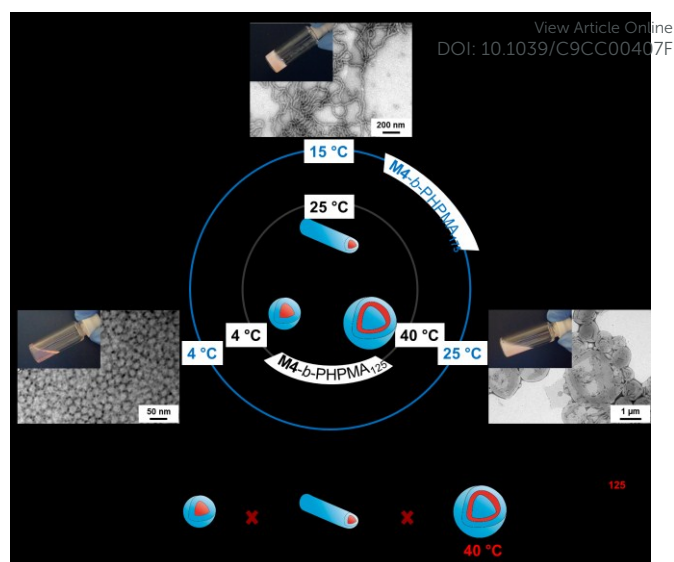



Figure 2. Temperature-induced morphological transformation of (A) original nanofibers (**M4-b-PHPMA**₁₂₅, 20 wt% at 25 °C) and vesicles (**M4-b-PHPMA**₁₇₅, 15 wt% at 25 °C) in as-synthesized dispersions, and (B) vesicles (**M4-b-PHPMA**₁₂₅, 0.1 wt% at 40 °C) at low concentration. Representative solutions and TEM images in (A) from the original nanofiber sample.

were obtained (Table S7 and Figure S27) and expected maxima absorption and emission for fluorescein and rhodamine B (Figure S28).

To assess the biocompatibility and ability of FMA-labeled PETox NPs to evade clearance by the reticuloendothelial system (RES), murine macrophages (RAW 264.7), human umbilical vein endothelial cells (HUVEC), and human epithelial lung cancer cells (A549) were incubated for 24 h, using fluorescein-labeled carboxylated polystyrene (PS-COOH) NPs as reference material.³⁸ RVB-labeled NPs were administered to zebrafish embryos and their biocompatibility, biodistribution, and clearance were examined for 24 h post-injection (hpi). As controls, PS-COOH NPs as well as rhodamine-labeled dextran were used in parallel. Both *in vitro* and *in vivo* studies are reported in more detail in the Supporting Information.

Briefly, as expected for NPs covered with stealth polymers, PETox NPs show none-to-very low uptake in all cell types and did not reduce cell viability up to 100 μg mL⁻¹ (Figures S31–S33). In the zebrafish embryos, no noticeable morphological or behavioral change was detected after intravenous injection of a 1 mg mL⁻¹ dispersion of RVB-labeled NPs (Figure 3). In contrast to dextran, which was rapidly cleared and only slightly accumulated in endothelial cells in the caudal vein (CV) after 24 h (C, F, C', and F'), RVB-PETox NPs mainly circulated in the bloodstream (B, E and B', E'). For comparison, PS-COOH NPs were not detected in the circulation but were, as expected, entrapped in the RES (macrophages and endothelial cells) in the CV (D, and D'). However, contrary to the more simplistic *in vitro* experiments employing murine macrophages, a small fraction of RVB-PETox NPs could be detected in macrophages *in vivo* (E, and E'). In summary, our PETox NPs are biocompatible and display enhanced retention in the blood circulation. Furthermore, to accurately monitor clearance by the RES, the



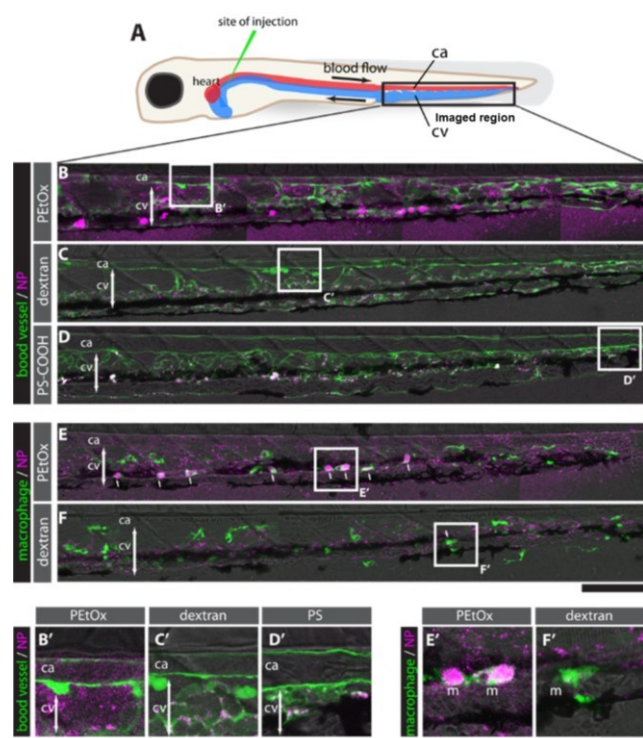


Figure 3. (A) Schematic of a 3 day-post-fertilization zebrafish embryo highlighting the artery (red), vein (blue), and site of NP injection, as well as the imaged region (rectangular region) shown in panels B-F. Orientation of embryos is dorsal up, anterior left. (B-D) Caudal region of zebrafish embryos at 24 hpi injected with either PETox NP (magenta, B), rhodamine-conjugated 3 kDa dextran (magenta, C) or PS-COOH NPs (magenta, D). Blood vessels are demarcated with transgenic fluorescence (green). (E-F) Same region of embryos highlighting the location of macrophages (green, arrows) injected either with PETox NPs (E) or dextran (F). ca: caudal artery; cv: caudal vein; m: macrophage; n: notochord. Scale bar: 100 μm (B-F) and 20 μm (B'-F').

zebrafish model seems to be better suited than conventional cell culture studies.

In the present communication, we described for the first time the synthesis of biocompatible PAOx-based diblock copolymer NPs by PISA. Control of morphology was achieved by varying the lengths of each block as well as the reaction mixture concentration. Dispersion based on pure phases of spheres, fibers, or vesicles were obtained. The nanoobjects display a thermosensitive behavior, enabling morphological transformation, which could be an asset for the preparation of bioactive materials. Importantly, the present PETox-based nanoparticles are non-toxic and exhibit prolonged circulation in the bloodstream. The versatility of PISA combined with the high potential of polyoxazolines in drug delivery and bioscaffolding promises a rapid access to corresponding functional (nano)materials.

D. L. thanks the Alexander von Humboldt Foundation for his postdoctoral fellowship. G.G.A. thanks the Mexican National Council for Science and Technology (CONACyT). G. D. thanks the German Federal Ministry of Education and Research (BMBF, Grant No. 031A095C) for funding (Molecular Interaction Engineering program, Biotechnologie 2020+). The Macroarc group (ITCP, KIT) and Levkin lab (KIT, ITG) are thanked for access to SEC and DLS, respectively. D. Keller and Edgar Molle (ITG, KIT)

are acknowledged for the synthesis of RVB and SPTP, respectively. View Article Online
DOI: 10.1039/C9CC00407F

Conflicts of interest

There are no conflicts to declare.

Notes and References

- 1 T. X. Viegas, M. D. Bentley, J. M. Harris, Z. Fang, K. Yoon, B. Dizman, R. Weimer, A. Mero, G. Pasut and F. M. Veronese, *Bioconjug. Chem.*, 2011, **22**, 976–986.
- 2 T. Lorson, M. M. Lübtow, E. Wegener, M. S. Haider, S. Borova, D. Nahm, R. Jordan, M. Sokolski-Papkov, A. V. Kabanov and R. Luxenhofer, *Biomaterials*, 2018, **178**, 204–280.
- 3 B. Verbraken, B. D. Monnery, K. Lava and R. Hoogenboom, *Eur. Polym. J.*, 2016, **88**, 451–469.
- 4 M. Glassner, M. Vergaelen and R. Hoogenboom, *Polym. Int.*, 2018, **67**, 32–45.
- 5 R. W. Moreadith, T. X. Viegas, M. D. Bentley, J. M. Harris, Z. Fang, K. Yoon, B. Dizman, R. Weimer, B. P. Rae, X. Li, C. Rader, D. Standaert and W. Olanow, *Eur. Polym. J.*, 2017, **88**, 524–552.
- 6 A. M. Kelly and F. Wiesbrock, *Macromol. Rapid Commun.*, 2012, **33**, 1632–1647.
- 7 M. Hartlieb, K. Kempe and U. S. Schubert, *J. Mater. Chem. B*, 2015, **3**, 526–538.
- 8 T. R. Dargaville, J.-R. Park and R. Hoogenboom, *Macromol. Biosci.*, 2018, **18**, 1800070.
- 9 R. Konradi, B. Pidhatika, A. Mühlebach and M. Textor, *Langmuir*, 2008, **24**, 613–616.
- 10 M. Schmidt, L. K. Bast, F. Lanfer, L. Richter, E. Hennes, R. Seymen, C. Krumm and J. C. Tiller, *Bioconjug. Chem.*, 2017, **28**, 2440–2451.
- 11 G. Gil Alvarado, M. Glassner, R. Hoogenboom and G. Delaittre, *RSC Adv.*, 2018, **8**, 9471–9479.
- 12 P. Wilson, P. C. Ke, T. P. Davis and K. Kempe, *Eur. Polym. J.*, 2017, **88**, 486–515.
- 13 G. Gil Alvarado, H. V.-T. Nguyen, P. Harvey, N. M. Gallagher, D. Le, M. F. Ottaviani, A. Jasanoff, G. Delaittre and J. A. Johnson, *submitted*.
- 14 C. Zhang, R. J. P. Sanchez, C. Fu, R. Clayden-Zabik, H. Peng, K. Kempe and A. K. Whittaker, *Biomacromolecules*, 2018, **20**, 365–374.
- 15 N. A. Hutter, M. Steenackers, A. Reitingner, O. A. Williams, J. A. Garrido and R. Jordan, *Soft Matter*, 2011, **7**, 4861–4867.
- 16 R. Luxenhofer, Y. Han, A. Schulz, J. Tong, Z. He, A. V. Kabanov and R. Jordan, *Macromol. Rapid Commun.*, 2012, **33**, 1613–1631.
- 17 G. Delaittre, J. Nicolas, C. Lefay, M. Save and B. Charleux, *Chem. Commun.*, 2005, **1**, 614.
- 18 N. J. Warren and S. P. Armes, *J. Am. Chem. Soc.*, 2014, **136**, 10174–10185.
- 19 D. Le, D. Keller and G. Delaittre, *Macromol. Rapid Commun.*, 2018, 1800551.
- 20 J. Lesagedelahaie, X. Zhang, I. Chaduc, F. Brunel, M. Lansalot and F. D'Agosto, *Angew. Chem. Int. Ed.*, 2016, **55**, 3739–3743.
- 21 J. Yeow and C. Boyer, *Adv. Sci.*, 2017, **4**, 1700137.
- 22 W.-J. Zhang, C.-Y. Hong and C.-Y. Pan, *Macromol. Rapid Commun.*, DOI: 10.1002/marc.201800279.
- 23 J. Rieger, *Macromol. Rapid Commun.*, 2015, **36**, 1458–1471.
- 24 J. Liu, Y. Liao, X. He, J. Yu, L. Ding and M. Xie, *Macromol. Chem. Phys.*, 2011, **212**, 55–63.
- 25 D. B. Wright, M. A. Touve, L. Adamiak and N. C. Gianneschi, *ACS Macro Lett.*, 2017, **6**, 925–929.
- 26 J. C. Foster, S. Varlas, L. D. Blackman, L. A. Arkinstall and R. K. O'Reilly, *Angew. Chem. Int. Ed.*, 2018, 10672–10676.
- 27 O. L. Torres-Rocha, X. Wu, C. Zhu, C. M. Crudden and M. F. Cunningham, *Macromol. Rapid Commun.*, 2019, **40**, 1800326.
- 28 D. Le, M. Dilger, V. Pertici, S. Diabaté, D. Gimes, C. Weiss and G. Delaittre, *Angew. Chem. Int. Ed. Engl.*, DOI:10.1002/anie.201813434.
- 29 C. E. Boott, J. Gwyther, R. L. Harniman, D. W. Hayward and I. Manners, *Nat. Chem.*, 2017, **9**, 785.
- 30 K. Knop, R. Hoogenboom, D. Fischer and U. S. Schubert, *Angew. Chem. Int. Ed.*, 2010, **49**, 6288–6308.
- 31 A. Krieg, C. Weber, R. Hoogenboom, C. R. Becer and U. S. Schubert, *ACS*



- Macro Lett.*, 2012, **1**, 776–779.
- 32 A.-K. Trützscher, M. N. Leiske, M. Strumpf, J. C. Brendel and U. S. Schubert, *Macromol. Rapid Commun.*, 2019, **40**, 1800398.
- 33 H. Willcock and R. K. O'Reilly, *Polym. Chem.*, 2010, **1**, 149–157.
- 34 D. Zhou, R. P. Kuchel and P. B. Zetterlund, *Polym. Chem.*, 2017, **8**, 4177–4181.
- 35 R. Hoogenboom and H. Schlaad, *Polym. Chem.*, 2017, **8**, 24–40.
- 36 A. Blanazs, R. Verber, O. O. Mykhaylyk, A. J. Ryan, J. Z. Heath, C. W. I. Douglas and S. P. Armes, *J. Am. Chem. Soc.*, 2012, **134**, 9741–9748.
- 37 N. J. Warren, J. Rosselgong, J. Madsen and S. P. Armes, *Biomacromolecules*, 2015, **16**, 2514–2521.
- 38 S. R. Mane, I. L. Hsiao, M. Takamiya, D. Le, U. Straehle, C. Barner-Kowollik, C. Weiss and G. Delaittre, *Small*, 2018, **14**, 1801571.

View Article Online
DOI: 10.1039/C9CC00407F

