

ChemComm

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: M. Dharmarwardana, R. P. Welch, S. Kwon, V. K. Nguyen, G. T. McCandless, M. A. Omary and J. J. Gassensmith, *Chem. Commun.*, 2017, DOI: 10.1039/C7CC04346E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [author guidelines](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the ethical guidelines, outlined in our [author and reviewer resource centre](#), still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

Thermo-Mechanically Responsive Crystalline Organic Cantilever

Received 00th January 20xx,
Accepted 00th January 20xxMadushani Dharmawardana,^a Raymond P. Welch,^a Sunah Kwon,^b Victoria K. Nguyen,^a Gregory T. McCandless,^a Mohammad A. Omary,^c and Jeremiah J. Gassensmith^a

DOI: 10.1039/x0xx00000x


www.rsc.org/

We report thermo-mechanically responsive and thermochromic behavior in the single crystalline organic semiconductor butoxyphenyl N-substituted naphthalene diimide (BNDI). We show that initially monoclinic single crystals of BNDI undergo a single-crystal to single-crystal transition to a triclinic phase. This transition accompanies large changes in the crystal packing, a visible decrease in crystal size, reversible thermochromic behavior, and motion including bending, jumping, and splitting. We have shown that by fixing single crystals to a surface, we can harness the energy of the phase transition to create a single crystal cantilever capable of lifting small weights.

Kinetic stimuli responsive behavior—the ability to move in response to the input of energy from an external source—has been engineered in a wide range of flexible materials from bulk polymers^{1–7} to viral nanoparticles.^{8–10} These soft materials readily undergo chemical functionalization and stimuli responsiveness can be straightforward to introduce.¹ Finding such motion in highly crystalline solids is still unusual and surprising.^{11, 12} That said, recent examples of single crystals that bend, jump^{13, 14} split,^{15, 16} coil,¹⁷ and explode¹⁸ when prodded into undergoing either a phase transition or topochemical reaction^{19–23} have emerged in the literature. This rapid and controllable dynamic behavior has attracted some interest owing to potential applications as micron or nanoscale actuators for smart medical devices, artificial muscles, sensors, and memory devices.^{12, 24–27} In most cases, this induced motion leads to disintegration after the phase transition; thus, such crystals are not suitable for structure determination following actuation. In contrast, only a few examples^{14–29} of organic molecular crystals showing thermo-mechanical single crystal-

to-single crystal (SC-SC) transitions have been reported. Donor-accepter stacks containing electron deficient naphthalene diimide subunits and electron rich dialkoxynaphthalene subunits have been shown to undergo phase transitions in response to temperature changes—giving rise to thermochromism.²⁸ What is not clear is if this thermal responsiveness is a general phenomenon to planar aromatics or if it is unique to donor-acceptor systems.^{29–31} In other words, we wondered if similar thermo-responsive behavior could be achieved with just a single type of subunit—either single crystals containing only an electron donor or an electron acceptor. In the course of this study, we discovered that the monoclinic polymorph (α -phase) of single crystals containing exclusively butoxyphenyl N-substituted naphthalene diimide (BNDI) (Figure 1a) not only undergo significant intermolecular changes in stacking distance, but also, when heated, undergo a thermo-mechanical responsive SC-SC change to a reversibly thermochromic triclinic (β -phase) system.

Figure 1. (a) Chemical structure of BNDI; Photographs of polymorphs: the (b) non-thermochromic α -phase and the (c) thermochromic β -phase.

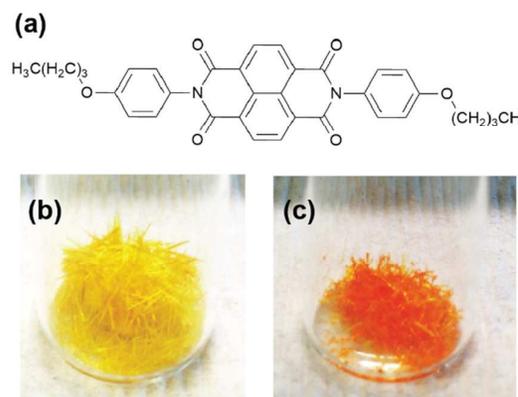

This is made all the more interesting because naphthalene diimide structures are one of only a handful of n-type organic semiconductors³² and BNDI is known to have n-type semiconducting properties^{32, 33} in the solid state. Intriguingly, the concurrent existence of polymorphism³⁴ and thermo-mechanical behavior in the solid state have yet to be reported


^a Department of Chemistry and Biochemistry, University of Texas at Dallas, 800 West Campbell Road, Richardson, TX 75080-3021. gassensmith@utdallas.edu.

^b Department of Material Science and Engineering, University of Texas at Dallas, 800 West Campbell Road, Richardson, TX 75080-3021.

^c Department of Chemistry, University of North Texas, 1155 Union Circle, Denton, TX 76203.

†Electronic Supplementary Information (ESI) available: Experimental details, single crystal X-ray data, NMR spectra, DSC curves are given in the supporting information and Movie S1-S10. CCDC numbers are CCDC 1497526 and CCDC 1497523. These data can be obtained free of charge from the Cambridge crystallographic data Centre. See DOI: 10.1039/x0xx00000x

for any naphthalene diimide—or any perylene derivative for that matter—despite several examples of liquid crystalline systems^{35–37} and polymers³⁸ of these materials showing such behavior.³⁹ During our initial investigation of BNDI single crystals, we found we could induce the quantitative growth of two phase-pure BNDI derivatives by changing the solution growth conditions. Specifically, we found the known yellow monoclinic polymorph (α -phase shown in Figure 1b), which we initially believed to be thermally inert based on temperature dependent single crystal X-ray diffraction (SXRD) experiments and a thermochromic triclinic polymorph (β -phase), which produces orange crystals at room temperature (Figure 1c). While testing the presumed “thermal-inertness” of the yellow α -phase crystals, we discovered that, after heating to around 400 K and then upon cooling, the crystals became orange and displayed identical thermochromic behavior as the triclinic β -phase. We suspected that the crystals interconverted between the two polymorphs, which would have been surprising given the large difference in unit cell parameters (Table S1).

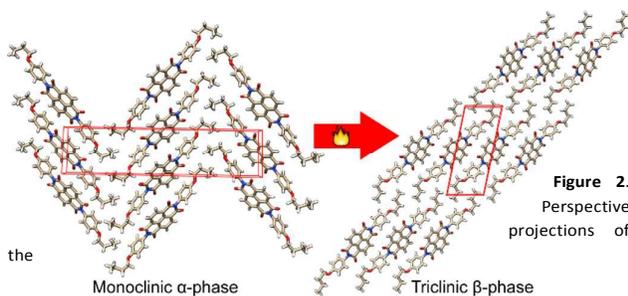


crystallographic packing in the SC-SC transition from the monoclinic α -phase to the triclinic β -phase. Upon heat treatment, the crystal lattice changes from herringbone packing to infinite 1D chains stacked co-facially along their π surfaces. The red box represents the unit cells of the respective crystals. Both images are oriented along the crystallographic a -axis.

In most reported cases, thermo-mechanically responsive molecular crystals are isosymmetric after the phase transition and only minor changes of the unit cell are noted.^{40–44} In the instance of BNDI, however, crystal symmetry is not preserved and a comparatively massive change in the unit cell is observed. Figure 2, for instance, shows both polymorphs along the crystallographic a -axis and clearly illustrates these large anisotropic changes in packing. We witnessed this first-hand when a single crystal of the monoclinic α -phase was evaluated by SXRD analysis at room temperature. The crystal was then heated in a round bottom flask using an oil bath to around 400 K, cooled down to 90 K, and SXRD data were collected. The thermally transformed polymorph, now in the β -phase, continued to diffract, though with some attenuation in long range order (Figure S3 and Table S1) and the emergence of disorder presumed to be associated with twinning.

Frequently, we found that the crystals would undergo even more extreme motion; for instance, rapid vibration and jumping were seen, though, about 75% of the time, the crystals would bend out of plane (Figure S4–S8).

We characterized this dynamic behavior using hot-stage microscopy to analyze the morphological and color changes of the α -phase during this anomalous transition. When millimeter-sized single crystals in the α -phase were heated on the stage of a polarized optical microscope, the crystal initially expanded, but no movement was observed until the temperature reached around 400 K. At that point, a clear “wave front” began at one extreme end of a crystal and propagated to the other end followed by a change from bright yellow to dark yellow (Figure 3 and Movie S1). At this point the crystal started showing movements such as cracking, splitting, jumping, and bending (Figure S6–S9 and Movie S1–S2). If the crystal did not jump out of view, we could then lower the temperature of the stage. Once the crystals underwent a transformation to the thermochromic β -phase, they changed color to red/orange as the stage was reduced to cryogenic

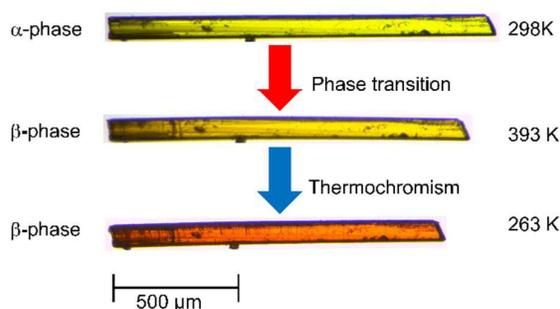


temperatures (Figure 3).

Figure 3. Changes of crystal dimensions during the α -phase to the β -phase transformation.

While most of the crystals ended up irreversibly bending during the phase transition, some crystals of the α -phase were either much less dramatic in movement (Figure S10) or bent back into plane following the transition. This allowed us to record the contraction of the crystal while it was heated beyond the phase transition and then cooled. The crystal contracted approximately 5% following the phase transition and a further 13% upon cooling to 263 K (Table S2–S3, Figure 3, and Figure S4). From our SXRD data it is clear that the transition from α -phase to β -phase results in a radically different unit cell and it is quite clear the crystals themselves change in size.

Whilst the dynamic behavior we describe here is uncommon, several elegant studies^{13, 16, 18, 41–43, 45–47} have postulated that the stress accumulation within the crystal due to the molecular rearrangement is transformed into mechanical force. We sought to quantify this mechanical force, at least rudimentarily, by converting the single crystals into molecular single crystal cantilevers. To do this, we glued one end of the crystal to the surface of a glass cover slip and a metal ball was loaded onto the other end of the crystal (Figure 4). The

coverslip was then placed onto a heated stage and we recorded its behavior as the temperature passed and then retreated from the phase transition temperature. We tried a range of crystal sizes and two sizes of metal balls to quantify the thermo-mechanical behaviour of this unique system (Table S4, Figure S12-S16, and Movies S4-S10). The maximum load we were able to lift with 3.5 mm long BNDI crystal was a 4.113 mg stainless steel metal ball to a height of 0.24 mm (Figure S15 and Movie S7). In this case, the metal ball is 91 times heavier than the BNDI crystal, the amount of work done by the BNDI

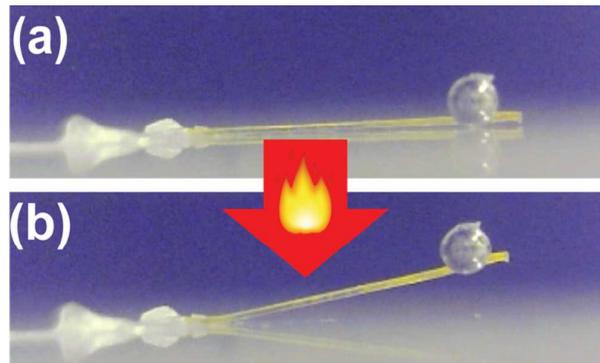


cantilever is about 0.01 μJ , and the force generated from the α -phase to the β -phase transition is 40 μN .

Figure 4. Thermo-mechanical work of a BNDI cantilever. (a) Before the phase transition. (b) After the phase transition. The crystal was heated on a glass slide on the heating stage of polarized optical microscope. The mass of the crystal and a 0.5 mm diameter tungsten carbide ball is ~ 0.0100 mg and 0.8320 mg, respectively.

Differential scanning calorimetry (DSC) analysis on bulk samples of the yellow monoclinic α -phase had yet another surprise in store for us—a second transition at an even higher temperature. The DSC scans shown in Figure 5a reveal the multiple phase transitions: (1) the expected transition from the α -phase to the β -phase at 388 K; (2) followed by a transition to a new γ -phase at 479 K; and (3) a return to the β -phase upon cooling below 408 K. When this thermal cycle is repeated on the same sample, only the transition between the β -phase and γ -phase is observed, indicating that this transition is reversible. The DSC data of both polymorphs clearly indicated that this phase transition is transforming the α -phase to a more thermodynamically stable and highly thermochromic β -phase (Figure 5b and Figure S17). During the β -phase to γ -phase transformation, the crystals lose some of their crystallinity which results in the peak shifting in the second heating cycle (Figure 6a).^{48, 49}

We confirmed the bulk material underwent reversible crystallographic phase transitions using variable temperature powder X-ray diffraction (PXRD). As shown in Figure 5b, as the temperature increases on a sample of pure α -phase BNDI, the reflections of the α -phase peaks decrease and a new set of reflections corresponding to the β -phase appears. As we further increase the temperature, the α -phase completely transforms to the β -phase, which then gives way to the γ -phase at temperatures above 480 K. As we cool down the sample to room temperature, the intensity of the β -phase peaks increases and the γ -phase completely disappears. Thus

far, we have been unable to obtain SXRD data of this high temperature γ -phase, as the single crystals become polycrystalline. Curiously, at these high temperatures, the β -phase is a bright yellow. Once it enters the γ -phase it suddenly becomes orange, indicating that the packing conformation has clearly changed into something quite distinct. Notably, upon

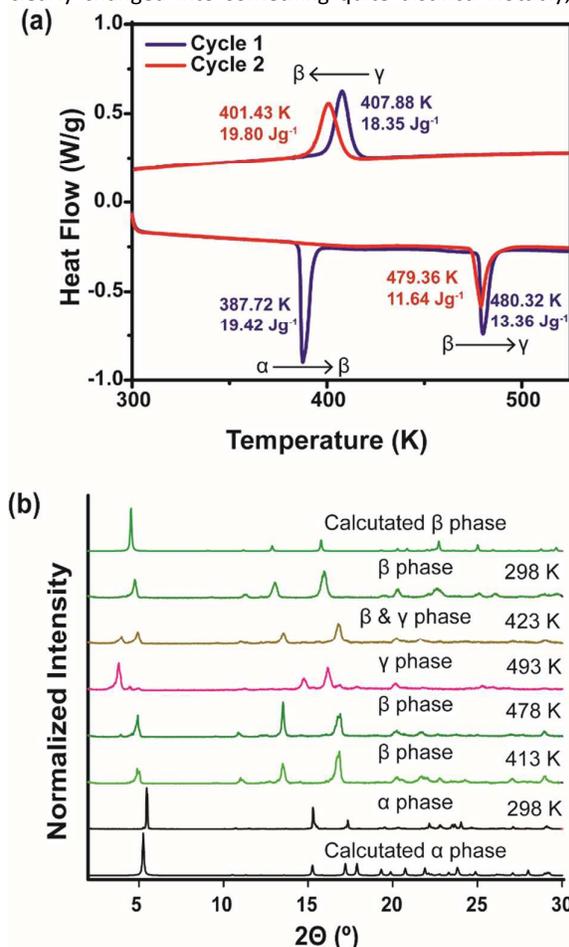

cooling, the crystals again turn yellow at the phase transition and then are again thermochromic, and they still strongly diffract by PXRD.⁵⁰

Figure 5. (a) DSC curves for the α -phase; Heating rate is 10 K/min (b) Variable temperature PXRD data for the α -phase.

Conclusions

In summary, we have demonstrated the SC-SC polymorphic transition of the α -phase of the organic semiconductor BNDI to its highly thermochromic β -phase followed by a reversible polymorphic transition to a γ -phase, which only exists at high temperatures. During the polymorphic α -phase to β -phase transition, the crystal symmetry has been changed from monoclinic to triclinic, which accompanied massive stress accumulation within the crystal. According to our polarized optical microscope data, the α -phase of BNDI shows mechanical responses such as bending, jumping, cracking, and splitting upon heating. This thermally induced phase transition

could be very useful in microelectronic devices. As a proof of principle, we used the force generated by this thermally driven phase transition to lift a metal ball nearly two orders of magnitude heavier than the crystal itself. Further, the notion that polymorphs of naphthalene diimides—an important class of organic semiconducting materials—are thermo-mechanically sensitive, with each polymorph showing distinct solid state behavior, could have important implications for the field of organic semiconductors.

Acknowledgement

We would like to thank Prof. M. C. Biewer for and Dr. H. Nyugen for assistance with collecting hot stage polarized optical microscopy data. JJG would like to acknowledge the ACS-PRF (57627-DNI10) for funding.

References

- 1 Y. Yu, M. Nakano and T. Ikeda, *Nature*, 2003, **425**, 145.
- 2 E. Smela, *Adv. Mater.*, 2003, **15**, 481-494.
- 3 G. M. Spinks, G. G. Wallace, L. S. Fifield, L. R. Dalton, A. Mazzoldi, D. De Rossi, I. I. Khayrullin and R. H. Baughman, *Adv. Mater.*, 2002, **14**, 1728-1732.
- 4 R. H. Baughman, *Science*, 1999, **284**, 1340-1344.
- 5 R. Pelrine, *Science*, 2000, **287**, 836-839.
- 6 M. H. Li, P. Keller, B. Li, X. Wang and M. Brunet, *Adv. Mater.*, 2003, **15**, 569-572.
- 7 A. Natansohn and P. Rochon, *Chem. Rev.*, 2002, **102**, 4139-4176.
- 8 S. Li, M. Dharmawardana, R. P. Welch, Y. Ren, C. M. Thompson, R. A. Smaldone and J. J. Gassensmith, *Angew. Chem.*, 2016, **55**, 10691-10696.
- 9 Z. Chen, N. Li, S. Li, M. Dharmawardana, A. Schlimme and J. J. Gassensmith, *WIREs Nanomed. Nanobiotechnol.*, 2016, **8**, 512-534.
- 10 Z. Chen, N. Li, L. Chen, J. Lee and J. J. Gassensmith, *Small*, 2016, **12**, 4563-4571.
- 11 F. Terao, M. Morimoto and M. Irie, *Angew. Chem.*, 2012, **51**, 901-904.
- 12 S. Kobatake, S. Takami, H. Muto, T. Ishikawa and M. Irie, *Nature*, 2007, **446**, 778-781.
- 13 M. Lusi and J. Bernstein, *Chem. Commun.*, 2013, **49**, 9293-9295.
- 14 M. K. Panda, T. Runcevski, A. Husain, R. E. Dinnebieer and P. Naumov, *J. Am. Chem. Soc.*, 2015, **137**, 1895-1902.
- 15 R. Medishetty, S. C. Sahoo, C. E. Mulijanto, P. Naumov and J. J. Vittal, *Chem. Mater.*, 2015, **27**, 1821-1829.
- 16 G. Liu, J. Liu, X. Ye, L. Nie, P. Gu, X. Tao and Q. Zhang, *Angew. Chem.*, 2017, **56**, 198-202.
- 17 Z. Chen, C. Majidi, D. J. Srolovitz and M. Haataja, *Appl. Phys. Lett.*, 2011, **98**, 011906.
- 18 N. K. Nath, M. K. Panda, S. C. Sahoo and P. Naumov, *CrystEngComm*, 2014, **16**, 1850.
- 19 A. Pathigoolla and K. M. Sureshan, *Angew. Chem.*, 2014, **53**, 9522-9525.
- 20 J. W. Lauher, F. W. Fowler and N. S. Goroff, *Acc. Chem. Res.*, 2008, **41**, 1215-1229.
- 21 Z. Li, Frank, F. W. Fowler and J. W. Lauher, *Am. Chem. Soc.*, 2009, **131**, 634.
- 22 A. Pathigoolla, R. G. Gonnade and K. M. Sureshan, *Angew. Chem.*, 2012, **51**, 4362-4366.
- 23 L. J. Barbour, *Aust. J. Chem.*, 2006, **59**, 595.
- 24 P. Naumov, S. Chizhik, M. K. Panda, N. K. Nath and E. Boldyreva, *Chem. Rev.*, 2015, **115**, 12440-12490.
- 25 I. Burgert and P. Fratzl, *Phil. Trans. R. Soc. A*, 2009, **367**, 1541-1557.
- 26 V. Balzani, A. Credi, F. M. Raymo and J. F. Stoddart, *Angew. Chem.*, 2000, **39**, 3348-3391.
- 27 M. Morimoto and M. Irie, *J. Am. Chem. Soc.*, 2010, **132**, 14172-14178.
- 28 J. J. Reczek, K. R. Villazor, V. Lynch, T. M. Swager and B. L. Iverson, *J. Am. Chem. Soc.*, 2006, **128**, 7995-8002.
- 29 T. Yuan, M. Vazquez, A. N. Goldner, Y. Xu, R. Contrucci, M. A. Firestone, M. A. Olson and L. Fang, *Adv. Funct. Mater.*, 2016, **26**, 8566-8566.
- 30 T. Yuan, M. Vazquez, A. N. Goldner, Y. Xu, R. Contrucci, M. A. Firestone, M. A. Olson and L. Fang, *Adv. Funct. Mater.*, 2016, **26**, 8604-8612.
- 31 X. Hou, C. Ke, C. J. Bruns, P. R. McGonigal, R. B. Pettman and J. F. Stoddart, *Nat. Commun.*, 2015, **6**, 6884.
- 32 R. Rybakiewicz, I. Tsydel, J. Zapala, L. Skorka, D. Wamil, D. Djurado, J. Pecaut, J. Ulanski, M. Zagorska and A. Pron, *RSC Adv.*, 2014, **4**, 14089-14100.
- 33 J. Yin, K. Chaitanya and X.-H. Ju, *Can. J. Chem.*, 2015, **93**, 740-748.
- 34 T. He, M. Stolte, C. Burschka, N. H. Hansen, T. Musiol, D. Kalblein, J. Pflaum, X. Tao, J. Brill and F. Wurthner, *Nat. Commun.*, 2015, **6**, 5954.
- 35 W. Pisula, M. Kastler, D. Wasserfallen, J. W. Robertson, F. Nolde, C. Kohl and K. Mullen, *Angew. Chem.*, 2006, **45**, 819-823.
- 36 E. Schab-Balcerzak, A. Iwan, M. Grucela-Zajac, M. Krompiec, M. Podgorna, M. Domanski, M. Siwy and H. Janeczek, *Synth. Met.*, 2011, **161**, 1660-1670.
- 37 F. Würthner, C. Thalacker, S. Diele and C. Tschierske, *Chem. Eur. J.*, 2001, **7**, 2245-2253.
- 38 B. Stempfلة, A. Grosse, B. Ferse, K. F. Arndt and D. Woll, *Langmuir*, 2014, **30**, 14056-14061.
- 39 This claim is made to the best of our knowledge and a good-faith effort was put forward to identify reports to this effect. To establish this claim we conducted a series of searches between (1st of August 2016 to 5th of June 2017). The search terms and parameters used to define novelty are outlined in the supporting information.
- 40 E. Nauha, P. Naumov and M. Lusi, *CrystEngComm*, 2016, **18**, 4699-4703.
- 41 Ž. Skoko, S. Zamir, P. Naumov and J. Bernstein, *J. Am. Chem. Soc.*, 2010, **132**, 14191-14202.
- 42 S. Chandra Sahoo, N. K. Nath, L. Zhang, M. H. Semreen, T. H. Al-Tel and P. Naumov, *RSC Adv.*, 2014, **4**, 7640.
- 43 T. Shima, T. Muraoka, N. Hoshino, T. Akutagawa, Y. Kobayashi and K. Kinbara, *Angew. Chem.*, 2014, **126**, 7301-7306.
- 44 T. Siegrist, C. Besnard, S. Haas, M. Schiltz, P. Pattison, D. Chernyshov, B. Batlogg and C. Kloc, *Adv. Mater.*, 2007, **19**, 2079-2082.
- 45 S. Ghosh, M. K. Mishra, S. Ganguly and G. R. Desiraju, *J. Am. Chem. Soc.*, 2015, **137**, 9912-9921.
- 46 M. Horie, Y. Suzaki, D. Hashizume, T. Abe, T. Wu, T. Sassa, T. Hosokai and K. Osakada, *J. Am. Chem. Soc.*, 2012, **134**, 17932-17944.
- 47 P. Commins, I. T. Desta, D. P. Karothu, M. K. Panda and P. Naumov, *Chem. Commun.*, 2016, **52**, 13941-13954.
- 48 W. K. Ng, J. W. Kwek, A. Yuen, C. L. Tan and R. Tan, *AAPS PharmSciTech.*, 2010, **11**, 159-167.
- 49 A. A. Van Dooren and B. W. Müller, *Thermochim. Acta*, 1982, **54**, 115-129.
- 50 Color changes in response to temperature in BNDI are clear indications of bandgap changes within this semiconducting material. This is quite curious and this behavior, and a full

Journal Name

COMMUNICATION

solid-state and computational analysis of it will be followed up in a subsequent publication.